Svarog TRAC boom mould v4: closed three-piece tool (2 lower V clamps + silicone top plug), envelope bag round all, autoclave

A Section, assembled and bagged (mm)

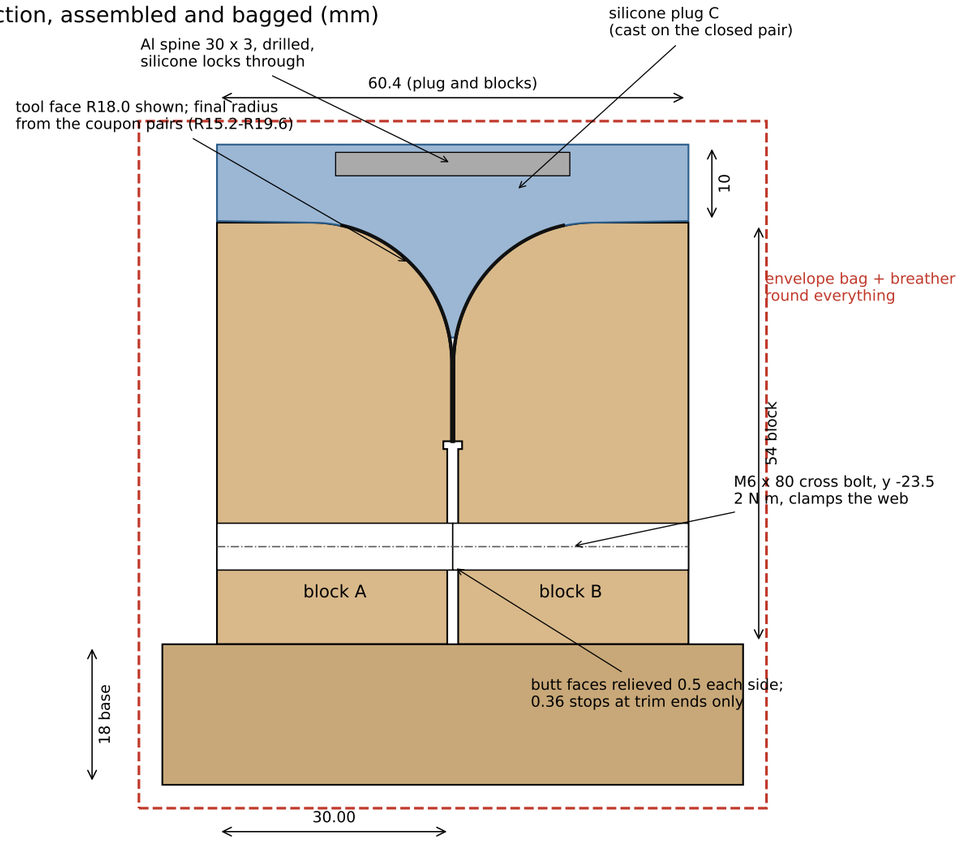

B Exploded: A and B clamp the V, C presses from the top

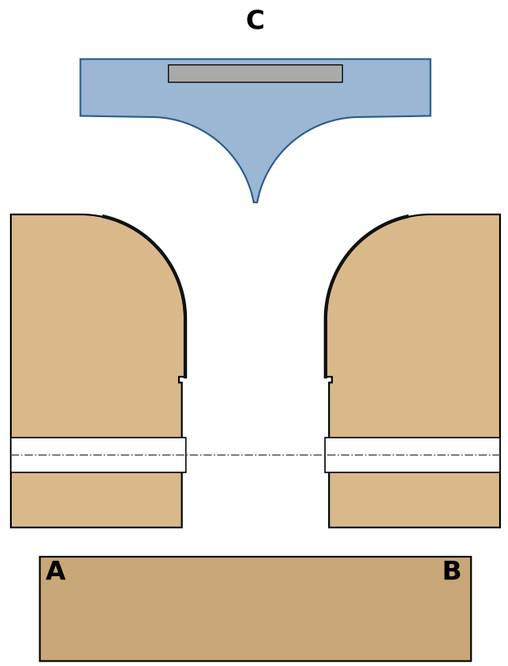

C Root detail: web, merge point, plug tip, gallery

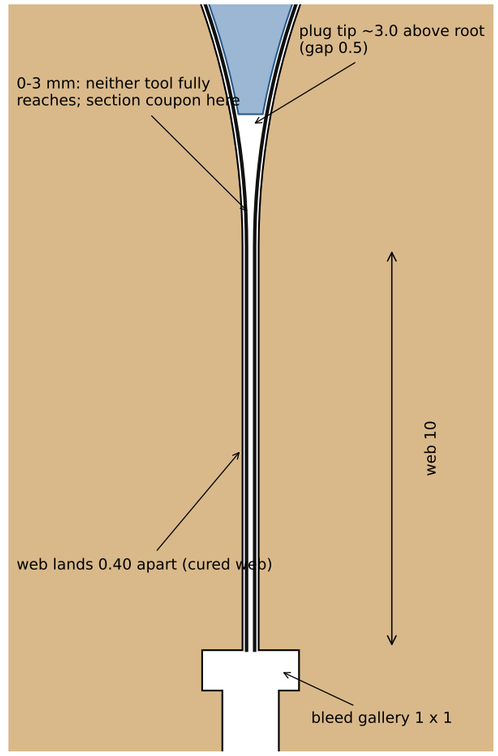

D Side elevation of block A (B mirrors; bolt and dowel holes drilled through both blocks together)

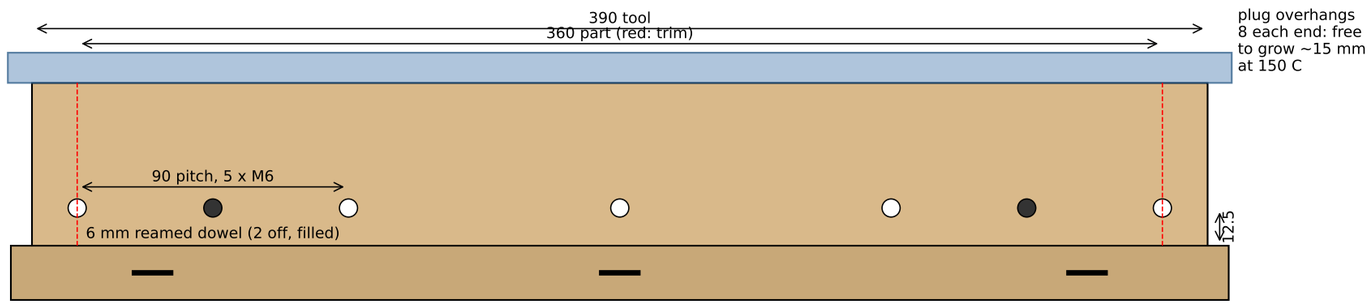

base screws in slotted holes; the slots run ACROSS the tool (seen end-on here) so the blocks can close

Tool face R18.0 shown. Spring-in measured on this process (Leclerc et al. 2017/2018, Caltech: mould R12.7 cured R10.6, 90 -> 105 deg) puts the tool ABOVE the part.
calc3's R14.83 had the sign backwards. Tomorrow: coupon pairs at R(15.2, 16.5, 18.0, 19.6); ROUGH the long blocks only; finish the arc once the coupons are read.
Blocks: one 35 mm phenolic birch strip each, sheet parallel to the web land (no glueline); rough, bake to constant mass, finish, seal.
Plug C: Mold Max XLS II (204 C) cast on the closed pair over a measured 0.22-0.25 mm spacer; drilled Al spine; no FEP across the V.
Clamp: bolts at 2 N m clamp the web as at Caltech; butt faces relieved; autoclave adds 1.4-2.9 MPa (net area ratio 3.6). Bag round everything.
Sources: calc4_output.txt, research-v4-autoclave.md, review-v4-adversarial.md. Draft 2 Nov 2026 for the 18:00 session; nothing cut yet.