

苏州苏德兰铁路配件有限公司尺寸检测报告

DIMENSIONAL TEST REPORT

品名 Product Name: 螺纹道钉 Screw Spike

规格 Size: $\varnothing 25\times 199$

等级 Grade: Gr5.6 , UIC864-1

标记 Mark: PANDROL 25 5.6 GS195-J15 SDL

合同编号 Contract NO: PO-IND02339

检测日期 Inspection date: 2025.03.04

发货日期 Date of shipment: 2025.03.05



序号 No	检测项目 Test feature	技术要求 Specification	实测数值 Actual Size	结果 Result
1	对边尺寸 opposite side	27 +0/-1	26.1~26.3	OK
2	头部厚度 head thickness	15.5±0.5	15.3~15.7	OK
3	头部R radius of head	R2	R2	OK
4	头部R radius of head	R2±0.5	R2	OK
5	头部角度 Head Angle	15°	15°	OK
6	头部总高 head total length	20 +1.5/-0	20.3~20.8	OK
7	圆盘直径 head diameter	$\varnothing 40 +0/-1$	39.2~39.5	OK
8	圆盘直径 head diameter	$\varnothing 42 +3/-1$	41.4~41.6	OK
9	杆部直径 shank diameter	$\varnothing 25 +0.7/-0.5$	24.8~25.1	OK
10	白杆长度 unthreaded shank length	95±5	93.2~95.3	OK
11	杆部总长 shank length	199±3	198.1~201.0	OK
12	螺纹内径 ID	$\varnothing 19 +0/-1$	18.2~18.6	OK
13	螺纹外径 OD	$\varnothing 25 +0/-1$	24.2~24.6	OK
14	5牙距 screw pitch	60±0.5	59.7~60.3	OK
15	单牙距 single screw pitch	12±0.1	11.95~12.05	OK
16	螺纹底部R角 Thread R angle	R0.5 +0.5/-0	R1	OK
17	螺纹底部R角 Thread R angle	R1 +1/-0.5	R1	OK
18	螺纹头部R角 Thread R angle	R0.5 +0.5/-0	R1	OK
19	螺纹头部R角 Thread R angle	R1 +1/-0.5	R1	OK
20	牙尖宽度 Tooth width	3	2.9~3.1	OK
21	螺纹角度 Thread angle	30°	30°	OK
22	螺纹角度 Thread angle	30°	30°	OK
23	尖部深度 Point depth	≤8	4.1~6.8	OK
24	表面处理 surface treatment	热镀锌 ≥55 μm Hot-dip Galvanise	60~97	OK
数量 Quantity			475件 (Pieces)	
检验 Inspector			张全恢 Zhang-QuanHui	
审核 In Charge			杨黎程 Yang-LiCheng	

苏州苏德兰铁路配件有限公司性能检测报告

PERFORMANCE TEST REPORT

品名 Product Name: 螺纹道钉 Screw Spike

规格 Size: $\varnothing 25\times 199$

等级 Grade: Gr5.6 , UIC864-1


标记 Mark : PANDROL 25 5.6 GS195-J15 SDL

合同编号 Contract NO: PO-IND02389

检测日期 Inspection date: 2025.03.04

发货日期 Date of shipment: 2025.03.05

数量 Quantity: 475 (件 Pieces)

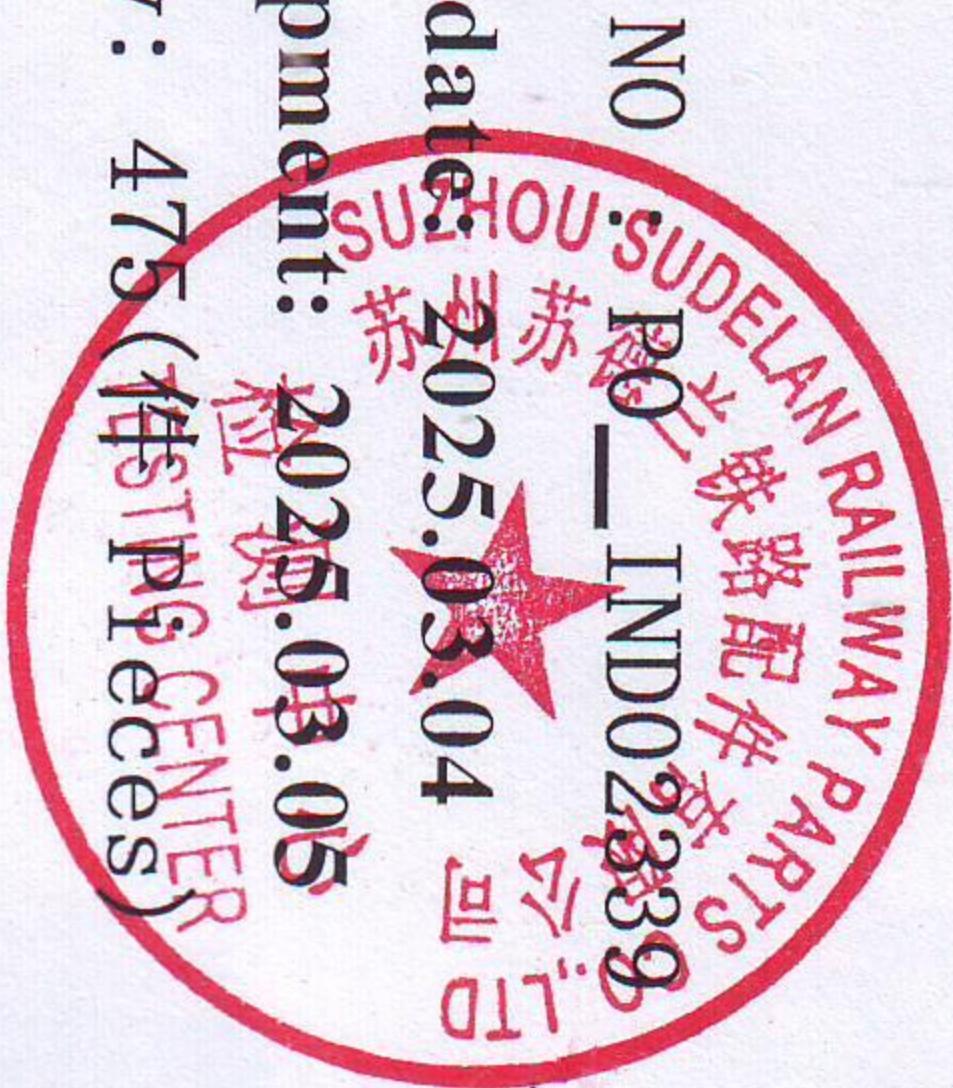

规格 Size	材料 Material	炉批号 Raw material Heat No	化学成分 Chemical composition (%)					机械性能 Mechanical properties				结果 Result
			C	S	Si	Mn	P	屈服强度 Yield strength	抗拉强度 Tensile Strength	延伸率 Elongation δ5"	冷弯 Bend Test	
$\varnothing 25\times 199$	35K	G531100697	0.35	0.002	0.14	0.71	0.015	$\geq 300\text{Mpa}$	$\geq 500\text{Mpa}$	Min20%	15°	
								365	592	22	OK	OK
								358	586	23	OK	OK

检验 Inspector: 张全恢 Zhang-QuanHui

审核 In Charge: 杨黎程 Yang-LiCheng



江苏沙钢集团有限公司
Jiangsu Shagang Group CO., LTD.
高速线材质量证明书

SG03B-1914E

High-speed Wire Rod Quality Certificate

江苏省张家港市锦丰镇 邮编: 215625
Jinfeng, Zhangjiagang, Jiangsu, P. R. CHINA
TEL: (0512) 58568866, 58568829
FAX: (0512) 58550366, 58550818

沙 钢

订货单位CUSTOMER		用户代码CUSTOMER CODE		合同号CONTRACT NO.		X52A00640010
牌号STEEL GRADE	SWRCH35K	提货单号DELIVERY	250220134001	发货日期DATE OF DELIVERY		20250220
交货标准 SPECIFICATION	Q/320582 SGY303-2024	质证书号CERTIFICATE NO.	2502201340 015837	签发日期DATE OF ISSUE	1	20250220
		用途USE		精炼方式REFINING METHOD		炉外精炼

序号 NO	炉号 HEAT NO.	直径 Dia. mm.	盘数 Coils	重量 kg	化学成分CHEMICAL COMPOSITION %										拉伸试验TENSILE TEST			顶锻 试验 H. T.	硬度 试验 HRB	脱碳层 D. of. D	晶粒度 Micro- Grade	索氏体 Sorbite %	备注 REMARKS	
					C	Si	Mn	P	S	Cr	Ni	Cu			Rm	Rel	A11.3							Z
					1= $\times 10^{-1}$	2= $\times 10^{-2}$	3= $\times 10^{-3}$	4= $\times 10^{-4}$	5= $\times 10^{-5}$						MPa		%							
1	G531100697	26.0	5	11077	35	14	71	15	2	3	1	2			586			42.0	0	81.00	0.01	8		
2	G533001017	26.0	10	22338	36	14	71	15	3	3	1	2			578			44.0	0	81.00	0.01	8		
合计 Total				15	33415	说明 NOTES 1. 本质量证明书适用于合金线材; 本产品不含有任何辐射元素。It is guaranteed that the products don't contain radiochemical impurities. 3. We, SHAGANG, hereby certify that the products specified in the present certificate have been fully processed in china. (facility and address information is stated above. *1. H. T.—Head-colding Test; *2 D. of D.—Depth of Decarburization;																		

综合判定 FINAL RESULT	合格 PASS	注意事项 ATTENTIVE ITEMS	1. 质量证明书复印件不作有效证明文件, 除非盖章; The copy of this Certificate is not valid except stamped. 2. 用户验货后使用如有异议应及时告知炉号、牌号, 并保留实物及标志。Please inform us the steel grade and the heat number of under quanlified material(s) found in inspection on time, and keep the material(s) and the marking card	签证人 VISA
-------------------------	------------	----------------------------	---	-------------

