

1
2
3 **Anti-Corrosion performance of conductive copolymers of**
4 **Polyaniline/Polythiophene on the stainless steel surface in acid media**

5 Shouqing Xue *, Qinghua Liu, Fenghai Li

6 *(Department of Chemistry and Chemical Engineering, Heze University, Heze 274015,*
7
8 *China)*

9
10
11
12 **Abstract:** The composite conductive copolymers of Polyaniline/ Polythiophene(Pani/PTH) were
13
14 successfully prepared by electrochemical method on the surface of stainless steel containing
15
16 aniline and thiophene in 0.3 mol/L oxalic acid solutions. The SS/Pani/PTH copolymers film
17
18 strongly adhered to the surface of stainless steel. Its anti-corrosion performance of the
19
20 SS/Polyaniline/ Polythiophene was investigated in acid media by Polarization curves test and
21
22 electrochemical impedance spectroscopy (EIS), and the surface morphology of film was observed
23
24 by Scanning electron microscope (SEM). The results show that, compared with the bare stainless
25
26 steel, Composite Conductive copolymers of Polyaniline/Polythiophene has well anti-corrosion
27
28 resistance, its can improve corrosion potential about 400 mV, while in the corrosion current
29
30 density decreased by 2 orders of magnitude, which is according to result of SEM. And the
31
32 Polyaniline/ Polythiophene film has uniform, dense and shiny structure, has a better anti-corrosion
33
34 behavior.
35

36
37 **Key words:** Anti-Corrosion, Polyaniline/Polythiophene, corrosion protection, Composite
38
39 conductive copolymer
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57

58
59 _____
60 * corresponding author,
61 Department of Chemistry and Chemical Engineering, Heze University, Heze 274015, E-mail:
62 xueshouqing@163.com
63
64
65

1. Introduction

For many last decades, with the development of modern oil transportation pipelines, corrosion problems has become an important industrial and academic topics[1]. Corrosion caused economic losses, while also caused the waste of resources and energy. it is very huge to the number of scrap metal devices and components, and these scrap metal regeneration process will not only caused a lot of energy waste, but also damaged to the environment of emission a large number of toxic and harmful smelting exhaust, because of this scrap metal contains other impurities (such as rubber, resin, etc). So it is very important to obtain a good anti-corrosion surface technology of metals for decreasing corrosion damage and to prolong effective life of the pipes, especially in acid media [2, 3].

The conducting polymer films have the most effective, cheaper and more environmentally friendly means of protecting the severe internal corrosion of Stainless steel because of their special structure, superior physical and chemical properties. Since the discovery of conductive polyaniline based on inhibitors have a highly anti-inhibition ability in acidic media, they are widespread used to minimize corrosion in the acidic solution [4-5]. Extensive research has been carried out in domains of conducting polymers over the last fifty years. But the conductive homo-polymers were lower binding force to the active metal, prone to irreversible electrochemical oxidation degradation. Therefore, its application prospect has been seriously limited. There are many researches on some effective and environmentally friendly methods to increase the corrosion performance and improve the adhesion properties between the polymer film and the matrix metal. Using copolymer or doping technology can effectively improve the anti-corrosion resistance, but using electrochemical synthesis of copolymer films and doping techniques increasing the corrosion resistance of Stainless steel have rarely reported in the literature.

In view of in continuation of our studies, In order to improve the cross each other between the two kinds of polymer molecules and increasing the adhesion to metal substrates, the aim is to make it a good anti-corrosion for stainless steel, alloy steel, copper and magnesium. The Pani/PTH copolymer was synthesized while containing aniline and thiophene in 0.3 mol/L oxalic acid solutions. By using the scanning electronic microscope, potentiodynamic polarization curves,

electrochemistry impedance spectrum studied the conducting polymers electrochemistry performance and explored the protective effect of the stainless steel surface. in addition, the composite conductive polymers provides a theoretical basis for widespread application prospect in domains of metal anti-corrosion.

2. Materials and Electrochemical measurements

2.1 Materials

The monomer, aniline (AR), thiophene (AR) (Shenzhen HCH Chemical Co, Ltd.), were reagent grades and were distilled under reduced pressure prior to use. Other chemicals (not including stainless steel) employed in this study were of reagent grade and without further purification. And the surface of stainless steel (including working electrode) working electrode used 1 to the 5th metallographic sandpaper progressively polished to mirror-bright, degreased with acetone, and washed with ethanol, distilled water and dried in cool flowing air, Placed in the dryer alternate.

2.2. Electrochemical measurements

The Composite Conductive copolymers of Polyaniline /Polythiophene were prepared using the electrochemical workstation (CHI660B). The electrolytic cell was a standard three-electrode system containing platinum electrode (area 2.25 cm²) was a auxiliary electrode, a saturated calomel electrode was a reference electrode, a smoothly polished stainless steel (10 mm×10 mm×10 mm) was a working electrode in the test. And the back of the working electrode by soldering copper leads wire, sealed with epoxy resin, the exposed area of 10 mm×10 mm. Polarization curves were made using CHI630C Potentiostat (CH Instruments Inc., USA) tested the corrosion of the Composite Conductive copolymers Polyaniline/ Polythiophene. Scan from negative to positive. The Electrochemical impedance spectroscopy (EIS) tests frequency range of 10⁻²~10⁵Hz, using specimens with 1cm² of working area exposed to the 3.5 m % NaCl aqueous solution. Corrosion morphologies of the stainless steel were observed by a JSM-6700F analytical scanning electron microscope (SEM). All the electrochemical measurements were performed at room temperature.

3. Results and Discussion

3.1 Preparation of the Pani /PTH copolymer films

Fig.1 shows the typical cyclic voltammogram process of the 1st to 3rd cycle recorded at the surface of Stainless steel in a 0.3mol/L oxalic acid aqueous solution containing aniline and thiophene at the potential window of -0.5 ~ 1.35V, the scan rate of 20mV/s. In the first scan, when scanning a significant three Pani redox peaks appeared, indicating that the Stainless steel surface to generating a thin layer Pani film. But after in the first laps, scanning that the aniline oxidation peak current significantly reduced and partially reduced peak disappears, leaving only a reduction peak, and the Polythiophene reduction peak appeared at 0.7V the oxidation current increased, the anode polarization current increases, and with increasing number the cycles of oxidation reduction current increases, indicating that the formation of Pani/ PTH composite conductive polymer films.

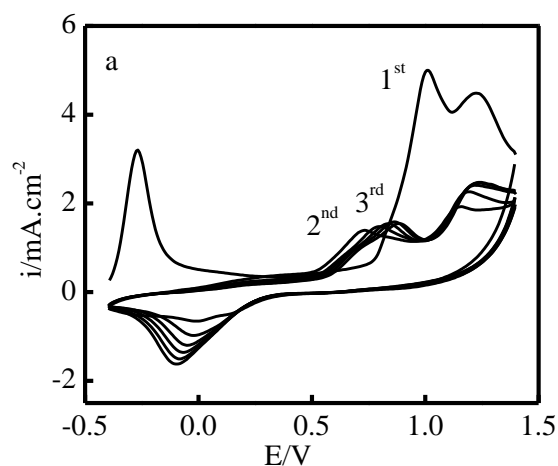


Fig.1 Cyclic voltammograms process at Stainless steel in oxalic acid solution containing aniline and thiophene

3.2 SEM images of the Pani /PTH copolymer films

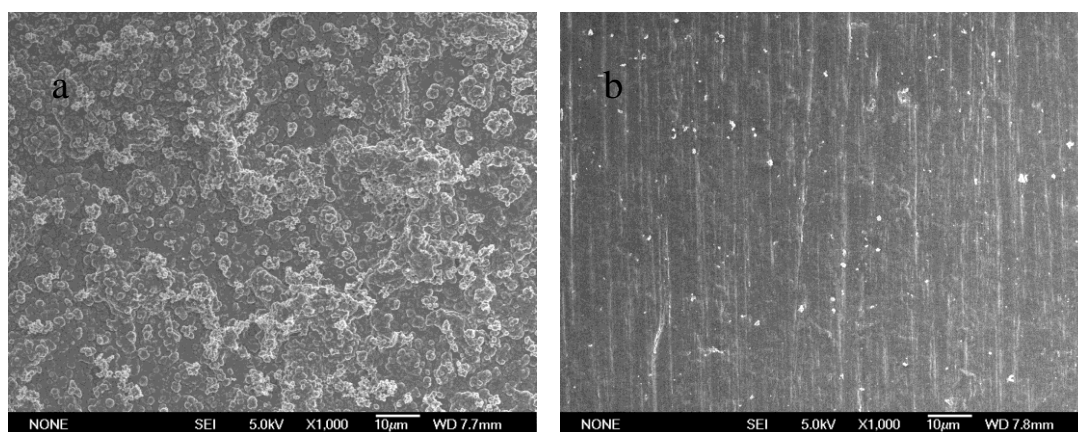


Fig.2 SEM images of the Pani /PTH copolymers films (a): 1st scan (b):10th scan

Fig.2 (a, b) shows the SEM images of the Pani /PTH copolymer films morphology when the scanning laps at 1, 10, respectively. In the initial stage of polymerization (In the first scan), it has generated a sheet showing the uniform distribution, with a small amount of fiber and a large pores of the Pani. With the polymerization proceeds (extension of the scan laps), morphology of the films have been very different from the initial stage of polymerization. The dense polymer films increased presents a uniform, compact structure. This is because solution of thiophene generated polymerization. With the extension of polymerization time, we obtained the uniform and compact Pani /PTH copolymer films.

3.3 Polarization curves of the Pani /PTH copolymer films

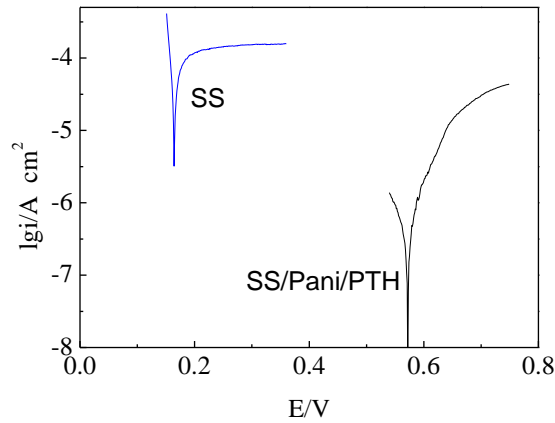


Fig.3 polarization curves of SS and SS/Pani /PTH in 1 mol/L H₂SO₄

Fig. 3 is polarization curves of a bare stainless steel (SS) and the attached with stainless steel sheet with Pani /PTH copolymer films (SS/Pani /PTH) after soaking 1 mol/L H₂SO₄ solution 4d. As can be seen from Figure 3, compared with bare stainless steel, the corrosion potential of the SS/Pani /PTH elevated about 400 mV, while the corrosion current density decreased by 2 orders of magnitude, indicating that the bare stainless steel surface covered by a protection film. Pani /PTH copolymer films uniformity and density were significantly improved can be effectively improving the metals anti-corrosion in acid solution.

Table 1. Corrosion parameters from Potentiodynamic polarization

	$i_{\text{corr}}(\mu\text{A} \cdot \text{cm}^{-2})$	$E_{\text{corr}}(\text{V})$
blank	-0.420	3.06×10^3
1 st cycle	0.507	30
3 rd cycle	0.573	2.9
10 th cycle	0.272	0.57

Table 1 present i_{corr} and E_{corr} of potentiodynamic polarization on the surface of SS at different situation. As can be seen from Table 1, compared with the blank, the SS covered with Pani /PTH copolymer films, the corrosion current density reduces more than 6000 times. It has the better anti-corrosion performance.

3.4 EIS of the Pani /PTH copolymer films

In order to examine the copolymer film in the redox state of the protective effect of stainless steel, EIS of Stainless steel and Stainless steel/PPy/Pani copolymer films were tested in 3.5% NaCl solution after soaking 4d. As can be seen from Figure 4, the capacitive diameter arc radius of Stainless steel/PPy/Pani copolymer films is larger than Stainless steel, i.e. it has the large electrochemical charge transfer resistance, which is attributed to physical shielding of copolymer films. Indicating that the copolymer films have better denseness, which were according to result of the SEM and polarization curves.

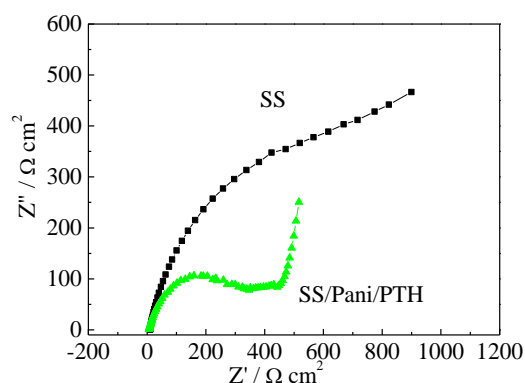


Fig.4 EIS of Stainless steel (SS) and Stainless steel / PPy / Pani copolymer films in 3.5% NaCl solution

4. Conclusion

1. From the results obtained to far, to protect SS corrosion, the Composite Conductive copolymers of Polyaniline/ Polythiophene(Pani/PTH) were prepared by electrochemical cyclic voltammetry on the surface of Stainless steel containing aniline and thiophene in 0.3 mol/L oxalic acid solutions, which strongly adhered to the surface of SS.

2. Compared with bare stainless steel sheet, attachment with PPy / Pani copolymer films corrosion potential shifts 220 mV, while the corrosion current density decreased by 2 orders of magnitude and the corrosion current density reduces more than 6000 times indicating that the PPy / Pani copolymer films has excellent corrosion resistance. The dense polymer films increased presents a uniform, compact structure. It provides a theoretical basis for widespread application prospect future in domains of metal anti-corrosion.

Acknowledgments: We gratefully acknowledge the support for this research by a grant from the Natural Science Foundation of Shandong Province, China (ZR2014EL004, ZR2014BM014).

References:

- [1] J. Yano, A. Muta, Y. Harima, et al. Poly(2,5-dimethoxyaniline) film coating for corrosion protection of iron, J Solid State Electrochem (2011) 15:601–605
- [2] M. Omastová, M. Mičušík. Polypyrrole coating of inorganic and organic materials by chemical oxidative polymerization, Chemical Papers 66 (5) 392–414 (2012)
- [3] Wang Jihui, Fu Congwei, Gao Zhiming, et al. Corrosion Process Detection of Tinplate in Deaerated Functional Beverage by EIS, Trans. Tianjin Univ. 2013, 19: 235-240
- [4] XUE Shouqing. Synthesis and Properties of Schiff Base Self-Assembled Monolayers on Stainless Steel Surface, Chinese Journal Of Applied Chemistry, 2013, 30(3):349-353
- [5] ZHANG Xin, ZHANG Kui, LI Xinggang, et al. Effect of solid-solution treatment on corrosion and electrochemical behaviors of Mg-15Y alloy in 3.5 wt.% NaCl solution, Journal Of Rare Earths, Vol. 30, No. 11,

1 Nov. 2012, P. 1158-1167

2
3 [6]Jing Huang, Yi Liu,Jianhui Yuan,et al. Al/Al₂O₃ Composite Coating Deposited by Flame Spraying for Marine
4
5 Applications: Alumina Skeleton Enhances Anti-Corrosion and Wear Performances, Journal of Thermal Spray
6
7 Technology, April 2014, Volume 23, Issue 4, pp 676-683
8
9

10
11 [7] Y. M. Volfkovich, D. A. Bogachev, A. A. Mikhalin,et al. Supercapacitor carbon electrodes with high
12
13 capacitance, Journal of Solid State Electrochemistry, May 2014, Volume 18, Issue 5, pp 1351-1363
14
15

16
17 [8] K. Mosnáčková, M. Chehimi, P. Fedorko,et al. Polyamide grafted with polypyrrole: formation, properties, and
18
19 stability, Chemical Papers, August 2013, Volume 67, Issue 8, pp 979-994
20
21

22
23 [9] Wen-Tyng Li,Mu-Feng Shie, Chung-Feng Dai, Jui-Ming Yeh . Electrospinning Poly(*o*-methoxyaniline)
24
25 Nanofibers for Tissue Engineering Applications, XII Mediterranean Conference on Medical and Biological
26
27 Engineering and Computing 2010 IFMBE Proceedings Volume 29, 2010, pp 596-599
28
29

30
31 [10] Dong-Mei Zhou, Yi-Qing Dai, Kwok-Keung Shiu. Poly(phenylenediamine) film for the construction of
32
33 glucose biosensors based on platinized glassy carbon electrode Journal of Applied Electrochemistry, November
34
35 2010, Volume 40, Issue 11, pp 1997-2003
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65