
VDX3-6790

Company: DMP
Site: www.dmp.com.tw
Oven Name: Line-D-VDX3-6790-A1-TOP
Process Window Name: Senju spec (DMP)

Setpoints (攝氏)

Zone	1	2	3	4	5	6	7	8	9	10	11	12
Top	160	162	165	170	180	200	215	215	220	230	260	265
Bottom	160	162	165	170	180	200	215	215	220	230	260	265

Conveyor Speed (cm/min): 83.00

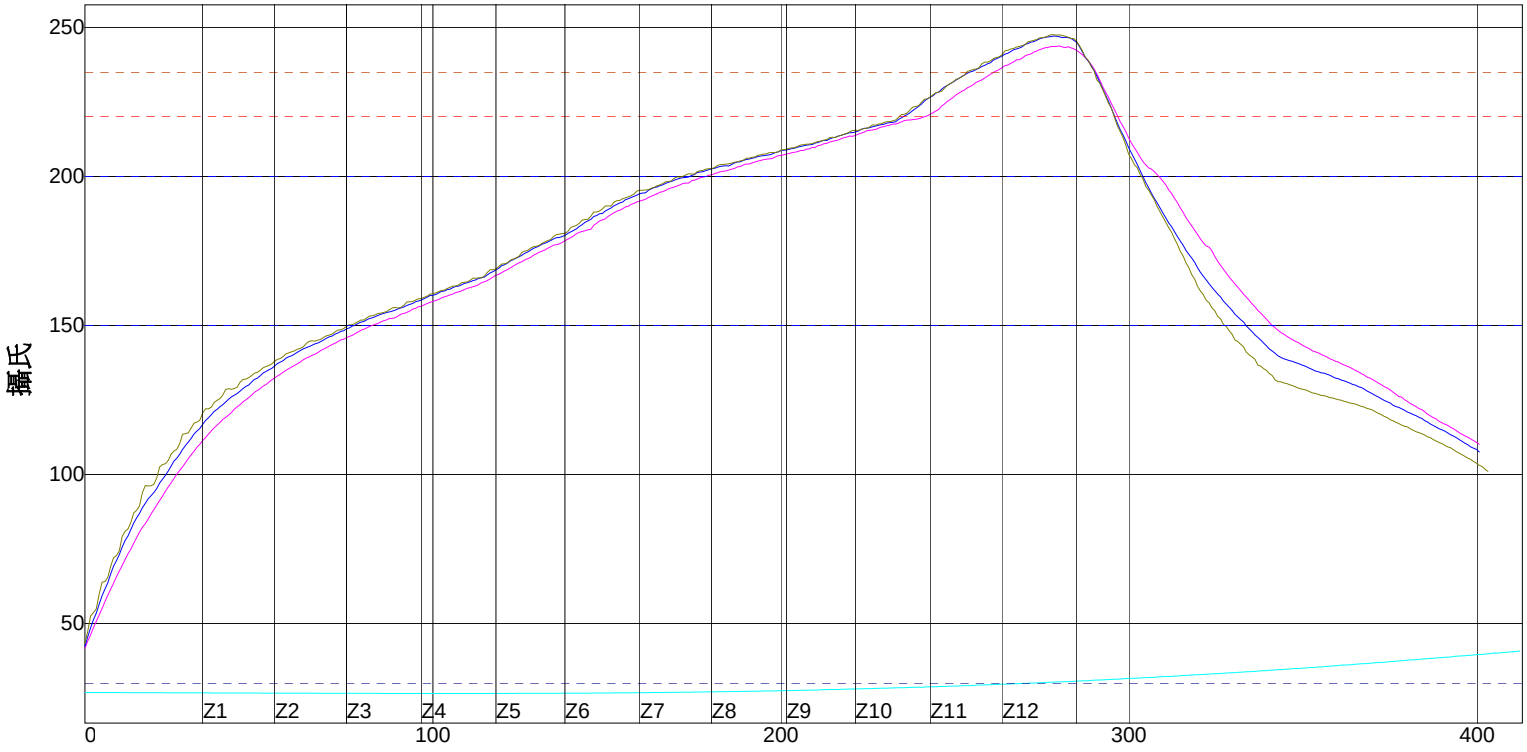

PWI= 66%	Max Rising Slope		Max Falling Slope		Preheat 30-150C		Soak Time 150-200C		Reflow Time /220C		Peak Temp		Tot Time /235C	
VX86DX	2.31	-47%	-1.95	53%	81.75	-28%	95.82	19%	55.62	-44%	243.80	10%	29.14	-9%
DDR2-128M*8	2.53	-27%	-2.42	29%	76.95	-44%	96.07	20%	61.01	10%	247.16	37%	35.85	58%
ADM213	2.63	-19%	-2.49	26%	74.70	-51%	96.22	21%	61.90	19%	247.62	41%	36.64	66%
Delta	0.33		0.54		7.05		0.40		6.28		3.81		7.50	

Process Window:

Solder Paste: Senju spec (DMP)

Statistic Name	Low Limit	High Limit	Units
Max Rising Slope (Target=2.8) (Calculate Slope over 20 Seconds)	1.7	4.0	Degrees/Second
Max Falling Slope (Calculate Slope over 20 Seconds)	-5.0	-1.0	Degrees/Second
Preheat Time 30-150C	60	120	Seconds
Soak Time 150-200C	60	120	Seconds
Time Above Reflow - 220C	50	70	Seconds
Peak Temperature	230	255	Degrees Celsius
Total Time Above - 235C	20	40	Seconds

Description:

測溫員:_____ 審核:_____

KIC
San Diego, CA USA

Profiled Using KIC 2000 Technology
Tel: +1 858 673 6050
Fax: +1 858 673 0085

www.kicthermal.com
tech@kicmail.com