

Test Report



No:250267646

Verification Website: www.gttctech.com

Verification Code: BCYN-5504-54

Scan to download



Issue Date:2025-09-30

Applicant: 温州市金宸胶板有限公司

Address: 浙江省温州市瑞安市马屿镇篁社工业区时代创业园32幢101室

Information confirmed by applicant:

Talalay Latex Pillow

Quantity: 1 piece

Basis of judgement:

FZ/T 62036-2017 <Latex pillow and cushion>

Date Received/Date Test Started: 2025-09-27

Conclusion:

75% compression set

M

Rebound rate

M

65%/25% indentation ratio

M

Latex content analysis

Note: "M"-Meet the standard's requirement "F"-Fail to meet the standard's requirement

"---"-No comment

Remark:

All the tested items are tested under the standard condition (except for indication).

First-class product

This report is the english translation version of the report 250267428.

Copies of the report are valid only re-stamped.

The experiment was carried out at No.1, Zhujiang Road, Panyu District, Guangzhou, Guangdong, P.R.China.


Approved By: Shao Juan Chen

ShaoJuan Chen Engineer



Test Report

No:250267646

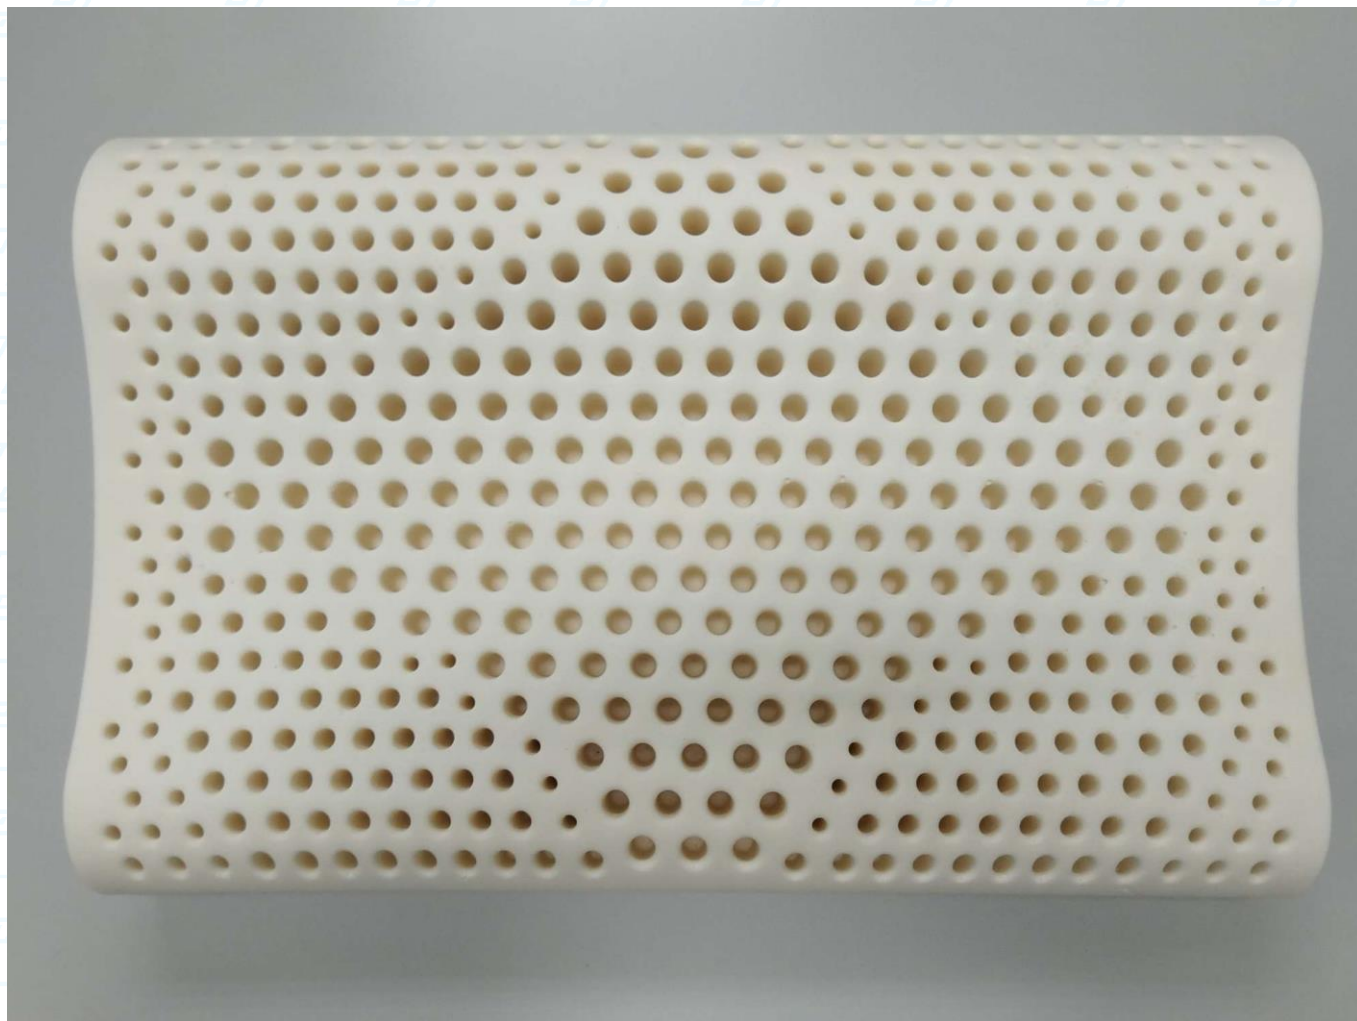

Headquarters: No.1, Zhujiang Road, Panyu District, Guangzhou, Guangdong, P.R.China.

Tel: +86-20- 61994598/61994599

Huadu Laboratory: No.1, Hebin West Road, Qiling, Huadu District, Guangzhou, Guangdong, P.R.China.

Tel: +86-20- 37721161/66348638

Test Report

No:250267646

75% compression set(%)

M

(GB/T 6669-2008 Method A Test conditions: 70°C, 22h)

5

Requirement
≤15

(FZ/T 62036-2017)

Rebound rate(%)

M

(GB/T 6670-2008 Method A)

69

Requirement
≥50

(FZ/T 62036-2017)

Remark: The sample contains holes and the test surface has no holes, the result is only for reference.

65%/25% indentation ratio

M

(GB/T 10807-2006 Method B Type of specimen: finished product)

2.4

Requirement
≥2.4

(FZ/T 62036-2017)



Page 1 of 1

Test Report

No: 250267428

● Latex content analysis

Test method:

1. Identification of polymer components:

GB/T 6040-2019, FTIR

GB/T 14837.1-2014, TGA

GB/T 29613.1-2013, (PyGC-MS)

2. Ash determination:

GB/T 4498.1-2013, method A

3. Determination of water-soluble protein content:

GB/T 21870-2008, Method A, ultraviolet visible spectrophotometer (UV-VIS)

4. Solvent extract

GB/T 3516-2006



Test Report

No: 250267428

Results:

Results(%):	The content of natural latex		93
	Ash		3
	Other substances		4
Remark	1	Natural latex includes polyisoprene, water-soluble protein, free fatty acid and other substances.	
	2	The sample was extracted by soxhlet before testing to remove the interference additive.	
	3	Pyrolysis analysis was used to assist qualitative analysis of polymer components.	
	4	The quantitative results are for reference only.	

—End of Report—



Note

1. The report is invalid without authorized stamp.
2. Copies of this report are invalid without authorized stamp.
3. Any dispute should be raised within 15 days after receiving the report.
4. The result is only valid for the tested sample.
5. The results of unapproved items are for reference only.
6. This report is invalid if altered.
7. Our company does not accept any responsibility for the authenticity of the information supplied by customers (including sample information).
8. The report shall not be duplicated separately or partly, without prior written permission approved by GTTC, except duplicated in full version.