KK-G-476c
June 6, 1966
SUPERSEDING
Fed. Spec. KK-G-476b
February 13, 1963

FEDERAL SPECIFICATION

GLOVES, LEATHER, GAUNTLET, LINEMEN'S

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers leather gauntlet work gloves where contact with live wires is not involved (see 6.1).

1.2 Classification.

1.2.1 *Type and sizes.* The gloves covered by this specification shall be of one type and furnished in the following sizes as specified (see 6.2):

Small.
Medium.
Large.
Extra large.

2. APPLICABLE DOCUMENTS

2.1 The following specifications and standards, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein.

Federal Specifications:

V-T-285—Thread, Polyester.
KK-L-311—Leather; Methods of Sampling and Testing.
UU-P-268—Paper, Kraft, Untreated, Wrapping.
CCC-C-419—Cloth, Duck, Cotton, Unbleached, Plied-Yarns, Army and Numbered.
CCC-T-191—Textile Test Methods.
DDD-L-20—Label; for Clothing, Equipage, and Tentage, (General Use).

Federal Standards:

Fed. Std. No. 123—Marking for Domestic Shipment (Civilian Agencies).
Fed. Std. No. 751—Stitches, Seams, and Stitchings.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, D. C. 20402.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, and Seattle, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Specification:

MIL-B-17757—Boxes, Fiber, Corrugated (Modular Sizes).

Military Standards:

MIL-STD-105—Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129—Marking for Shipment and Storage.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

3. REQUIREMENTS

3.1 Guide samples. Samples, when furnished, are solely for guidance and information to the supplier (see 6.3). Variations from the specification may appear in the sample, in which case the specification shall govern.

3.2 Material.

3.2.1 *Leather.* The leather used shall be as specified in 3.8.1 and 3.8.2. The leather shall be chrome tanned. When grain horsehide is used, it shall be full grain horsehide fronts, i.e., sides with the butts trimmed off and the front shanks cut off. When grain cattlehide is used, it shall be full grain cattlehide sides or bends produced from thin spready cattlehides, selected for thinness. When split horsehide is used, it shall be flesh splits of horsehide fronts. When split cattlehide is used, it shall be made from flesh split cattlehide. Middle splits, head and shoulder, or belly splits of horsehide or cattlehides shall not be used.

3.2.1.1 *Thickness.* The thickness of leather glove parts shall be not less than 2-1/2 ounces nor more than 3-1/2 ounces. (Note: An ounce is equivalent in thickness to 1/64 inch.) Thickness determinations shall be conducted as specified in 4.2.2.1.2.

3.2.1.2 *Color.* The color of all leather components shall be cream or light gray. All leather components used in each pair of gloves shall be of the same color.

3.2.1.3 *Physical requirements.*

3.2.1.3.1 *Stitch tearing strength.* Not less than 80 percent of the specimens tested shall have a stitch tearing strength of not less than 25 pounds when tested as specified in 4.2.1.1. This requirement shall not apply to the leather welting or reinforcements.

3.2.1.3.2 *Stiffness.* Not less than 80 percent of the leather specimens, when tested as specified in 4.2.1.1.1, shall each have a load scale reading, before and after soaking of not more than those specified below.

Stiffness test	Load scale reading
Before soaking	12
After soaking	15

3.2.1.3.3 *Shrinkage temperature.* The shrinkage temperature of the leather shall be not less than 97°C. when tested as specified in 4.2.1.1.

3.2.1.3.4 *Chemical requirements.* The leather shall be fully chrome tanned and shall conform to the requirements of table I when tested as specified in 4.2.1.1.

TABLE I. *Chemical requirements of leather*

	Minimum	Maximum
Chromic oxide, percent[1]	3.0	—
Chloroform extract, percent[1]	10.0	25.0
Ash, percent[1]	—	12.0
Acidity (pH)	3.5	5.0

[1] Calculated on a moisture-free basis.

3.2.2 *Thread.* The thread used for stitching and seaming the gloves shall be white thread, polyester, size E, conforming to type I or II, class 1 or 2, subclass A of V-T-285.

3.2.3 *Gauntlet lining.* The gauntlet lining shall be either unbleached cotton duck conforming to the requirements for type I, number 8, hard texture numbered duck described in CCC-C-419, or gauntlet lining fabric composed of two thicknesses of unbleached cotton fabric securely laminated together. The laminated fabric shall be composed of a cotton twill face fabric weighing not less than 5 ounces per square yard and plain weave cotton backing fabric weighing not less than 2.5 ounces per square yard. The finished fabric (laminated) shall contain not less than 14 ounces of natural rub-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

ber, synthetic rubber, or synthetic resin and weigh not less than 21.5 ounces per square yard.

3.2.4 *Label.* Each glove shall have a combination size and identification label conforming to type III or IV, class 4 of DDD-L-20. The marking medium shall be dark blue or black and shall show fair color fastness to accelerated laundering when tested as specified in DDD-L-20.

3.3 Stitches, seams, and stitching. All stitching and seaming shall be done with stitch type 301 and seam types as specified in table II in conformance with the requirement of Fed. Std. No. 751, using not less than 7 nor more than 10 stitches per inch. The stitching margin shall be 1/16 to 1/8 inch. All ends of stitching shall be backstitched not less than 1/2 inch. All thread ends shall be trimmed.

TABLE II. *Stitches and seams in linemen's gloves*

Operation	Rows of stitching	Gage	Seam and stitching types
		Inch	
Uniting welt, palm, and fourchette	Double	1/16 to 3/32	LSa-2
Joining palm and thumb	Single	—	SSa-1
Joining fingers .	Single	—	SSa-1
Sewing back seam	Double	1/16 to 3/32	LSa-2
Making gauntlet	Double	1/8 to 3/16	LSa-2
Hemming gauntlet	Single	—	EFa-1
Joining gauntlet to hand section	Double	1/8 to 3/16	LSa-2
Turning flap over gauntlet	Double	1/8 to 3/16	SSa-2
Closing seam[1] ..	Single	—	SSa-1

[1] A second row of stitching 1/16 inch back of the first row shall be stitched on the hand section.

TABLE III. *Finished dimensions of gloves*

Measurement	Sizes				Tolerance plus or minus
	Small	Medium	Large	Extra large	
	Inches	*Inches*	*Inches*	*Inches*	*Inch*
A. Top edge of cuff to tip of second finger	12 3/4	13	13 1/2	14	1/2
B. Bottom edge of cuff to tip of second finger	7 3/4	8	8 1/2	8 3/4	1/4
C. Across palm at thumb, crotch, seam to seam	4 1/2	5	5 1/2	5 3/4	1/8
D. Tip of index finger to thumb crotch ...	4 3/4	5	5 1/2	5 3/4	1/8
E. Thumb crotch to tip of thumb	2 3/4	3	3 1/4	3 1/2	1/8
F. Across bottom edge of cuff	4 3/4	5	5 1/2	6	1/4
G. Across top edge of cuff	6 1/4	6 3/4	7	7 1/2	1/4

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

3.4 Dies and patterns. The dies or patterns for cutting all parts of the gloves shall be furnished by the supplier and shall be of the proper proportions to provide good fitting gloves conforming to finished measurements in table III.

3.5 Figures. Figure 1 is furnished for information purposes only. To the extent of any inconsistencies between the written specification and the figures, the written specification shall govern.

3.6 Dimensions of gloves. The finished gloves shall conform to the dimensions shown in table III. Measurements shall be taken as shown in figure 1.

3.7 Dimensions of reinforcements. The flap reinforcing front seam, joining palm and bottom of gauntlet, shall be approximately 2 inches wide. The thumb welt shall be approximately 1/2 inch wide; the welt for base of fingers approximately 5/8 inch wide; and the welt for the "Davey" tips shall be cut approximately 5/8 inch wide.

3.8 Detail requirements—leather.

3.8.1 *Hand section.* The back of the glove shall be split cattlehide leather. The palm, thumb, fingers, and reinforcing pieces shall be full grain horsehide or cattlehide leather as specified. All grain leather components shall be made of the same kind of leather.

3.8.2 *Gauntlet.* The gauntlet shall be split horsehide or split cattlehide leather.

3.9 Design. The design of the glove shall be a two-piece, half outseamed, slip-on style, Gunn-cut glove, with a hemmed gauntlet. The continuous thumb shall be inseamed around all edges with a welt of the leather inserted in the seam. The seam at the base and tips of the fingers shall include a leather reinforcing welt turned up to protect the stitching. A palm reinforcing flap is attached to the top of the hand and bottom of the gauntlet, on the palm side, as shown in figure 1.

3.10 Marking. The label, specified in 3.2.4, shall be applied to the inside of the back of each glove at center, approximately 1/2 inch down from the finished top edge.

3.11 Construction.

3.11.1 *General.*

3.11.1.1 *Glove section.* The thumb shall be of "inseam" construction, the fingers of "outseam" construction; the thumb shall be finished with an "all-around-turn-back" welt, and the ends of the fingers with similar welts, "Davey" tips. A protective welt shall be provided for the fourchette stitching, caught in the seaming of the fourchette and turned back over the bottom of the fingers. In addition, the top of the palm and fingers shall be reinforced with a flap which shall be caught in the seaming of the gauntlet, turned back, and sewed down to the gaunlet.

3.11.1.2 *Gauntlet.* The gauntlet shall be made in two pieces, each piece lined with cotton duck or laminated cotton fabric extending to within 3/8 inch of the top edge of the gauntlet to facilitate the hemming of the top edge. The remainder of the glove shall be unlined. The joining of the gauntlet and the closing shall be of outseam construction.

3.11.2 *Detailed.*

3.11.2.1 *Cutting.* Skins shall be dampened and all the stretch in the lengthwise direction pulled out before cutting gloves. Each leather component shall be cut in the length direction.

3.11.2.2 *Join palm to fourchette.* Lap the palm over the fourchette, position the welt piece on top on a line with the edge of the palm, with the grain of the leather of welt over and against the grain of the leather of the palm. Unite welt, palm, and fourchette with a double row of stitching 1/16 to 3/32 inch gage; 301 stitch type, seam type LSa-2. The welt piece shall be so positioned that

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

when turned back over the seam, it shall measure not less than 1/2 inch wide and match the grain of the palm. The contacting corners of the welt piece shall be caught in the seaming of the first finger and little finger, respectively. The beginning and end of the stitching shall be securely backstitched with not less than three stitches. Special care shall be exercised in the operation to avoid any twisting or distortion of the fingers.

3.11.2.3 *Join thumb and palm—inseam construction.* Seam the thumb to the palm all around the edge of the thumb; stitch type 301, seam type SSa-1. The welt strip shall be so positioned on top of the seam and caught in the stitching that when turned back it shall match the grain of the leather thumb. The welt strip shall extend to the top of the glove. The top edges of the thumb and welt shall be caught in the seam joining the gauntlet to the hand section.

3.11.2.4 *Join fingers—outseam construction.* The end of each of the four fingers shall have protective welt strips like the welt strip of the thumb, positioned as indicated by figure 1. Seam the backs to the fronts around the fingers with the welts laid on the seam and caught in the stitching, so positioned that when turned back, they shall match the grain of the finger leather. The seaming shall be so performed as to prevent any twisting or distortion of the fingers. The end of the seaming shall be securely backstitched not less than 1/2 inch. Stitch type 301 and seam type SSa-1 shall be used.

3.11.2.5 *Back seam.* Lap the front of the glove over the back of the glove and unite with a double row of stitching 1/16 to 1/8 inch gage; stitch type 301, seam type LSa-2. (See fig. 1.)

3.11.2.6 *Making gauntlet.* The two lined gauntlet pieces (see 3.11.1.2) shall be joined on the side next to thumb side of glove by overlapping the face over the back and double stitching 1/8 to 3/16 inch gage; 301 stitch type, seam type LSa-2.

3.11.2.7 *Hemming gauntlet.* The top leather edge of gauntlet shall be turned in 1/2 to 5/8 inch and single stitched 1/16 to 1/8 inch from raw edge, 301 stitch type, seam type EFa-1.

3.11.2.8 *Joining gauntlet to hand section.* The bottom edge of lined gauntlet shall be attached to top of hand at wrist by overlapping the gauntlet over the hand and stitching with a double row of stitching, 1/8 to 3/16 inch gage; 301 stitch type, seam type LSa-2.

3.11.2.9 *Attach flap (reinforcement piece) at wrist.* The flap shall be caught in seam joining palm side of gauntlet to hand portion and turned over seam with grain side facing outward. It shall then be stitched to the gauntlet with a double row of stitching around the sides and top edge of flap, 1/8 to 3/16 inch gage; 301 stitch type, seam type SSa-2.

3.11.2.10 *Closing.* The side seam from the tip of fourth finger down to hem of gauntlet shall be outseamed single stitched; 301 stitch type, seam type SSa-1. A second row of stitching 1/16 inch back of first row shall be stitched on glove section from tip of fourth finger down the side to joining of gauntlet with hand section.

3.12 Pairing. The gloves shall be matched, paired, and tacked together with thread. Tacking shall be done with not less than two stitches using a cord thread which will permit the pair to be pulled apart without tearing the leather.

3.13. Workmanship. The finished gloves shall conform to the quality and grade of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels (AQLs).

4. QUALITY ASSURANCE PROVISIONS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.2 Inspection. Inspection shall be in accordance with the provisions of MIL-STD-105, except where otherwise indicated herein. In addition to sampling inspection as set forth in MIL-STD-105, process inspection will be performed during manufacture of the gloves, to determine compliance with all required operations and processes which cannot be determined in the completely fabricated gloves. Any deviation found in process inspection may be cause for rejection of the end item or items.

4.2.1 *Component and material inspection.* In accordance with 4.1, components and materials shall be tested in accordance with all requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable purchase documents. In addition, testing shall be performed on components as specified in 4.2.1.1 and 4.2.1.2.

4.2.1.1 *Testing of leather.* In addition to the quality assurance provisions of applicable subsidiary specifications and standards, testing shall be performed on components listed in table IV for the characteristics shown. The test methods listed in table IV shall be in accordance with KK-L-311, wherever applicable. Sampling procedure and location from which the sample unit is to be obtained shall be in accordance with the sampling of nonfabricated leather, as defined in sampling and acceptance procedures of KK-L-311. The lot shall be rejected if any one of the following conditions exist:

a. More than 3 of the test specimens fail to meet the specified requirements for stitch tearing strength or stiffness.
b. More than one test failure occurs for any of the remaining requirements applicable to the sample unit.
c. Any lot average or composite value fails to meet the specified requirement.

TABLE IV. *Leather components tests*

Component and lot size expressed in terms of:	Characteristic	Requirement paragraph	Requirement applicable to:			
			Test method	Sample unit	Lot average	Composite
Leather (when horsehide 1 front) (when cattlehide 1 side or 1 bend)	Material identification	3.2.1	[1]	—	—	—
	Tannage	3.2.1	[1]	—	—	—
	Stitch tearing strength	3.2.1.3.1	2151[2]	X	—	—
	Stiffness	3.2.1.3.2	4.2.1.1.1	X	—	—
	Chromic oxide	3.2.1.3.4	6515	—	—	X
	Chloroform extract	3.2.1.3.4	6311	—	—	X
	Ash, total	3.2.1.3.4	6421	—	—	X
	Acidity (pH)	3.2.1.3.4	6621	—	—	X
	Shrinkage temperature	3.2.1.3.3	7011[3]	—	X	—

[1] A supplier's certificate of compliance will be acceptable for this characteristic. It shall be accompanied by actual test, inspection, or other verifiable data.
[2] The thickness of the specimen need not be determined.
[3] Exception to method 7011. The heating medium shall be water.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE V. *Fabric component tests*

Component	Characteristic	Requirement reference	Test method
Face fabric	Material identification	3.2.3	1200[1]
	Weight (oz. per sq. yd.)	3.2.3	5041[1]
	Weave	3.2.3	Visual
Backing fabric	Material identification	3.2.3	1200[1]
	Weight (oz. per sq. yd.)	3.2.3	5041[1]
	Weave	3.2.3	Visual
Finished fabric	Weight (oz. per sq. yd.)	3.2.3	5041

[1] A supplier's certificate of compliance will be acceptable for this characteristic. It shall be accompanied by actual test, inspection, or other verifiable data.

4.2.1.1.1 *Stiffness.*

4.2.1.1.1.1 *Before soaking.* The leather specimen shall be 3 by 4 inches, cut with the long dimension perpendicular to the backbone. The specimen shall be folded in half, grain side out, to form a rectangle 3 by 2 inches (crease parallel to backbone), then carefully folded in half again to form a rectangle approximately 3 by 1 inch, 4 layers thick. The folded specimen shall be secured with the staples across the width, 1/4 inch from each end. The ends shall be gripped between thumb and forefinger, and the specimens shall be twisted torquewise 40 times back and forth approximating an angle of 180° in each direction. One end of the specimen shall then be fastened in the vise of the tester in such a way that the cut edges on the upper side face outward from the machine. The other end of the specimen shall extend 2 inches from the vise. The stiffness of the specimen shall be determined as specified in method 4211 of KK-L-311 by bending the specimen 20° using a 1-inch span and a load unit of 0.5 pound. The results shall be recorded in terms of the load scale reading.

4.2.1.1.1.2 *After soaking.* The folded and stapled specimens which pass the requirement applicable to 4.2.1.1.1.1, shall then be immersed in distilled water of 140° ± 5°F. (60° ± 3°C.) for 20 ± 2 hours. One thousand ml. of water shall be used for 15 specimens. Complete immersion of the specimens shall be accomplished by placing a floating cover on the vessel used for the immersion. The specimens shall be removed, air dried and conditioned for 72 hours in the standard atmosphere specified in section 7 of KK-L-311, and tested for stiffness in folded and stapled condition in accordance with the preparation and test method described in 4.2.1.1.1.1.

4.2.1.2 *Fabric testing.* The fabric shall be tested for the characteristics in table V. The test methods listed in table V shall be in accordance with CCC-T-191, wherever applicable. Testing for all requirements listed in table V are applicable to the sample unit. The sample size shall be as follows:

Lot size (yards)	Sample size
800 or less	2
801 up to, and including 22,000	3
22,001 and over	5

The lot shall be unacceptable if one or more units fail to meet any requirements specified.

4.2.2 *Inspection of the end item.*

4.2.2.1 *Examination of the end item.* The defects found during examination of the end product shall be classified in accordance with 4.2.2.1.1 and 4.2.2.1.2 The applicable inspection levels and AQL's shall be as indicated in 4.2.2.1.3. The sample unit for this examination shall be one glove. Selection of the sample shall be by pairs. The sample unit for pairing defects shall be one pair. Defects for pairing shall be classified as a single defect. The lot size shall be expressed in terms of one glove each.

4.2.2.1.1 *Visual examination of gloves.* The gloves shall be examined for defects in

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

pairing, color, design, construction, material, workmanship, and marking as indicated in table VI.

TABLE VI. *Classification of defects*

Examine	Defect	Classification	
		Major	Minor
Pairing	Not properly mated, e.g., not right and left of same size ..	X	
	Not tacked together		X
	Wide variation in color in the pair ..		X
Color	Not as specified ...	X	
	Color not uniform or shaded parts clearly noticeable .		X
Design	Any characteristic not in accordance with the specified requirements (unless otherwise classified herein) .	X	
Cleanliness	Spots or stains, clearly noticeable .		X
Material	Any through hole, cut, tear, or rip ..	X	
Leather, general	Not cattlehide or horsehide (where specified)	X	
	Not full grain (where specified) .	X	
	Not split leather (where specified) .		X
	When cattlehide or horsehide split leather is middle split or is cut from head, shoulder, or belly split	X	
Leather	Loose or spongy ..	X	
	Flanky leather seriously affecting serviceability	X	
	Flanky leather affecting serviceability but not seriously		X
	Not soft and pliable	X	
	Open vein		X
	When applicable, grain damage penetrating deeply into leather fibers ...	X	
	When applicable, grain damage not penetrating deeply into leather fibers		X
	Deep open scratch or grub hole	X	
	Scratch or grub or tick marks not penetrating deeply into leather fibers seriously affecting appearance		X
	Deep fat wrinkles .	X	
	Deep flesh cut	X	
	Any scar, brittle or bony area, weak or thin spot, or abraded area seriously affecting serviceability	X	
	Any scar, bony or abraded area affecting serviceability but not seriously		X
	Cluster of healed grub marks or other healed damage seriously affecting appearance		X
	Flesh side of grain leather or either side of split leather not smooth or contains excessively loose flesh more than two square inches in total area		X
	Leather improperly cut, i.e. excessive stretch in length direction of glove .	X	
Gauntlet lining	Any hole, cut, or tear	X	
	Multiple floats, loose ends, smashes, or slubs		X
	Any broken or missing pick or end ..		X
	Any mend in fabric (except restitching of seams)		X
Construction and workmanship	Any component or operation omitted .	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE VI. *Classification of defects (cont'd)*

Examine	Defect	Classification	
		Major	Minor
General (applicable to all components unless otherwise indicated herein)	Any component misplaced or not serving purpose intended		X
	Any component missing	X	
	Any component or assembly damaged	X	
	Any component not securely affixed, e.g., gauntlet loosely attached to back or palm of glove ..	X	
	Any workmanship damage, e.g., scissor or knife cut ..	X	
	Any mend in leather, e.g., patch (not applicable to restitched seam repair)	X	
	Needle chews	X	
Seams and stitching	Any open seam .... Note: When one or more stitches are broken or two or more consecutive skipped stitches or run-offs occur on a single stitched seam or on both rows of stitching on a double stitched seam, it shall be classified a *major* defect. When one or more stitches are broken or two or more consecutive skipped stitches or run-offs occur on only one row of a double stitched seam, it shall be classified as a *minor* defect.		
	Not specified seam type	X	
	Not specified stitch type	X	
	Any row of stitching omitted	X	
	Loose stitch tension resulting in a loosely secured seam ..	X	
Seams and stitching (cont'd)	Tight stitch tension resulting in cutting of leather or breaking of stitches when normal pull is applied	X	
	Ends of stitching not backstitched as specified		X
	Gage or margin of stitching irregular or not as specified affecting serviceability seriously ..	X	
	Gage or margin of stitching irregular or not as specified affecting serviceability but not seriously		X
	Any part caught in unrelated row of stitching	X	
	One or two stitches per inch less than specified		X
	Three or more stitches per inch less than specified	X	
	More than the specified maximum number of stitches per inch damaging leather	X	
	More than the specified maximum number of stitches per inch not damaging leather		X
Assembly detail	Glove not neatly laid off		X
	Not outseam or inseam construction where specified ...	X	
	Finger distorted or twisted affecting comfort of wearer	X	
	Thread ends not trimmed throughout glove		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE VI. *Classification of defects (cont'd)*

Examine	Defect	Classification	
		Major	Minor
Assembly detail (cont'd)	Not properly trimmed or finished, e.g., lump or bulk in finger inseam because leather was not properly trimmed .	X	
	Not constructed with specified number of pieces of leather (except welting and reinforcements) ..	X	
	Welting reinforcing flap or reinforcements, missing, or not caught by stitching	X	
	Binding loosely applied, or any edge not turned under and caught in stitching		X
	Gauntlet not lined .	X	
Marking	Missing, incomplete, incorrect, not legible, not specified size, not in proper location, or not accomplished in the specified manner ..		X

4.2.2.1.2 *Dimensional examination.* The gloves shall be examined for dimensional defects including thickness of leather. Any dimension that is not within the established tolerance shall be classified a defect.

Note: Each leather part of the glove shall be checked for thickness, i.e., palm, thumb, and body of gloves. Any of these parts that are not within the required thickness range shall constitute a defect. (Thickness shall be determined in accordance with the procedure for "Fabricated-Leather Articles" of method 1011 KK-L-311.) Where glove parts are lined, the lining should be parted from the leather and the thickness of the leather should be taken doubled. This dimension is then divided by two.

4.2.2.1.3 *Inspection levels and AQL's.* The inspection levels and AQLs, expressed in defects per 100 units, shall be as follows:

Examination	Inspection level	AQL	
		Major	Total
Par 4.2.2.1.1	II	2.5	6.5
Par 4.2.2.1.2	S-3	—	4.0

4.2.3 *Examination of preparation for delivery requirements.* An examination shall be made to determine that packaging, packing, and marking requirements of section 5 are complied with. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery with the exception that it need not be sealed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the AQL shall be 2.5 defects per hundred units.

Examine	Defect
Marking (exterior and interior)	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing or damaged.
Workmanship	Inadequate application of components, such as: Incomplete closure of container flaps, loose strapping, inadequate stapling.
	Bulging or distortion of containers.
Content	Number of bundles per shipping container is more or less than required.
	Number of pairs of gloves per bundle is more or less than required.[1]

[1] For this defect, two bundles shall be examined from each shipping container in the sample.

5. PREPARATION FOR DELIVERY

5.1 Packaging shall be level A or C, as specified (see 6.2).

5.1.1 *Level A.* Four pairs of gloves, of one size only, shall be evenly stacked in a bundle. The gloves shall be alternately reversed, fingertip to gauntlet, with the small fingers of each pair positioned in each corner of the bundle. Each glove bundle shall be securely tied with cotton tape or twine.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

5.1.2 *Level C.* Gloves shall be packaged in accordance with the industry's practice.

5.2 **Packing.** Packing shall be level A, B, or C, as specified (see 6.2).

5.2.1 *Level A.* Eighty pairs of gloves of one size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled, closed, and reinforced conforming to class weather-resistant, size 3 of MIL-B-17757. Level A packages shall be packed flat, four in length, one in width, and five in depth within a shipping container. Each container shall have the contents completey covered on the top and bottom with a sheet of 30-pound minimum basis weight kraft paper conforming to grade B of UU-P-268.

5.2.2 *Level B.* Eighty pairs of gloves of one size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled and closed conforming to class domestic, size 3 of MIL-B-17757. Level A packages shall be packed flat, four in length, one in width, and five in depth within a shipping container. Each container shall have the contents completely covered on the top and bottom with a sheet of 30-pound minimum basis weight kraft paper conforming to grade B of UU-P-268.

5.2.3 *Level C.* Gloves, packaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. Containers shall be in accordance with rules or regulations of carriers applicable to the mode of transportation.

5.3 **Marking.**

5.3.1 *Military requirements.* In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with MIL-STD-129.

5.3.2 *Civil agencies.* In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with Fed. Std. No. 123.

6. NOTES

6.1 **Intended use.** This glove is intended for use by linemen or others where contact with live wires is not involved.

6.2 **Ordering data.** Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(*a*) Title, number, and date of this specification.

(*b*) Size required (see 1.2).

(*c*) Selection of applicable levels of packaging and packing required (see 5.1 and 5.2).

6.3 **Samples.** For access to samples, address the procuring activity issuing the invitation for bids.

MILITARY CUSTODIANS:

Army—GL
Navy—SA
Air Force—67

Review activities:
Navy—SA, YD
Air Force—67

User activities:
Army—SM
Navy—WP, MC, CG

Preparing activity:
Army—GL

Review and user information is current as of the date of this document. For future coordination of changes to this document, draft circulation should be based on the information in the current Federal Supply Classification Listing of DOD Standardization Documents.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

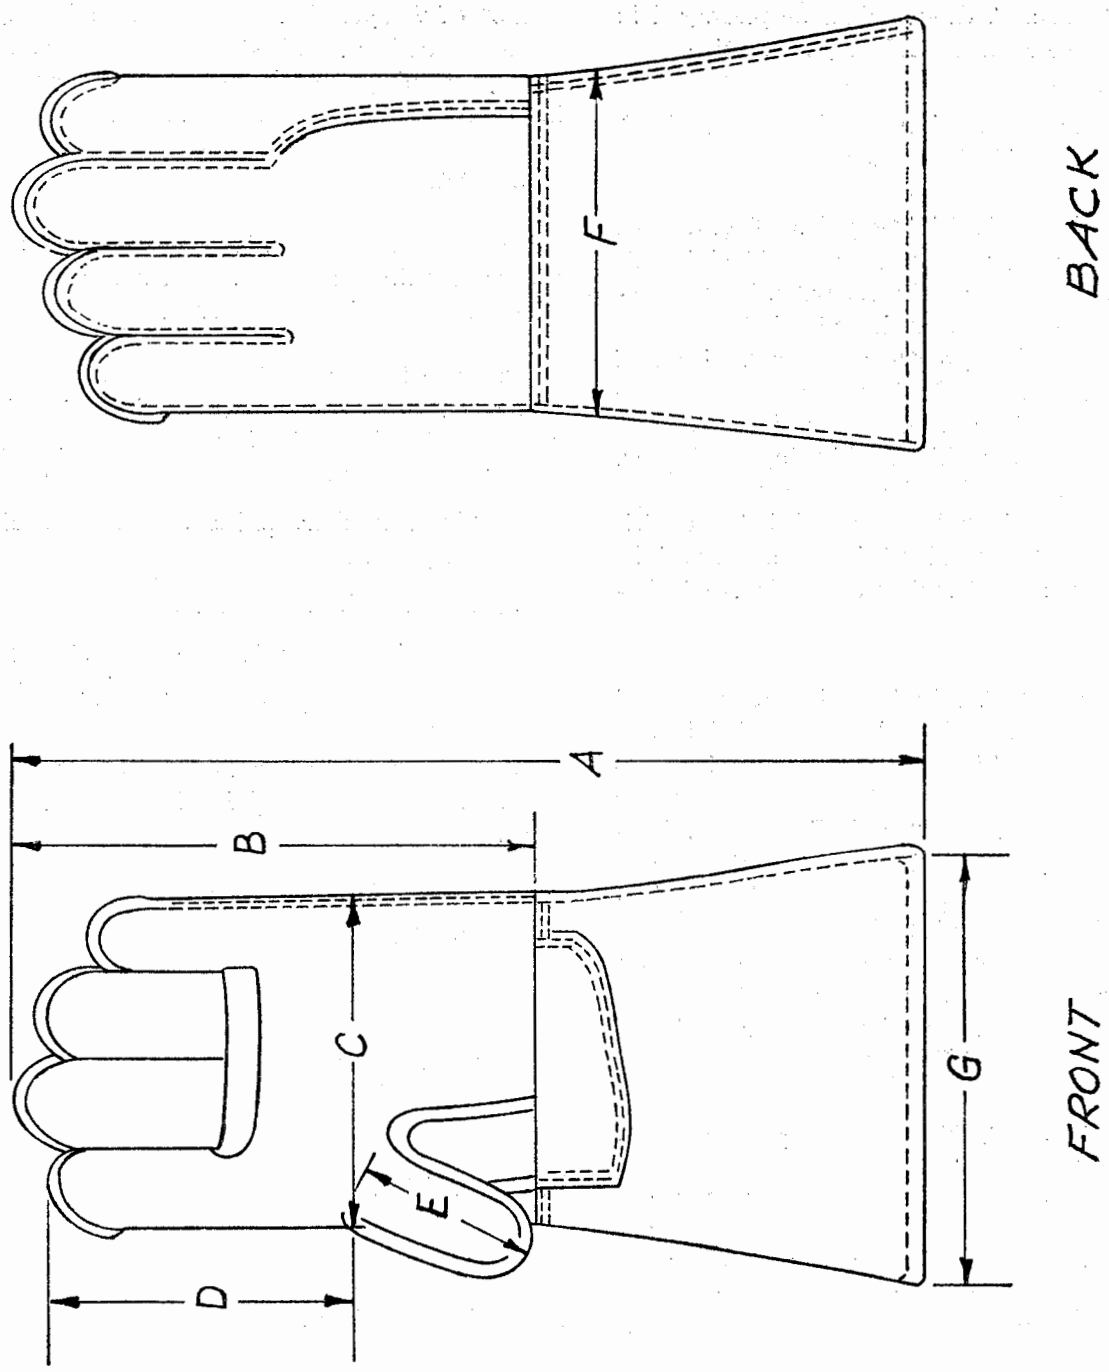


FIGURE 1. Gloves, leather, gauntlet, linemen's

Orders for this publication are to be placed with General Services Administration, acting as an agent for the Superintendent of Documents. See section 2 of this specification to obtain extra copies and other documents referenced herein. [illegible]nts each.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

"To detach this form, cut along this line"

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 119-R004

INSTRUCTIONS

This sheet is to be filled out by personnel either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity.

SPECIFICATION

Gloves, Leather, Gauntlet, Linemen's KK-G-476c

ORGANIZATION	CITY AND STATE

CONTRACT NO.	QUANTITY OF ITEMS PROCURED	DOLLAR AMOUNT
		$

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO IF "YES", IN WHAT WAY?

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity)*	DATE

DD FORM 1 OCT 64 1426

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE ARMY
U. S. Army Natick Laboratories
Natick, Massachusetts 01762

POSTAGE AND FEES PAID
DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS

Commanding General
U. S. Army Natick Laboratories
ATTN: AMXRE-SS
Natick, Massachusetts 01762

FOLD

"to detach this form, cut along this line"

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.