KK-G-476D
August 6, 1969
SUPERSEDING
Fed. Spec. KK-G-476C
June 6, 1966

FEDERAL SPECIFICATION

GLOVES, LEATHER, GAUNTLET, LINEMEN'S

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers leather gauntlet work gloves used where contact with live wires is not involved (see 6.1).

1.2 Classification.

1.2.1 Type and sizes. The gloves covered by this specification shall be of one type and furnished in the following sizes as specified (see 6.2):

Small
Medium
Large
Extra large

2. APPLICABLE DOCUMENTS

2.1 The following specifications and standards, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Specifications:

V-T-285	-	Thread, Polyester.
KK-L-162	-	Leather, Cattlehide, Chrome-Tanned, for Gloves, Garments, and Equipage.
KK-L-169	-	Leather, Horsehide, Chrome Tanned, for Gloves, Garments, and Equipage.
UU-P-268	-	Paper, Kraft, Untreated, Wrapping.
CCC-C-419	-	Cloth, Duck, Cotton, Unbleached, Plied-Yarns, Army and Numbered.
DDD-L-20	-	Label; for Clothing, Equipage and Tentage, (General Use).
PPP-B-636	-	Box, Fiberboard.
PPP-F-320	-	Fiberboard; Corrugated and Solid, Sheet Stock (Container Grade), and Cut Shapes.

FSC 8415

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

Federal Standards:

Fed. Std. No. 123 - Marking for Domestic Shipment (Civilian Agencies).
Fed. Test Method Std. No. 191 - Textile Test Methods.
Fed. Test Method Std. No. 311 - Leather, Methods of Sampling and Testing.
Fed. Std. No. 751 - Stitches, Seams, and Stitchings.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington, D. C. 20402.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Fort Worth, Denver, San Francisco, Los Angeles and Seattle, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Specification:

MIL-B-17757 - Boxes, Fiberboard, Corrugated (Modular Sizes).

Military Standards:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issues in effect on date of invitation for bids or request for proposal shall apply:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

National Classification Board:

National Motor Freight Classification.

(Application for copies shall be addressed to the National Classification Board, 1616 P Street, N.W., Washington, D. C. 20036).

Uniform Classification Committee:

Uniform Freight Classification.

(Application for copies shall be addressed to the Uniform Classification Committee, 202 Union Station, 516 West Jackson Boulevard, Chicago, Ill. 60606.)

3. REQUIREMENTS

3.1 Guide samples. Samples, when furnished, are solely for guidance and information to the supplier (see 6.3). Variations from the specification may appear in the sample, in which case the specification shall govern.

3.2 Material.

3.2.1 Leather. The leather used shall be as specified in 3.8.1 and 3.8.2. When horsehide leather is used, the full grain horsehide shall conform to type I, class 2 and the horsehide splits shall conform to type III, class 2 of KK-L-169 except that the requirements for staining, cracking, and maximum elongation are not applicable. When cattlehide leather is used, the full grain cattlehide shall conform to type I, class 2 and the cattlehide splits shall conform to type III, class 2 of KK-L-162, except that the requirements for staining, cracking, and maximum elongation are not applicable. Application of a finish to the grain surface is prohibited.

3.2.1.1 Thickness. The thickness of leather glove parts shall be not less than 2-1/2 ounces nor more than 3-1/2 ounces. (Note: An ounce is equivalent in thickness to 1/64 inch). Thickness determinations shall be conducted as specified in 4.2.2.1.2.

3.2.1.2 Color. The color of all leather components shall be cream or light gray. All leather components used in each pair of gloves shall be of the same color.

3.2.1.3 Physical requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

3.2.1.3.1 Stiffness. Not less than 80 percent of the leather specimens tested shall have a load scale reading of not more than 40.0 before soaking and not more than 50.0 after soaking when tested as specified in 4.3.1.

3.2.2 Thread. The thread used for stitching and seaming the gloves shall be white thread, polyester, size E, conforming to type I or II, class 1 or 2, subclass A of V-T-285.

3.2.3 Gauntlet lining. The gauntlet lining shall be either unbleached cotton duck conforming to the requirements for type I, number 8, hard texture numbered duck described in CCC-C-419, or gauntlet lining fabric composed of two thicknesses of unbleached cotton fabric securely laminated together. The laminated fabric shall be composed of a cotton twill face fabric weighing not less than 3.7 ounces per square yard and plain weave cotton backing fabric weighing not less than 1.7 ounces per square yard. The finished fabric (laminated) shall contain not less than 14 ounces of natural rubber, synthetic rubber, or synthetic resin and weigh not less than 19.4 ounces per square yard.

3.2.4 Label. Each glove shall have a combination size and identification label conforming to type III or IV, class 4 of DDD-L-20. The marking medium shall be dark blue or black and shall show fair color fastness to accelerated laundering when tested as specified in DDD-L-20. The label shall include the information required by the applicable products labeling act.

3.3 Stitches, seams, and stitching. All stitching and seaming shall be done with stitch type 301 and seam types as specified in table I and **shall be in conformance with the requirement of Fed. Std. No. 751,** using not less than 7 nor more than 10 stitches per inch. Ends of all seams and stitching produced with 301 stitch type, when not caught in other seams or stitching, shall be backstitched not less than 1/2 inch. Thread breaks shall be secured by stitching back of break not less than 1/2 inch. Skipped stitches or thread breaks may be repaired using 301 stitch type. All thread ends shall be trimmed.

TABLE I. Stitches and seams in linemen's glove

Operation	Rows of stitching	Gage	Seam and stitching types
Uniting welt, palm, and fourchette	Double	1/16 to 3/32	LSa-2

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE I. Stitches and seams in linemen's glove (con.)

Operation	Rows of stitching	Gage	Seam and stitching types
Joining palm and thumb	Single	---	SSa-1
Joining fingers	Single	---	SSa-1
Sewing back seam	Double	1/16 to 3/32	LSa-2
Making gauntlet	Double	1/8 to 3/16	LSa-2
Hemming gauntlet	Single	---	EFa-1
Joining gauntlet to hand section	Double	1/8 to 3/16	LSa-2
Turning flap over gauntlet	Double	1/8 to 3/16	SSa-2
Closing seam 1/	Single	---	SSa-1

1/ A second row of stitching 1/16 inch back of the first row shall be stitched on the hand section.

3.4 Dies and patterns. The dies or patterns for cutting all parts of the gloves shall be furnished by the supplier and shall be of the proper proportions to provide good fitting gloves conforming to finished measurements in table II.

3.5 Figures. Figure 1 is furnished for information purposes only. To the extent of any inconsistencies between the written specification and the figures, the written specification shall govern.

3.6 Dimensions of gloves. The finished gloves shall conform to the dimensions shown in table II. Measurements shall be taken as shown in figure 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

3.7 Dimensions of reinforcements. The flap, reinforcing front seam, joining palm and bottom of gauntlet, shall be approximately 2 inches wide. The thumb welt shall be approximately 1/2 inch wide; the welt for base of fingers approximately 5/8 inch wide; and the welt for the "Davey" tips shall be cut approximately 5/8 inch wide.

TABLE II. Finished dimensions of gloves

Measurements	Sizes				Tolerance plus or minus
	Small	Medium	Large	Extra Large	
	Inches	Inches	Inches	Inches	Inch
A. Top edge of cuff to tip of second finger	12-3/4	13	13-1/2	14	1/2
B. Bottom edge of cuff to tip of second finger	7-3/4	8	8-1/2	8-3/4	1/4
C. Across palm at thumb, crotch, seam to seam	4-1/2	5	5-1/2	5-3/4	1/8
D. Tip of index finger to thumb crotch	4-3/4	5	5-1/2	5-3/4	1/8
E. Thumb crotch to tip of thumb	2-3/4	3	3-1/4	3-1/2	1/8
F. Across bottom edge of cuff	4-3/4	5	5-1/2	6	1/4
G. Across top edge of cuff	6-1/4	6-3/4	7	7-1/2	1/4

3.8 Detail requirements, leather.

3.8.1 Hand section. The back of the glove shall be split horsehide or split cattlehide leather. The palm, thumb, fingers, and reinforcing pieces shall be full grain horsehide or cattlehide leather as specified. All grain leather components shall be made of the same kind of leather.

3.8.2 Gauntlet. The gauntlet shall be split horsehide or split cattlehide leather.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

3.9 Design. The design of the glove shall be a two-piece, half outseamed, slip-on style, Gunn-cut glove, with a hemmed gauntlet. The continuous thumb shall be inseamed around all edges with a welt of the leather inserted in the seam. The seam at the base and tips of the fingers shall include a leather reinforcing welt turned up to protect the stitching. A palm reinforcing flap is attached to the top of the hand and bottom of the gauntlet, on the palm side as shown in figure 1.

3.10 Marking. The label, specified in 3.2.4, shall be applied to the inside of the back of each glove at center, approximately 1/2 inch down from the finished top edge.

3.11 Construction.

3.11.1 General.

3.11.1.1 Glove section. The thumb shall be of "inseam" construction, the fingers of "outseam" construction; the thumb shall be finished with an "all-around-turn-back" welt, and the ends of the fingers with similar welts, "Davey" tips. A protective welt shall be provided for the fourchette stitching, caught in the seaming of the fourchette and turned back over the bottom of the fingers. In addition, the top of the palm and fingers shall be reinforced with a flap which shall be caught in the seaming of the gauntlet, turned back, and sewed down to the gauntlet.

3.11.1.2 Gauntlet. The gauntlet shall be made in two pieces, each piece lined with cotton duck or laminated cotton fabric extending to within 3/8 inch of the top edge of the gauntlet to facilitate the hemming of the top edge. The remainder of the glove shall be unlined. The joining of the gauntlet and the closing shall be of outseam construction.

3.11.2 Detailed.

3.11.2.1 Cutting. Skins shall be dampened and all the stretch in the lengthwise direction pulled out before cutting gloves. Each leather component shall be cut in the length direction.

3.11.2.2 Join palm to fourchette. Lap the palm over the fourchette, position the welt piece on top on a line with the edge of the palm, with the grain of the leather of welt over and against the grain of the leather of the palm. Unite welt, palm, and fourchette with a double row of stitching 1/16 to 3/32 inch gage; 301 stitch type, seam type LSa-2. The welt piece shall be so positioned that when turned back over the seam, it shall measure not less than 1/2 inch wide and match the grain of the palm.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

The contacting corners of the welt piece shall be caught in the seaming of the first finger and little finger, respectively. The beginning and end of the stitching shall be securely backstitched with not less than three stitches. Special care shall be exercised in the operation to avoid any twisting or distortion of the fingers.

3.11.2.3 Join thumb and palm-inseam construction. Seam the thumb to the palm all around the edge of the thumb; stitch type 301, seam type SSa-1. The welt strip shall be so positioned on top of the seam and caught in the stitching that when turned back it shall match the grain of the leather thumb. The welt strip shall extend to the top of the glove. The top edges of the thumb and welt shall be caught in the seam joining the gauntlet to the hand section.

3.11.2.4 Join fingers - outseam construction. The end of each of the four fingers shall have protective welt strips like the welt strip of the thumb, positioned as indicated by figure 1. Seam the backs to the fronts around the fingers with the welts laid on the seam and caught in the stitching, so positioned that when turned back, they shall match the grain of the finger leather. The seaming shall be so performed as to prevent any twisting or distortion of the fingers. The end of the seaming shall be securely backstitched not less than 1/2 inch. Stitch type 301 and seam type SSa-1 shall be used.

3.11.2.5 Back seam. Lap the front of the glove over the back of the glove and unite with a double row of stitching 1/16 to 1/8 inch gage; stitch type 301, seam type LSa-2 (see fig. 1).

3.11.2.6 Making gauntlet. The two lined gauntlet pieces (see 3.11.1.2) shall be joined on the side next to thumb side of glove by overlapping the face over the back and double stitching 1/8 to 3/16 inch gage; 301 stitch type, seam type LSa-2.

3.11.2.7 Hemming gauntlet. The top leather edge of gauntlet shall be turned in 1/2 to 5/8 inch and single stitched 1/16 to 1/8 inch from raw edge, 301 stitch type, seam type EFa-1.

3.11.2.8 Joining gauntlet to hand section. The bottom edge of lined gauntlet shall be attached to top of hand at wrist by overlapping the gauntlet over the hand and stitching with a double row of stitching, 1/8 to 3/16 inch gage; 301 stitch type, seam type LSa-2.

3.11.2.9 Attach flap (reinforcement piece) at wrist. The flap shall be caught in seam joining palm side of gauntlet to hand portion and turned over seam with grain side facing outward. It shall then be stitched to the gauntlet with a double row of stitching around the sides and top edge of flap, 1/8 to 3/16 inch gage; 301 stitch type, seam type LSbj-2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

3.11.2.10 Closing. The side seam from the tip of fourth finger down to hem of gauntlet shall be outseamed single stitched; 301 stitch type, seam type SSa-1. A second row of stitching 1/16 inch back of first row shall be stitched on glove section from tip of fourth finger down the side to joining of gauntlet with hand section.

3.12 Pairing. The gloves shall be matched, paired and tacked together with thread or soft metal staples. Tacking shall be done with not less than one soft metal staple or not less than two stitches using a cord thread just below the hem approximately 1/2 inch from the closing seam, which will permit the pair to be pulled apart without tearing the leather.

3.13 Workmanship. The finished gloves shall conform to the quality and grade of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels (AQL's).

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated hereinafter. In addition to sampling inspection as set forth in MIL-STD-105, process inspection will be performed during manufacture of the gloves, to determine compliance with all required operations and processes which cannot be determined in the completely fabricated gloves. Any deviation found in process inspection may be cause for rejection of the end item or items.

4.2.1 Component and material inspection. In accordance with 4.1, components and materials shall be tested in accordance with all requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable purchase documents. In addition, testing shall be performed on components as specified in 4.2.1.1 and 4.2.1.2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

4.2.1.1 Leather testing. In addition to the quality assurance provisions of applicable subsidiary specifications and standards, the leather shall be tested for stiffness in accordance with 4.3.1. The sampling procedure and location from which the sample unit is to be obtained shall be in accordance with KK-L-169 and KK-L-162 as applicable. The lot shall be rejected if more than three test failures occur for this characteristic.

4.2.1.2 Fabric testing. The fabric shall be tested for the characteristics in table III. The test methods listed in table III shall be in accordance **with Fed. Test Method Std. No. 191, wherever applicable. Testing for all requirements listed in table III are applicable to the sample unit. The sample unit shall be one linear yard. The sample size shall be as follows:**

Lot size (yards)	Sample size
800 or less	2
801 up to, and including 22,000	3
22,001 and over	5

The lot shall be unacceptable if one or more units fail to meet any requirements specified.

TABLE III. Fabric component tests

Component	Characteristic	Requirement reference	Test method
Face fabric	Material identification	3.2.3	1200 1/
	Weight (oz. per sq. yds)	3.2.3	5041 1/
	Weave	3.2.3	Visual
Backing fabric	Material identification	3.2.3	1200 1/
	Weight (oz. per sq. yd.)	3.2.3	5041 1/
	Weave	3.2.3	Visual
Finished fabric	Weight (oz. per sq. yd.)	3.2.3	5041

1/ Unless otherwise specified, a certificate of compliance shall be submitted and will be acceptable for the stated requirement.

4.2.2 Inspection of the end item.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

4.2.2.1 Examination of the end item. The defects found during examination of the end product shall be classified in accordance with 4.2.2.1.1 and 4.2.2.1.2. The applicable inspection levels and AQL's shall be as indicated in 4.2.2.1.3. The sample unit for this examination shall be one glove. Selection of the sample shall be by pairs. The sample unit for pairing defects shall be one pair. Defects for pairing shall be classified as a single defect. The lot size shall be expressed in terms of one glove each.

4.2.2.1.1 Visual examination of gloves. The gloves shall be examined for defects in pairing, color, design, construction, material workmanship, and marking as indicated in table IV.

TABLE IV. Classification of defects

Examine	Defect	Classification Major	Minor
Pairing	Not properly mated, e.g., not right and left of same size.	X	
	Not tacked together.		X
	Wide variation in color in the pair.		X
Color	Not as specified.	X	
	Color not uniform or shaded parts affecting appearance.		X
Design	Any characteristic not in accordance with the specified requirements (unless otherwise classified herein).	X	
Leather	Not cattlehide or horsehide (where specified).	X	
	Not full grain (where specified).	X	
	Not split leather (where specified).	X	
	Not soft and pliable.	X	
	Any through hole (except pinhole), cut, tear or rip.	X	
	Three or more pinholes in a glove.		X
	Grain damage or imperfections:		
	-Seriously affecting serviceability.	X	
	-Affecting serviceability, but not seriously.		X
	Deep open scratch.	X	
	Deep wrinkles, seriously affecting serviceability.	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE IV. Classification of defects (con.)

Examine	Defect	Classification Major	Minor
Leather (con.)	Wrinkles affecting serviceability but not seriously.		X
	Any scar or abraded area: -Seriously affecting serviceability.	X	
	-Affecting serviceability, but not seriously.		X
	Bony area or thin spot: -Seriously affecting serviceability.	X	
	-Affecting serviceability, but not seriously.		X
	Flesh side of grain leather or either side of split leather contains excessively loose flesh more than two square inches in total area.		X
	Loose or spongy leather.	X	
	Flanky leather: -Seriously affecting serviceability.	X	
	-Affecting serviceability, but not seriously.		X
Finish (Leather)	Finish applied to grain surface.	X	
Gauntlet lining	Any hole, cut, or tear.	X	
	Multiple floats, loose ends, smashes, or slubs.		X
	Any broken or missing pick or end.		X
	Any mend in fabric (except restitching of seams).		X
Construction and workmanship	Any component or operation omitted.	X	
General (applicable to all components unless otherwise indicated herein.)	Any component misplaced or not serving purpose intended.		X
	Any component missing.	X	
	Any component or assembly damaged.	X	
	Any component not securely affixed, e.g., gauntlet loosely attached to back or palm of glove.	X	
	Any workmanship damage, e.g., scissor or knife cut.	X	
	Any mend in leather, e.g., patch (not applicable to restitched seam repair).	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE IV. Classification of defects (con.)

Examine	Defect	Classification Major	Minor
General (applicable to all components unless otherwise indicated herein). (con.)	Needle chews.	X	
Seams and stitching	Any open seam.		
	NOTE: When one or more stitches are broken or two or more consecutive skipped stitches or run-offs occur on a single stitched seam or on both rows of stitching on a double stitched seam, it shall be classified a major defect. When one or more stitches are broken or two or more consecutive skipped stitches or run-offs occur on only one row of a double stitched seam, it shall be classified as a minor defect.		
	Not specified seam type.	X	
	Not specified stitch type.	X	
	Any row of stitching omitted.	X	
	Loose stitch tension resulting in a loosely secured seam.	X	
	Thread breaks backstitched less than 1/2 inch.		X
	Ends of 301 stitching not backstitched or backstitched less than 1/2 inch when not caught in another row of stitching.		X
	Tight stitch tension resulting in cutting of leather or breaking of stitches when normal pull is applied.	X	
	Gage or margin of stitching irregular or not as specified:		
	-Affecting serviceability seriously.	X	
	-Affecting serviceability but not seriously.		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE IV. Classification of defects (con.)

Examine	Defect	Classification Major	Minor
Seams and stitching (con.)	Any part caught in unrelated row of stitching.	X	
	One or two stitches per inch less than specified.		X
	Three or more stitches per inch less than specified.	X	
	More than the specified maximum number of stitches per inch damaging leather.	X	
	More than the specified maximum number of stitches per inch not damaging leather.		X
Assembly detail	Glove not neatly laid off.		X
	Not outseam or inseam construction where specified.	X	
	Finger distorted or twisted affecting comfort of wearer.	X	
	Thread ends not trimmed throughout glove.		X
	Not properly trimmed or finished, e.g., lump or bulk in finger inseam because leather was not properly trimmed.	X	
	Not constructed with specified number of pieces of leather (except welting and reinforcements).	X	
	Welting reinforcing flap or reinforcements, missing, or not caught by stitching.	X	
	Binding loosely applied, or any edge not turned under and caught in stitching.		X
	Gauntlet not lined.	X	
Marking	Missing, incomplete, incorrect, not legible, not specified size, not in proper location, or not accomplished in the specified manner.		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

4.2.2.1.2 Dimensional examination. The gloves shall be examined for dimensional defects including thickness of leather. Any dimension that is not within the established tolerance shall be classified a defect.

NOTE: Each leather part of the glove shall be checked for thickness, i.e., palm, thumb, and body of gloves. Any of these parts that are not within the required thickness range shall constitute a defect. (Thickness shall be determined in accordance with the procedure for "Fabricated-Leather Articles" of method 1011 in FED-STD-311, except that two determinations shall be made on each part. Where glove parts are lined, the lining should be parted from the leather and the thickness of the leather should be taken doubled. This dimension is then divided by two.

4.2.2.1.3 Inspection levels and AQLs. The inspection levels and AQLs, expressed in defects per 100 units, shall be as follows:

Examination	Inspection level	AQL	
		Major	Total
Par 4.2.2.1.1	II	2.5	6.5
Par 4.2.2.1.2	S-3	-	4.0

4.2.3 Examination of preparation for delivery requirements. An examination shall be made to determine that packaging, packing, and marking requirements of section 5 are complied with. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery with the exception that it need not be sealed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the AQL shall be 2.5 defects per hundred units.

Examine	Defect
Marking (exterior and interior)	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing or damaged.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

Examine	Defect
Workmanship	Inadequate application of components, such as: Incomplete closure of container flaps, loose strapping, inadequate stapling. Bulged or distorted container.
Content	Number of bundles per shipping container is more or less than required. Number of pairs of gloves per bundle is more or less than required. 1/

1/ For this defect, two bundles shall be examined from each shipping container in the sample.

4.3 Tests.

4.3.1 Stiffness. The stiffness test shall consist of two phases i.e., before soaking (paragraph 4.3.1.1) and after soaking (paragraph 4.3.1.2). A specimen shall not be reported as passing unless it passes both phases. A specimen that fails to pass the first phase shall not be tested in the second phase.

4.3.1.1 Before soaking. The leather specimen shall be 3 by 4 inches, cut with the long dimension perpendicular to the back bone. The specimen shall be folded in half, (grain side out for grain leather) to form a rectangle 3 by 2 inches (crease parallel to backbone), then carefully folded in half again to form a rectangle approximately 3 by 1 inch, 4 layers thick. The folded specimen shall be secured with the staples across the width, 1/4 inch from each end. The ends shall be gripped between thumb and forefinger, and the specimens shall be twisted torquewise 40 times back and forth approximating an angle of 180 degrees in each direction. One end of the specimen shall then be fastened in the vise of the tester in such a way that the cut edges on the upper side face outward from the machine. The other end of the specimen shall extend 2 inches from the vise. The stiffness of the specimen shall be determined as specified **in method 4211 of Fed. Test Method Std. No. 311 by bending the specimen 20 degrees using a 1 inch span and a total moment weight equivalent to 0.5 inch pound.**

4.3.1.2 After soaking. The folded and stapled specimens which pass the requirement applicable to 4.3.1.1, shall then be immersed in distilled water of 140° ± 5°F. (60° ± 3°C.) for 20 ± 2 hours. One thousand ml. of water shall be used for 15 specimens. Complete immersion of the specimen shall be accomplished by placing a floating cover on the vessel used for the immersion. The specimens shall be removed, air dried and conditioned for 72 hours in the standard atmosphere as defined in **Fed. Test Method Std. No. 311, and tested for stiffness in folded and stapled condition in accordance with the preparation and test method described in 4.3.1.1.**

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

5. PREPARATION FOR DELIVERY

5.1 Packaging. Packaging shall be level A or C, as specified (see 6.2).

5.1.1 Level A. Four pairs of gloves, of one size only, shall be evenly stacked in a bundle. The gloves shall be alternately reversed, finger-tip to gauntlet, with the small fingers of each pair positioned in each corner of the bundle. Each glove bundle shall be securely tied with cotton tape or twine.

5.1.2 Level C. Gloves shall be packaged to afford adequate protection against physical damage during shipment from the supply source to the first receiving activity. The supplier may use his standard practice when it meets this requirement.

5.2 Packing. Packing shall be level A, B, or C, as specified (see 6.2)

5.2.1 Level A. Eighty pairs of gloves of one size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled, closed, and reinforced conforming to class weather-resistant, grade V2s, size 3A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class weather-resistant, variety DW, grade V15c of PPP-F-320. Level A packages shall be packed flat, four in length, one in width, and five in depth within a shipping container. Each container shall have the contents completely covered on the top and bottom with a sheet of 30-pound minimum basis weight kraft paper conforming to grade B of UU-P-268. Toward the end of the contract or order, or when there is less than the required amount per container of the same size, mixed sizes may be packed within the same shipping container.

5.2.2 Level B. Eighty pairs of gloves of one size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled and closed conforming to class domestic, grade 275, size 3A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class domestic, variety DW, grade 275 of PPP-F-320. Level A packages shall be packed flat, four in length, one in width, and five in depth within a shipping container. Each container shall have the contents completely covered on the top and bottom with a sheet of 30-pound minimum basis weight kraft paper conforming to grade B of UU-P-268. Toward the end of the contract or order, or when there is less than the required amount per container of the same size, mixed sizes may be packed within the same shipping container.

5.2.2.1 When specified (see 6.2), the shipping container shall be a grade V3c or V3s fiberboard box fabricated in accordance with PPP-B-636 and closed in accordance with the appendix of PPP-B-636. The shipping container material may also be grade V4s of PPP-F-320.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

5.2.3 Level C. Gloves, packaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. Containers shall be in accordance with Uniform Freight Classification Rules or National Motor Freight Classification Rules, as applicable.

5.3 Marking.

5.3.1 Military requirements. In addition to any special marking required by the contract or order, shipping container shall be marked in accordance with MIL-STD-129.

5.3.2 Civil agencies. In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with Fed. Std. No. 123.

5.3.3 Labels, mixed sizes. Each shipping container, packed with mixed sizes only, shall have securely attached to the end or side, directly under the printing or stencilling, a white paper label 5 by 4 inches with the words "MIXED SIZES" plainly stamped or printed thereon and under these words shall be legibly stamped or printed the correct quantity and sizes contained therein.

6. NOTES

6.1 Intended use. This glove is intended for use by linemen or others where contact with live wires is not involved.

6.2 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number, and date of this specification.
(b) Size required (see 1.2).
(c) Selection of applicable levels of packaging and packing required (see 5.1 and 5.2).
(d) When weather-resistant grade fiberboard shipping containers are required for level B packing (see 5.2.2.1).

6.3 Samples. For access to samples, address the procuring activity issuing the invitation for bids.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

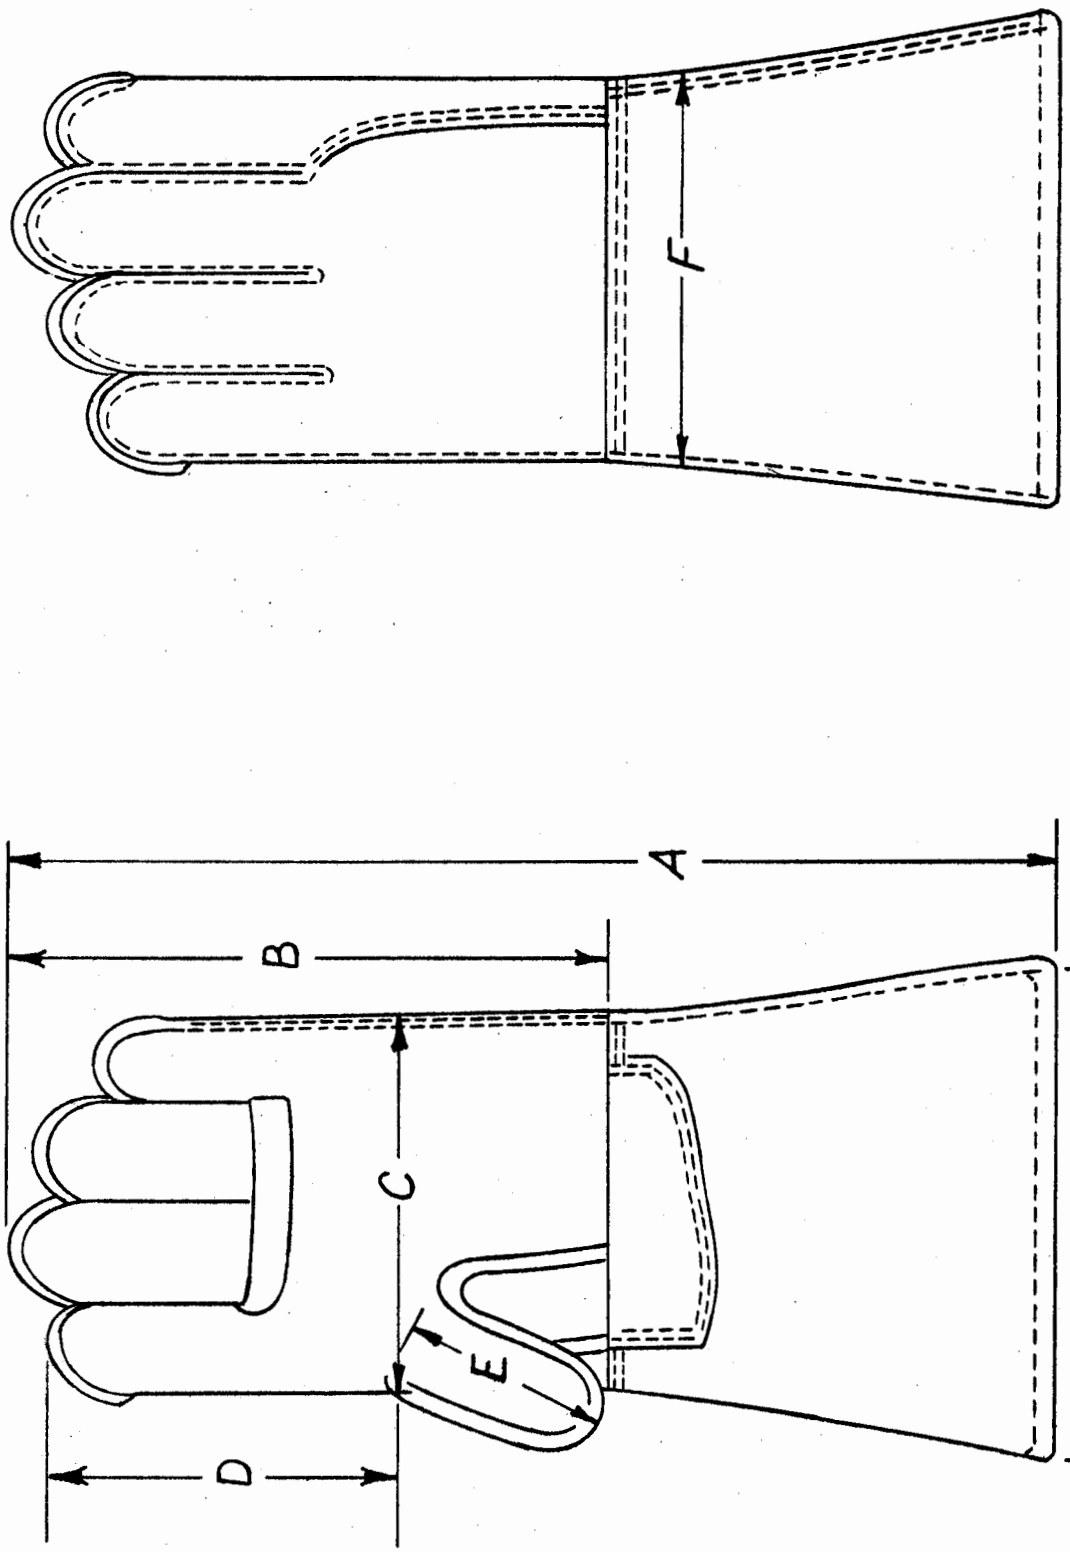


FIGURE 1. Gloves, leather, gauntlet, linemen's

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

MILITARY CUSTODIANS:

Army - GL

Navy - SA

Air Force - 82

Review activities:

Army - MD

Navy - SA

Air Force - 45

User activities:

Army - SM

Navy - OS, MC

Preparing activity:

Army - GL

CIVIL AGENCIES INTEREST:

AGR
COM
GSA
HEW
INT
VA
FPI

Project No. 8415-0291

Orders for this publication are to be placed with General Services Administration, acting as an agent for the Superintendent of Documents. See Section 2 of this specification to obtain extra copies and other documents referenced herein. - cents each.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 22-R255

INSTRUCTIONS: This sheet is to be filled out by personnel, either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments and suggestions submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or serve to amend contractual requirements.

SPECIFICATION
Gloves, Leather Gauntlet, Linemen's KK-G-476D

ORGANIZATION

CITY AND STATE

CONTRACT NUMBER

MATERIAL PROCURED UNDER A
☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?
   A. GIVE PARAGRAPH NUMBER AND WORDING.

   B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?
   ☐ YES ☐ NO *(If "yes", in what way?)*

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity - Optional)*

DATE

DD FORM 1 JAN 66 1426 REPLACES EDITION OF 1 OCT 64 WHICH MAY BE USED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE ARMY
U. S. Army Natick Laboratories
Natick, Massachusetts 01760

OFFICIAL BUSINESS

POSTAGE AND FEES PAID
DEPARTMENT OF THE ARMY

Commanding General
U. S. Army Natick Laboratories
ATTN: AMXRES-EQS
Natick, Massachusetts 01760

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.