INCH-POUND

MS51524C
15 November 2017
SUPERSEDING
MS51524B
17 March 2016

DETAIL SPECIFICATION SHEET

# TEE, TUBE TO SWIVEL, SWIVEL ON BRANCH, 37 DEGREE FLARED

Reactivated after 15 November 2017 and may be used for new and existing designs and acquisitions.

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-DTL-18866.

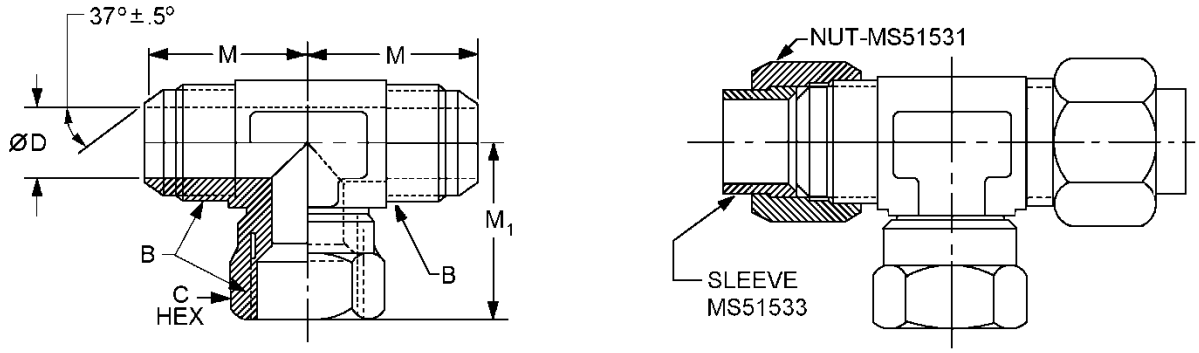



FIGURE 1. T-tube to swivel.

AMSC N/A

FSC 4730

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T18:05Z
Check the source to verify that this is the current version before use.

| Suffix designator (see note 7) | | Tube OD nom. | B Straight thread Class A or B | C Hex flat Nom. | D diameter | |
|---|---|---|---|---|---|---|
| Assembly | Body | | | | Basic inches (mm) | Tolerance inches (mm) |
| A2 | B2 | .1250 (3.175) | .3125-24 UNF-2 | 7/16 | .062 (1.57) | ±.003 (0.08) |
| A3 | B3 | .1875 (4.763) | .3750-24 UNF-2 | 1/2 | .125 (3.18) | |
| A4 | B4 | .2500 (6.350) | .4375-20 UNF-2 | 9/16 | .172 (4.37) | |
| A5 | B5 | .3125 (7.936) | .5000-20 UNF-2 | 5/8 | .234 (5.94) | |
| A6 | B6 | .3750 (9.525) | .5625-18 UNF-2 | 11/16 | .297 (7.54) | ±.004 (0.10) |
| A8 | B8 | .5000 (12.700) | .7500-16 UNF-2 | 7/8 | .391 (9.93) | |
| A10 | B10 | .6250 (15.875) | .8750-14 UNF-2 | 1 | .484 (12.29) | |
| A12 | B12 | .7500 (19.050) | 1.0625-12 UN-2 | 1 1/4 | .609 (15.47) | ±.005 (0.13) |
| A14 | B14 | .8750 (22.225) | 1.1875-12 UN-2 | 1 3/8 | .718 (18.24) | |
| A16 | B16 | 1.0000 (25.400) | 1.3125-12 UN-2 | 1 1/2 | .844 (21.44) | ±.007 (0.18) |
| A20 | B20 | 1.2500 (31.750) | 1.6250-12 UN-2 | 2 | 1.078 (27.38) | +.008 -.005 (+0.20 -0.13) |
| A24 | B24 | 1.5000 (38.100) | 1.8750-12 UN-2 | 2 1/4 | 1.312 (33.32) | |
| A32 | B32 | 2.0000 (50.800) | 2.500-12 UN-2 | 2 7/8 | 1.781 (45.24) | +.010 -.005 (+0.25 -.013) |

| Suffix designator | | M inches (mm) ±.030 (0.08) | $M_1$ inches (mm) ±.060 (0.15) |
|---|---|---|---|
| Assembly | Body | | |
| A2 | B2 | .770 (19.56) | .970 (24.64) |
| A3 | B3 | .830 (21.08) | 1.000 (25.40) |
| A4 | B4 | .890 (22.61) | 1.000 (25.40) |
| A5 | B5 | .950 (24.13) | 1.060 (26.92) |
| A6 | B6 | 1.060 (26.92) | 1.250 (31.75) |
| A8 | B8 | 1.250 (31.75) | 1.380 (35.05) |
| A10 | B10 | 1.450 (36.83) | 1.620 (41.15) |
| A12 | B12 | 1.660 (42.16) | 1.750 (44.45) |
| A14 | B14 | 1.730 (43.94) | 1.780 (45.21) |
| A16 | B16 | 1.810 (45.97) | 2.000 (50.80) |
| A20 | B20 | 2.060 (52.32) | 2.310 (58.67) |
| A24 | B24 | 2.330 (59.18) | 2.590 (65.79) |
| A32 | B32 | 3.060 (77.72) | 3.380 (85.85) |

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for information only.
3. Break all sharp edges; remove all burrs and slivers.
4. Dimensions and tolerances not shown shall be in accordance with SAE-J514 for 37° flared fittings.
5. The drawing is for identification purposes only and is not intended to restrict designs and shapes not dimensioned.
6. Threads shall be in accordance with ASME B1.1.
7. Assemblies are only furnished to this specification (body, nuts, and sleeves). Bodies are not to be stocked, stored, or issued.

FIGURE 1. T-tube to swivel - Continued.



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T18:05Z
Check the source to verify that this is the current version before use.

REQUIREMENTS:

Fittings shall be as specified on figure 1 and in table I.

Components of the assemblies shall be of the same material and finish.

Materials shall be in accordance with MIL-DTL-18866.

Finish. Finishes shall be as specified in table I. All plating's shall be capable of meeting a minimum of 96 hours salt spray test in accordance with ASTM B117. The fittings shall show no evidence of red corrosion after 96 hours of salt spray. Fluid passages, other openings and internal threads shall not be subject to the plating thickness requirement and may have bare areas provided they are protected with a light film of oil.

TABLE I. Material and finish identification codes.

| PIN code material/plating finish | Material | Plating finish |
|---|---|---|
| Blank | Steel | Cadmium plating in accordance with SAE-AMS-C-81562, type II, class 3 or SAE-AMS-QQ-P-416, type II, class 2. 1/ |
| H | Steel | Zinc-Aluminum in accordance with ASTM F1136/F1136M, grade 3, NC. 2/ |
| J | Steel | Zinc-nickel in accordance with SAE-AMS2417, type 2, grade B. 2/ 3/ |
| M | Nickel-copper alloy UNS N04400 | No additional finish. |
| N | High-chromium nickel alloy UNS N06690 | No additional finish. |
| P | Steel | Zinc phosphate finish in accordance MIL-DTL-16232 type Z, class 1. 4/ |
| R | Steel | Zinc plating in accordance with ASTM B633; type III or V, Fe/Zn 8. 4/ |
| S | Corrosion resistant steel | No additional finish. Passivation in accordance with SAE-AMS2700, method 1, type 6 or 7. |
| T | Titanium | Anodize in accordance with SAE-AMS2488 type 2. 5/ |
| TF | Titanium | Fluoride phosphate in accordance with SAE-AMS2486. 5/ |
| Z | Steel | Zinc plating in accordance with ASTM B695, type II, class 8. 4/ |
| ZC | Steel | Zinc may be any zinc plating from PIN codes J, R, and Z with a colored chromate coating. 4/ |

1/ Embrittlement test need not be run. Cadmium shall not be used in oxygen or potable water systems. Cadmium is prohibited from use in NAVSEA owned shipboard systems.
2/ Hexavalent chromium free. Finish shall be ROHS compliant.
3/ The zinc-nickel alloy plate shall contain 12% to 16% nickel. The coating thickness shall be 315µ inches (8µm) minimum.
4/ Not for use in aircraft. Requires approval from the Program Office for all applications.
5/ A pretreatment, a modification of the fluoride treatment, or a post treatment shall be applied so the final color of the fittings shall be similar to SAE-AMS-STD-595 colors 36076 through 36293. Titanium shall not be used in oxygen or potable water systems.



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T18:05Z
Check the source to verify that this is the current version before use.


Trivalent wrenchability. When the finish has been damaged due to poor wrenchability, the surface of the connector shall be touched up using one of the brush plating processes below as appropriate to primary finish. The term “trivalent wrenchability” is used to evaluate the ability of the finish to withstand abrasion from an excessive amount of wrenching.

a. Brush plating of hard chromium by electrodeposition shall be in accordance with SAE-AMS-2451/5.

b. Brush plating of medium-hardness, low stress nickel by electrodeposition shall be in accordance with SAE-AMS-2451/9.

Maximum operating pressure. Maximum operating pressure shall be in accordance with SAE-J514.

PIN: The PIN consists of the letters “MS”, the specification number, a letter and number for tee size, and a letter for material finish designator.

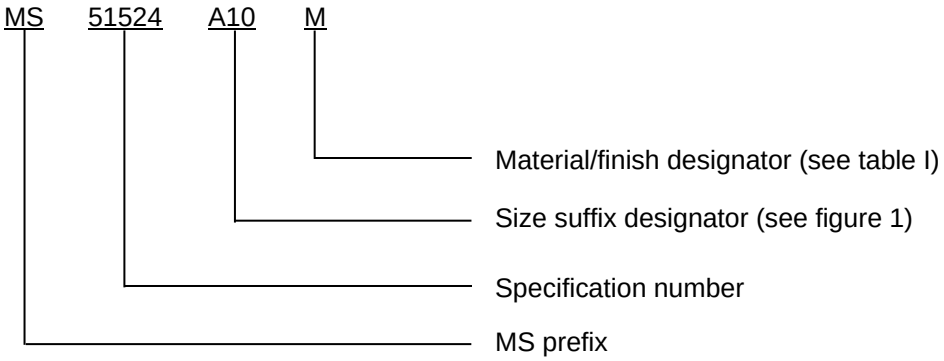


PIN example: MS51524A10M indicates a tee, tube to swivel, .6250 inch (15.875 mm), nickel-copper alloy.

Cadmium is not recommended. To the users of this document, it is recommended that the use of carbon steel material with cadmium plating be used only when other materials and finishes specified in this document cannot meet performance requirements.

Cadmium is prohibited from use in NAVSEA owned shipboard systems in accordance with the requirements of T9070-AL-DPC-020/077-2.

Class I and II ODS shall not be used in MS51514 or any referenced procedures.

Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Referenced documents shall be of the issue in effect on date of invitations for bid.

Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue, due to the extent of the changes.



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T18:05Z
Check the source to verify that this is the current version before use.

Referenced documents. In addition to MIL-DTL-18866, this document references the following:

| | | |
|---|---|---|
| MIL-DTL-16232 | SAE-AMS-STD-595/36081 | SAE-AMS-STD-595/36280 |
| MS51531 | SAE-AMS-STD-595/36099 | SAE-AMS-STD-595/36293 |
| MS51533 | SAE-AMS-STD-595/36118 | SAE-AMS2417 |
| ASME B1.1 | SAE-AMS-STD-595/36134 | SAE-AMS2451/5 |
| ASTM B117 | SAE-AMS-STD-595/36152 | SAE-AMS2451/9 |
| ASTM B633 | SAE-AMS-STD-595/36170 | SAE-AMS2486 |
| ASTM B695 | SAE-AMS-STD-595/36173 | SAE-AMS2488 |
| ASTM F1136/F1136M | SAE-AMS-STD-595/36176 | SAE-AMS2700 |
| SAE-AMS-C-81562 | SAE-AMS-STD-595/36231 | SAE-J514 |
| SAE-AMS-QQ-P-416 | SAE-AMS-STD-595/36251 | T9070-AL-DPC-020/077-2 |
| SAE-AMS-STD-595/36076 | SAE-AMS-STD-595/36270 | |

## CONCLUDING MATERIAL

Custodians:
Army - AR
Navy - OS
Air Force - 99
DLA - CC

Preparing activity:
DLA - CC

(Project 4730-2017-106)

Review activities:
Army - AT, MI
Navy - CG, MC, SA, SH
Air Force - 71

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T18:05Z
Check the source to verify that this is the current version before use.