INCH-POUND

MIL-A-53079(ME)
9 January 1989

MILITARY SPECIFICATION

ANCHOR, NAVMOOR CAUSEWAY MOORING

This specification is approved for use within the USA Belvoir Research, Development and Engineering Center, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification establishes the requirements for manufacture and acceptance of two sizes of NAVMOOR anchors for use in a causeway mooring system.

1.2 Classification. The anchors shall be of the following types as specified (see 6.2):

Type I - NAVMOOR-120 pound anchor with a weight of 120 pounds (see 3.5) for use in water depths less than 50 feet.
Type II - NAVMOOR-2 anchor with a weight of 2,400 pounds (see 3.5).

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: USA Belvoir Research, Development, and Engineering Center, ATTN: STRBE-TSE, Fort Belvoir, VA 22060-5606 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 2040
DISTRIBUTION STATEMENT A. Approved for public release, distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

SPECIFICATIONS

MILITARY

| | |
|---|---|
| MIL-T-704 | - Treatment and Painting of Materiel. |
| MIL-M-47230 | - Magnetic Particle Inspection: Soundness Requirements for Materials, Parts, and Weldments. |

STANDARDS

MILITARY

| | |
|---|---|
| MIL-STD-129 | - Marking for Shipment and Storage. |
| MIL-STD-248 | - Welding and Brazing Procedure and Performance Qualification. |
| MIL-STD-45662 | - Calibration System Requirements. |

(Unless otherwise indicated, copies of federal and military specifications and standards are available from the Naval Publications and Forms Center, (ATTN: NPODS), 5801 Tabor Avenue, Philadelphia, PA 19120-5099.)

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues are those in effect on the date of the solicitation.

DRAWINGS

ME

| | |
|---|---|
| TA13228E5290 - | Anchor Assembly, Mooring, NAVMOOR-2, 2400 pounds |
| TA13228E5310 - | Anchor Assembly, Mooring, NAVMOOR, 120 pounds |

(Copies of drawings required by contractors in connection with specific acquisition functions should be obtained from the USA Belvoir Research, Development, and Engineering Center, ATTN: STRBE-FRS, Fort Belvoir, VA 22060-5606.)

2.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues are those in effect on the date of the solicitation.

AMERICAN BUREAU OF SHIPPING (ABS)

Rules for Building and Classing Steel Vessels

(Application for copies should be addressed to the American Bureau of Shipping, 45 Eisenhower Drive, P.O. Box 910, Paramus, NJ 07653.)



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

AMERICAN SOCIETY FOR TESTING AND MATERIAL (ASTM)

A 27 - Specification for Steel Castings, Carbon, for General Application.
A 36 - Specification for Structural Steel.
A 148 - Specification for Steel Castings, High Strength, for Structural Purposes.
A 370 - Test Methods and Definitions for Mechanical Testing of Steel Products.
A 570 - Specification for Hot-Rolled Carbon Steel Sheet and STrip, Structural Quality.
A 588 - Specification for High Strength Low-Alloy Structural Steel with 50 ksi (345 MPa) Minimum Yield Point to 4 in. (100 mm) Thick.
A 668 - Specification for Steel Forgings, Carbon and Alloy for General Industrial Use.
E 30 - Method for Chemical Analysis of Steel, Cast Iron, Open Hearth Iron, and Wrought Iron.
E 186 - Reference Radiographs for Heavy-Walled (2 to 4-1/2 inches (51 to 114 mm)) Steel Castings.
E 280 - Reference Radiographs for Heavy-Walled (4-1/2 to 12-inches (114 to 305 mm)) Steel Castings.
E 446 - Reference Radiographs for Steel Castings up to 2 inches (51 mm) in Thickness.
E 709 - Practice for Magnetic Particle Examination.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia PA 19103.)

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION, INC., AGENT

National Motor Freight Classification

(Application for copies should be addressed to the American Trucking Association, Inc., Traffic Department, 2200 Mil Road, Alexandria, VA 22309.)

UNIFORM CLASSIFICATION COMMITTEE, AGENT

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Tariff Publishing Officer, Room 1106, 222 South Riverside Plaza, Chicago, IL 60606.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, (except for related associated detail specifications, specification sheets or MS standards), the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Description. The NAVMOOR anchor, hereinafter refereed to as "anchor", shall be in accordance with TA13228E5310 for type I anchors and TA13228E5290 for type II anchors.

3.1.1 Drawings. The drawings forming a part of this specification are end product drawings. No deviations from the prescribed dimensions or tolerances is permissible without prior approval of the contracting officer. Where tolerances could cumulatively result in incorrect fits, the contractor shall provide tolerances within those prescribed on the drawings to insure correct fit, assembly, and operating of the anchor. Any data (e.g., shop drawings, layouts, flow sheets, processing procedures, etc.) prepared by the contractor or obtained from a vendor to support fabrication and manufacture of the production item shall be made available, upon request, for inspection by the contracting officer or the designated representative.

3.2 First article. When specified (see 6.2), a sample shall be subjected to first article inspection (see 6.3) in accordance with 4.4.

3.3 Materials. Materials shall be as specified herein and on the drawings. Materials not specified shall be selected by the contractor and shall be subject to all provisions of this specification. Materials used in normal production shall have the same composition and properties as material used in the first article.

3.3.1 Castings. Castings shall be in accordance with ASTM A 27, grade 70-36, class 2 or ASTM A 148, grade 80-50 steel as specified in 3.3.4.

3.3.2 Forgings. Forgings shall be in accordance with ASTM A 668, class D: normalized and tempered of class F; normalized, quenched and tempered as specified in 3.3.4.

3.3.3 Structural steel. All structural steel shall conform to ASTM A 36; ASTM A 570, grade 36; or ASTM A 588, grade A unless otherwise noted on the drawings.

3.3.4 Component materials.

3.3.4.1 Anchor shank. The anchor shank for type I anchors shall be either machined from structural steel conforming to ASTM A 36; forged from ASTM A 668, class D steel; or cast from steel conforming to ASTM A 27, grade 70-36, class 2 and shall be in accordance with drawing 13228E5315. The anchor shank for type II anchors shall be either cut from structural steel conforming to



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

ASTM A 588, grade A; forged from ASTM A 668, class F steel; or cast from steel conforming to ASTM A 148, grade 80-50 and shall be in accordance with drawing 13228E5291.

3.3.4.2 Anchor palm. The anchor palm shall be cast from ASTM A 27, grade 70-36, class 2 steel. Type I anchor palm shall be in accordance with drawing 13228E5313. Type II anchor palm shall be in accordance with drawing 13228E5288.

3.3.4.3 Flukes. Type I flukes shall be fabricated from ASTM A 36 or ASTM A 570, grade 36 steel and welded to the palm. Type II flukes shall be fabricated form ASTM A 36 steel and welded to the palm. Type I flukes shall be in accordance with drawing 13228E5314. Type II flukes shall be in accordance with drawing 13228E5289.

3.3.4.4 Stoppers. The 32 degrees stoppers shall be of cast ASTM A 27, grade 70-36, class 2 steel; forged ASTM A 668, class D steel; or machined ASTM A 36 steel. The 50 degrees stopper shall be cast as part of the palm. Stoppers shall be machined as per drawing 13228E5286 so as to maximize contact between the potential bearing surfaces of the 50 degree stopper, the 32 degree stopper, and the shank. Stoppers on type I and type II anchors shall be in accordance with drawing 13228E5286-1 and drawing 13228E5286-2, respectively.

3.3.4.5 Hardware. Hardware certifications shall be supplied to the contracting officer with delivery of the anchors (see 4.7 and 6.3).

3.3.5 Recovered materials. For the purpose of this requirement, recovered materials are those materials which have been collected from solid waste and reprocessed to become a source of raw materials, as distinguished from virgin raw materials. The components, pieces and parts incorporated in the anchor may be newly fabricated from recovered materials to the maximum extent practicable, provided the anchor produced meets all other requirements of this specification. Used, rebuilt or remanufactured components, pieces and parts shall not be incorporated in the anchor.

3.4 Physical properties. The physical properties of the anchor shall conform to the following:

3.4.1 Structural integrity. The anchor cast components shall withstand rough handling by not suffering loss of structural integrity (no fracturing, cracking, or deformation) when dropped from a height of 12 feet on to a steel slab, as specified in ABS, Rules for Building and Classing Steel Vessels, section 43.11.4b, Details of Tests for Anchors, Drop Tests.

3.4.2 Strength. The anchors shall be completely assembled, without stabilizers, and subjected to a 2/3 fluke length test and a shank to tandem link test. The 2/3 fluke length test shall be in accordance with ABS, Rules for Building and Classing Steel Vessels, section 43.11.4e, Details of Tests for Anchors, Proof Tests, for anchors of proven superior holding ability. Type I anchors shall withstand test loads of not less than 7,120 pounds without fracture or permanent deformation. An additional 250 pound load shall be applied to each



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

lifting eye on the top and the bottom of the shank of type I anchors. Type II anchors shall withstand test loads of not less than 60,580 pounds without fracture or permanent deformation. An additional 5,000 pound load shall be applied to each lifting eye on the top and the bottom of the shank of type II anchors. The pull tests shall verify the structural integrity of the anchor.

3.5 Weight. The weight of the first article type I anchor shall not exceed 120 pounds, excluding shackles. The weight tolerance for the type I production anchors shall not vary more than +6.5 percent to -5 percent of the measured first article weight. The weight of the first article type II anchor shall not exceed 2,400 pounds, excluding shackles. The weight tolerance for the type II production anchors shall not very more than +5 percent to -3 percent of the measured first article weight.

3.6 Color and finish. After testing and examination and before painting, all parts shall be blasted in accordance with MIL-T-704. Paint shall be applied immediately after blasting in accordance with paint noted on TA13228E5310 and TA13228E5290 for type I and type II anchors, respectively. Paint material certifications shall be supplied to the contracting officer with delivery of the anchors (see 4.7 and 6.3).

3.7 Identification marking. Anchors shall be identified with markings cast or welded in the palm and shank in the approximate locations shown on drawing 13228E5313 and drawing 13228E5315 for type I anchors. The location of the identification markings for type II anchors shall be in the approximate locations shown on drawing 13228E5288 and drawing 13228E5291.

3.8 Workmanship.

3.8.1 Castings and forgings. All parts and components of the anchor which include castings and forgings shall be clear of harmful extraneous material such as sand, dirt, spurs, scale, and flux. Rework shall be limited to procedures which do not reduce mechanical properties or affect function.

3.8.2 Metal fabrication. Metal used in fabrication shall be free from kinks and sharp bends. The straightening of material shall be done by methods that will not cause injury to the material. Corners shall be square and true. Flame-cutting, using tips suitable for the thickness of the steel, may be employed instead of shearing and sawing. All bends shall be made with controlled means to insure uniformity of size and shape. Precautions shall be taken to avoid overheating. Heated steels shall be allowed to cool slowly. External surface shall be free from burrs, sharp edges and corners, except when sharp edges or corners are required or where they are not detrimental to safety.

3.9 Welding. Weld types shall be in accordance with those specified on the drawings. Where ASTM A 27 steel is being welded, a low hydrogen welding rod shall be employed. Weldments shall be in accordance with drawing 13214E9223, class 1, type 4 and drawing 13214E9224, class 1, type 4, as required. Welding procedures shall be qualified in accordance with MIL-STD-248 and shall be supplied to the contracting officer five days prior to any welding.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

## 4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.1.2 Component and material inspection. The contractor is responsible for insuring that components and materials are manufactured, examined, and tested in accordance with referenced specifications and standards, as applicable.

4.1.3 Test equipment. Test and measuring equipment shall be currently calibrated and maintained in accordance with a calibration system meeting the requirements of MIL-STD-45662. A copy of calibration certification of all test and measuring equipment shall be supplied to the contracting officer (see 4.7 and 6.2.1).

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.4).
b. Quality conformance inspection (see 4.5).
c. Inspection of packaging (see 4.9).

4.3 Inspection conditions. Unless otherwise specified in a test, test instruments, anchor parts, and other devices used in dimensioning, gauging, and performance testing shall be stabilized at, and used in, an ambient temperature of 100 to -15 °F.



Source: https://assist.dla.mil -- Downloaded: 202610-26T04:12Z
Check the source to verify that this is the currentversion before use.

4.4 First article inspection.

4.4.1 Examination. The first article shall be examined as specified in 4.6.1 and in table I. The presence of one or more defects shall be cause for rejection.

TABLE I. Examination schedule.

| Number | Defects | Requirement paragraph |
|---|---|---|
| Critical | | |
| 1 | Damaged parts, including evidence of cracks, blow holes, or pits in castings or forgings, which would render the parts unsound or unsuitable. | 3.8 |
| Major | | |
| 101 | Dimensions not as specified. | 3.1 |
| 102 | Material not as specified. | 3.3 |
| 103 | Used, rebuilt, or remanufactured components, pieces, or parts incorporated. | 3.3.5 |
| 104 | Color not as specified. | 3.6 |
| 105 | Finish not as specified. | 3.6 |
| 106 | Identification marking missing, incomplete or illegible. | 3.7 |
| 107 | Cleaning not as specified. | 3.8 |
| 108 | Workmanship not as specified. | 3.8 |
| 109 | Welder qualification and welding not as specified. | 3.9 |

4.4.2 First article tests. The first article test shall be as specified in 4.6.2 and in column 1 of table II. Failure of any test shall be cause for rejection.



Source: https://assist.dla.mil -- Downloaded: 202610-26T04:12Z
Check the source to verify that this is the currentversion before use.

TABLE II. Test schedule.

| First Article | Quality Conformance | Test | Test Paragraph | Requirement Paragraph |
|---|---|---|---|---|
| 1 | 2 | 3 | 4 | 5 |
| X | X | Materials | 4.6.2.1 | 3.3 |
| X | X | Chemical Analysis | 4.6.2.1.4 | 3.3 |
| X | X | Mechanical Properties | 4.6.2.1.5 | 3.3 |
| X | | Cast component radiographic inspection | 4.6.2.2 | |
| X | X | Cast component drop test | 4.6.2.3 | 3.4.1 |
| X | X | Anchor Pull Test | 4.6.2.4 | 3.4.2 |
| X | X | 2/3 fluke length pull test | 4.6.2.4.1 | 3.4.2 |
| X | X | Shank/tandem link test | 4.6.2.4.2 | 3.4.2 |
| X | X | Lifting eye test | 4.6.2.4.3 | 3.4.2 |
| X | X | Post-test magnetic particle inspection | 4.6.2.4.4 | 3.4.2 |
| X | X | Examination | 4.6.1 | 3. |
| X | X | Anchor weight | 4.6.2.5 | 3.5 |

4.5 Quality conformance inspection.

4.5.1 Examination. Each anchor shall be examined as specified in 4.6.1.

4.5.2 Tests. Each anchor shall be subjected to the tests marked "X" in column 2 of table II. Failure of any test shall be cause for rejection.

4.6 Examination procedure.

4.6.1 Examination. The anchor shall be measured and visually examined for the defects listed in table I.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

4.6.2 Tests.

4.6.2.1 Material tests. Material certification shall be provided for all anchor steel, hardware, and fittings to verify conformance to ASTM A 27, grade 70-36, class 2; ASTM A 148, grade 80-50; ASTM A 570, grade 36; ASTM A 588, grade A; ASTM A 668, class D or class F; or applicable hardware, fitting, and paint specifications; as applicable.

4.6.2.1.1 Casting material test samples. Test coupons for chemical analysis in 4.6.2.1.4 and mechanical property tests in 4.6.2.1.5 shall be integrally cast with any cast components unless damage to the component would result, in which case a separate cast coupon will be required. Adequate measure shall be taken to ensure test coupon soundness. The coupons shall undergo all heat treatment with the casting.

4.6.2.1.2 Forging material test samples. Forging test blocks for chemical analysis in 4.6.2.1.4 and mechanical property test in 4.6.2.1.5 shall be made from prolongations in accordance with ASTM A 370.

4.6.2.1.3 Structural steel. Certification of chemical analysis, mechanical properties, and ASTM classification, from suppliers shall be acceptable as evidence of material conformance.

4.6.2.1.4 Chemical analysis. Chemical analysis shall be performed in accordance with ASTM E 30 to verify composition of ASTM A 27, grade 70-36, class 2; ASTM A 148, grade 80-50; ASTM A 36; ASTM A 570, grade 36; ASTM A 588, grade A; or ASTM A 668, class D or class F; as applicable. Certification of the results shall be provided to the contracting officer (see 6.3).

4.6.2.1.5 Mechanical property tests. Mechanical property tests shall be performed on all steel components in accordance with ASTM A 370. Mechanical properties shall meet or exceed requirements of ASTM A 27, grade 70-36, class 2; ASTM A 148, grade 80-50; ASTM A 36; ASTM A 570, grade 36; ASTM A 588, grade A; or ASTM A 668, class D or class F; as applicable. Certification of the results shall be provided to the contracting officer (see 6.3).

4.6.2.2 Pre-test cast component radiographic inspection. Radiographic inspection shall be conducted on first article cast anchor components before conducting the pull and drop tests. The cast components shall be tested in accordance with ASTM E 186; ASTM E 280, or ASTM E 446 as applicable with the following acceptance levels:

Category A - Level 3
Category B - Level 3
Category C - Level 3
Category D to category G - Not allowed



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

The radiographic films and certification (see 6.3) which verify that the inspected areas meet the required acceptance levels shall be supplied to the contracting officer prior to pull and drop testing.

4.6.2.3 Cast component drop test. Each cast piece of the anchor shall be raised to a height of 12 feet and dropped on a steel slab. The casting shall withstand the drop test without fracture, cracking, or deformation. Certification of the drop test results shall be provided to the contracting officer (see 6.3).

4.6.2.4 Anchor pull tests. The anchor shall be completely assembled, except stabilizers, and shall be subjected to an ABS 2/3 fluke length pull test, a shank to tandem link test, and a lifting eye test. The pull tests shall verify the structural integrity of the anchor. The anchor shall be unpainted during these tests. The contractor shall notify the contracting officer 14 days prior to testing so that a Government representative may be present during the tests. Tests shall be in accordance with 4.6.2.4.1 through 4.6.2.4.4. The contractor shall provide the pull test fixture. The pull test fixture to be used in 4.6.2.4.1 shall transmit the test load into flukes uniformly so as to prevent local damage or collapsing of the fluke. A certification that each anchor was pull tested in accordance with 4.6.2.4.1 through 4.6.2.4.3 and passed the magnetic particle inspection of 4.6.2.4.4 shall be supplied to the contracting officer.

4.6.2.4.1 2/3 fluke length pull test. Perform the pull test to each fluke as follows:

a. Position the anchor in the test fixture such that the line of action of the test load intersects the shackle pin point and point A as shown in figure 1.
b. Apply 50 percent of the test load to anchor, hold; inspect anchor for deformations.
c. Continue pull test.
d. Terminate the pull test at a minimum load of 7,120 pounds for type I anchors and 60,580 pounds for type II anchors.

4.6.2.4.2 Shank and tandem ling pull test. The anchor shall be placed in the test fixture and a tension test load shall be applied to the shank and the link. The test load shall be a minimum of 7,120 pounds for type I anchors or 60,580 pounds for type II anchors.

4.6.2.4.3 Lifting eye test. The anchor shall be placed in the test fixture and a tension test load shall be applied to the shank lifting eyes. The test load shall be 250 pounds for type I anchors and 5,000 pounds for type II anchors.



Source: https://assist.dla.mil -- Downloaded: 202610-26T04:12Z
Check the source to verify that this is the current version before use.

4.6.2.4.4 Post-test magnetic particle inspection. Magnetic particle inspection shall be conducted on components and welds in accordance with ASTM E 709. Magnetic particle inspection shall be performed after proof testing and shall be 100 percent for all parts except pins, fasteners, and stabilizers. Acceptance requirements shall be in accordance with MIL-M-47230, grade B.

4.7 Anchor test data. The contractor shall prepare anchor test data for each anchor. The report shall contain the following minimum information:

a. Test equipment calibration certifications (4.1.3).
b. Material certifications (4.6.2.1).
c. Radiographic films prior to proof load (if required) (4.6.2.2).
d. Radiographic certification prior to proof load (if required) (4.6.2.2).
e. Cast component drop test certification (4.6.2.3).
f. Pull tests and magnetic particle certifications (4.6.2.4).
g. Anchor weight (4.6.2.5).
h. Welding procedure and welder qualifications (3.9).

The data shall be delivered to the contracting officer for approval prior to delivery of the respective anchor.

4.8 Noncompliance. If an anchor fails to pass any required inspection, the manufacturer shall notify the contracting officer and the cognizant inspection activity of such failure and take approved corrective action on the materials or processes, or both, as warranted, and on all units of product which can be corrected and which were manufactured with essentially the same materials and processes, and which are considered subject to the same failure. Acceptance and shipment of the product shall be discontinued until corrective action, acceptable to the contracting officer has been taken. In the event of failure after reinspection, information concerning the failure shall be furnished to the cognizant inspection activity and the contracting officer.

4.9 Inspection of packaging.

4.9.1 Packaging. Packaging shall be in accordance with the quality assurance provisions of the Uniform Freight or National Motor Freight Classification Rules and Regulations or other carrier rules, as applicable.

4.9.2 Marking. Marking shall be in accordance with the quality assurance provisions of MIL-STD-129.

5. PACKAGING

5.1 Packaging. Anchors and stabilizers shall be individually prepared for shipment (see 6.2). Shipping containers (boxes), when used, shall be provided with skids. All movable parts shall be securely fastened to prevent movement, dislodgement, or loss during handling, shipment, and storage. Anchors and stabilizers shall be arranged, secured, and packed for shipment in a manner acceptable to the carrier and which will ensure safe delivery at the destination in a satisfactory condition. The method of packing, packaging media (skids,



Source: https://assist.dla.mil -- Downloaded: 202610-26T04:12Z
Check the source to verify that this is the current version before use.

pallets, containers, etc.) when used, and loading shall comply with the Uniform Freight or Nation Motor Freight Classification Rules and Regulations or other carrier rules as applicable to the mode of transportation.

5.2 Marking. When specified (see 6.2), in addition to the anchor identification marking (see 3.7), shipping containers and unpacked anchors and stabilizers shall be marked in accordance with MIL-STD-129. In addition, shipping containers shall contain structural markings as required by MIL-STD-129.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. Anchors procured under this specification are to be used in connection with a causeway mooring system.

6.2 Acquisition requirements. Acquisition documents shall specify the following:

a. Title, number, and date of the specification (see 2.1.1).
b. Type required (see 1.2).
c. When a first article is required (see 3.2).
d. Packaging required (see 5.1).
e. When additional marking is required (see 5.2).

6.3 Consideration of data requirements. The following data requirements must be listed, as applicable, on the Contract Data Requirements List (DD Form 1423) when this specification is applied on a contract, in order to obtain the data, except where DoD FAR Supplement 27.475-1 exempts the requirement for a DD Form 1423.

| Reference paragraph | DID Number | DID Title |
|---|---|---|
| a. 3.9 | UDI-H-23384 | Qualification Data Welding Procedures |
| b. 4.7 | UDI-A-23264B | Certification Data/Report |

The above DIDs were those cleared as of the data of this specification. The current issue of DoD 5010.12-L, Acquisition Management Systems and Data Requirements Control List (AMSDL), must be researched to ensure that only current, cleared DIDs are cited on the DD Form 1423.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

6.4 First article. When a first article inspection is required, the item(s) should be a preproduction model. The first article should consist of one or more units. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examinations, approval of the first article test results and disposition of the first articles. Invitation for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection to those bidders offering a product which has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending contract. Bidders should not submit alternate bids unless specifically requested to do so in the solicitation.

6.5 Subject term (key word) listing.

Anchor
Anchor, causeway
Anchor, mooring system

Custodian:
Army - ME

Preparing activity:
Army - ME

Project 2040-A180



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.

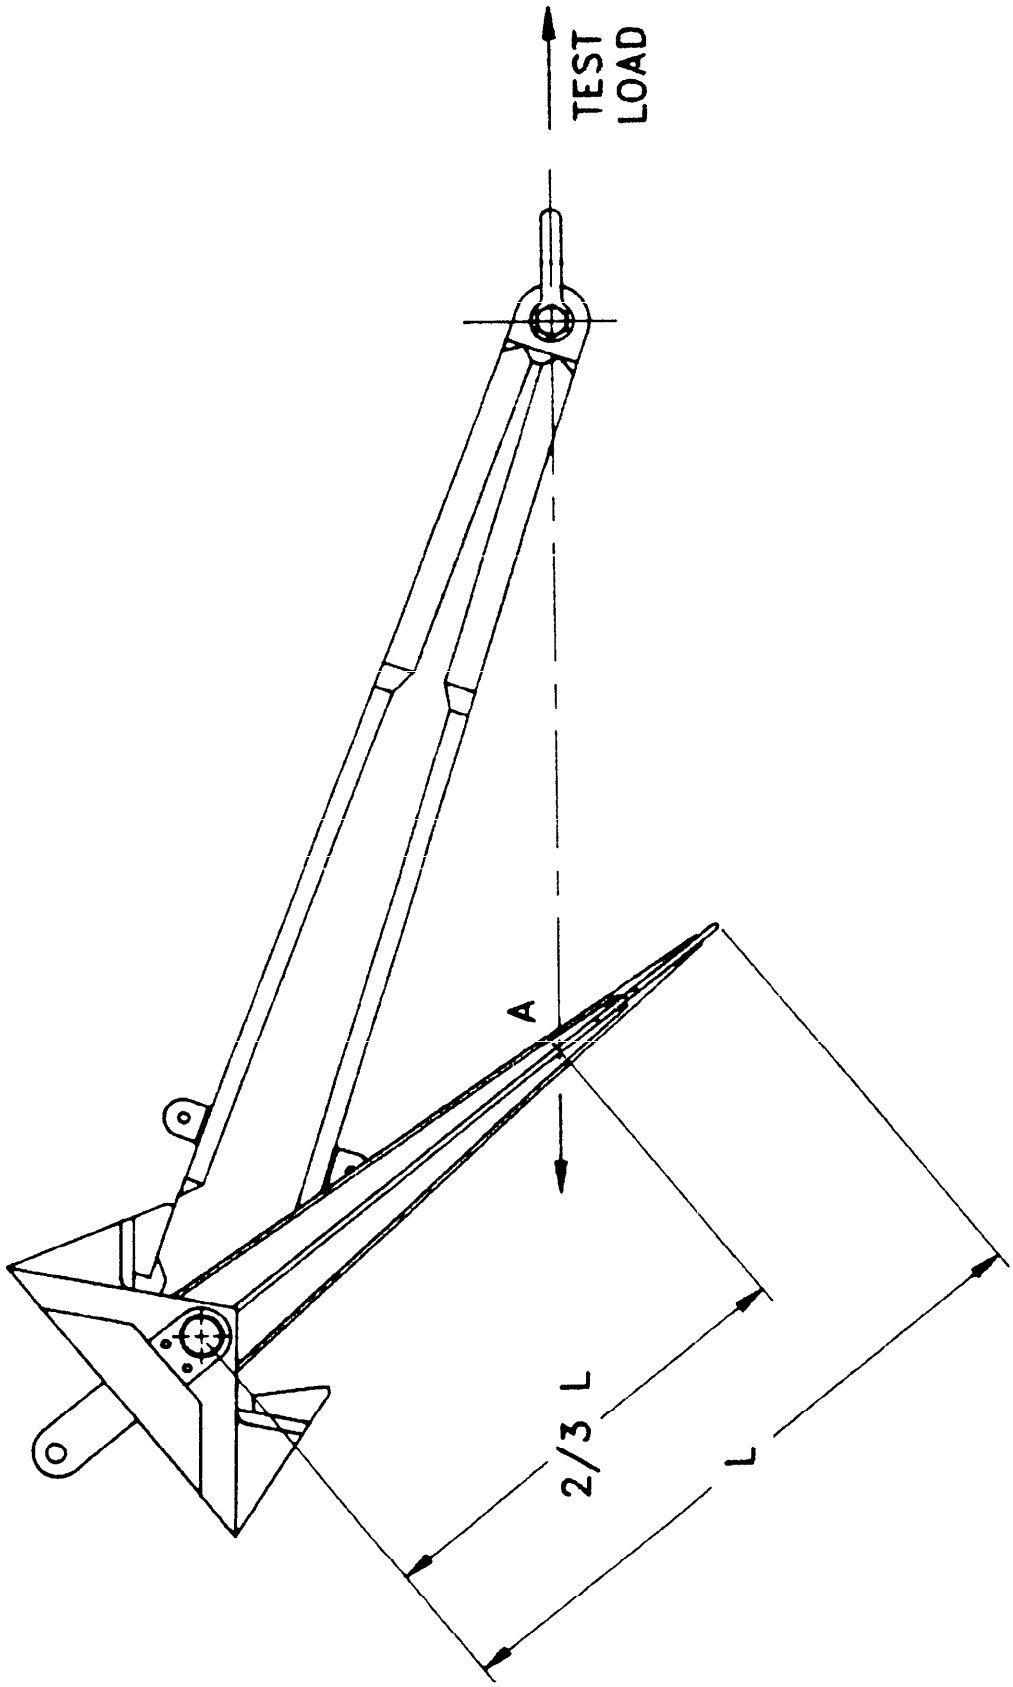



FIGURE 1. 2/3 FLUKE LENGTH PULL TEST

X-4830

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:12Z
Check the source to verify that this is the current version before use.

# STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

*(See Instructions – Reverse Side)*

| 1. DOCUMENT NUMBER | 2. DOCUMENT TITLE |
|---|---|
| MIL-A-53079(ME) | Anchor, Navmoor Causeway Mooring |

| 3a. NAME OF SUBMITTING ORGANIZATION | 4. TYPE OF ORGANIZATION *(Mark one)* |
|---|---|
| | ☐ VENDOR |
| b. ADDRESS *(Street, City, State, ZIP Code)* | ☐ USER |
| | ☐ MANUFACTURER |
| | ☐ OTHER *(Specify)*: _____ |

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

| 7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional | b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional |
|---|---|
| c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional | 8. DATE OF SUBMISSION *(YYMMDD)* |

*(TO DETACH THIS FORM, CUT ALONG THIS LINE.)*

DD FORM 1426 PREVIOUS EDITION IS OBSOLETE

Source: https://assist.dla.mil -- Downloaded: 2026-02-26T04:12Z
Check the source to verify that this is the current version before use.

**INSTRUCTIONS:** In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

*(Fold along this line)*

*(Fold along this line)*

DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

**BUSINESS REPLY MAIL**
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Belvoir RDE Center
ATTN: STRBE-TSE
Fort Belvoir, VA 22060-5606

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:12Z
Check the source to verify that this is the current version before use.