NOT MEASUREMENT SENSITIVE

MIL-DTL-11030G
4 May 2026
SUPERSEDING
MIL-S-11030F
14 September 1990

DETAIL SPECIFICATION

SEALING COMPOUND, SINGLE-COMPONENT, NON-CURING, POLYSULFIDE BASE

REACTIVATED AFTER 4 MAY 2026 AND MAY BE USED FOR NEW AND EXISTING DESIGN AND ACQUISITIONS.

This specification is approved for use by the Department of the Army and is available for use by all Departments and Agencies of the Department of Defense

1. SCOPE

1.1 Scope. This specification covers single-component black, inert, thermoplastic, mastic, non-curing, sealing compounds. These sealing compounds are not to be used as an integral fuel tank or pressure cabin standards. The service temperature of the sealing compounds is -40°C to 82°C (-40° to 180°F) (see 6.1).

1.2 Classification. Sealing compound should be furnished in the following types:

Type I	-	For static sealing of metal; glass, polyacrylic plastics to each other and in combinations with each other.
Type II	-	For rotary sealing of metal to metal having a cone penetration of approximately 200.
Type III	-	Extruded tape (see 3.1.3).

Comments, suggestions, or questions on this document should be addressed to: Director, U.S. Army DEVCOM Army Research Laboratory, Army Research Directorate, Specifications and Standards Office, Attn: FCDD-RLA-M, Aberdeen Proving Ground, MD 21005-5069. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil/.

AMSC N/A FSC 8030

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified (see 6.2), the issues of these documents are those cited in the solicitation or contract.

COMMERCIAL ITEM DESCRIPTIONS

A-A-55828	-	Sulfuric Acid, Technical
A-A-59123	-	Sodium Dichromate Dihydrate, Technical

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-23827	-	Grease, Aircraft and Instruments, Gear and Actuator Screw
MIL-PRF-8184	-	Plastic Sheet, Acrylic, Modified

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-129	-	Marking for Shipment and Storage
MIL-STD-1916	-	DoD Preferred Methods for Acceptance of Product
MIL-STD-2073-1	-	DoD Material Procedure for Development and Application of Packaging Requirements

FEDERAL STANDARDS

FED-STD-313	-	Material Safety Data, Transportation Data, and Disposal Data for Hazardous Materials Furnished to Government Activities.

(Copies of these documents are available online at https://quicksearch.dla.mil/.)

2.2.2 Other Government documents, drawings, and publications.

DEPARTMENT OF TRANSPORTATION (DOT)

49 CFR 100-199	-	Rules and Regulations for the Transportation of Hazardous Materials

(Copies of this document are available online at https://www.ecfr.gov/current/title-49.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified (see 6.2), the issues of these documents are those cited in the solicitation or contract.

THE AMERICAN NATIONAL STANDARDS INSTITUTE

ANSI/ASQ Z1.4	-	Sampling Procedures and Tables for Inspection by Attributes

(Copies of this document are available online at https://ansi.org/.)

ASTM INTERNATIONAL

ASTM A794/A794M	-	Standard Specification for Commercial Steel (CS), Sheet, Carbon (0.16 % Maximum to 0.25 % Maximum), Cold-Rolled
ASTM D217	-	Standard Test Methods for Cone Penetration of Lubricating Grease
ASTM D329	-	Standard Specification for Acetone
ASTM D471	-	Standard Test Method for Rubber Property - Effect of Liquids
ASTM D897	-	Standard Test Method for Tensile Properties of Adhesive Bonds
ASTM D3951	-	Packaging, Commercial
ASTM D4397	-	Standard Specification for Polyethylene Sheeting for Construction, Industrial, and Agricultural Applications
ASTM E2016	-	Standard Specification for Industrial Woven Wire Cloth

(Copies of these documents are available online at https://www.astm.org.)

CHEMICAL ABSTRACTS SERVICES

CAS 577-11-7	-	Dioctyl Sulfosuccinate Sodium Salt

(Copies of this document are available from https://commonchemistry.cas.org/.)

SAE INTERNATIONAL STANDARDS / Aerospace Material Specifications

SAE-AMS-QQ-A-250/4	-	Aluminum Alloy 2024, Plate and Sheet

(Copies of these documents are available from https://www.sae.org.)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein (except for related specification sheets), the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 Material.

3.1.1 Type I. Type I sealing compound shall be a non-curing mastic organic polysulfide polymer. The sealing compound shall be homogeneous, stable, and noncorrosive.

3.1.2 Type II. Type II sealing compound shall consist of 7.0 parts (by weight) of type I sealing compound plus 2.0 parts (by weight) of grease as specified in MIL-PRF-23827 (see 4.5.13).

3.1.3 Type III. Type III sealing compound shall be of the same consistency and as specified in 3.1.1 except for the following: Type III sealing compound shall be in tape form 0.05 inch (1.1 mm) thick-by 1.5 inch (38 mm) wide applied to a suitable release paper. Approximately 50 feet (15 m) of the tape shall be rolled on fiberboard cores having an inside diameter of approximately 3 inches (76 mm).

3.2 Volatile content. The volatile content of type I and type III sealing compound shall be not greater than 1.5 percent when tested as specified in 4.5.1. There is no requirement for type II compound.

3.3 Water solubility. The water solubility of type I and type III sealing compound shall be not greater than 0.4 percent when tested as specified 4.5.2. There is no requirement for type II compound.

3.4 Oil resistance. Type I and type III sealing compound shall show no evidence of blistering, softening, or loss of adhesion when exposed to mineral oil and tested as specified in 4.5.3. There is no oil resistance requirement for type II sealing compound.

3.5 Adhesion. Type I and type III sealing compound shall have a bond strength of not less than 25 psi (1.75 kg/cm^2). Failure shall occur only in the sealing material itself when tested as specified in 4.5.4. Type II sealing compound has no adhesion requirements.

3.6 Aging. When tested as specified in 4.5.5, the sealing compound shall show a cone penetration before and after aging as specified in table I.

TABLE I. Cone Penetration.

Penetration Condition	Types I and III	Type II
Depth of cone penetration before aging in 0.10 mm	40 - 80	150 - 250
Depth of cone penetration after aging in 0.10 mm	20 max	40 max

3.7 Effect of volatile compounds. For type I and type III, there shall be no evidence of chemical attack such as crazing, pitting, or etching on the surface of poly (methyl methacrylate) when exposed to volatile components of freshly prepared sealing compound and tested as specified in 4.5.6. There is no requirement for type II.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

3.8 Crazing on stressed acrylic plastic. Type I and type III sealing compound shall not cause crazing or cracking of acrylic plastic under stress when tested as specified in 4.5.7.

3.9 Low temperature flexibility. Type I and type III sealing compound shall show no evidence of cracking or loss of adhesion when subjected to flexing at -40° ± 1°C (-40° ± 2°F) and tested as specified in 4.5.8.

3.10 Fluid resistance at elevated temperature. Type I and type III sealing compound shall show no evidence of hardening, blistering, or any other deleterious property when tested as specified in 4.5.9. There is no heat resistance requirement for type II sealing compound.

3.11 Water vapor permeability. When tested as specified in 4.5.10, the water vapor permeability rate of the sealing compound shall not exceed the following requirements:

Types I and III	-	Not greater than 0.010 gm/hr/sq. inch
Type II	-	Not greater than 0.012 gm/hr/sq. inch

3.12 Color. The color shall be black (see 4.5.11).

3.13 Toxicity. The materials shall not contain any asbestos, lead, mercury, or chromate compounds. The material shall have no adverse effects on the health of personnel when used for its intended purpose. Questions pertinent to this effect shall be referred by the contracting activity to the appropriate departmental medical service who will act as an advisor to the contracting agency (see 4.5.12).

3.14 Workmanship. The sealing compound shall be homogeneous and contain no foreign matter, and shall conform to the quality and grade of product established by this specification.

3.15 Shelf life. The sealing compound should be packaged such that the preservation of the product lot will be such to remain viable for one full year from the date of manufacture and indelibly printed on the packaging.

3.16 SDS. The manufacturer shall comply with the requirements as specified in the OSHA Brief:

(https://www.osha.gov/dsg/hazcom/osha-brief.html.)

and, as specified in Appendix D of 29 CFR 1910.1200 see:

(https://www.osha.gov/laws-regs/regulations/standardnumber/1910/1910.1200AppD.)

A SDS shall be prepared for the material in accordance with FED-STD-313 and forwarded to the qualifying activity (see 6.4.3). The SDS shall be included with each shipment of the material covered by this specification and submitted to pertinent Government agencies as stated in FED-STD-313.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

4. VERIFICATION

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract, the contractor may use their own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Lot acceptance tests. A lot shall consist of all materials of the same type, from the same batch or blending operation, subjected to the same processing operations and conditions, produced by one manufacturer and offered for delivery at one time. Unless otherwise specified, for the purpose of lot acceptance tests, representative results shall be reported from the results obtained on a frequency basis for grades of sealing compound which are monitored using process control systems and procedures which ensure no defects and shall be the basis for acceptance or rejection of the lot. Lot acceptance tests shall consist of the test indicated in table II.

TABLE II. Lot acceptance test requirements.

Characteristic	Type I	Type II	Type III	Test Method
Volatile Content	3.2	---	3.2	4.5.1
Water Solubility	3.3	---	3.3	4.5.2
Oil Resistance	3.4	---	3.4	4.5.3
Adhesion	3.5	---	3.5	4.5.4
Aging	3.6	3.6	3.6	4.5.5
Effect of Volatile Compounds	3.7	---	3.7	4.5.6
Crazing	3.8	---	3.8	4.5.7
Low Temperature Flexibility	3.9	---	3.9	4.5.8
Fluid Resistance	3.10	---	3.10	4.5.9
Water Vapor Permeability	3.11	3.11	3.11	4.5.10
Color	3.12	3.12	3.12	4.5.10
Toxicity	3.13	3.13	3.13	4.5.12

4.3 Sampling.

4.3.1 Sampling for examination of sealing compound. Unless otherwise specified a random sample of filled containers shall be selected following MIL-STD-1916 guidance in accordance level 1 of ANSI/ASQ Z1.4.

4.3.2 Sampling for tests. A sample consisting of 1 qt (0.95 liter) of sealant or one roll of 50 ft (15 meter) tape, representative of the lot shall be selected and placed in a wide-mouth, glass, 1 qt (0.95 liter) container and sealed tightly.

4.4 Examination.

4.4.1 Examination of sealing compound. Sample units of sealing compound selected in accordance with 4.3.1 shall be examined for defects listed in table III. Sampling plan acceptance and rejection numbers apply collectively to all characteristics.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

TABLE III. Classification of defects in sealing compound.

Defect Classification	Defect	Inspection Method
Major 101	Evidence of settling or separation (see 3.1)	Visual
Major 102	Milling and blending not as specified (see 3.1)	Visual
Major 103	Evidence of corrosion on inside of containers (see 3.1)	Visual
Major 104	Type III tape not on suitable release paper (see 3.1.3)	Manual and Visual
Major 105	Type III tape on improper cores or not wound (see 3.1.3)	Manual and Visual
Major 106	Type III tape of wrong dimensions (see 3.1.3)	Manual and Visual
Major 107	Evidence of foreign matter (see 3.14)	Visual
Major 108	Workmanship not as specified (see 3.14)	Visual

4.4.2 Cleaning on test panels. Except where otherwise specified herein, 2024 aluminum metal panels (SAE-AMS-QQ-A-250/4) and steel (ASTM A794/A794M) test panels shall be cleaned in preparation for tests using steel wool or number 400 emery cloth, rinsed with ASTM D329 (acetone) solvent and blotted dry with lint-free cheesecloth or lint-free laboratory wipes.

4.5 Tests.

4.5.1 Volatile content. Weigh a 2 by 4 inch (5.0 by 10.1 cm) aluminum panel to the nearest 0.001 g. Approximately 2 g of the sealing compound shall be spread uniformly to approximately 0.0625 in. (1.5 mm) thick on one side of the panel. The panel with the compound shall be weighed and then placed in an oven at 65.5° ± 1°C (150 ± 2°F) for two hours. The panel with the compound shall then be reweighed. The loss in weight divided by the weight of the original coating multiplied by 100 shall constitute the percent of volatile content. Tests shall be performed in duplicate. Failure of either sample shall be cause for rejection of the lot (see 3.2).

4.5.2 Water solubility. The panels used in determining volatile content shall be immersed in distilled water and heated at 65.5° ± 1°C (150° ± 2°F) for 4 hours. They shall then be removed and dried at 65.5° ± 1°C (150° ± 2°F) for 4 hours. The loss in weight divided by the weight of the coating after determination of the volatile content and multiplied by 100 shall constitute the percent of water soluble material. Failure of the sample shall be cause for rejection of the lot (see 3.3).

4.5.3 Oil resistance. Approximately 2 g of the sealing compound shall be spread uniformly on one side of a 1 by 4 inch (2.5 by 10.1 cm) aluminum panel. The aluminum shall have first been cleaned by dipping in ASTM D329 (acetone) solvent, immersing in 3% alkaline cleaner (90% sodium metasilicate and 10% Aerosol OT-B - see CAS 577-11-7) at 80°C (176°F) for 5 minutes, washing in running tap water, immersing in dichromate solution (85 grams of sodium dichromate, A-A-59123, and 250 ml of concentrated sulfuric acid, A-A-55828 to 2 liters of distilled water) at 75°C (167°F) for 5 minutes, washing in running tap water and distilled water and drying. The sample shall then be partially immersed for 96 hours in oil conforming to Oil No. 2 (ASTM D471). The test shall be conducted at room temperature. The panel shall be removed and the sample examined for evidence of blistering, softening and lack of adhesion. Test shall be performed in duplicate. Failure of either sample shall be cause for rejection of the lot (see 3.4).

4.5.4 Adhesion. Test shall be made as described in ASTM D897 except that there shall be 3 types of specimens: (a) steel specimens as described in ASTM D897 and ASTM A794/A794M: (b) steel

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

specimens with a thin glass wafer bonded with suitable adhesive (epoxy resin base) to the steel working surfaces; (c) steel specimen with a polyacrylic plastic (conforming to MIL-PRF-8184) wafer bonded to the working surface. The sealing compound shall be applied to both surfaces. The specimen shall be compressed under a load of 200 lb (90 kg) for about 20 seconds to ensure a minimum gap between the adherents of the specimen. The prepared specimen shall be conditioned at room temperature 72° - 77°F (22° - 25°C) for 49 hours prior to testing. The bond strength of the assembly shall be measured in a tensile testing machine whose jaw separation speed is 1 inch per minute. The specimens shall be examined for failure in cohesion of the sealing material. The tests shall be performed in duplicate. Failure of either sample from any of the specimen types shall be cause for rejection of the lot (see 3.5).

4.5.5 Aging. The consistency of the sealing compound shall be determined in the original condition and after aging for 24 hours at 65.5° ± 1°C (150 ± 2°F). The sample shall be tested in accordance with ASTM D217 tested for unworked penetration, using a 150 g total load for 5 seconds. Four readings shall be taken on each sample. More than one unsatisfactory reading shall be cause for rejection of the lot (see 3.6).

4.5.6 Effect of volatile components. A 5-6 g sample of the sealing compound shall be placed on a 2 inch (5.0 cm) diameter watch glass and then placed in an enclosed vessel which contains a polished polymethylmethacrylate (conforming to MIL-PRF-8184) window as shown on figure 1. The test fixture shall be placed in an oven at 71° ± 1°C (160° ± 2°F) for 3 hours, then removed and allowed to cool to a temperature of approximately 38°C (100°F). The outer surface of the polymethylmethacrylate window shall be cooled by placing a piece of dry ice having a flat size of about 0.5 in^2 onto the window of the fixture and allowing it to remain in contact with the window until condensation is observed on the inner surface of the window or for a period not greater than 20 minutes. The fixture shall then be allowed to remain at room temperature for a period of 2 hours. The window of the fixture shall be removed and its inner surface washed with tap water and wiped with a soft cloth. The surface shall then be examined with the aid of a 10X magnifier in the area where condensation had formed for visual evidence of crazing, pitting, or etching. Visual examination shall be done by viewing perpendicular to the surface and then at an angle of 30 to 45 degrees to the surface. The tests shall be performed in duplicate. Failure of either sample shall be cause for rejection of the lot (see 3.7).

4.5.7 Crazing on stressed acrylic plastic. A piece of sheet plastic in accordance with MIL-PRF-8184 shall be set up as a cantilever beam under load, as shown in figure 2. After the beam has been loaded for 10 minutes and while still under load, the compound shall be applied to the top (tension) side of the plastic specimen two inches from the clamped end and directly above the support and allowed to remain an additional 10 minutes under load. The acrylic plastic sheet shall be examined with the aid of a 10 power magnifier for visual evidence of crazing or other attack while under stress. Visual examination shall be done by viewing perpendicular to the surface and then at an angle of 30 to 45 degrees to the surface. Visible evidence of crazing or other attack while under stress constitutes failure of this test. Failure of the test shall be cause for rejection of the lot (see 3.8).

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

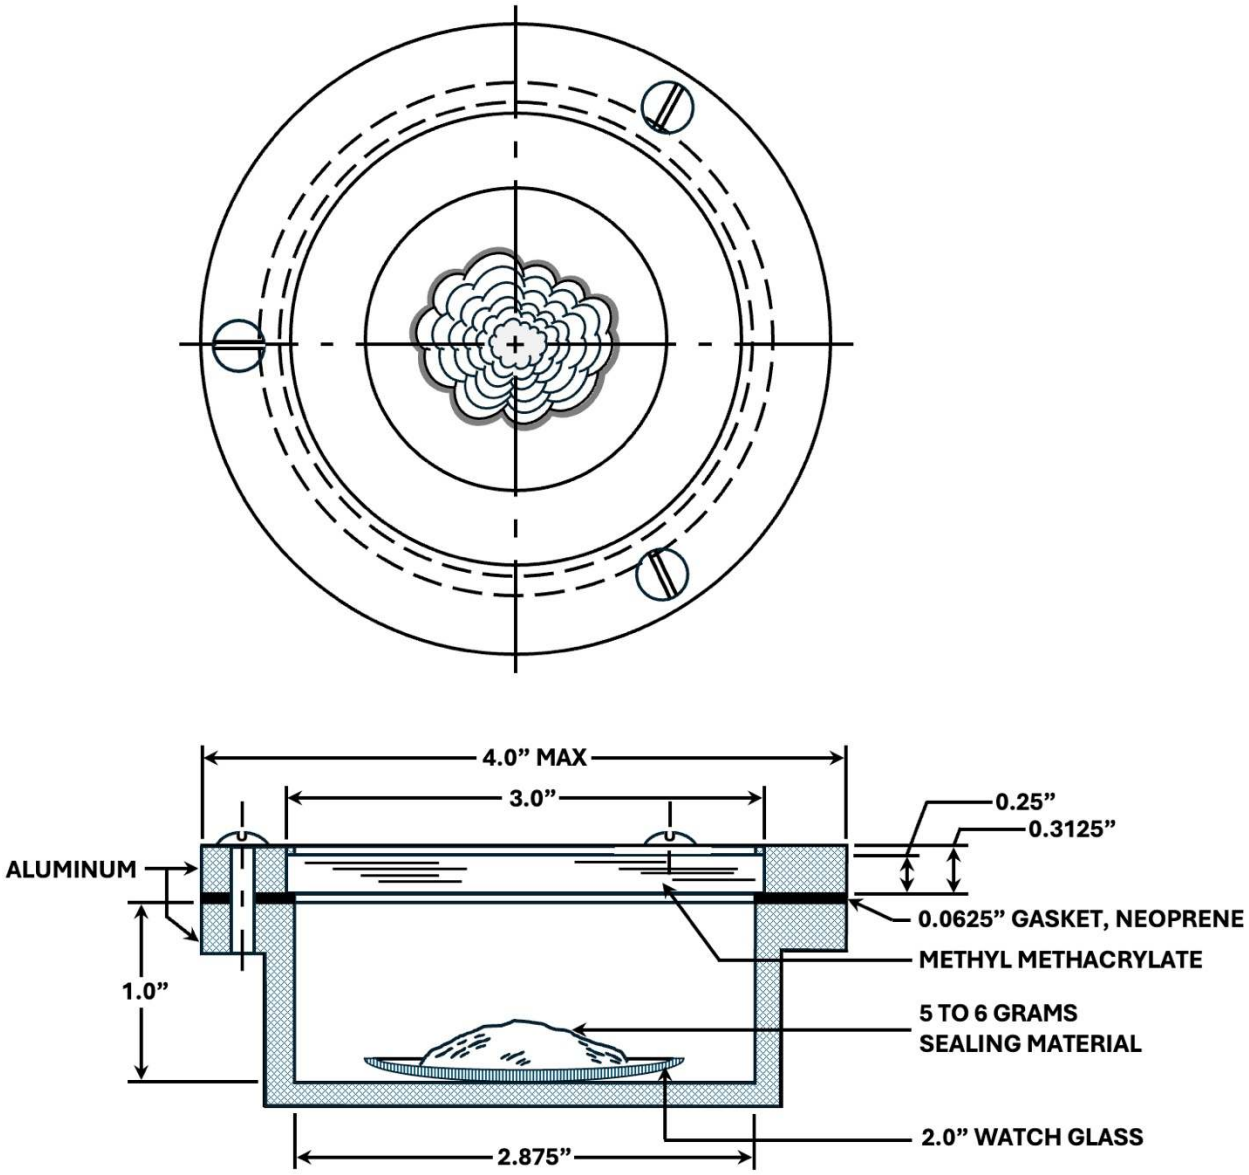


FIGURE 1. Assembly for test on effect of volatile components.
(Dimensions in inches.)


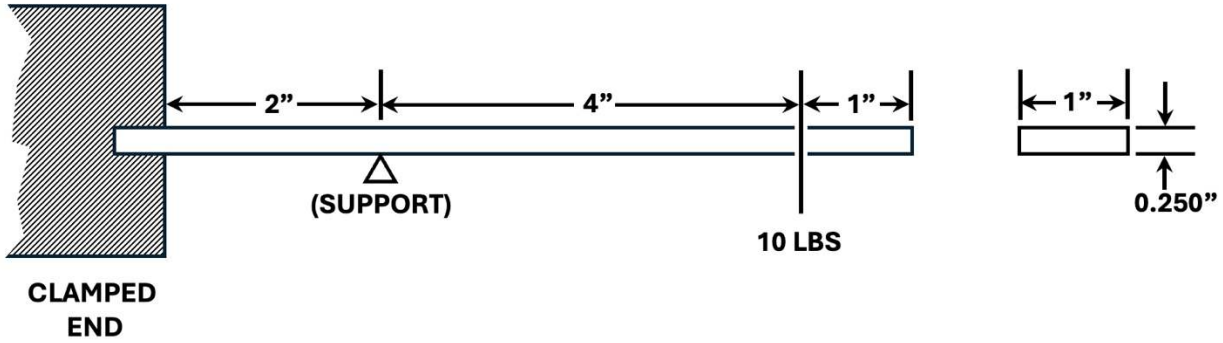


FIGURE 2. Stress crazing test configuration.
(Dimensions in inches.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

4.5.8 Low temperature flexibility. Two panels, 1.0 x 6.0 x 0.030 in. (2.5 x 15.2 x 0.07 cm) of aluminum surfaced aluminum alloy 2024, conforming to SAE-AMS-QQ-A-250/4, shall be coated on one side with the sealing compound to a thickness of 0.03 in. (0.07 cm) or for the test of type III a single thickness of tape. The panels shall then be immersed for 48 hours at 38° ± 10°C (100° ± 2°F) in 30 percent aromatic hydrocarbon test fluid, conforming to ASTM D471. At the completion of the immersion period, the panels and the flexibility jig (figure 3), shall be subjected to a temperature of -40° ± 1°C (-40° ± 2°F) for two hours. While at this temperature, one end of the test panel shall be placed in the slotted position and the other bent around the curved portion of the flexibility test jig, at a steady uniform rate such that 3 seconds are required to complete the bend. The panels shall be removed and examined. Failure of either panel shall be cause for rejection of the lot (see 3.9).

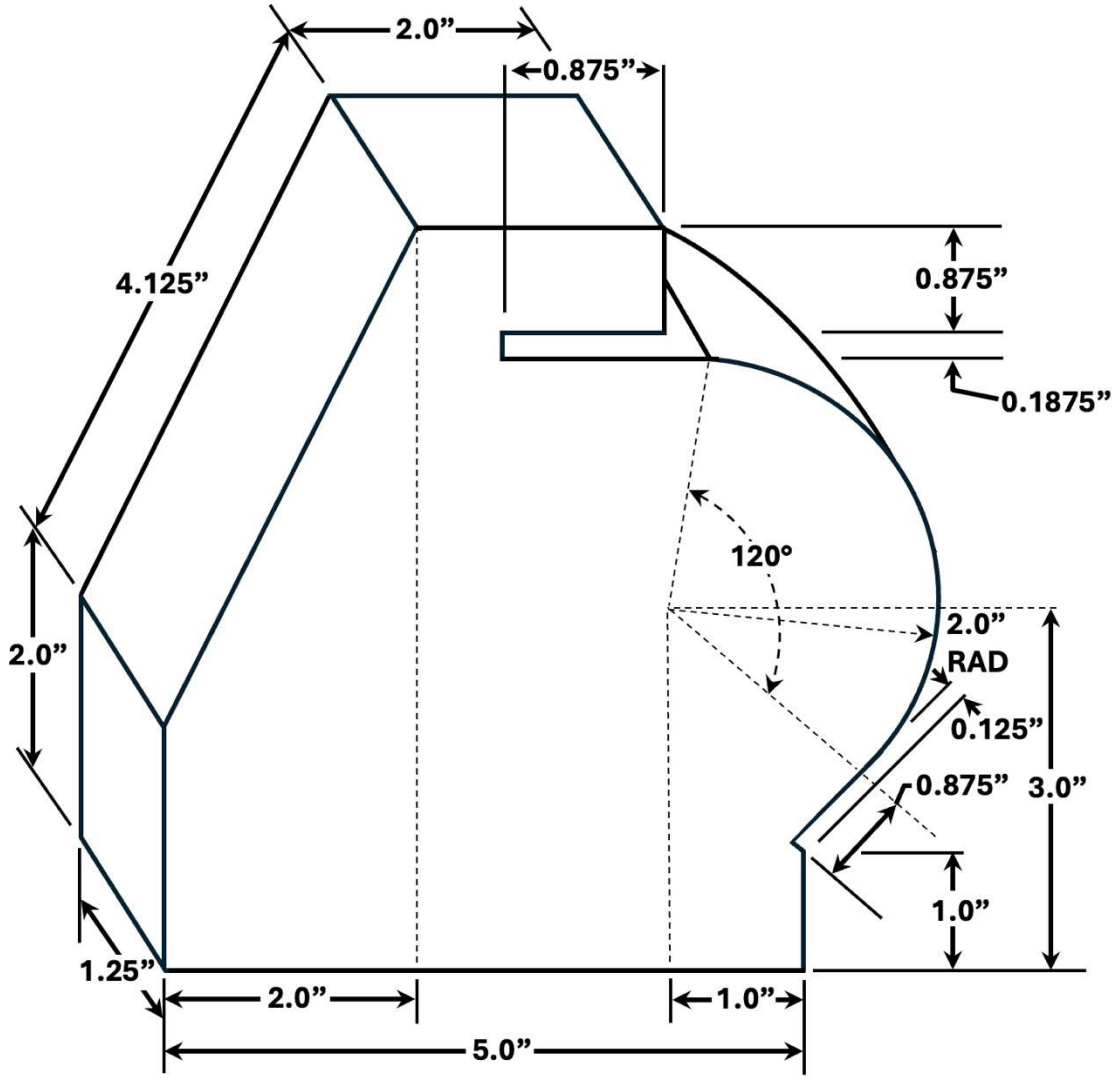

NOTE: MAPLE WOOD


FIGURE 3. Low temperature flexibility test jig.
(Dimensions in inches.)

4.5.9 Fluid resistance at elevated temperatures. Two panels, 3 by 5 inches (7.6 by 12.7 cm) of aluminum surfaced alloy conforming to SAE-AMS-QQ-A-250/4, shall be coated on one side with

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

the sealing compound to a thickness of 0.0625 in. (0.16 cm) or for the test of type III at a single thickness of the tape. The panels shall be immersed for 48 hours at 38° ± 1°C (100° ± 2°F) in aromatic hydrocarbon test fluid conforming to ASTM D471, so that one half of the material is above the liquid level. The panels shall then be removed, air dried for 24 hours, and baked at 82° ± 1°C (180° ± 2°F) for 72 hours. The panels shall then be examined for changes in film properties. Visible evidence of change in the film property shall constitute failure of this test. Failure of the sample shall be cause for rejection of the lot (see 3.10).

4.5.10 Water vapor permeability. A sufficient amount of sealing compound shall be pressed between two sheets of polyethylene film (0.003-0.004 inches thick), according to ASTM D4397 to form a film about 0.075 in. (0.19 cm) thick and 2 in. (5.0 cm) in diameter. One of the polyethylene sheets shall be peeled off and a suitable size screen which shall retain the sealing compound shall be placed on the sealing compound. Use 2.5 inch (6.3 cm) diameter 30 mesh plain weave screening with 0.010 inch (0.025 m) diameter wire made of type 5056 aluminum or brass, according to ASTM E2016. The polyethylene sheet shall be placed on the screen, and the assembly shall be compressed until the overall thickness of the sealing compound, and the screen is 0.064 ± 0.002 in. (0.16 ± 0.01 cm). The polyethylene sheets shall be removed, and the screen-supported film shall be trimmed to size and placed in a position as shown in figure 4. Next, 5 ml of distilled water shall be placed in a Petri dish. The two metal plates holding the film of sealing compound and the Petri dish shall be screwed tightly to ensure a good seal between the edge of the Petri dish and the sealing material (see 3.11).

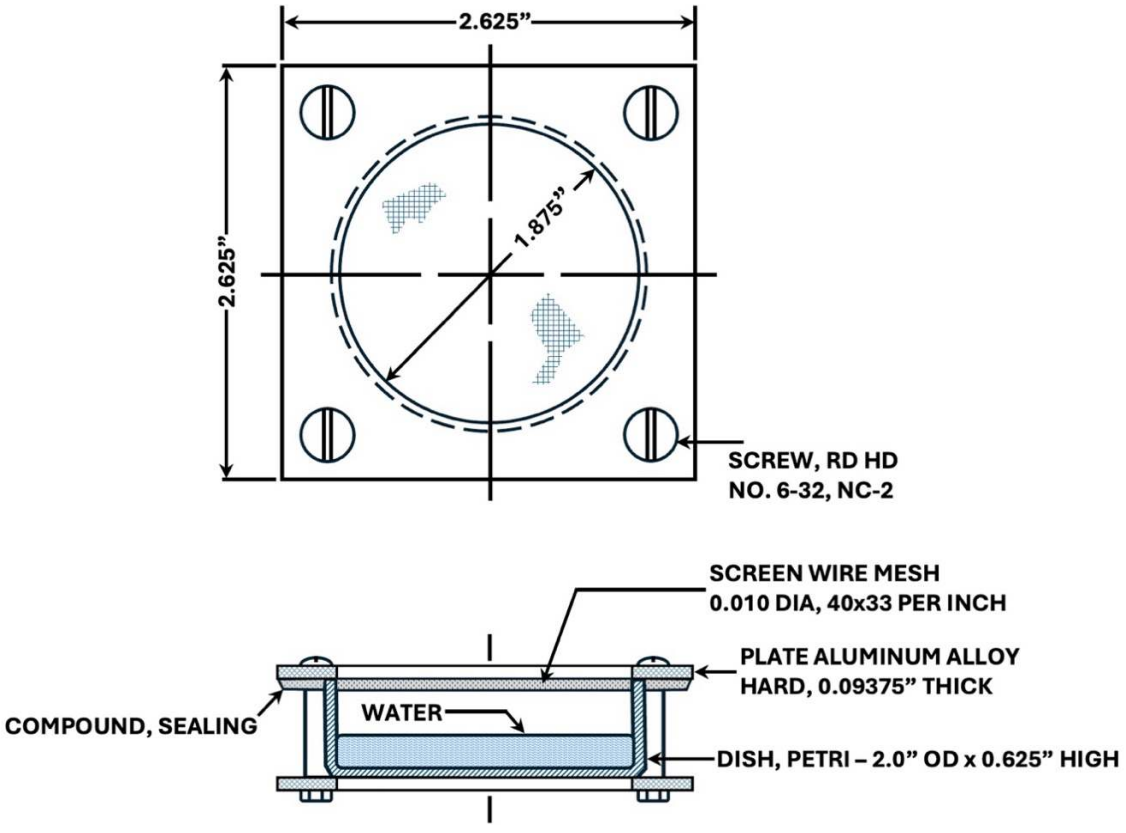

NOTE: TOP AND BOTTOM PLATES ARE IDENTICAL, EXCEPT THAT SCREW HOLES ARE TAPPED INTO BOTTOM PLATE

FIGURE 4. Assembly for water vapor permeability test.
(Dimensions in inches.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

4.5.10.1 Assemblies. Two assemblies shall be prepared as described in 4.5.10. A third assembly shall be prepared in the same manner except that no water shall be placed in the Petri dish. The three assemblies shall be weighed to the nearest 0.001 grams and then placed in an oven at 71° ± 1°C (160° ± 2°F) for 4 hours. The loss in weight of the dry assembly shall be subtracted from the weight of each of the other two assemblies. The water vapor transmission rates shall be calculated in units of g of water/hr/in^2 of open area. The open area is the area of the 1.875 inch hole in the metal plate minus the area occupied by the wires of the screen within the hole. Failure of either sample shall be cause for rejection of the lot. Percent of water vapor is calculated as follows:

$$\frac{\text{wt of (sample + water + dish)}}{\text{wt of dish}} \times 100$$

conducted at 1 hr intervals until constant weight.

4.5.13 Certification. The test procedures for type II for the quantity of grease and for the grease to be specified in MIL-PRF-23827 may be waived by the procuring activity upon certification by the supplier that the lot for acceptance meets the requirements of the specification. The certificate shall be signed by a responsible agent of the certifying organization and shall be accompanied by evidence of this agent's authority to bind his principal. The Government reserves the right to check test material submitted by the supplier under certification.

4.6 Safety Data Sheet (SDS). Safety Data Sheets shall be inspected to determine conformance to FED-STD-313 (see 3.16).

4.7 Inspection of packaging.

4.7.1 Quality conformance inspection of packaging.

4.7.1.1 Unit of product. For the purpose of inspection, a complete commercially prepared pack ready for shipment in accordance ASTM-D3951 and/or MIL-STD-2073-1 shall be considered a unit of product (see 3.15). NOTE: significant changes to packaging practices for acquisition have occurred since the prior revision of this specification and modern standard packaging practices cited in 5.1 shall be followed unless otherwise indicated in the contract or purchase order.

4.7.1.2 Sampling. Unless otherwise indicated in the contract or purchase order, sampling for packaging examination shall be in accordance with MIL-STD-1916 and ANSI/ASQ Z1.4.

4.7.2 Examination. Samples selected in accordance with 4.7.1.2 shall be examined for the following defects. Presence of one or more defects shall be cause for rejection (see table IV).

TABLE IV. Classification of defects, packaging requirements.

Defect Classification	Defect	Inspection Method
Major 109	Preservation not as specified (see 3.15)	Visual
Major 110	Packing not as specified (see 5.1)	Visual
Major 111	Marking missing, illegible, incorrect or incomplete (see 3.15, 3.16, and 6.3.1(	Visual

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system command. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

5.5.1 Packaging and preservation notes. Due to the substantial passage of time since the last revision of this specification, additional select packaging information that may be helpful including any remaining viable past definitions and procedures for unit of product, sampling, packaging inspection, and exterior container markings are included in 6.3 and its sections therein. This legacy content will be deleted in the next revision or amendment to this specification.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended uses. The sealing compounds covered by this specification are intended for use in sealing metal to metal, glass to metal and acrylic to metal and for general purpose as deemed necessary by the using activity. This material is not to be used as an integral fuel tank or pressure cabin sealant.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number and date of the specification.
b. Type of material required (see 1.2).
c. Quantity of material desired.
d. Level of preservation required (see 3.15)
e. Level of packing required (see 5.1).
e. Special marking if required (see 3.15 and 6.3.1)

6.3 Packaging and preservation considerations. Due to the substantial length of time since the last revision of this specification, additional packaging information including past definitions and procedures for unit of product, sampling, and packaging inspection are included as a courtesy in this section.

6.3.1 Marking. In addition to any special marking required by the contract (see 6.2), all unit intermediate and exterior- shipping containers should be marked in accordance with MIL-STD-129.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

6.4 Subject term (key word) listing.

Adhesion	Black sealer	Water proofing

6.5 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.

CONCLUDING MATERIAL

Custodian:
Army - MR
Air Force - 20
Navy - AS

Preparing activity:
Army - MR

Project 8030-2026-002

Review activities:
Army - AR, AT, MI
Air Force - 84
Navy - CG, OS, SH, YD
Other DoD - FAS

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T15:00Z
Check the source to verify that this is the current version before use.