MIL-H-13719C
17 March 1969
SUPERSEDING
MIL-H-13719B
20 January 1961

MILITARY SPECIFICATION
HOSE ASSEMBLY, RUBBER; HYDRAULIC BRAKE

This specification is mandatory for use by all departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers two types of hose assemblies for use as flexible connections on hydraulic brake equipment for Military vehicles.

1.2 Classification. Hose assemblies shall be of the following types, as specified (see 6.2):

Type I - Regular expansion, (see 6.1)
Type II - Low expansion, (see 6.1, 6.3.1)

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein.

SPECIFICATIONS

Federal

QQ-P-416 - Plating, Cadmium (Electrodeposited).
QQ-Z-325 - Zinc Coating, Electrodeposited, Requirements For.
VV-B-680 - Brake Fluid, Automotive.

Military

MIL-T-3520 - Tube, Steel, Round.
MIL-F-13927 - Fungus Resistance Test; Automotive Components.

STANDARDS

Federal

Fed. Test Method Std. No. 601 - Rubber: Sampling and Testing.
Fed. Test Method Std. No. 151 - Metals: Test Methods.

Military

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-166 - Visual Inspection Guide for Rubber Hose.
MIL-STD-190 - Identification Marking of Rubber Products.

FSC 2530

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following document forms a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

NATIONAL BUREAU OF STANDARDS
Handbook H28 - Screw-Thread Standards for Federal Services.

(Application for copies should be addressed to the Superintendent of Documents, U. S. Government Printing Office, Washington, D.C. 20402.)

3. REQUIREMENTS

3.1 Qualification. The hose assembly furnished under this specification shall be a product which is qualified for listing on the applicable qualified products list at the time set for opening of bids (see 4.2 and 6.4).

3.2 Materials. Unless otherwise specified herein, materials shall conform to the applicable drawings and specifications (see 6.2).

3.2.1 Rubber. Rubber shall be a nonblooming synthetic compound as specified.

3.2.1.1 Tube. Tube shall be seamless and made from compounds utilizing a copolymer product of butadiene and styrene or polymerized chloroprene as the basic material.

3.2.1.2 Cover. Cover shall be black, made of compounds utilizing polymerized chloroprene as the basic material, and shall be free of holes exposing braid.

3.2.2 Reinforcement. Reinforcement shall consist of two braids of material imbedded in and bonded to the rubber, and shall meet the performance requirements of this specification.

3.2.3 Fittings. Fittings of hose assemblies shall be securely attached to the hose. Dimensions and materials of fittings shall conform to the applicable standard or drawing. Steel fittings shall be cadmium plated, conforming to type II, class 3 of QQ-P-416, or zinc coated, conforming to type II, class 3 of QQ-Z-325. Threads on fittings shall conform to the applicable drawings or with Screw-Thread Standards for Federal Services Hankbook H28.

3.3 Dimensions. Inside diameter (nominal) of the hose shall be 1/8 inch, 3/16 inch, or 1/4 inch. Hose assemblies shall be furnished in the nominal inside diameter, and the length as specified (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

3.4 Performance.

3.4.1 Pressure resistance. All hose assemblies shall be tested as specified in 4.4.2, and shall show no evidence of leakage.

3.4.2 Constriction. When tested as specified in 4.4.3, plug gages shall drop, of their own weight, a distance of 3 inches into the hose in not more than 5 seconds.

3.4.3 Expansion resistance. When tested as specified in 4.4.4, hose shall expand not more than the values shown in table I.

Table I. Maximum hose expansion.
c.c. per foot free length

Hose size Inch I.D.	1000 PSI		1500 PSI	
	Reg.expansion hose type I	Low expansion hose type II	Reg.expansion hose type I	Low expansion hose type II
1/8	0.66	0.33	0.79	0.42
3/16	0.86	0.55	1.02	0.72
1/4	1.04	(a)	1.30	(a)

(a) At present there is no 1/4 inch I. D. low expansion hose available.

3.4.4 Bursting strength. When tested as specified in 4.4.5, hose assemblies shall withstand internal hydrostatic pressure for the 2-minute hold period specified in table II without bursting and shall not leak or burst at any pressure up to and including the burst value specified in the same table.

Table II. Hold and burst pressures.

Nominal ID of hose Inch	Hydrostatic pressure	
	2-minute hold PSI	Minimum burst PSI
1/8	4,000	5,000
3/16	3,000	4,500
1/4	3,000	4,500

3.4.5 Fatigue life. When tested as specified in 4.4.6, hose assemblies shall have a minimum life of 35 hours.

3.4.6 Low temperature flexibility. When tested as specified in 4.4.7, hose assemblies shall show no evidence of breaks, cracks, or leakage.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

3.4.7 Tensile strength. When tested as specified in 4.4.8, hose assemblies shall evidence no rupture of the hose or loosening of the end fittings.

3.4.8 Ozone resistance. When tested as specified in 4.4.9, hose shall show no evidence of cracks or breaks.

3.4.9 Fluid resistance. When tested as specified in 4.4.10, the volume of the tube specimen shall not increase by more than 20 percent nor decrease by more than 3 percent.

3.4.10 Fungus resistance. When tested as specified in 4.4.11, hose assemblies shall meet the requirements of 3.4.1.

3.4.11 Corrosion resistance. When tested as specified in 4.4.12, fittings shall show not more than one red rust spot 1/16 inch in diameter. No white corrosion shall occur on areas that can be contacted by a 0.5 inch diameter ball.

3.5 Marking.

3.5.1 Hose assemblies. Hose assemblies, having a free length of 12 inches or longer, shall have the outer cover marked with an oil-resistant, continuous blue stripe. The following information shall be legibly marked or broken into the stripe, at repeated intervals of not more than 12 inches on the lay line of the hose:

Specification number.
Size (nominal diameter).
Date of manufacture (quarter and year).
Capital letters "OZ".
Manufacturer's code symbol.

3.5.2 Short lengths. Hose assemblies having a free length of less than 12 inches shall have the following information stamped on the fittings:

Manufacturer's code.
Capital letters "OZ".

The unit package containing the hose shall, in addition to other required marking, show the following:

Specification number.
Date of manufacture (quarter and year).
Size (nominal diameter).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

3.5.3 Rough hose cover. Hose assemblies having a free length of 12 inches or longer, meeting all other requirements of this specification, may, at the discretion of the Government inspector, be marked as specified in 3.5.2, when the cover is too rough, or for any other reason, it is determined that the use of a stripe is impractical on the outside cover. Permanence and legibility of markings shall conform to MIL-STD-190.

3.6 Condition. All hose assemblies offered to the Government for acceptance shall be in good condition and free of defects and shall not have been used or subjected to any tests except as specified in 4.4.2. Tubing used in the hose assemblies shall have been manufactured not more than 2 quarters prior to presentation for acceptance.

3.7 Workmanship. Workmanship shall be such as to produce hose assemblies that are free of imperfections such as cuts, breaks, blisters, and pitting. Swivel type fittings shall move freely. Seating surfaces of all fittings shall be free of damage.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Qualification testing. A sample of 20 hose assemblies, 1/8-inch I.D. (see 6.3) and a free hose length (measured between fittings) of 14 inches shall be submitted for qualification testing. The samples shall be representative of the units proposed to be furnished to the Government. Qualification testing shall be conducted by the qualifying activity at a place designated by the Government (see 6.4) and shall consist of examination for the defects specified in 4.3.2.2 and testing as specified in table III.

Table III. Order of qualification testing.

Sample No.	Paragraph No.
1, 2, 3, 4	4.4.3, 4.4.2, 4.4.6
5, 6	4.4.4, 4.4.5, 4.4.10
7,8	4.4.9
9, 10	4.4.7, 4.4.2
11, 12	4.4.8
13, 14, 15, 16	4.4.11, 4.4.2, 4.4.12

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

4.2.1 Failure. Failure of a qualification sample to pass any examination or test specified herein may be cause for refusal to conduct additional tests until it has been proved to the satisfaction of the Government that the faults revealed by the tests have been corrected.

4.3 Quality conformance inspection.

4.3.1 Sampling.

4.3.1.1 Lot formation. A lot shall consist of all units of one type and part number, from an identifiable production period, from one manufacturer, submitted at one time for acceptance.

4.3.1.2 Sampling for examination. Samples for quality conformance examination shall be selected in accordance with inspection level II of MIL-STD-105.

4.3.1.3 Sampling for testing. Samples for quality conformance testing shall be selected in accordance with inspection level S-4 of MIL-STD-105.

4.3.2 Quality conformance examination.

4.3.2.1 Acceptable quality level. Using MIL-STD-166 as a guide for visual inspection, each sample selected in accordance with 4.3.1.2 shall be examined for conformance to the following acceptable quality levels (AQL), on the basis of percent defective:

Classification	AQL
Major	1.0
Minor	2.5

4.3.2.2 Classification of defects. Examination shall be conducted as specified in table IV. Any hose assembly in the sample containing one or more defects shall be rejected, and if the number of defective hose assemblies in any one sample exceeds the acceptance number for that sample, the lot represented by the sample shall be rejected.

Table IV. Classification of defects.

Categories	Defects
Critical:	None defined.
Major:	
101	Holes in cover exposing braid (see 3.2.1.2).
102	Assembly length incorrect (see contract or order).
103	Reinforcement braids not imbedded in and bonded to the rubber (see 3.2.2).
104	Steel fittings not properly plated (see 3.2.3).
105	Fittings not securely attached to hose (see 3.2.3).
106	Dimensional nonconformance of fittings affecting the interchangeability (see 3.2.3).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

Table IV. Classification of defects (cont'd).

Categories	Defects
Major:	
107.....	Diameter nonconformance (see 3.3).
108.....	Tubing overage (see 3.6).
Minor:	
201.....	Improper marking (see 3.5).
202.....	Illegible marking (see 3.5).

4.3.3 Testing.

4.3.3.1 Quality conformance tests. Samples selected in accordance with 4.3.1.3 shall be subjected to the tests specified in table V, using an AQL of 6.5 percent defective:

Table V. Order of quality conformance tests.

Type	Test sequence
Constriction.....	4.4.3
Burst.....	4.4.5

4.3.4 Inspection of preparation for delivery.

4.3.4.1 Materials and processes. The Government inspector shall, at unscheduled intervals, inspect all materials and processes involved in the preparation for delivery to determine conformance to requirements of section 5 and the specifications referenced therein. Any evidence of deviation from specified requirements shall be cause for refusal to conduct further inspection until objective evidence has been provided by the contractor that corrective action has been taken.

4.4 Test procedures.

4.4.1 Ambient air conditions. Unless otherwise specified (see 6.2), tests shall be conducted at an ambient air temperature of 77° ± 15°F and all samples shall be stabilized at that temperature before testing.

4.4.2 Pressure resistance test. To determine conformance to 3.4.1, hose assemblies shall be tested using air or water as the pressure medium. Test pressure shall be 1500 pounds per square inch (psi) minimum for air, and 3000 psi minimum for liquid. (Special care should be taken when air is used, as under the pressure specified, air is explosive if a failure should occur in the hose or hose assembly.) The pressure shall be applied for not less than 10 nor more than 25 seconds.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

4.4.3 Constriction test. To determine conformance to 3.4.2, hose assemblies shall be tested for constriction of the bore by means of plug gages as shown in figure 1. Hose assembly shall be held in a vertical position and the "A" diameter end of the gage inserted into the end of the fitting. Gage shall be permitted to drop of its own weight into the hose assembly.

4.4.4 Expansion test.

4.4.4.1 Apparatus. Test apparatus (see 6.5) shall include the following: A source for the required fluid pressures, pressure gages, piping, valves, fittings in which the hose assembly can be mounted in a vertical position for application of pressure under controlled conditions, and a graduated burette for measuring the volume of liquid corresponding to the expansion of the hose under the pressure. All piping and connections shall have a bore devoid of roughness and without recesses or offsets, so that all air can be freely removed from the system before running each test. The valves shall be of such design as to open and close with minimum displacement of liquid. The apparatus shall be capable of applying the pressure at a rate of 25,000 ± 10,000 psi per minute.

4.4.4.2 Calibration. The apparatus shall be tested prior to use to determine its calibration correction factor. For this purpose, 1/4-inch diameter steel tubing conforming to type II of MIL-T-3520 shall be used in place of the hose assembly. Calibration correction factors shall be established at pressures of 1,000 and 1,500 psi, and these shall be subtracted from the expansion readings obtained on the test samples. The maximum permissible calibration correction factor shall be 0.08 cubic centimeters at 1,500 psi.

4.4.4.3 Procedure. To determine conformance to 3.4.3, the hose assembly shall be carefully threaded into position on the apparatus in such a way as to provide a leakproof seal, care being taken to avoid twisting, and to maintain the hose in a vertical position without tension while under pressure. Water shall be run through the hose until all air bubbles are removed. The pressure in the hose shall be raised to 1,500 psi for not more than 10 seconds and then released. The water level in the burette shall then be set at zero; and the pressure in the hose shall be raised to 1,000 psi sealed in the hose, and then released by opening the upper valve allowing the water in the expanded hose to rise in the burette. As soon as the liquid level is constant, the upper vlave shall be closed and the reading taken on the burette. This operation shall be repeated so that the final reading taken on the burette will be the total of three expansions. This final reading divided by three, minus the calibration factor, shall be considered as the final expansion of the hose at 1,000 psi. The water level in the burette shall be readjusted to zero as above and the procedure repeated at 1,500 psi to obtain the expansion at that pressure.

4.4.5 Bursting test. To determine conformance to 3.4.4, hose assemblies shall be tested as specified in method 10011 of Fed. Test Method Std. No. 601,

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

except the pressure shall be raised to the hold pressure specified in table II. Pressure shall then be increased until the minimum burst pressure, as specified in table II, has been reached.

4.4.6 Fatigue life (whip) test.

4.4.6.1 Apparatus. Test machine shall include two parallel, horizontal headers, each provided with four standard end connections spaced 3-1/2 inches apart to mount four hose assemblies in parallel. One header shall be ball bearing mounted at the ends on disks, which rotate in the same vertical plane, so that the attached hose assembly ends describe 8-inch diameter circles. The other header shall be horizontally adjustable in the plane of the disk centers to accommodate hose assemblies of different lengths. The end connections to the moving header shall effectively cap the hose assemblies, while those on the stationary header shall be open to a monifold, through which water pressure shall be applied by means of a weight operated plunger in a pressure cylinder. A limit switch operated by the plunger weight shall stop the machine when hose failure causes the water pressure to fall. A revolution counter and time interval recorder shall be provided.

4.4.6.2 Procedure. To determine conformance to 3.4.5, hose assemblies shall be mounted in the test machine so that the horizontal projected length is less than their straight length by the amount indicated as slack in table VI. Hose assemblies shall be installed in the machine in their natural lay; that is, without any twist. When all four hose assemblies are installed, the water pressure shall be applied and all hoses and passages bled to eliminate air pockets and bubbles. During the test a constant pressure between 225 and 250 psi shall be maintained. The disks shall revolve at 800 ± 10 revolutions per minute (rpm). Failure of any hose assembly by water leakage through rupture, and consequent loss of pressure, shall terminate the test.

Table VI. Slack required for fatigue life (whip) test.

Free length between fittings	Slack required		
	1/8 diameter	3/16 diameter	1/4 diameter
Inches	Inches	Inches	Inches
14	1.750 ± 0.015	1.000 ± 0.015	1.000 ± 0.015

4.4.7 Low-temperature flexibility test. To determine conformance to 3.4.6, the hose assemblies shall be conditioned for 72 hours at a temperature of minus 65° ± 2°F. At the end of this period and while still at the specified temperature, the sample shall be bent, within 10 seconds, through 180° from the centerline over a mandrel with a diameter equal to 10 times the nominal outside

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

diameter of the hose. While still at the specified temperature, the sample shall then be bent through 360° in the opposite direction over the same mandrel within the next 10 seconds. After completion of the bending at the specified temperature, the sample shall be subjected to the test specified in 4.4.2.

4.4.8 Tensile strength test. To determine conformance to 3.4.7, hose assembly shall be attached to a testing machine by means of the two hose assembly fittings, and subjected to a straight pull at a speed of 1 inch per minute, until a pull of 325 pounds is attained.

4.4.9 Ozone resistance test.

4.4.9.1 Testing apparatus. Apparatus for performing the test shall include an exposure chamber that will maintain a mixture of air and ozone in the proportion of 50 ± 5 parts of ozone per 100 million parts of air by volume. The chamber shall be capable of maintaining an air temperature of 100° ± 2°F during the test.

4.4.9.2 Procedure. To determine conformance to 3.4.8, the test shall be conducted in an ambient temperature of 100° ± 5°F. The sample shall be bent around a mandrel, the diameter of which shall be 7 times the outside diameter of the hose being tested, and bound with twine or tape at the point where the ends of the hose cross one another. If collapse of the hose occurs, provision shall be made to support the hose internally. The sample shall be conditioned 45 minutes in air at room temperature. The sample, while still on the mandrel, shall be placed into the chamber and exposed to the mixture of ozone and air for a period of 168 hours. At the end of the 168-hour period, the hose cover shall be examined under 9-power magnification, ignoring the areas immediately adjacent to or within the area of the sample where taped or tied.

4.4.10 Fluid resistance test. To determine conformance to 3.4.9, sample of tube shall be tested as specified in method 6211 of Fed. Test Method Std. No. 601, except that the aging shall be for 70 hours at a temperature of 212° ± 5°F, and the immersion fluid shall conform to VV-B-680.

4.4.11 Fungus resistance test. To determine conformance to 3.4.10, hose assemblies shall be tested in accordance with class 3, method A of MIL-F-13927, then tested as specified in 4.4.2.

4.4.12 Corrosion resistance test. To determine conformance to 3.4.11, hose assemblies shall be subjected to a 24 hour salt spray in accordance with method 811.1 of Fed. Test Method Std. No. 151.

5. PREPARATION FOR DELIVERY

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

5.1 Preservation, packaging, packing, and marking. Preservation, packaging, packing, and marking shall be in accordance with the applicable packaging standard or packaging data sheets specified by the procuring activity (see 6.2).

6. NOTES

6.1 Intended use. The hose assemblies furnished under this specification are for use as flexible connections on automotive hydraulic brake components. Type I requirements may be met with either type I or type II assemblies. Type II requirements must be met with type II assemblies (one way interchangeability only).

6.2 Ordering data. Procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) Type hose required (see 1.2).
(c) Applicable drawings (see 3.2), length and inside diameter of hose assemblies (see 3.3).
(d) If ambient air conditions other than specified are required (see 4.4.1).
(e) Selection of applicable packaging standard or packaging data sheet (see 5.1).

6.3 Special provisions for establishing qualification. Hose assemblies, submitted by a manufacturer, should be 1/8-inch. Upon being qualified, the 1/8-inch size hose assembly should then be recognized as establishing qualification of all other hose assembly sizes by that same manufacturer.

6.3.1 New type II hose. Successful completion of testing of type II hose will establish qualification of type I hose. If the situation in the industry develops as expected, it is probable that type I hose will be completely replaced by type II hose at some future date. If this happens, all reference to types may be removed from the specification; in which case any drawing referencing type I or type II will automatically be taken as referring to the hose described in the then current revision of the specification.

6.4 Qualification. With respect to products requiring qualification, award will be made only for products which are at the time set for opening of bids, qualified for inclusion in the applicable Qualified Products List, whether or not such products have actually been so listed by that date. The attention of the suppliers is called to this requirement, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. The activity responsible for the Qualified Products List is the U. S. Army Tank-Automotive Command, Warren, Michigan 48090, and information pertaining to qualification of products may be obtained from that activity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

6.5 Apparatus. The equipment described for the test specified in 4.4.4 is similar to that used in ASTM-D571.

Custodians:
Army - AT
AF - 84


Review activity:
AF - 85

User activities:
Army - ME, SM
Navy - MC

Preparing activity:
Army - AT

Project No. 2530-0119

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

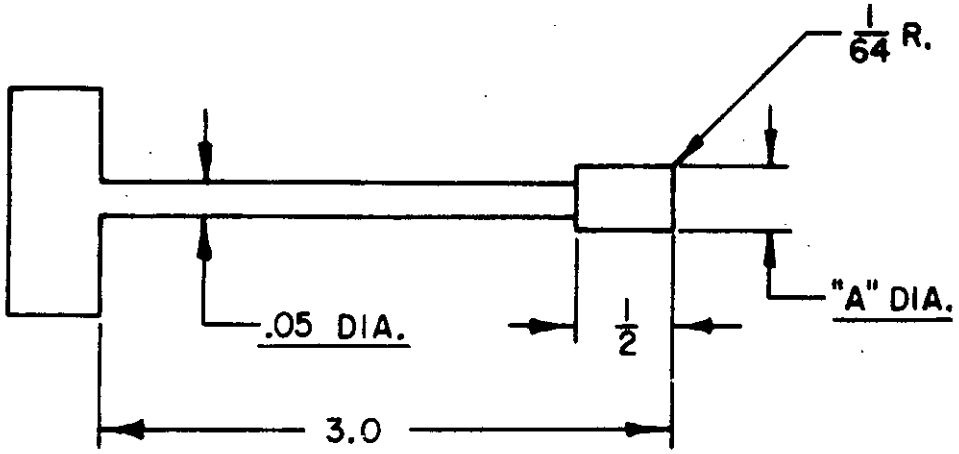

HOSE I.D.	1/8	3/16	1/4
"A" DIAMETER ±.002	.080	.120	.165
GAGE WEIGHT	2 oz. ±.1 oz.		

PLUG GAGE

FIGURE 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Tank-Automotive Command
ATTN: DRSTA-GSS
Warren, MI 48080

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR ☐ USER ☐ MANUFACTURER ☐ OTHER *(Specify)*: _____
b. ADDRESS *(Street, City, State, ZIP Code)*	

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

DD FORM 82 MAR 1426

PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:12Z
Check the source to verify that this is the current version before use.