MILITARY SPECIFICATION

# SHEETING AND TAPE, REFLECTIVE; OPEN TYPE SECURED LENS, ADHESIVE BACKING, PRESSURE SENSITIVE

## 1 SCOPE

1.1 This specification covers the following types and colors of flexible, reflective sheeting and tape, open type secured lens, coated on one side with a pressure sensitive adhesive backing protected by a removable liner:

Type I - Sheeting, reflective (sheets or rolls)

Type II - Tape, reflective (rolls)

Colors - White, yellow, and silver

## 2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on the date of invitation for bids form a part of this specification to the extent specified herein:

SPECIFICATIONS

Federal

| | |
|---|---|
| QQ-A-250/5 | Aluminum Alloy, Alclad 2024, Plate and Sheet |
| TT-T-266 | Thinner, Dope and Lacquer (Cellulose-Nitrate) |

STANDARDS

Federal

| | |
|---|---|
| Fed. Test Method Std. Nr. 141 | Paint, Varnish, Lacquer, and Related Materials; Methods of Inspection, Sampling, and Testing |

FSC 9390

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T09:54Z
Check the source to verify that this is the current version before use.

Military

MIL-STD-105 Sampling Procedures and Tables for Inspection by Attributes

2.2 Other publications. The following documents form a part of this specification to the intent specified herein. Unless otherwise indicated, the issue in effect on the date of invitation for bids or request for proposal shall apply.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM) STANDARDS

D-1004-66 Method of Test for Tear Resistance of Plastic Film and Sheeting

(Application for copies should be addressed to The American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

3. REQUIREMENTS

3.1 Preproduction. This specification makes provisions for preproduction inspection (see 4.3 and 6.3).

3.2 Description. The reflective material shall have a surface which consists of uniform spherical lens elements with a transparent clear finish which secures the reflective elements to the light reflecting binder coat. The reflective material shall have a precoated adhesive backing protected by a removable liner.

3.3 Material. Material shall be as specified herein. Material not specified shall be selected by the supplier and shall be subject to all provisions of this specification.

3.4 Material components.

3.4.1 Exterior finish. The exterior finish shall be a clear, transparent, flexible, moisture-resisting material. The finish may be applied as a sprayed-on coating or by any other method that will produce the specified characteristics.

3.4.2 Spherical elements. A uniform monolayer of spherical glass lens elements shall be imbedded in the binder. The glass spheres shall not become opaque or otherwise be affected by acid (see 4.6.1).

3.4.3 Binder. The binder shall be formulated to provide a base for the light-reflecting material and serve as a permanent bonding agent that secure the glass spheres in place. The binder shall also produce a firm bond between the exterior finish and the glass spheres.



Source: https://assist.dla.mil -- Downloaded: 202610-23T09:54Z
Check the source to verify that this is the current version before use.

3.4.4 Adhesive backing. The adhesive backing of the reflective sheeting and tape shall have an average adhesion over bare metal surfaces of not less than 50 ounces per inch of width at standard conditions (see 4.6.2).

3.4.5 Removable liner. The adhesive backing of the reflective sheeting and tape shall be completely covered by a protective removable liner. The liner shall be removable from the adhesive backing without soaking in water or other solvents. The liner shall evidence no sticking, tearing or increased removability from the adhesive after storage at a temperature of 190°F for a period of 24 hours while being subjected to a static load of 3.3 pounds per square inch (see 4.6.3).

3.5 Physical requirements.

3.5.1 Tensile strength and elongation. The reflective sheeting and tape, with the liner removed, shall have a tensile strength of not less than 1000 psi, and of not more than 1500 psi. The material shall have an elongation of not less than 80% and not more than 150% (see 4.7.1).

3.5.2 Tear strength. The tear strength of the reflective sheeting and tape shall not be less than 175 pounds, nor more than 210 pounds (see 4.7.2).

3.5.3 Flexibility. The reflective material shall be flexible at both low and high temperatures without cracking, crazing, blistering or loss of spherical elements when bent around a ¼ inch mandrel at -20°F and at 160°F (see 4.7.3).

3.5.4 Thickness. The thickness of the reflective material without the protective liner shall not be less than 7 mils thick (see 4.7.4).

3.5.5 Solvent resistance. The reflective material shall show no evidence of dissolving, puckering, or blistering when immersed in kerosene, gasoline, diesel fuel, motor oil (SAE #20), xylene and methyl alcohol (see 4.7.5).

3.5.6 Fungus resistance. After innoculation with the test organism, aspergillus niger, and an incubation period of 14 days, the reflective material shall show no appreciable formation of fungus growth. Any fungus growth shall be noninjurious to the material surface and shall be removable by wiping with a soft wet cloth. After completion of the incubation and after being wiped clean, the reflective material shall retain the full reflective brightness values as specified in Table I (see 4.7.6).

3.6 Surface requirements.

3.6.1 Specular gloss. The reflective material shall have a specular gloss reading of not more than 1.0. The transparent clear finish, used as a surface coating, shall have no mirror type reflection. Mirror type reflection is



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T09:54Z
Check the source to verify that this is the current version before use.

defined as the reflected ray which is projected at an angle approximately equal to the incident ray from a line normal to the reflective material surface (see 4.8.1).

3.6.2 Reflective brightness. The reflective brightness of the material shall not be less than the values specified in Table I for each color as applicable (see 4.8.2).

3.6.3 Accelerated weathering. The reflective material after being subjected to accelerated weathering for 1200 hours, shall show no detectable discoloration to the naked eye when viewed from a distance of 25 feet and compared to an unweathered specimen. The reflective material shall show no evidence of cracking, loss of adhesion, blistering, or more than 1/32 inch shrinkage or expansion and shall retain not less than 90 percent of the reflective brightness values specified in Table I (see 4.8.3).

3.6.4 Rainfall. The reflective brightness of the reflective material, expressed in light-level numbers, shall not be reduced by more than 30% of the dry measured reflective material samples (see 4.8.4).

3.7 Design, dimensions and instructions.

3.7.1 Shape and size. The Type I reflective sheeting shall be furnished either in sheets or rolls. Sheeting shall be any width over six inches. Tolerance for width and length shall be plus or minus 1/8 inch. The Type II reflective tape shall be furnished in rolls only. Tape shall be in widths up to and including six inches. Tolerance for width shall be plus or minus 1/16 inch.

3.7.2 Splicing. The reflective sheeting and tape furnished in rolls shall have no more than three splices per 50 yards of material. Splices shall be butted and shall be suitable for application as supplied. Rolls shall be evenly and tightly wound on commercial type cores and the ends secured to prevent unwinding.

3.7.3 Instructions. Instructions outlining a step-by-step procedure for application of the reflective material shall be included with each package of material. Any restrictions relative to the application procedure, or any precautions to be exercised regarding surface preparation and applicable temperature, shall be specified.

3.7.4 Workmanship. The reflective materials shall be manufactured in accordance with high-grade commercial practice for this type of material. The material shall be free of blisters, cracks, ragged edges, foreign matter or other harmful defects.



Source: https://assist.dla.mil -- Downloaded: 202610-23T09:54Z
Check the source to verify that this is the current version before use.

TABLE I

REFLECTIVE BRIGHTNESS
MINIMUM VALUES

| DIVERGENCE ANGLE DEGREES | INCIDENCE ANGLE DEGREES | COLOR | | |
|---|---|---|---|---|
| | | SILVER | WHITE | YELLOW |
| 0.2 | 0 | 211 | 37 | 40 |
| .2 | 10 | 226 | 37 | 40 |
| .2 | 20 | 226 | 34 | 34 |
| .2 | 30 | 130 | 34 | 32 |
| .2 | 40 | 98 | 28 | 30 |
| .2 | 50 | 65 | 23 | 24 |
| .2 | 60 | 28 | 12 | 18 |
| .2 | 70 | 10 | 5 | 8 |
| 0.5 | 0 | 92 | 14 | 20 |
| .5 | 10 | 106 | 20 | 21 |
| .5 | 20 | 130 | 21 | 21 |
| .5 | 30 | 74 | 20 | 20 |
| .5 | 40 | 65 | 20 | 18 |
| .5 | 50 | 40 | 14 | 16 |
| .5 | 60 | 20 | 10 | 10 |
| .5 | 70 | 10 | 2 | 3 |
| 2.0 | 0 | 18 | 5 | 5 |
| 2.0 | 10 | 18 | 5 | 5 |
| 2.0 | 20 | 20 | 10 | 4 |
| 2.0 | 30 | 20 | 10 | 4 |
| 2.0 | 40 | 16 | 8 | 3 |
| 2.0 | 50 | 13 | 6 | 3 |
| 2.0 | 60 | 10 | 2 | 1 |
| 2.0 | 70 | 3 | 1 | 0.6 |
| 8.0 | 0 | 1.7 | 1.2 | 1.3 |
| 8.0 | 10 | 1.6 | 1.6 | 1.1 |
| 8.0 | 20 | 1.3 | 1.5 | 1.0 |
| 8.0 | 30 | 1.3 | 1.3 | 0.9 |
| 8.0 | 40 | 1.1 | 1.3 | 0.8 |
| 8.0 | 50 | 0.8 | 1.1 | 0.7 |
| 8.0 | 60 | 0.6 | 0.7 | 0.5 |
| 8.0 | 70 | 0.1 | 0.1 | 0.1 |



Source: https://assist.dla.mil -- Downloaded: 202610-23T09:54Z
Check the source to verify that this is the current version before use.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Classification of inspection. Inspection shall be classified as follows:

a. Preproduction inspection (see 4.3).

b. Quality conformance inspection (see 4.4).

4.3 Preproduction inspection. Preproduction inspection shall consist of all tests specified in 4.6, 4.7, and 4.8.

4.3.1 Sampling instructions. The preproduction samples shall consist of a sufficient quantity of the reflective material to complete all the tests. Samples shall be tested in a laboratory designated by the procuring activity, or, when so stated in the contract or order, at the contractor's plant under the inspection of the procuring activity (see 6.3).

4.3.2 Test report. A test report in triplicate, shall be furnished the procuring activity certifying that the ingredient materials and the test results, except the accelerated weathering test, meet the requirements of this specification. Approval of preproduction inspection shall not relieve the contractor of his obligation to meet the quality conformance inspection.

4.3.3 For the accelerated weathering test, certification that the material meets the requirements of this specification shall be submitted at the time of inspection. At the end of the 1200 hours exposure, the reflective material shall be tested and shall pass the preproduction inspection as specified in 4.8.3.

4.4 Quality conformance inspection. Quality conformance inspection shall consist of all the examinations and tests of this specification except accelerated weather resistance. Tests shall be conducted in accordance with Federal Test Method Standard Nr. 141, or as otherwise specified.

4.4.1 Sampling



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T09:54Z
Check the source to verify that this is the current version before use.

4.4.1.1 Lot. For sampling purposes, a lot shall consist of all the reflective material manufactured at one time and forming part of one contract or order for delivery at one time.

4.4.1.2 For visual and dimensional examinations. A random sample of reflective material shall be selected from each inspection lot in accordance with MIL-STD-105, inspection level I and acceptable quality level (AQL) of 2.5 percent defective to verify compliance with this specification regarding packaging, packing, marking, dimensions, and other requirements not involving physical tests.

4.4.1.3 For tests. A sufficient quantity of the reflective material to perform the quality conformance tests shall be selected at random from each lot.

4.4.2 Examination of product. The reflective material shall be examined to determine conformance of this specification with respect to material, workmanship, and preparation for delivery.

4.5 Test conditions.

4.5.1 Standard conditions. Unless otherwise specified herein, all applied and unapplied test samples and specimens shall be conditioned in accordance with Federal Test Method Standard Nr. 141, Section 7, for 24 hours.

4.5.2 Test panels. When tests are to be performed using test panels, the specimens of reflective material shall be applied to aluminum panels, conforming to QQ-A-250/5, temper T3.

4.6 Test method.

4.6.1 Glass sphere acid resistant test. Extract the spherical glass lens elements from the reflective material by cutting test specimens of the material into approximately 1/4-inch segments. Immerse the segments in lacquer thinner, conforming to TT-T-266, after the thinner has been heated to approximately 130°F. Stir the thinner until the film is dissolved and the lens elements have settled. Decant the thinner and repeat the process until the extracted lens elements are clean. Immerse approximately 0.1 cc. of the lens elements in 1.00 cc. of a 5N solution of concentrated sulfuric acid ($H_2SO_4$) and distilled water for 30 minutes, and examine the lens elements microscopically. Examine the extracted lens elements microscopically to determine the presence of any opaque lenses. Nonconformance to 3.4.2 shall constitute failure of this test.



Source: https://assist.dla.mil -- Downloaded: 202610-23T09:54Z
Check the source to verify that this is the current version before use.

4.6.2 Adhesion. Three strips of the reflective material, each 1 by 8 inches, shall be applied separately over 2- by 4-inch bare aluminum panels (with one end of the strip flush to one end of the panel) so that a 1- by 3-inch area of the panel shall be adhered to the material. The free end of the material shall be doubled back at 180 degrees. The bare end of the aluminum panel shall be clamped in the lower jaw of the tensile testing machine and the free end of the marking shall be clamped in the upper jaw. Adhesion shall be determined on a dead-weight pendulum or cross-head type testing machine. The material shall be pulled back from the test panel at a constant rate of head travel of 12 inches per minute. After the first inch is removed, the average tension required to remove the next inch shall be determined. If the material breaks at any point during removal, the test shall be terminated and the material considered satisfactory if the value is above 50 ounces, and unsatisfactory if below 50 ounces (see 3.4.4).

4.6.3 Removable liner. Condition three, 3-inch diameter specimens of the reflective material at a temperature of 190°F for a period of 24 hours while being subjected to a static load of 3.3 psi. Allow the specimens to cool to room temperature and remove the liner. Nonconformance to paragraph 3.4.5 shall constitute failure of this test.

4.7 Physical tests.

4.7.1 Tensile and elongation test. Five strips of the reflective material, each 1 by 6 inches, shall be cut from the sample and conditioned in accordance with 4.5.1. Remove liner and test in accordance with method 6224 of Federal Test Method Standard Nr. 141, except that head travel rate shall be 12 inches per minute. The average strength of the 5 specimens shall conform to 3.5.1. Specimens shall be simultaneously tested for elongation in accordance with method 6225 of Federal Test Method Standard Nr. 141 (see 3.5.1).

4.7.2 Tear strength. The tear strength test shall be performed in accordance with ASTM test method D-1004-66 (see 3.5.2).

4.7.3 Flexibility test. Condition a 1 by 6 inch strip of reflective material and a 1/4-inch steel mandrel for 24 hours at -20°F. While the strip of reflective material and mandrel are at this temperature, test for compliance with paragraph 3.5.3. Repeat the above procedure at 160°F and check for compliance with paragraph 3.5.3.

4.7.4 Film thickness. Strips of the reflective material approximately 1 by 6 inches shall be cut. The protective liner shall be removed and the material applied to strips of aluminum foil approximately 0.001 inch thick and firmly rolled down. The thickness of the aluminum foil shall have been previously measured by micrometer. Four micrometer readings shall be taken at random location on each strip. All the measurements shall fall within the specified value after subtraction of the thickness of the aluminum foil (see 3.5.4).



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T09:54Z
Check the source to verify that this is the current version before use.

4.7.5 Solvent resistance. Determine the resistance of the reflective material to the solvents specified herein by immersing one test specimen in a glass exposure container, for each solvent separately, at room temperature in accordance with Method 6011 of Federal Test Method Standard Nr. 141. Specimens, each 1 by 6 inches, shall be applied to test panels. Solvents and immersion time shall be as follows:

| Solvents | Immersion Time |
|---|---|
| Motor Oil (SAE #20), Gasoline, Kerosene, and Diesel Fuel | 10 minutes |
| Mineral Spirits and Xylene | 1 minute |

At the end of the immersion period, remove the test panels from the exposure containers and allow to dry before examining for evidence of dissolving of the exterior film and adhesive, puckering or blistering. Failure to any solvent shall be cause for rejection of the lot (see 3.5.5).

4.7.6 Fungus resistance. Determine the fungus resistance of the reflective material by the following method.

4.7.6.1 Test organism. The test organism used in this test shall be Aspergillus niger, ATCC No. 6275 (see 6.4). Cultures of this organism shall be carefully maintained on a potato-dextrose agar medium and promptly renewed if there is evidence of contamination. The stock cultures may be kept for not more than four months in a refrigerator at a temperature from 3° to 10°C, (37.4° to 50°F). Subcultures incubated at 28° to 30°C (82.4° to 86°F) for 10 to 14 days shall be used in preparing the inoculum.

4.7.6.2 Culture medium. The culture medium shall have the following composition:

| | |
|---|---|
| $NaNO_3$ | - 3.0 grams |
| $K_2HPO_4$ | - 1.0 gram |
| $MgSO_4.7H_2O$ | - 0.5 gram |
| KCl | - 0.25 gram |
| Agar | - 15.0 grams |

Distilled water to make 1,000 ml.



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T09:54Z
Check the source to verify that this is the current version before use.

The pH shall be 5.5 to 6.5; if otherwise, adjust to that range with HCl or NaOH. After mixing, the ingredients shall be sterilized by autoclaving for 15 minutes at 15 psi (121°C). Under steril conditions, the medium shall be poured into six 150 by 20 mm. petri dishes, about 65 ml. per dish, and allowed to harden.

4.7.6.3 Inoculum. Add about 10 ml. of sterile, distilled water containing about 0.005 percent of a nontoxic wetting agent to a subculture (10 to 14 days old) of the test organism in a ripe, fruiting condition. The spores shall be forced into suspension with a sterile camel's hair brush (or other suitable means) and diluted to 100 ml. with sterile, distilled water.

4.7.6.4 Preparation of specimens. Cut three, 3 by 3-inch specimens from the sample and apply to test panels with the reflective surface up. Completely immerse the test specimens in a leaching tank of continuously flowing water for 24 hours and then remove and dry. The leaching tank shall be large enough to hold an amount of water weighing not less than 50 times the weight of the specimens. The water entering the tank shall not fall directly on the specimens and shall flow at a rate of 5 to 10 liters per hour. The pH of the water shall be in the range of 6.0 to 8.0.

4.7.6.5 Inoculation. Under aseptic conditions, dip each specimen in 70 percent ethanol for a few seconds, rinse in distilled water, and place firmly on the furface of the solidified agar medium contained in the petri dishes. Place specimens with the reflective surface facing up, one specimen to each dish. With a sterile pipette, distribute 1.0 to 1.5 ml. of inoculum over the surface of each specimen and the surrounding medium.

4.7.6.6 Incubation period. The period of incubation shall be 14 days at a temperature of 29° to 32°C (84.2° to 89.6°F) and 85 to 90 percent relative humidity.

4.7.6.7 Control. Test three control specimens of untreated, porous-grade filter paper with the specimens of the reflective material to check the viability of the inoculum. At the end of the incubation period, the controls should be covered with fungus growth.

4.7.6.8 Test results. Upon completion of the incubation period, examine the specimens visually for fungus growth. Wipe the specimens with a soft cloth wet with a 70 percent ethanol solution. Condition the specimens at standard conditions for 48 hours. Test the specimens in accordance with 4.4.7, and when finished, attempt to remove specimen from the test panel.

4.8. Surface characteristics tests.



Source: https://assist.dla.mil -- Downloaded: 202610-23T09:54Z
Check the source to verify that this is the current version before use.

4.8.1 Sepcular gloss. The reflective tape and sheeting shall be tested in accordance with Federal Test Method Standard 141, Method #6103, for compliance with paragraph 3.6.1.

4.8.2 Reflective brightness. The reflective brightness shall be determined by the method specified in paragraph 4.8.2.1.

4.8.2.1 Apparatus. A projector, having a lens diameter of one inch and capable of projecting a uniform beam of light, shall be used to illuminate the test surface. The illumination source shall be a 750 watt tungsten lamp of 2,850°K minimum color temperature, with a minimum of 4 candlepower per square inch falling on the test surface. The light reflected from the test surface shall be measured with a photoelectric receiver single lens reflex optical system type, with a cadmium sulfide sensitive cell, color corrected and with an acceptable angle of 1° and a viewing angle of 21° (see 6.5). The effective area of the test surface shall be 12 inches by 12 inches (one square foot). The distance from the center of the test surface to both the front lens of the projector and the receiver shall be 50 feet ± 2 inches. The arrangement shall be as shown in Figure 1.

4.8.2.1 Test procedure. Measure the distance from the projector to the specimen, and the area of the test surface. Measure the illumination incident on the receiver due to reflection from the test surface at nine angles of incidence for each of four angles of divergence. The angles of the incidence shall be 0°, plus 10°, 20°, 30°, 40°, 50°, 60°, and 70°; the angles of divergence shall be 0.2, 0.5, 2.0, and 8.0 degrees. Three determinations at each angle of incidence and divergence shall be made, and an average of the three reported. The reflective brightness, expressed in light-level numbers, is read directly from the light-level scale located on the viewing screen of the photoelectric receiver. These light-level numbers are converted to reflective brightness by use of the values listed in Table II.

4.8.3 Accelerating weathering. The reflective material shall be tested for compliance with paragraph 3.6.3 after 1200 hours exposure in accordance with Method 6151 of Federal Test Method Standard Nr. 141. The material shall be applied to three 12 by 12 inch test panels and tested as above.

4.8.4 Reflective brightness during rainfall. The reflective brightness during rainfall shall be determined as follows using the water nozzle and test setup shown in figure 2:

Place the specimens in an upright position 6 inches below and 4 inches in front of the nozzle as shown in figure 2.

Apply sufficient water pressure so that the upper surface of the spray envelope strikes the top of the specimen.

With water falling on the specimen, measure the reflective brightness as specified in 4.8.2 except that the measurement shall be made at angles of 0.2° divergence and 0° incidence only. One determination shall be made on each specimen and the reflective brightness during rainfall shall be the average of the five determinations.



Source: https://assist.dla.mil -- Downloaded: 202640-23T09:54Z
Check the source to verify that this is the current version before use.

## 5. PREPARATION FOR DELIVERY

5.1 Preparation for delivery shall be in accordance with the instructions of the procuring activity.

TABLE II

LIGHT LEVEL NUMBER CONVERSION TO REFLECTIVE BRIGHTNESS

X = LIGHT LEVEL NUMBER

| X INTEGER ↓ / X DECIMAL → | 0 | 1 | 2 | 3 | 4 | 5 | 6 | 7 | 8 | 9 |
|---|---|---|---|---|---|---|---|---|---|---|
| 3 | .08 | .08 | .09 | .10 | .10 | .11 | .12 | .12 | .14 | .15 |
| 4 | .16 | .17 | .18 | .20 | .21 | .22 | .24 | .26 | .28 | .30 |
| 5 | .31 | .34 | .36 | .39 | .42 | .45 | .48 | .51 | .55 | .59 |
| 6 | .63 | .68 | .73 | .78 | .83 | .89 | .96 | 1.03 | 1.10 | 1.18 |
| 7 | 1.3 | 1.4 | 1.5 | 1.6 | 1.7 | 1.8 | 1.9 | 2.0 | 2.2 | 2.4 |
| 8 | 2.5 | 2.7 | 2.9 | 3.1 | 3.3 | 3.6 | 3.8 | 4.1 | 4.4 | 4.7 |
| 9 | 5.0 | 5.4 | 5.8 | 6.2 | 6.6 | 7.1 | 7.6 | 8.2 | 8.8 | 9.4 |
| 10 | 10.0 | 10.8 | 11.6 | 12.4 | 13.3 | 14.2 | 15.2 | 16.3 | 17.5 | 18.8 |
| 11 | 20.0 | 21.5 | 23.1 | 24.7 | 26.5 | 28.4 | 30.4 | 32.6 | 34.9 | 37.4 |
| 12 | 40.0 | 43.0 | 46.1 | 49.4 | 52.9 | 56.7 | 60.8 | 65.1 | 69.8 | 74.8 |
| 13 | 80.0 | 85.9 | 92.1 | 98.6 | 106 | 113 | 121 | 130 | 139 | 149 |
| 14 | 160 | 172 | 184 | 197 | 211 | 226 | 242 | 260 | 278 | 298 |
| 15 | 320 | 343 | 367 | 394 | 422 | 452 | 484 | 519 | 556 | 596 |
| 16 | 640 | 684 | 733 | 786 | 842 | 902 | 967 | 1036 | 1111 | 1190 |
| 17 | 1280 | 1367 | 1464 | 1570 | 1682 | 1802 | 1932 | 2070 | 2218 | 2378 |
| 18 | 2560 | - | - | - | - | - | - | - | - | - |

## 6. NOTES

6.1 Intended use. The reflective sheeting and tape are intended for use in reflectorizing surfaces such as aerospace ground equipment, automotive equipment, and markers to assure their visibility at night under normal and blackout conditions, dry or wet, when exposed to a light source.

6.2 Ordering data. Procurement documents should specify the following:

a. Title, number, and date of this specification.
b. Type required.
c. Color required.
d. Preparation for delivery required.



Source: https://assist.dla.mil -- Downloaded: 202610-23T09:54Z
Check the source to verify that this is the current version before use.

6.3 Preproduction testing. The activity responsible for preproduction testing is the Warner Robins Air Materiel Area (WRNETM), Robins AFB, Georgia 31093. Contracting Officers are hereby advised that they shall contact this office on matters of testing, test reports and acceptable private laboratories.

6.4 Fungus test organism. The organism used in the fungus resistance test (see 4.7.6.1) may be obtained upon request from the American Type Culture Collection (ATCC), 12301 Parklawn Drive, Rockville, Maryland 20852; or Mycology Laboratory, PRL, U.S. Army Natick Laboratories, Natick, Massachusetts 01760.

6.5 The photoelectric receiver described in paragraph 4.8.2.1 is the Honeywell Pentax 10/21° Meter, manufactured by Honeywell Corporation, 5200 East Evans, Denver, Colorado 80222.

Custodian:
Air Force - 84

Preparing Activity:
Air Force - 84
Project Nr. 9390-F031



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T09:54Z
Check the source to verify that this is the current version before use.

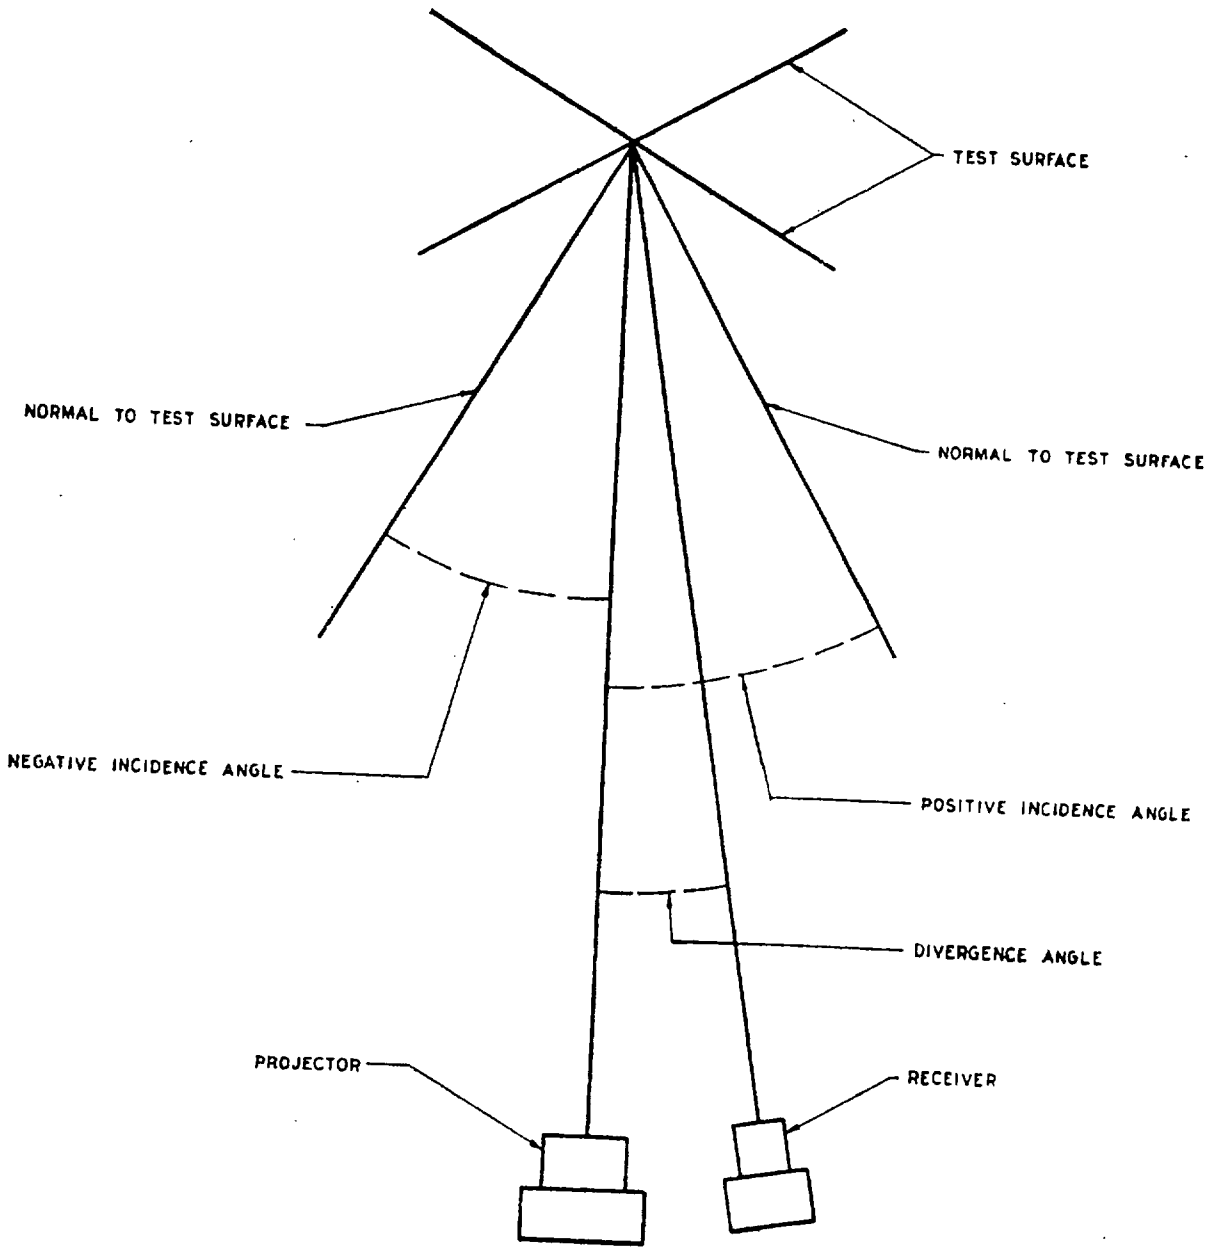



FIGURE 1. INCIDENCE AND DIVERGENCE ANGLES

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T09:54Z
Check the source to verify that this is the current version before use.

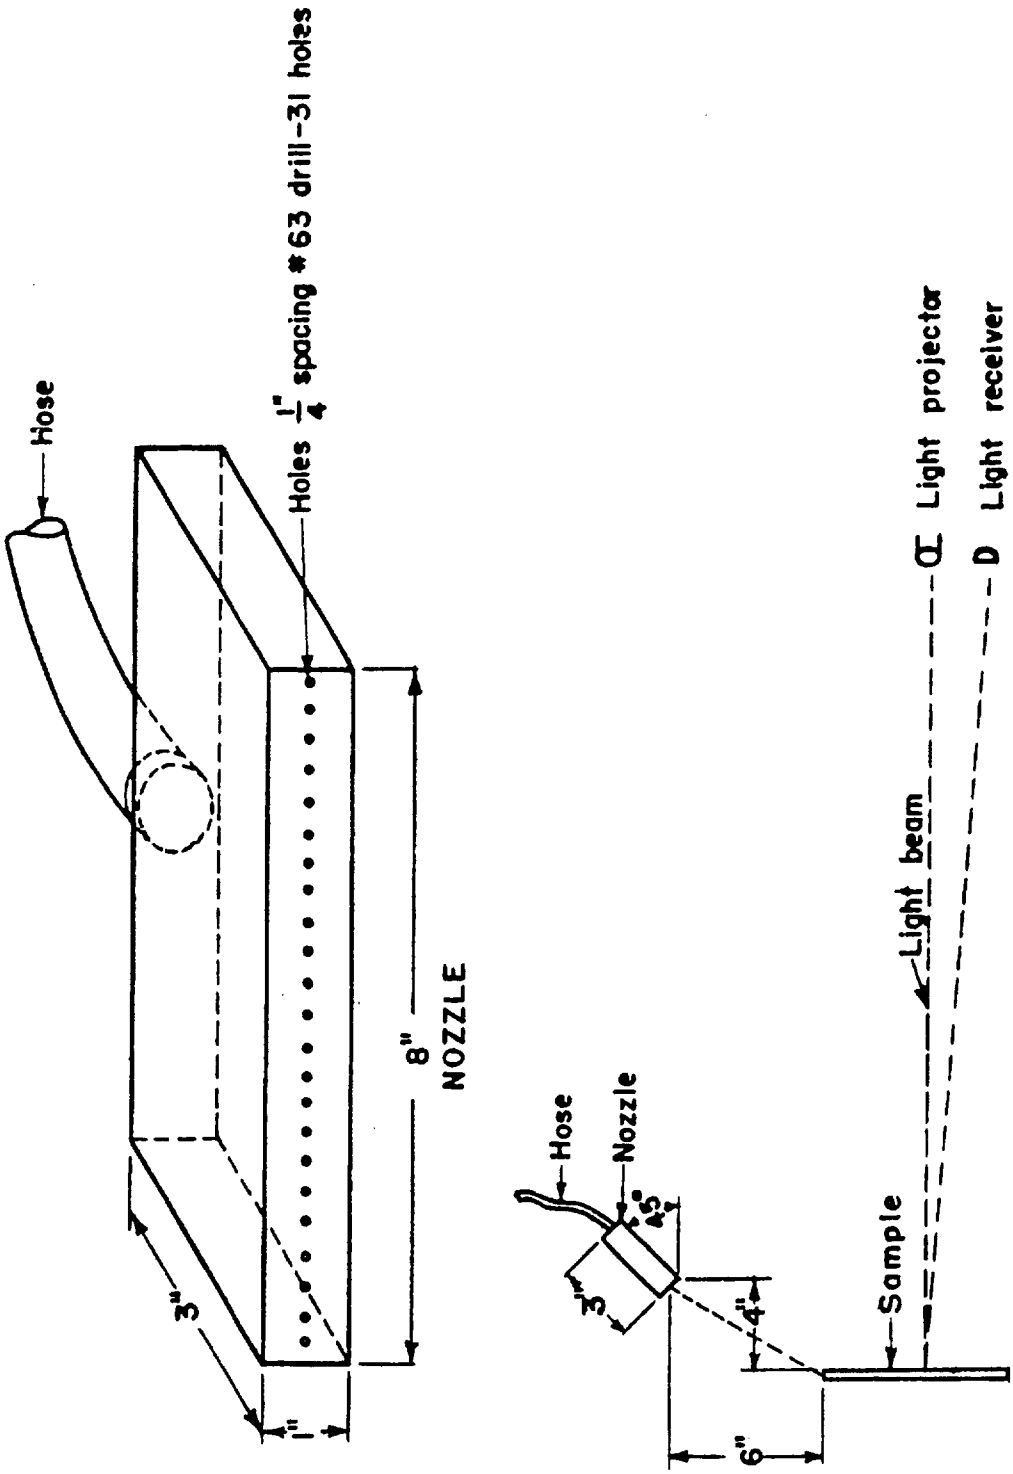



Figure 2. Test set up for rainfall test.

Source: https://assist.dla.mil -- Downloaded: 202610-23T09:54Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T09:54Z
Check the source to verify that this is the current version before use.