METRIC
MIL-PRF-15719B
20 April 2021
SUPERSEDING
MIL-L-15719A
06 May 1952

PERFORMANCE SPECIFICATION

LUBRICATING GREASE (HIGH-TEMPERATURE, ELECTRIC MOTOR, BALL AND ROLLER BEARINGS)

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers high-temperature grease (type HTG) for the lubrication of ball and roller bearings, primarily for lubricating class H-insulated (silicone) electric motors with heat-stabilized ball bearings. It is also used for boiler sliding feet grease lubrication. The normal temperature range of the grease is -18 to 149 °C (0 to 300 °F).

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

FEDERAL STANDARDS

FED-STD-791 - Testing Method of Lubricants, Liquid Fuels, and Related Products

(Copies of this document are available online at https://quicksearch.dla.mil.)

2.2.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of this document are those cited in the solicitation or contract.

Comments, suggestions, or questions on this document should be addressed to Commander, Naval Sea Systems Command, ATTN: SEA 05S, 1333 Isaac Hull Avenue, SE, Stop 5160, Washington Navy Yard DC 20376-5160 or emailed to CommandStandards@navy.mil, with the subject line "Document Comment". Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A FSC 9150

DISTRIBUTION STATEMENT A. Approved for public release. Distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

NAVAL SEA SYSTEMS COMMAND (NAVSEA) PUBLICATIONS

T9070-AL-DPC-020/077-2 - NAVSEA Hazardous Material Avoidance Process

(Copies of this document are available online via Technical Data Management Information System (TDMIS) at https://mercury.tdmis.navy.mil/ by searching for the document number without the suffix. Refer questions, inquiries, or problems to: DSN 296-0669, Commercial (805) 228-0669. This document is available for ordering (hard copy) via the Naval Logistics Library at https://nll.navsup.navy.mil. For questions regarding the NLL, contact the NLL Customer Service at nllhelpdesk@navy.mil, (866) 817-3130, or (215) 697-2626/DSN 442-2626.)

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

ASTM INTERNATIONAL

ASTM D217 - Standard Test Methods for Cone Penetration of Lubricating Grease

ASTM D445 - Standard Test Method for Kinematic Viscosity of Transparent and Opaque Liquids (and Calculation of Dynamic Viscosity)

ASTM D942 - Standard Test Method for Oxidation Stability of Lubricating Grease by the Oxygen Pressure Vessel Method

ASTM D972 - Standard Test Method for Evaporation Loss of Lubricating Greases and Oils

ASTM D1092 - Standard Test Method for Measuring Apparent Viscosity of Lubricating Greases

ASTM D1264 - Standard Test Method for Determining the Water Washout Characteristics of Lubricating Greases

ASTM D2265 - Standard Test Method for Dropping Point of Lubricating Grease Over Wide Temperature Range

ASTM D4048 - Standard Test Method for Detection of Copper Corrosion from Lubricating Grease

ASTM D4057 - Standard Practice for Manual Sampling of Petroleum and Petroleum Products

ASTM D6184 - Standard Test Method for Oil Separation from Lubricating Grease (Conical Sieve Method)

(Copies of these documents are available online at www.astm.org.)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Qualification. The electric motor ball and roller bearing high-temperature lubricating grease (type HTG) furnished under this specification shall be a product that is authorized by the qualifying activity for listing on the applicable qualified products list before contract award (see 4.2 and 6.4).

3.2 Composition. The grease shall be a smooth, homogeneous mixture of a polymethylphenyl silicone or dimethyl-diphenyl polysiloxane fluid and a lithium soap that is free from any abrasive or other undesirable fillers as impurities. Minor proportions of additives to improve oxidation stability, rust inhibition, mechanical stability, texture, and wear resistance may be included.

3.3 Appearance. The lubricant shall be completely homogeneous and shall be of a smooth consistency that is free from lumps or granulation.

3.4 Odor. Any odor of rancidity or perfume shall be sufficient cause for rejection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

3.5 Corrosiveness (copper strip). When tested in accordance with 4.4.3, the grease shall have a copper strip corrosion test maximum rating of 1b in accordance with ASTM D4048.

3.6 Penetration, worked (60 double strokes). When tested in accordance with 4.4.4, the worked penetration of the grease sample shall be not more than 330 nor less than 260 tenths of a millimeter.

3.7 Dropping point. When tested in accordance with 4.4.5, the dropping point shall be not less than 191 °C (375 °F).

3.8 Dirt. When tested in accordance with 4.4.6, the grease shall not contain dirt or other foreign particles exceeding the following limits:

a. 7,500 per cubic centimeter of grease at 25 microns diameter or above.

b. 1,600 per cubic centimeter of grease at 75 microns diameter or above.

c. None at 125 microns diameter or above.

3.9 Water washout. When tested in accordance with 4.4.7, not more than 15 percent by weight of the grease shall be washed from the bearing.

3.10 Oil separation. When tested in accordance with 4.4.8, not more than 12 percent by mass of separated oil shall occur during 100 hours at 149 °C (300 °F).

3.11 Evaporation loss. When tested in accordance with 4.4.9, the grease shall not lose more than 2.0 percent of its mass after 50 hours at 149 °C (300 °F).

3.12 Oxidation stability. When tested in accordance with 4.4.10, the grease shall not cause a pressure drop of more than 34.5 kilopascals (5 pounds per square inch) oxygen pressure after a 50-hour period at 149 °C (300 °F).

3.13 Penetration of lubricating greases after prolonged working (after 100,000 double strokes). When tested in accordance with 4.4.11, the penetration of the grease immediately after the mechanical working shall not be increased to more than 375 tenths of a millimeter.

3.14 Apparent viscosity. When tested in accordance with 4.4.12, the apparent viscosity of the grease shall not exceed 10,000 poises at a shear rate of 20 reciprocal seconds.

3.15 Low temperature torque. When tested in accordance with 4.4.13, the test bearing, filled with the grease, shall turn its first complete revolution in each direction in not more than 15 seconds.

3.16 Performance. When tested in accordance with 4.4.14, the grease shall show an average useful life of 2,500 hours or more.

3.17 Base fluid.

3.17.1 Viscosity of base fluid. When tested in accordance with 4.4.15, the viscosity at 40 °C (104 °F) and 100 °C (210 °F) of the base fluid of the grease shall be reported in square millimeters per second (mm^2/s).

3.17.2. Viscosity temperature coefficient. The calculation of viscosity temperature coefficient shall be performed in accordance with 4.4.16.

3.18 Toxicity. When evaluated in accordance with 4.4.17, the grease shall pose no serious or high risk to the health of personnel or the environment when used for its intended purpose (see 4.4.17 and 6.5).

3.19 Prohibited materials. The fluid shall not contain any chemicals categorized as “prohibited” in accordance with T9070-AL-DPC-020/077-2.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Conformance inspection (see 4.3).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

4.2 Qualification inspection. Qualification inspection shall be conducted at a laboratory acceptable to the Naval Sea Systems Command (NAVSEA). Qualification inspection shall consist of the tests specified in table I.

4.2.1 Samples. For qualification inspection, a 4.5-kilogram (10-pound) sample of grease and a 0.5-liter (1-pint) container of base fluid without additives shall be required.

4.3 Conformance inspection.

4.3.1 Tests. Conformance inspection shall be conducted at a laboratory acceptable to the bureau or agency concerned. Conformance inspection shall consist of the tests specified in table I.

4.3.2 Sampling. For conformance inspection, a 1.4-kilogram (3-pound) sample of grease and a 0.5-liter (1-pint) sample of the base fluid without additives shall be required from each lot (see 6.6.1). The sample of grease shall be selected in accordance with ASTM D4057.

4.3.3 Acceptance or rejection of lots. If the grease or base fluid tested fails any of the conformance or qualification inspections specified in table I, the entire lot shall be rejected.

TABLE I. Chemical and physical requirements and test methods for qualification and conformance inspection.

Test Requirement	Requirement Paragraph	Verification Paragraph	Applicable FED-STD-791 Test Method	Non-Government Test Method	Qualification	Conformance
Appearance	3.3	4.4.1	----	----	X	X
Odor	3.4	4.4.2	----	----	X	X
Corrosiveness (copper strip)	3.5	4.4.3	----	ASTM D4048	X	X
Penetration, worked (60 double strokes), tenths of a millimeter, maximum	3.6	4.4.4	----	ASTM D217	X	X
Dropping point, °C, minimum	3.7	4.4.5		ASTM D2265	X	X
Dirt count, count/cc., maximum	3.8	4.4.6	3005	----	X	X
Water washout at 38 °C (100 °F), percent by weight, maximum	3.9	4.4.7	----	ASTM D1264	X	----
Oil separation, mass percent, maximum	3.10	4.4.8	----	ASTM D6184	X	X

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

TABLE I. Chemical and physical requirements and test methods for qualification and conformance inspection - Continued.

Test Requirement	Requirement Paragraph	Verification Paragraph	Applicable FED-STD-791 Test Method	Non-Government Test Method	Qualification	Conformance
Evaporation loss, mass percent, maximum	3.11	4.4.9	----	ASTM D972	X	X
Oxidation stability, kilopascals, maximum	3.12	4.4.10	----	ASTM D942	X	----
Penetration of lubricating greases after prolonged working (after 100,000 double strokes), tenths of a millimeter, maximum[1/]	3.13	4.4.11	----	ASTM D217	X	----
Apparent viscosity, poises, maximum	3.14	4.4.12	----	ASTM D1092	X	X
Low temperature torque average, seconds	3.15	4.4.13	----	----	X	X
Performance, hours, minimum	3.16	4.4.14	----	----	X	----
Viscosity of base fluid, at 40 °C (104 °F) and 100 °C (210 °F), mm^2/s	3.17.1	4.4.15	----	ASTM D445	X	----
Viscosity temperature coefficient of base fluid	3.17.2	4.4.16	----	----	X	----
Toxicity	3.18	4.4.17	----	----	X	----
Prohibited materials	3.19	4.4.18	----	----	X	----

NOTE:

[1/] This test may be referred to as “worked stability” in some publications.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

4.4 Test procedures. Unless otherwise specified (see 6.2), all tests shall be performed in accordance with the requirements specified in table I on unworked grease.

4.4.1 Appearance. A 115-gram (4-ounce) portion of the grease shall be worked with a spatula on a clean glass. During working, the grease shall show no non-uniformity and shall spread with a straight edge to a smooth, glossy, level surface (see 3.3).

4.4.2 Odor. The odor of the grease shall be observed immediately upon opening the test container (see 3.4).

4.4.3 Corrosiveness (copper strip). The corrosiveness of the lubricating grease to the copper strip shall be tested in accordance with ASTM D4048. Test results shall be in accordance with 3.5.

4.4.4 Penetration, worked (60 double strokes). The worked penetration of the grease shall be determined in accordance with ASTM D217. The penetration of succeeding lots shall not differ from the penetration value established on qualification by more than ±15 tenths of a millimeter, but in no case shall it be more than 330 nor less than 260 tenths of a millimeter (see 3.6).

4.4.5 Dropping point. The dropping point of the grease shall be determined in accordance with ASTM D2265. Furthermore, the dropping point of any succeeding lot shall not differ from the dropping point established on qualification by more than 8 °C (15 °F), but in no case shall it be less than 191 °C (375 °F) (see 3.7).

4.4.6 Dirt count. Dirt in the grease shall be determined in accordance with method 3005 of FED-STD-791 (see 3.8).

4.4.7 Water washout. The water washout characteristics of the grease at 38 °C (100 °F) shall be determined in accordance with ASTM D1264 (see 3.9).

4.4.8 Oil separation. The oil separation of the grease shall be determined in accordance with ASTM D6184 (see 3.10).

4.4.9 Evaporation loss. Evaporation loss of the grease shall be determined in accordance with ASTM D972 (see 3.11), with the following exceptions:

a. The test shall be conducted at 149±0.6 °C (300±1 °F).

b. The duration of the test shall be 50 hours.

4.4.10 Oxidation stability. The oxidation stability of the grease shall be determined in accordance with ASTM D942 (see 3.12), with the following exceptions:

a. The test shall be conducted at 149 ±0.6 °C (300±1 °F). If desired, a properly designed air bath may be substituted for the oil bath.

b. The duration of the test shall be 50 hours.

4.4.11 Penetration of lubricating greases after prolonged working (after 100,000 double strokes). The penetration of the grease shall be determined in accordance with ASTM D217 (see 3.13).

4.4.12 Apparent viscosity. The apparent viscosity of the grease shall be determined in accordance with ASTM D1092 (see 3.14), except that the test shall be performed at -18 °C (0 °F) by placing the apparatus in a properly designed low-temperature box or cold bath. The grease shall be cooled to the test temperature in approximately 2 hours and maintained at this temperature for a period of 2 hours prior to making the viscosity determinations.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

4.4.13 Low temperature torque. These tests shall be carried out with a 204K Conrad-type, eight-ball bearing in a cold box capable of holding the temperature variation of the bearing during the test to not more than ±1 °C (±2 °F). A suitable design of the cold box is shown on figure 1. The test bearing shall be packed with 3.0±0.1 grams of grease, distributed on both sides of the bearing, and worked in so that no grease extends beyond the faces of the races. The bearings shall then be placed in a close-fitting housing similar to that shown on figure 2 so that the radial clearances between the inner race and the edge of the housing shall be 0.2032±0.0508 millimeter (0.008±0.002 inch). The bearing shall be rotated for approximately 100 revolutions in each direction at a speed not exceeding 200 revolutions per minute. The bearings shall be mounted on a spindle such as that shown on figure 2 and cooled to -18 °C (0 °F) in not more than 1½ hours and held at this temperature for a period of 2 hours. During the cooling period, the test spindle shall be rotated two complete revolutions in each direction at intervals of 15 minutes. A torque of 2,000 gram-centimeters shall be applied, and the time for a complete revolution of the spindle shall be recorded. After 15 minutes, the same torque shall be applied in the opposite direction, and the time for the first complete revolution shall be redetermined (see 3.15).

4.4.14 Performance.

4.4.14.1 Apparatus. The apparatus shall be as shown on figure 3 and shall consist of the following:

a. A test spindle that is supported in a cast-iron housing by two auxiliary bearings.

b. A driving motor belted to the test spindle that is capable of rotating the spindle at a speed of 1,700±75 revolutions per minute.

c. An electrically-heated oven that is thermostatically controlled to maintain the temperature of the test bearing within ±2 °C (±3 °F) of the chosen temperature.

d. A test bearing that is single-row, radial, deep-groove, unshielded with a pressed steel retainer, size 310, grade ABEC-1 with normal internal fit-up, made of SAE 52100 steel, enclosed in a housing, and maintained in a position on the test spindle by a light-press fit. Details of the bearing housing shall be as shown on figure 4 and figure 5.

4.4.14.2 Test procedure. The test bearing shall be packed with 20±0.2 grams of the grease that is evenly distributed throughout the bearing. The bearing shall be installed in the bearing housing. The bearing and housing assembly shall be installed onto the test spindle with a light-press fit and clamped in place by the end cap and screw. A 34-kilogram (75-pound) radial load shall be mounted outside the oven and shall be applied by means of a spring connected to the bearing housing. The bearing and grease shall be run-in by slowly increasing the drive motor speed up to 1,700 revolutions per minute over a 2- to 4-hour period. This run-in shall continue for one 24-hour period with the oven door open and no heat applied. At the end of the run-in period, with the oven door closed, the test time shall begin as soon as the drive motor and heater are started. The test oven temperature shall be stabilized over a 2- to 4-hour period and adjusted so that the outer race of the test bearing shall run at a temperature of 149±5 °C (300±9 °F). This oven temperature setting shall remain unchanged throughout the entire test run. Both the oven temperature and bearing temperature shall be monitored throughout the test run. The test shall run continuously for 150 hours followed by an 18-hour shutdown each week (this shall constitute one test cycle). A total of 2,500 running test hours (16 weeks and 5 days) shall constitute one complete test (see 3.16).

4.4.14.3 Failure. Failure of the grease will be indicated by a sudden increase in power consumption (tripping of the motor controller overload relay), excessive vibration, squealing, a broken bearing, or stalling of the motor upon starting. The grease shall be reported as failing if the temperature rise of the test bearing is observed to be 50 °C (90 °F) or greater. The grease shall be reported as failing if the total operating time at 149 °C (300 °F) is less than 2,500 hours (see 3.16). Duplicate runs shall be made. If the total operating time during one of the two duplicate runs is less than 2,500 hours, a third run shall be made. If two of the three runs successfully complete 2,500 hours, the grease shall be reported as passing. If two of the three runs fail to complete 2,500 hours, the grease shall be reported as failing.

4.4.15 Viscosity of base fluid. The viscosity of the base fluid of the grease at 40 °C (104 °F) and 100 °C (210 °F) shall be determined in accordance with ASTM D445 (see 3.17.1).

4.4.16 Viscosity temperature coefficient. The viscosity temperature coefficient (see 3.17.2) shall be calculated from the following formula:

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

Viscosity temperature coefficient = $1 - (\frac{n100\,^{\circ}C}{n40\,^{\circ}C})$

Where n40 °C and n100 °C are kinematic viscosities at 40 °C and 100 °C, respectively

4.4.17 Toxicity. A Health Hazard Assessment (HHA) will be conducted to ensure conformance to 3.18 as required by the qualifying activity. The Navy and Marine Corps Public Health Center (NMCPHC) will evaluate the grease using data provided by the manufacturer/distributor to the NMCPHC (see 3.18 and 6.5).

4.4.18 Prohibited materials. Prohibited materials shall be verified for conformance to 3.19 as required by the qualifying activity.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The grease covered under specification is high-temperature grease (type HTG) intended for use in the lubrication of ball and roller bearings, primarily for lubricating class H-insulated (silicone) electric motors with heat-stabilized ball bearings. It is also used for boiler sliding feet grease lubrication. Restrictions on composition, toxicity, and hazardous materials covered by this specification cause the grease to be military unique. Current stock of lubricating grease may be used until depleted. Future requisitions for lubricating grease should refer to the current version of this specification. Under no circumstances should this specification be applied to bearings in which the main action involves the sliding of metal on metal, as in journal bearings, spiral gears, gear trains, and similar applications.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. When tests should not be performed on unworked grease in accordance with the conditions specified in table I (see 4.4).

c. Packaging requirements(see 5.1).

d. Safety Data Sheet (SDS), when required (see 6.3).

6.3 Safety Data Sheet. When required (see 6.2), contracting officers will identify those activities requiring copies of completed SDSs prepared in accordance with FED-STD-313. In order to obtain the SDS, FAR clause 52.223-3 must be in the contract. The SDS should be included with each shipment of the material covered by this specification.

6.4 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Products List QPL No. 15719 whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Commander, Naval Sea Systems Command, ATTN: SEA 05S, 1333 Isaac Hull Avenue, SE, Stop 5160, Washington Navy Yard DC 20376-5160 or emailed to CommandStandards@navy.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

6.5 Toxicity evaluation. The NMCPHC requires sufficient information to permit an HHA of the product. Upon completion of the HHA, a copy will be provided by the NMCPHC to the Government for evaluation. The HHA process is described on the NMCPHC's website, https://www.med.navy.mil/sites/nmcphc/industrial-hygiene/Pages/health-hazard-assessment.aspx.

6.6 Definitions.

6.6.1 Lot. A lot consists of the grease produced by one manufacturer at one plant, from the same materials and under essentially the same conditions, provided the operation is continuous and does not exceed a 24-hour period.

6.7. Shelf-life. This specification covers items where the assignment of a Federal shelf-life code is a consideration. Specific shelf-life requirements should be specified in the contract or purchase order, and should include, as a minimum, shelf-life code, shelf-life package markings in accordance with MIL-STD-129 or FED-STD-123, preparation of a materiel quality storage standard for type II (extendible) shelf-life items, and a minimum of 85 percent shelf-life remaining at time of receipt by the Government. These and other requirements, if necessary, are in DoDM 4140.27, DoD Shelf-Life Management Program. The shelf-life codes are in the Federal Logistics Information System Total Item Record. Additive information for shelf-life management may be obtained from DoDM 4140.27, or the designated shelf-life Points of Contact (POC). The POC should be contacted in the following order: (1) the Inventory Control Points that manage the item and (2) the DoD Service and Agency administrators for the DoD Shelf-Life Program. Appropriate POCs for the DoD Shelf-Life Program can be contacted through the DoD Shelf-Life Management website: https://www.shelflife.dla.mil.

6.8. Subject term (key word) listing.

Dimethyl-diphenyl polysiloxane

Polymethylphenyl silicone

6.9 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

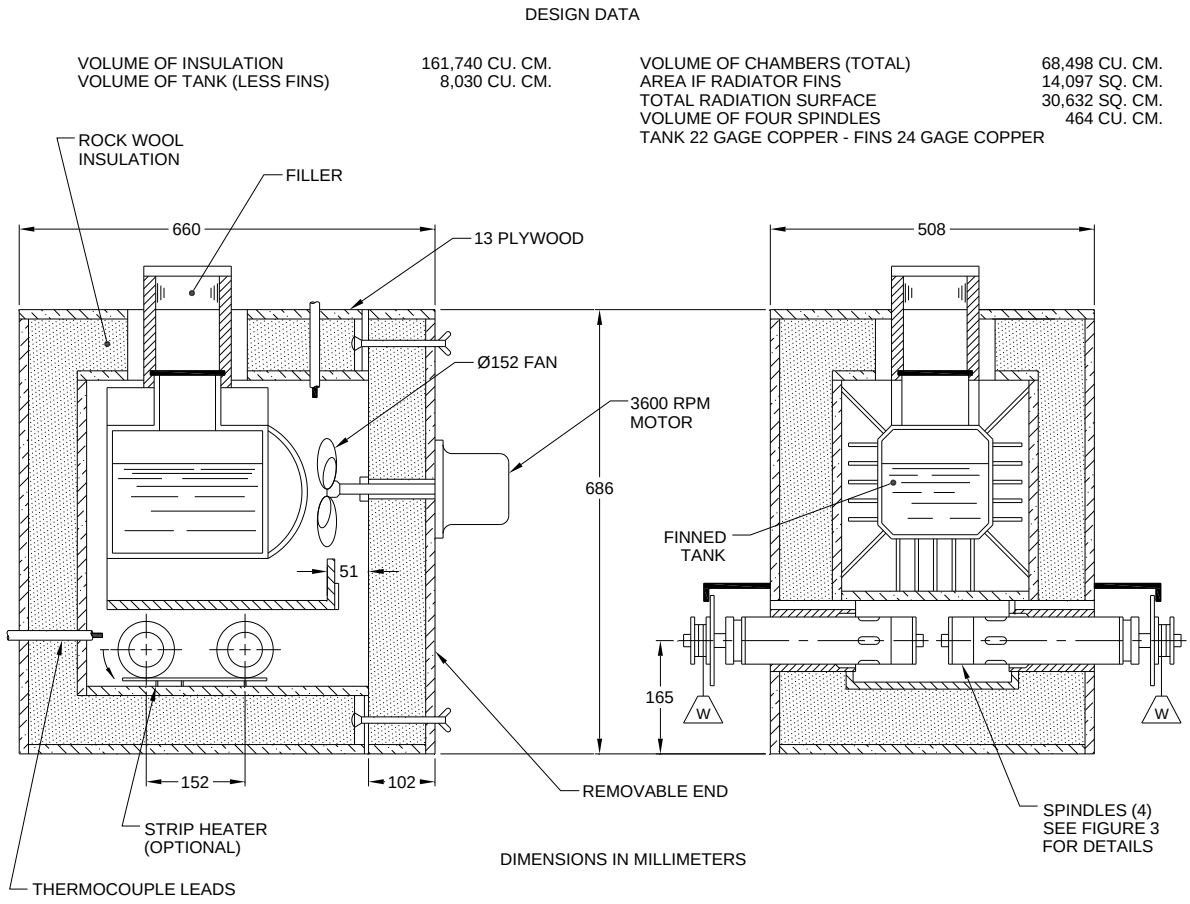


FIGURE 1. Cold test chamber.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

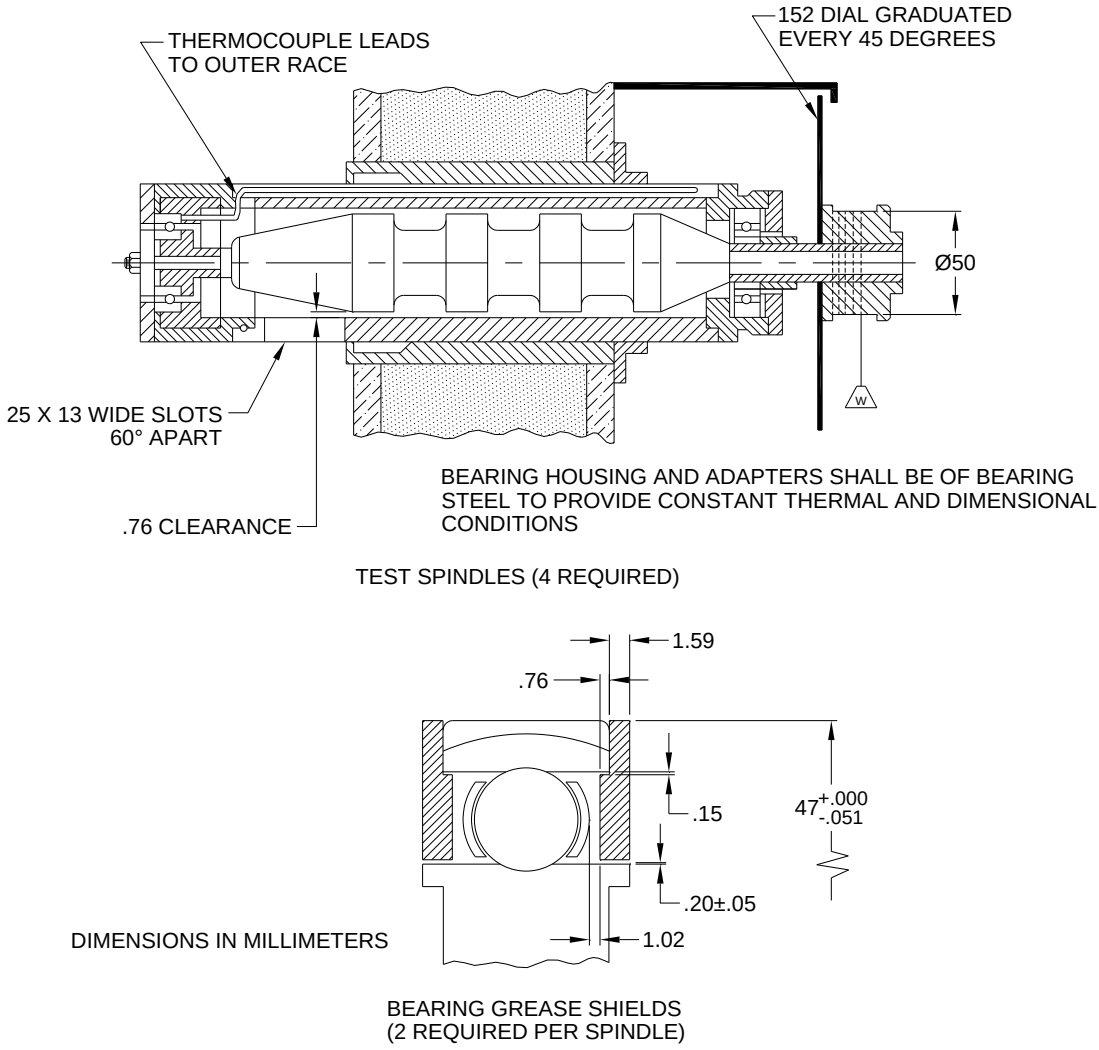


FIGURE 2. Details of spindles and bearing shields.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

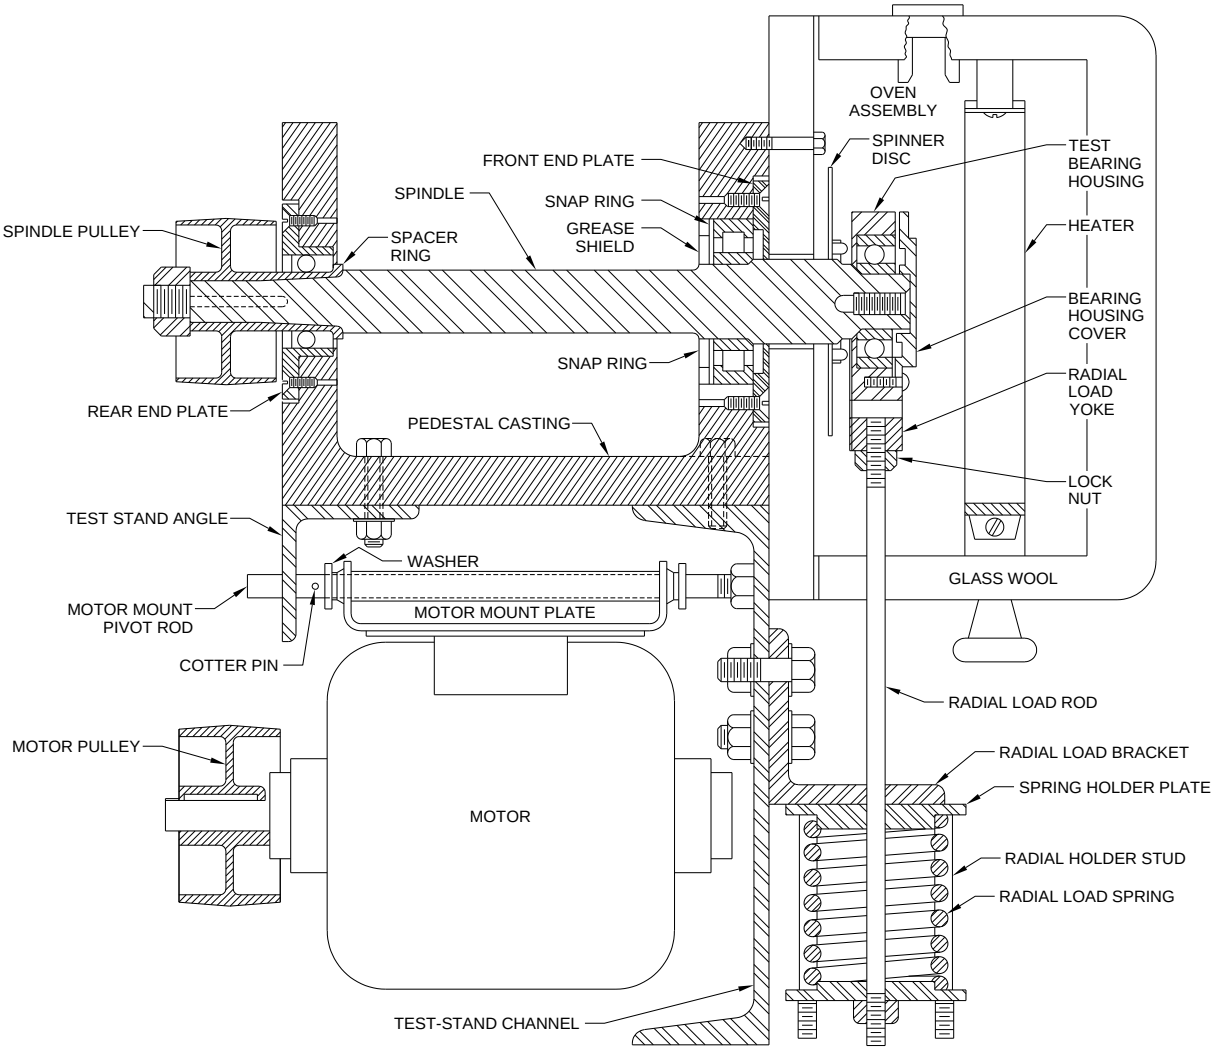


FIGURE 3. Performance tester for electric motor greases.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

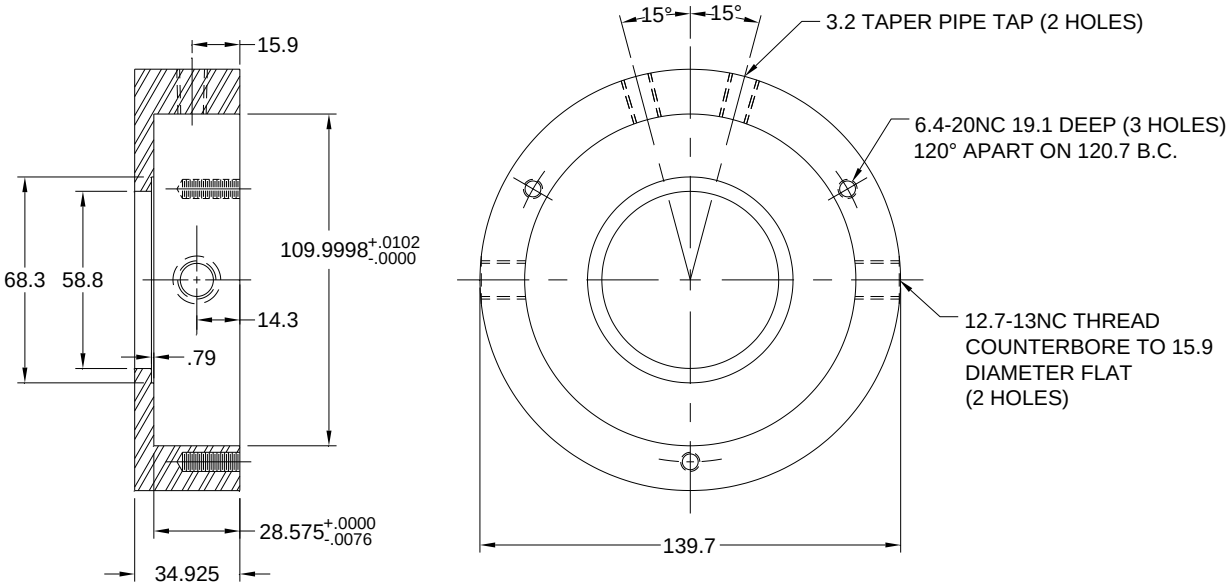


FIGURE 4. Test bearing housing.

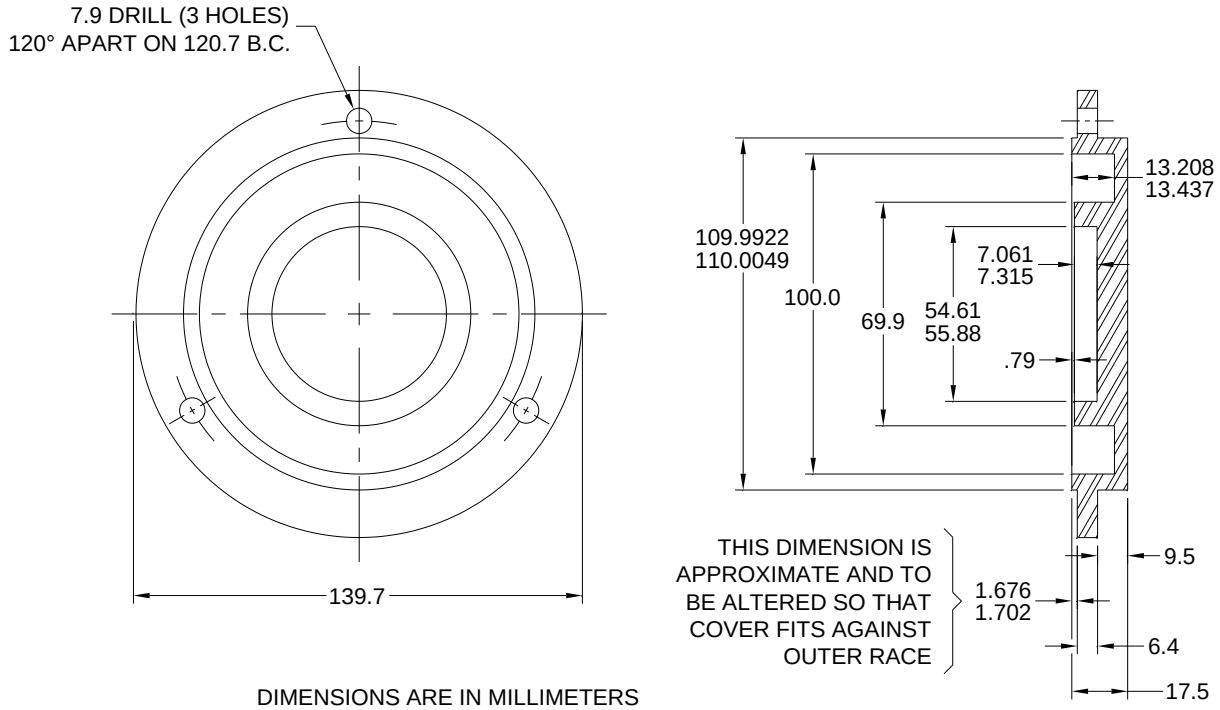


FIGURE 5. 310 bearing house cover.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.

CONCLUDING MATERIAL

Custodians:
Army – CR4
Navy – SH
Air Force – 20

Review activities:
Army – AT, EA, MI
Navy – AS, MC, SA
Air Force – 68
DLA – GS, PS

Preparing activity:
Navy – SH
(Project 9150-2021-001)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T07:11Z
Check the source to verify that this is the current version before use.