[INCH-POUND]
A-A-3104
June 27, 1997
SUPERSEDES
ZZ-A-605
December 19, 1966

COMMERCIAL ITEM DESCRIPTION

APRON, LABORATORY

The General Services Administration has authorized the use of this commercial item description by all Federal agencies.

1. SCOPE. This commercial item description (CID) covers a rubber coated laboratory apron for use in laboratories to protect the clothing of workers from chemical splashes.

2. SALIENT CHARACTERISTICS

2.1 Base cloth. The base cloth shall be 100% cotton cloth, plain weave, 3.0 ounces per square yard (111 g/m^2) minimum weight with a minimum breaking strength of 48 pounds (213 N) in the warp direction and 30 pounds (133 N) in the filling direction. The cloth weight shall be determined by ASTM D 3776. The breaking strength shall be determined by ASTM D 5034.

2.1.1 Coating compound. The coating compound shall be butadiene-acrylonitrile copolymers or chloroprene rubber suitably compounded, plasticized with phthalate or phosphate ester plasticizers and pigmented black.

2.1.2 Coated cloth. The coating compound shall be applied to both sides of the cloth. The coating weight shall be not less than 6.0 ounces per square yard (222 g/m^2) on the outside and not less than 1.0 ounce per square yard (37 g/m^2) on the inside. The overall weight of the coated cloth shall be as specified in Table I and shall be determined by ASTM D 3776. The coated cloth shall be fully vulcanized and shall conform to the physical requirements specified in Table I. Prior to packaging the apron shall be dusted with a suitable mineral powder to prevent adhesion to itself.

2.1.2.1 Acid resistance. A pocket shall formed from the apron material with the heavier coated side up. This pocket shall be filled with diluted sulfuric acid (sp. gr. 1.28 to 1.30), and remain filled with the acid for a period of 8 hours. At the end of this period, the specimen shall be thoroughly washed in cold water and dried at room temperature for a minimum of two hours. There shall be no appreciable stiffening and brittleness or softness and tackiness and there shall be no sign of acid penetration. Appreciable means a change that is immediately noticeable in comparing the tested specimen with the untested coated cloth.

2.1.2.2 Resistance to aging. The coated fabric shall be tested for resistance to aging in accordance with FED-STD-191 test method 5852 except that the time of exposure shall be 10 days. The specimens shall show no signs of becoming stiff and brittle or soft and tacky.

Beneficial comments, recommendations, clarifications, etc. and any data which may improve this document should be sent to: General Services Administration, Engineering Branch (7FXEE), 819 Taylor Street, Fort Worth, TX 76102

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:30Z
Check the source to verify that this is the current version before use.

2.1.4 Tie tapes. The tie tapes shall be 1/2 inch to 7/8 inch (1.3 cm to 2.2 cm) wide, with a minimum breaking strength of 80 pounds (356 N), white in color. The apron shall be supplied with 3 tapes, each 30 inches (76 cm) long minimum. The tapes shall be supplied secured to the apron, either individually or as a bundle.

Table I. Coated Cloth Requirements, minimums

Characteristics	Requirement	Test method
Overall weight	11.5 oz/sq yd (426 g/m^2)	ASTM D 3776
Breaking strength		
Initial - warp	58 lbs (258 N)	ASTM D 5034
filling	40 lbs (178 N)	ASTM D 5034
After acid resistance test		
warp	52 lbs (231 N)	ASTM D 5034
filling	35 lbs (156 N)	ASTM D 5034
Adhesion of coating	4.5 lbs (20 N)	5970 of FED-STD-191

2.1.5 Thread, sewing. The sewing thread shall be the same as that used in the standard product of the supplier.

2.1.6 Grommets. The grommets shall be brass or aluminum, 11/16 inch (1.7 cm) outside diameter normally used in industry practice.

2.1.7 Cement. When cement is used for adhering the reinforcement patches to the apron body, the cement shall possess good adhesion, flexibility, and all other characteristics compatible with those required of the coating after application to the cloth.

2.1.8 Design and construction. The apron shall be bib type with neck and waist ties. The apron shall be made from a single thickness of the coated cloth specified in 2.1.2, with the heavily coated side on the outside of the apron. Dimensions shall be as specified in figure 1, the tolerances shall be ±1 inch (2.5 cm). There shall be a hem, folded in on the underside, securely stitched around the entire apron, with reinforcement patches for grommets.

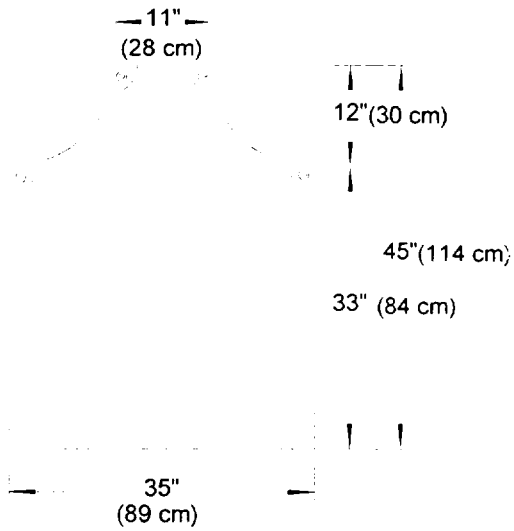


Figure 1

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:30Z
Check the source to verify that this is the current version before use.

2.1.9 Marking. The apron shall be marked in a plain and permanent manner with the manufacturer's name or recognized trademark.

2.2 Workmanship. The aprons shall be clean, wrinkle free (except for folding), and of best commercial quality. The aprons shall have no defects which may affect appearance, serviceability or durability.

2.3 Metric products. Products manufactured to metric dimensions will be considered on an equal basis with those manufactured using inch-pound units, providing they fall within tolerances specified and all other requirements of this document are met.

3. REGULATORY REQUIREMENTS

3.1 Regulatory requirements. The offeror/contractor is encouraged to use recovered materials to the maximum extent practicable, in accordance with paragraph 23.403 of the Federal Acquisition Regulation (FAR).

4. QUALITY ASSURANCE PROVISIONS

4.1 Product conformance. The products provided shall meet the salient characteristics of this CID, shall conform to the producer's own drawings, specifications, standards, and quality assurance practices, and shall be the same product offered for sale in the commercial market. The government reserves the right to require proof of such conformance.

5. PACKAGING, PACKING AND MARKING

5.1 Packaging, packing and marking. The packaging, packing, and marking shall be as specified in the contract or order.

6. NOTES

6.1 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

a. Title, number, and date of this CID.
b. The packaging, packing and marking desired.

6.2 Referenced documents.

Federal standards are available from the General Services Administration, Federal Supply Service Bureau, Specification Section, Suite 800, 470 East L'Enfant Plaza SW, Washington, DC 20407.

Copies of ASTM standards are available from ASTM, 100 Bar Harbor Dr., West Conshohocken, PA 19428-2959, (610-832-9500).

6.3 National Stock Numbers. NSN 8415-00-634-5023 uses this document.

Preparing Activity:
GSA - FSS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:30Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:30Z
Check the source to verify that this is the current version before use.