INCH-POUND

MIL-C-70810 (AR)
28 May 1991

MILITARY SPECIFICATIONS

COMBUSTIBLE CARTRIDGE CASE ASSEMBLY PARTS NITROCELLULOSE PAPER PROCESS, FOR CHARGE, PROPELLING, 155MM, M203A1

This specification is approved for use by the US Army Armament, Munitions and Chemical Command, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers requirements, quality assurance provisions and packaging for the paper used to manufacture combustible case components for the artillery propelling charge designated as M203A1 Charge, Propelling 155MM.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards and handbooks. The following specification, standards and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and Supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

MILITARY

MIL-A-48078	- Ammunition, Standard Quality Assurance Provisions, General Specifications For
MIL-C-70462	- Charge, Propelling, 155MM, M203A1 Loading, Assembly and Packing

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, U.S. Army ARDEC, ATTN: SMCAR-BAC-S, Picatinny Arsenal, New Jersey 07806-5000 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 1320

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

STANDARDS

MILITARY

MIL-STD-286	- Propellants, Solid: Sampling, Examination and Testing
MIL-STD-1168	- Lot Numbering of Ammunition

(Unless otherwise indicated, copies of the federal and military specifications, standards and handbooks are available from the Standardization Documents Order Desk, Bldg 4D, 700 Robbins Ave., Philadelphia, PA 19111-5094.)

2.1.2 Other government documents, drawings, and publications. The following other government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified the issues are those cited in the solicitation.

DRAWINGS

US ARMY ARMAMENT RESEARCH, DEVELOPMENT AND ENGINEERING CENTER (ARDEC)

9345094	- Wrapped Body M203A1
9355097	- Igniter Container
12598551	- Closure Cap F/Wrapped Body
12598552	- Wrapped Body Assembly
9345095	- Rear, Cap
9345109	- Composition
9357034	- Composition
9390469	- Packing and Marking for Box, Fiberboard for Igniter Container and Rear Cap, for Case Cartridge Assembly, 155MM, M203A1
9390470	- Packing and Marking for Box, Fiberboard for Body, Molded or Wrapped Body Assembly for Case Cartridge Assembly, 155MM, M203A1
9390475	- Packing and Marking for Box, Wood, Cleated Plywood for Box, Fiberboard for Igniter Container and Rear Cap for Case Cartridge Assembly, 155MM, M203A1
9390476	- Packing and Marking for Box, Wood, Cleated Plywood for Box, Fiberboard for Body, Molded or Wrapped Body Assembly for Case Cartridge Assembly, 155MM, M203A1
9345091	- Case Cartridge Assembly 155MM M203A1

(Copies of drawings, publications and other Government documents required by manufacturers in connection with specific acquisition functions should be obtained from the procuring activity or as directed by contracting officer.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

2.2 Non-Government publications. The following document(s) forms a part of this document to the extext specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issue of the documents cited in the solicitation (see 6.2).

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

ASTM D638 - Test Method for Tensile Properties of Plastics

(Applications for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103).

2.1.3 Order of precedence. In the event of a conflict between the text of this document and the reference cited herein, the text of this document shall take precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Materials. The constituent materials shall comply with the requirements of all applicable drawings and specifications.

3.2 Parts. The combustible cartridge case parts shall comply with all the requirements specified in applicable drawings and specifications.

3.3 Stability. The nitrocellulose in the combustible cartridge case parts shall not completey change the color of the methyl violet paper to salmon pink color in less than thirty-five (35) minutes when tested in accordance with 4.5.2.

3.4 Physical properties. The weights and tensile strength of combustible cartridge case parts shall meet the requirements of Table I.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:30Z
Check the source to verify that this is the currentversion before use.

Table I

Weight and tensile strength requirements for combustible cartridge case parts.

Part Description	Drawing	Weight	Tensile Strength	Density (1)
Rear Cap	9345095	2.0 ± 0.25 oz	N/A	TBD
Closure Cap	12598551	2.5 ± 0.35 oz	N/A	TBD
Wrapped Body	9345094	27.5 ± 1.00oz	1000 psi min	TBD
Igniter Cont.	9345097	6.8 ± 0.49 oz	N/A	0.85 ± 0.12g/cc

Note (1) Density is advisory

3.5 50-lb static test for assembly of wrapped body and igniter container. The assembly of wrapped body and igniter container shall pass the 50-lb static test and no separation of igniter container from the assembly shall occur when tested in accordance with 4.5.1.

3.6 Destructive pull test.

3.6.1 Wrapped body and closure cap. The force of the adhesive bond between wrapped body and closure cap shall be 200 lbs minimum when tested in accordance with 4.5.2.1.

3.6.2 Rear cap and igniter container. The force of the adhesive bond between rear cap and igniter container shall be 200 lbs minimum when tested in accordance with 4.5.2.2.

3.7 Assembly test for rear cap and igniter container. The mating surfaces between rear cap and igniter container shall be tight. The igniter container shall not be separated from the assembly when tested in accordance with 4.5.3.

3.8 Proving ground (see 4.5.9). Ballistic tests shall be performed for First Article (see 4.3.2) and the first lot of each new interfix at 70 Degrees F, 145 Degrees F and -65 Degrees F. The cartridge case components, when assembled and fired as 155MM M203A1 propelling charge shall be consumed such that there is no inert or burning combustible cartridge case residue in the gun tube.

Source: https://assist.dla.mil -- Downloaded: 2026l0-26T04:30Z
Check the source to verify that this is the currentversion before use.

3.9 First article inspection. This specification makes provisions for first article inspection. Requirements for the submission of first article samples by the contractor shall be as specificed in the contract.

3.9.1 First article test (see 6.6.3). Test samples shall be withdrawn from the first lot produced by the contractor and tested in accordance with all the requirements of this specification and with Table IV. Until the first article test has been performed and found to be acceptable, the contractor is in no way authorized by the Government to initiate second lot production unless otherwise directed by the contracting officer.

3.10 Workmanship. All parts shall be fabricated in a thorough, workmanslike manner, and shall be free of molding flaws, cracks, warpage outside the material envelope, crevassing, soft spots, frayed edges, foreign material greater than 1/4 inch in any dimension.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed rquirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspections set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all rquirements of the contract. Sampling inspection, as parts of manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to accept defective material.

4.2 Classification of inspections. The following types of inspection shall be conducted on this item:

a. First article inspection (4.3)
b. Quality conformance inspection (4.4)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

Prior to dimensional examination of combustible cartridge case, components shall be conditioned for a minimum of twelve (12) hours at 23 Degrees Centigrade ± 2 Degrees and at 50% ± 5% relative humidity.

4.3 First article inspection.

4.3.1 Submission. The contractor shall submit a first article sample, as designated by the contracting officer for first article tests. The sample shall consist of parts which have been produced by the contract or furnished by a supplier which have been manufactured using the same production process, procedures, molds, dies and equipment which will be used in fulfilling the contract. If parts are produced from more than one (1) mold or die, they shall be identified by a suitable mold or die mark. Samples shall be taken equally from each mold or die used in production. All parts and materials, including packaging and packing, shall be obtained from the same sources of supply as will be used in regular production. Prior to submission, the contractor shall inspect the sample to the degree necessary to ensure that it conforms to the requirements of the contract, and submit a record of this inspection with the sample, including statements of findings for materials, processes and tests. (A first article sample, or portion thereof, as directed by the contracting officer, shall also be submitteed whenever a change occurs in manufacturing process, material used, or source of supply as to significantly affect product uniformity as determined by the Government). The first article sample shall consist of the following items in sample quantities as indicated:

Part Description	Drawings	Quantity
Wrapped Body	9345094	80
Rear Cap	9345095	80
Closure Cap	12598551	80
Igniter Container	9345097	80

In addition, whenever there is a lapse in production for a period in excess of 90 days, a first article sample, as directed by the contracting officer shall also be submitted as follows:

Part Description	Drawings	Quantity
Wrapped Body	9345094	50
Rear Cap	9345095	50
Closure Cap	12598551	50
Igniter Container	9345097	50

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

4.3.2 Inspections to be performed. The first article parts consisting of quantity of 80 submitted in accordance with 4.3.1 will be subjected by the Government to any or all the requirements of the applicable drawings and specifications and to the inspections of Table II. The first article parts consisting of quantity of 50 submitted in accordance with 4.3.1 will be subjected by the Government to any or all the requirements of the applicable drawings or specifications and to the inspection of Table II with the exception of firing tests. All inspections listed in Table II shall be classified Major unless otherwise specified in referenced paragraphs and specifications.

4.3.3 Rejection. See MIL-A-48078.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

TABLE II. First article inspection

CLASSIFICATION OF CHARACTERISTICS

PARAGRAPH	TITLE	SHEET OF	DRAWING NUMBER
			NEXT HIGHER ASSEMBLY

CLASSIFICATION	EXAMINATION OR TEST	CONFORMANCE CRITERIA	REQUIREMENT PARAGRAPH	INSPECTION METHOD REFERENCE
	Wrapped Body M203A1 (Drawing 9345094) Examination for Defects	50	3.2	4.4.2.1
	Closure Cap F/Wrapped Body (Drawing 12598551) Examination for Defects	50	3.2	4.4.2.2
	Rear Cap (Drawing 9345095) Examination for Defects	50	3.2	4.4.2.3
	Igniter Container (Drawing 9345097) Examination for Defects	50	3.2	4.4.2.4
	Combustible Cartridge Case Components (all) assembled as part of the M203A1 propelling charge, Firing Tests at 70°F, 145°F, and -65°F	30	3.2	4.5.9

NOTES:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

4.4 Quality conformance inspection.

4.4.1 Inspection lot formation. Inspection lots shall comply with the lot formation provisions of MIL-A-48078 and MIL-STD-1168. In addition, inspection lots of parts for case shall contain:

a. Nitrocellulose from one manufacturer and from not more than two lot numbers with the same interfix number.

b. Diphenylamine from one manufacturer and from not more than two lot numbers with the same interfix number.

c. Resin from one manufacturer and from not more than two lot numbers with the same interfix number.

d. Kraft from one manufacturer and from not more than two lot lot numbers with the same interfix number.

e. Talc from one manufacturer and not more than two lot numbers with the same interfix number.

4.4.2 Examination. See MIL-A-48078.

a. Classification of Charateristics. Quality conformance examinations and tests are specified in the following Classification of Characteristics paragraphs. The contractor's quality program or detailed inspection system shall provide assurance of compliance of all characteristics with the applicable drawing and specification requirements utilizing as a minimum the conformance criteria specified. When cited in the classification of characteristics paragraphs, attributes sampling inspection shall be conducted in accordance with Table III below.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

Table III

Attributes sampling for Major and Minor Defects

Lot Size	Major Sample Size	Minor Sample Size
2 to 8	*	See note
9 to 15	*	5
16 to 25	*	5
26 to 50	32	5
51 to 90	32	12
91 to 150	32	12
151 to 280	32	14
281 to 500	32	17
501 to 1200	74	20
1201 to 3200	74	24
3201 to 10000	87	30
10001 to 35000	109	36
35001 to 150000	124	40
150001 to 500000	156	40
500001 and over	187	40

* 100 Inspection

NOTE: Use 100% inspection when lot size is less than 5 units. Use sample size of 5 when lot size is greater than 5 units.

b. Alternative quality conformance provisions. Alternative quality conformance provisions, methods, or equipment, such as statistical process control, tool control, other types of sampling procedures, etc. may be used by the contractor when they provide as a minimum the level of quality assurance required by the provisions specified herein. Prior to applying such alternative procedures, methods, or equipment, the contractor shall describe them in a written proposal submitttd to the Government for evaluation (see 6.8). When required, the contractor shall demonstrate that the effectiveness of each proposed alternative is equal to or better than the specified quality assurance provision(s) herein. In cases of dispute as to whether the contractor's proposed alternative(s) provides equivalent assurance, the provisions of this specification shall apply. All approved alternative inspection provisions shall be specifically incorporated into the contractor's quality program or detailed inspection system, as applicable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF CHARACTERISTICS

MIL-C-70810 (AR)

PARAGRAPH	TITLE	SHEET 1 OF 1	DRAWING NUMBER
4.4.2.1	Wrapped Body M203A1		9345094
			NEXT HIGHER ASSEMBLY

CLASSIFICATION	EXAMINATION OR TEST	CONFORMANCE CRITERIA	REQUIREMENT PARAGRAPH	INSPECTION METHOD REFERENCE
Critical	None defined			
Major				
101	Inside diameter	Table III	3.2	Gage
102	Material thickness	Table III	3.2	Gage
103	Length	Table III	3.2	Gage
104	Straightness	Table III	3.2	Gage
105	Weight	Table III	3.4	4.5.8
106	Composition	4.4.3.5	3.2	4.5.5
107	Tensile strength	4.4.3.6	3.4	4.5.6
108	Density	4.4.3.7	3.4	4.5.7
109	Diameter of holes (4 places)	Table III	3.2	Gage
110	Unequally spaced holes (4 places)	Note 1	3.2	Gage
111	Nitrocellulose stability	4.4.3.4	3.3	4.5.4
Minor				
201	Improper spiral grooves	Table III	3.2	Gage
202	Improper chamfer (angle and length)	Table III	3.2	Visual
203	Evidence of poor workmanship	Table III	3.10	Visual

NOTES: 1/ Tool Controlled Dimensions - Whenever a new tool is introduced, 25 samples shall be checked for conformance with the dimension requirements for qualification of tool prior to production.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF CHARACTERISTICS

MIL-C-70810 (AR)

PARAGRAPH	TITLE	SHEET	DRAWING NUMBER
4.4.2.2	Closure Cap F/Wrapped Body	1 OF 1	12598551
			NEXT HIGHER ASSEMBLY: 12598552

CLASSIFICATION	EXAMINATION OR TEST	CONFORMANCE CRITERIA	REQUIREMENT PARAGRAPH	INSPECTION METHOD REFERENCE
Critical	None defined			
Major				
101	Outside diameter	Table III	3.2	Gage
102	Material thickness	Table III	3.2	Gage
103	Length	Table III	3.2	Gage
104	Weight	Table III	3.4	Gage
105	Composition	4.4.3.5	3.2	4.5.8
106	Density	4.4.3.7	3.4	4.5.7
107	Nitrocellulose stability	4.4.3.4	3.3	4.5.4
Minor				
201	Improper chamber (angle and length)	Table III	3.2	Visual
202	Improper inside radius	Table III	3.2	Visual
203	Improper spiral grooves	Table III	3.2	Gage
204	Evidence of poor workmanship	Table III	3.10	Visual

NOTES:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

CLASSIFICATION OF CHARACTERISTICS

PARAGRAPH	TITLE	SHEET 1 OF 1	DRAWING NUMBER
4.4.2.3	Rear, Cap		9345095
			NEXT HIGHER ASSEMBLY 9345092

CLASSIFICATION	EXAMINATION OR TEST	CONFORMANCE CRITERIA	REQUIREMENT PARAGRAPH	INSPECTION METHOD REFERENCE
Critical	None defined			
Major				
101	Outside diameter of cap	Table III	3.2	Gage
102	Inside diameter of cap	Table III	3.2	Gage
103	Material thickness	Table III	3.2	Gage
104	Length of cap	Table III	3.2	Gage
105	Weight	Table III	3.4	4.5.8
106	Composition	4.4.3.5	3.2	4.5.5
107	Density	4.4.3.7	3.4	4.5.7
108	Diameter of hole	Note 1	3.2	Gage
109	True position of hole	Note 1	3.2	Gage
110	Diameter of rear flat portion	Note 1	3.2	Gage
111	True position of flat portion	Note 1	3.2	Gage
112	Presence of ribs on inside	Note 1	3.2	Gage
113	Nitrocellulose stability	4.4.3.4	3.3	4.5.4
Minor				
201	Improper taper angle	Note 1	3.2	Gage
202	Improper chamfer of hole	Note 1	3.2	Visual
203	Improper chamfer of lip	Note 1	3.2	Visual
204	Improper inside radius	Note 1	3.2	Visual
205	Evidence of poor workmanship	Table III	3.10	Visual

NOTES: 1/ Tool Controlled Dimensions - Whenever a new tool is introduced, 25 samples shall be checked for conformance with the dimension requirements for qualification of tool prior to regular production.

AMSMC Form 1570b, 1 Jul 89 Replaces 1570, 1 Feb 85, which may not be used.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANC INSPECTION

CLASSIFICATION OF CHARACTERISTICS

MIL-C-70810 (AR)

PARAGRAPH	TITLE	SHEET 1 OF 2	DRAWING NUMBER
4.4.2.4	Igniter Container		9345097
			NEXT HIGHER ASSEMBLY 9345103

CLASSIFICATION	EXAMINATION OR TEST	CONFORMANCE CRITERIA	REQUIREMENT PARAGRAPH	INSPECTION METHOD REFERENCE
Critical	None defined			
Major				
101	Maximum outer diameter of igniter container	Table III	3.2	Gage
102	Outer diameter of rear lip/rear cap	Table III	3.2	Gage
103	Length of container	Table III	3.2	Gage
104	Length of rear lip (0.60 in)	Table III	3.2	Gage
105	Length of rear lip edge to rear body interface (2.8 in)	Table III	3.2	Gage
106	Length of maximum out diameter	Table III	3.2	Gage
107	Front outer diameter	Table III	3.2	Gage
108	Thickness of material	Table III	3.2	Gage
109	Weight	Table III	3.4	4.5.8
110	Composition	4.4.3.5	3.2	4.5.5
111	Density	4.4.3.7	3.4	4.5.7
112	Inside diameter of rear lip measured at intersection of 15° and rear surface of lip	Note 1	3.2	Gage
113	Diameter of rear flat portion	Note 1	3.2	Gage
114	Length of rear edge of body interface to center of boss (4 places)	Note 1	3.2	Gage
115	Diameter of bosses (4 places)	Note 1	3.2	Gage
116	Unequally spaced bosses (4 places)	Note 1	3.2	Gage
117	Length of flat surface of boss (4 places)	Note 1	3.2	Gage
118	Angle on boss (4 places)	Note 1	3.2	Gage
119	Nitrocellulose stability	4.4.3.4	3.3	4.5.4

NOTES: 1/ Toolcontrolled Dimensions - Whenever a new tool is introduced, 25 samples shall be checked for conformance with the dimension requirements for qualification of tool prior to requalr production.

AMSMC Form 1570b, 1 Jul 89 Replaces 1570, 1 Feb 85, which may not be used.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:30Z
Check the source to verify that this is the currenversion before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF CHARACTERISTICS

MIL-C-70810 (AR)

PARAGRAPH	TITLE	SHEET 2 OF 2	DRAWING NUMBER
4.4.2.4			9345097
			NEXT HIGHER ASSEMBLY 9345103

CLASSIFICATION	EXAMINATION OR TEST	CONFORMANCE CRITERIA	REQUIREMENT PARAGRAPH	INSPECTION METHOD REFERENCE
Minor				
201	Improper chamfer (angle and length)	Table III	3.2	Gage
202	Radius of rear outside corner	Note 1	3.2	Gage
203	Imperper taper angle (7°)	Note 1	3.2	Gage
204	Improper tape angle (15°)	Note 1	3.2	Gage
205	Diameter of holes	Note 1	3.2	Gage
206	Number of holes	Note 1	3.2	Gage
207	Holes not properly spaced	Note 1	3.2	Gage
208	Evidence of poor workmanship	Table III	3.10	Visual

NOTES:

AMSMC Form 1570b, 1 Jul 89 Replaces 1570, 1 Feb 85, which may not be used.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

4.4.3 Testing.

4.4.3.1 50-lb static tests.

4.4.3.1.1 Assembly of wrapped body and igniter container. Ten (10) wrapped bodies and ten (10) igniter containers shall be randomly selected from the first article sample and from each of the first three production lots and tested in accordance with 4.5.1. If any sample fails to pass the test, the lot shall be rejected. When three consecutive lots have been accepted, sampling may be reduced to five (5) wrapped bodies and five (5) igniter containers from each lot. If a failure occurs, sampling shall revert to ten (10) wrapped bodies and ten (10) igniter containers per lot until three consecutive lots have been accepted. Any failure shall be cause for lot rejection.

4.4.3.2 Destructive pull test.

4.4.3.2.1 Wrapped body and closure cap. Five (5) wrapped bodies and five (5) closure caps shall be randomly selected from the lot and tested in accordance with 4.5.2.1. Any failure shall be cause for lot rejection.

4.4.3.2.2 Rear cap and igniter container. Five (5) rear caps and five (5) igniter containers shall be randomly selected from the lot and tested in accordance with 4.5.2.2. Any failure shall be cause for lot rejection.

4.4.3.3 Assembly test. Each rear cap and igniter container shall be tested in accordance with 4.5.3. If the assembly fails the test, the rear cap and igniter container shall be rejected and removed from the lot (see 6.10).

4.4.3.4 Stability. Ten (10) wrapped bodies, ten (10) closure caps, ten (10) rear caps and ten (10) igniter containers shall be randomly selected from the first article sample and from each of the first three production lots and tested in accordance with 4.5.4. If any sample fails to pass the test, the lot shall be rejected. When three consecutive lots have been accepted, sampling may be reduced to five (5) wrapped bodies, five (5) closure caps, five (5) rear caps and five (5) igniter containers from each lot. If a failure occurs, sampling shall revert to ten (10) wrapped bodies, ten (10) closure caps, ten (10) rear caps and ten (10) igniter containers per lot until three consecutive lots have been accepted. Any failure shall be cause for lot rejection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

4.4.3.5 Composition. Ten (10) wrapped bodies, ten (10) closure caps, ten (10) rear caps and ten (10) igniter containers shall be randomly selected from the first article sample and from each of the first three production lots and tested in accordance with 4.5.5. If any sample fails to pass the test, the lot shall be rejected. When three consecutive lots have been accepted, sampling may be reduced to five (5) wrapped bodies, five (5) closure caps, five (5) rear caps and five (5) igniter containers from each lot. If a failure occurs, sampling shall revert to ten (10) wrapped bodies, ten (10) closure caps, ten (10) rear caps and ten (10) igniter containers per lot until three consecutive lots have been accepted. Any failure shall be cause for lot rejection.

4.4.3.6 Tensile strength. Five (5) wrapped bodies shall be randomly selected from the first article and each production lot to provide the required test specimens for tensile tests in accordance with 4.5.6. Failure of any specimen is cause for lot rejection.

4.4.3.7 Density. Five (5) wrapped bodies, five (5) closure caps, five (5) rear caps and five (5) igniter containers shall be randomly selected from the first article sample and each production lot to provide the test specimens for density tests in accordance with 4.5.7. Testing is for informational purpose only.

4.4.4 Inspection equipment. The inspection equipment required to perform the examination and tests prescribed herein is described in the "Paragraph Reference/Inspection Method" column in the tables starting with paragraph 4.4.2.1. The contractor shall submit for approval inspection equipment designs in accordance with the terms of the contract. See section 6 of MIL-A-48078 and 6.3 herein.

4.5 Methods of inspection.

4.5.1 50-lb static test.

4.5.1.1 Assembly of wrapped body and igniter container. The inert loaded wrapped body assembly shall be assembled together with the igniter container with the lock-in device. The inert loaded assembly shall be lifted above the ground with the igniter container facing downward and clamped on a suitable test fixture for 5 minutes. Observation shall be made for separation of the igniter container from the body. Any separation occurrence in the testings would be cause for lot rejection.

4.5.2 Destructive pull test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

4.5.2.1 Wrapped body and closure cap. This test shall be performed after the adhesive bond between the wrapped body and closure cap has had sufficient time to set. The assembly shall be held in a suitable test fixture clamping on the wrapped body. The test apparatus shall apply a longitudinal load distributed over 360 degrees around the lip of the closure cap. Observation shall be for the force required for separation of the closure cap from the wrapped body. If any sample fails to meet the specified requirement, the lot shall be rejected.

4.5.2.2 Rear cap and igniter container. This test shall be performed after the adhesive bond between the rear cap and igniter container has had sufficient time to set. The assembly shall be held in a suitable test fixture clamping on the igniter container. The test apparatus shall apply a longitudinal load distributed over 360 degrees around the lip of the rear cap. Observation shall be for the force required for separation of the rear cap from the igniter container. If any sample fails to meet the specified requirement, the lot shall be rejected.

4.5.3 Assembly test. The rear cap shall be assembled to igniter container. The assembly shall be lifted above the surface by using fingers through the hole of the rear cap without touching the igniter container. Separation of the igniter container from the rear cap shall be cause for rejection of the assembly. The rejected assembly shall be removed from the lot for proper disposition (see 6.10).

4.5.4 Stability. The sample quantity of combustible case components shall be subjected to the stability heat test at 134.5 Degrees C in accordance with MIL-STD-286, Method 404.1.2.

4.5.5 Composition.

4.5.5.1 Preparation of specimen. Each specimen shall be divided into 1/8-inch (approximate) cubes or equivalent. The specimens shall then be thoroughly mixed to form a composite. From the composite, approximately 1.0 g. shall be selected as the analysis sample and weighed to the nearest 0.2 milligram (mg), (weight A) in an extraction thimble. The same thimble should be carried through the extractions in 4.5.5.3.1 and 4.5.5.3.3.

4.5.5.2 Total volatiles. The samples from 4.5.5.1 shall be dried for 3 hours at 100 $\pm$ 2 Degrees C, cooled in a desiccator (1/2 hr. min.), or placed in a microwave moisture analyzer and dry to constant weight and weighed to the nearest 0.2 mg (Weight W). Calculate the percent total volatiles as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

$$\% \text{ Total Volatiles} = \frac{A - W \times 100}{A}$$

4.5.5.3 Analytical procedure.

4.5.5.3.1 Extraction. Using a tared, extra-coarse, sintered glass thimble, extract each sample from 4.5.5.2, with methylene chloride, for a minimum of 16 hours in a Roweg extractor (MIL-STD-286, Method 104.1). Evaporate the extract to dryness, using a current of clean, dry air. This extract is to be used for diphenylamine determination in 4.5.5.3.2. Dry the residues (non-extractable material) in the extraction thimbles by aspirating the thimble and contents until the odor of methylene chloride is not discernable. Dry the thimble plus residue for 1/2 hour minimum at 100 ± 20 Degrees C. Cool in a desiccator (1/2 hour min). Determine the dry weight of this residue (weight C) to the nearest 0.2 mg as the difference between this weight and the weight of the empty thimble. This residue is to be used for the nitrocellulose determination in 4.5.5.3.3.

4.5.5.3.2 Diphenylamine (DPA).

4.5.5.3.2.1 Method 1. To the dried extract from 4.5.5.3.1, add 50 milliliters (ml) of glacial acetic acid. If necessary, warm slightly to dissolve the extract, then cool to room temperature. Complete the determination of diphenylamine in the solution according to Method 201.1 (starting with paragraph 5.5) of Standard MIL-STD-286, except that 25 ml of methylene chloride is to be added after addition of the potassium iodine solution. When the end point appears to have been reached, (absence of blue color) the flask is stoppered and shaken. If no color appears, the end point has been reached; otherwise, continue titration until the blue color is discharged and shaking produces no further color. Calculate the percent DPA as shown in Standard MIL-STD-286, Method 201.4, paragraph 5.11.

4.5.5.3.2.2 Tentative method 2. (Informational test for the first 3 production lots) see 6.7. Prepare 1.2 to 1.5 grams of finely cut sample. Dry in a microwave oven. Transfer the dried sample to a weighing bottle. Cool the weighing bottle in a desiccator for 5 minutes and weigh. Transfer the sample to a square beaker. Reweigh the empty weighing bottle. Sample weight = total weight minus weight of empty weighing bottle. Add 50 ml of 90% methanol to the square beaker, grind the mixture by the use of the polytron homogenizer for 3 minutes or until the sample is completely defiberized. Transfer the mixture to a millipore filtering apparatus with 0.45 micron cellulose nitrate membrane. Use a squeeze bottle with 90% methanol to wash the square beaker. Add the washing solution on top of the residue. Add

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

50 ml of fresh 90% methoanol to the square beaker. Grind this solution in the polytron for 1 minute. Use spatula to transfer the residue from the filtering apparatus to the square beaker containing the methanol. Place the beaker in an ultrasonic cleaner which has warm water (minimum 45 Degrees C) for 10 minutes. Transfer the mixture to the filtering apparatus without changing the filter. Use a squeeze bottle with 90% methanol to wash the square beaker and add the washing solution to the residue in the filtering apparatus. Repeat steps above two times except the time in the ultrasonic cleaner is reduced to 5 minutes. Transfer the filtrate into a 500 ml volumetric flask. Make up to the mark with 90% methanol. Shake the flask well enough to make sure the solution is uniform. Transfer exactly 15 ml of this solution into a 50 ml volumetric flask. Make up the mark with 90% methanol. Shake well. Measure the UV absorption of this solution at 285 nm. Calculate the DPA content according to the following formula:

$$\text{DPA \%} = \frac{(20A - 0.2) \times 2.5}{32.001 \times W}$$

Where A = absorbance

W = sample weight in gms.

4.5.5.3.3 Nitrocellulose - Schulze - Tiemann Method for Nitrocellulose (NC) determinations.

Assemble the 250 ml Kjeldahl flask, gas evolution apparatus eudiometer/condenser tube, NaOH bath, lead band, heating mantle, transformer and protective shield as shown in Figure I.

Calibrate the apparatus with dry standard A.C.S. grade KNO3. Weigh 0.5 - 0.7 g standard samples to 0.1 mg and analyze using the following procedure. The factor is determined using the following equation:

$$F = \frac{616.8\ W\ (273.15 + T)}{V\ (B - C - P - S)}$$

F = Eudiometer Factor
W = Mass of KNO3 (g)
T = Temperature of Condenser Water (Degrees C)
V = Volume of Gas in Eudiometer Tube (ml)
B = Barometric Pressure (mm Hg), Table IV
C = Temperature Correction (mm Hg) Table IV
P = Vapor Pressure of Water over 33% w/w NaOH at T (mm Hg) Table V
S = Local Gravity & Sea Level Values corrected to standard values

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

Prepare samples as follows: Cut a specimen into 1/4 inch or smaller squares. Dry to constant weight using microwave moisture analyzer.

Displace the nitric oxide (NO) from the previous run by aspirating the gases through the drain or venting through a hood. Open the stopcock at the top of the eudiometer tube and carefully raise the leveling bulb until all the gas has been expelled. Rest the bulb in its holder and stopper it. Loosen the eudiometer tube from the rubber stopper in the bottom of the bath and drain the NaOH in the tube into the tank. Fill the leveling bulb to 90% of its capacity and place the empty eudiometer tube back onto the rubber stopper and secure it. Fill the eudiometer to the 0.0 ml mark with the leveling bulb, removing all air bubbles, close the stopcock, secure the bulb and stopper it. Replace the 33% w/w NaOH as needed to maintain a constant level in the tank.

Quantitively transfer 0.8 - 1.0 g (weighed to $\pm$ 0.1 mg) of the dry sample into a 250 ml Kjeldahl flask, add 50 mL deionized water and a few glass beads to prevent bumping. Attach the addition funnel/check value assembly to the freshly greased joint of the Kjeldahl flask. Attach spring clamps or rubber bands to the ears of the flask and addition funnel. Adjust the gas evolution assembly so that the exit tube is gently resting on the bottom of the NaOH bath. Place the lead band round the exit tube opening.

Open the addition funnel stopcock and turn on the heating mantle. Following the purging of the Kjeldahl flask, close the addition funnel stopcock and purge the rest of the tubing for 5-10 minutes. The system is thoroughly purged when no more bubbles escape into the bath.

Remove the heating mantle from the Kjeldahl flask and observe the drawing of the NaOH solution into the exit tubing and the closing of the check valve. Remove the eudiometer tube from the rubber stopper, place it over the open end of the exit tube. Rest the bottom of the eudiometer tube on the lead band and secure the eudiometer. Refill the leveling bulb to 90% of its volume, stopper the bulb and place it back into its ring.

Place 25 ml of FeC12 solution into the addition funnel. Open the stopcock slowly and allow most of the FeC12 to flow into the flask. Retain a few drops in the stopcock to preclude the flow of air into the system. If air is allowed into the system, the analysis is invalid and must be repeated. Place 25 ml of concentrated HCl to the addition funnel and add it to the Kjeldahl flask. Add 10 ml deionized water in a similar fashion. Following the last addition, fill the

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

addition funnel with 30 ml deionized water and tighten the stopcock nut. Place the heating mantle around Kjeldahl flask and heat, for 20-30 minutes or until bubbling has stopped. Remove the heating mantle and check to see that the valve closes. Loosen the stopcock nut on the addition funnel, allow the water to drip into the Kjeldahl, then increase the flow to effectively rinse the walls of the flask, close stopcock before air enters and tighten the nut. Attach the heating mantle, tap the check valve lightly until it opens and continue for 5-10 more minutes.

Following the completion of the reaction, remove the heating mantle and observe the closing of the check valve. Carefully move the eudiometer tube from its present position back to the rubber stopper and secure it. Slowly release the vacuum inside the Kjeldahl flask by allowing water and air to enter the flask through the stopcock.

Tap the check valve to help it open. Allow the gas to equilibrate thermally with the water in the jacket around the eudiometer tube. Wait at least 20 minutes. Measure the volume of gas collected in the eudiometer tube by uncorking the leveling bulb and adjusting it so that the top of the fluid in the bulb is at exactly the same height as the top of the fluid in the eudiometer tube. Read the volume to the nearest 0.1 ml. Use the following equation to calculate the % NC in the sample.

$$\%NC = \frac{2.246\ V\ (B - C - P - S)\ F}{NW\ (273.15 + T)}$$

V = Volume of Gas in Eudiometer Tube (ml)
B = Barometric Pressure (mm Hg)
C = Temperature Correction (mm Hg) Table IV
P = Vapor Pressure of Water over 33% (w/w) NaOH at T (mm Hg) Table IV
F = Eudiometer Factor
N = Percent Nitrogen in NC (%)
W = Mass of Sample (g)
T = Temperature of Condenser Water (Degrees C)
S = Local Gravity & Sea Level values corrected to standard values

PREPARATION OF FeC12:

Prepare the solution by adding 1000 g of FeC12.4H20, 1200 ml deionized water and 70 ml of concentrated HCl to a 5 liter round bottom flask. Attach the reflux condenser and reflux for 20 minutes. Cool to room temperature. Slowly add 20 grams of iron filings or powder to the cool solution. When the gas evolution has stopped, filter quickly without aerating the solution to remove the fines. Use A.C.S. grade chemicals throughout th synthesis.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

Prepare the bath fluids by dissolving reagent grade NaOH in deionized water until the concentration is 33% weight to weight.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

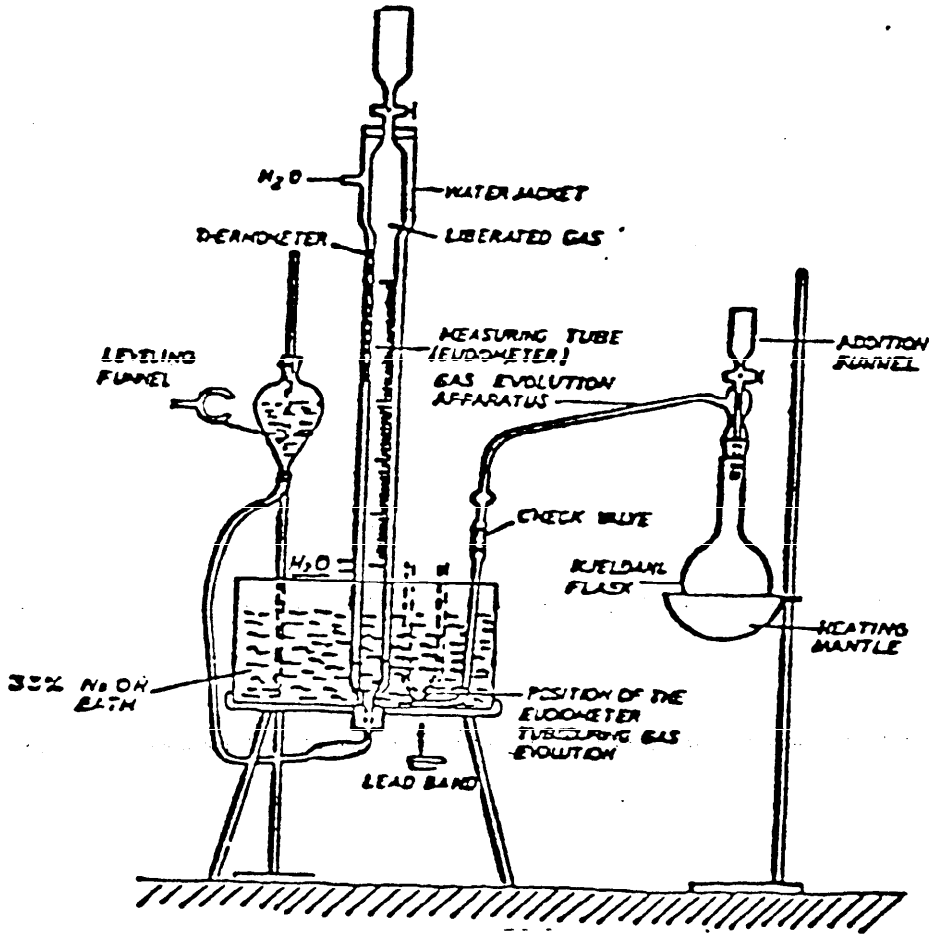


FIGURE 1.

SCHULTZ - TIEMANN APPARATUS

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:30Z
Check the source to verify that this is the current version before use.

TABLE IV

	BAROMETRIC PRESSURE IN mm Hg		
	740	760	780
Temp (See Note 1)			
14	1.69	1.73	1.78
15	1.81	1.86	1.91
16	1.93	1.98	2.03
17	2.05	2.10	2.16
18	2.17	2.23	2.29
19	2.29	2.35	2.41
20	2.41	2.47	2.54
21	2.53	2.60	2.67
22	2.65	2.72	2.79
23	2.77	2.84	2.92
24	2.89	2.97	3.05
25	3.01	3.09	3.17
26	3.13	3.21	3.30
27	3.25	3.34	3.42
28	3.37	3.46	3.55

Note 1: Temperature (Degrees C) on Barometer Thermometer.

Vapor Pressure of Water Dyer 33% (w/w) NaOH
Variable F

Temperature of Condenser Water (°C)	18	19	20	21	22	23	24	25
P =	11.6	12.4	13.2	14.0	14.9	15.8	16.8	17.8

Barometric pressure temperature correction, Variable C

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

TABLE V

Pressure correction value due to the vapor pressure of sodium hydroxide solution in the eudiometer tube.

TEMPERATURE ^{o}C	VAPOR PRESSURE OF NaOH SOLUTION (mm Hg)
18	11.6
19	12.4
20	13.2
21	14.0
22	14.9
23	15.8
24	16.8
25	17.8

Calculation of P_a (actual pressure) given a temperature T_a (actual temperature):

$$(T_a - T_1) \times (P_2 - P_1) + P_1 = P_a$$

Where: T_a = actual condenser water temperature

T_1 = next lowest tabulated temperature value from T_a

P_2 = pressure at next highest tabulated temp from T_a

P_1 = pressure at T_1

4.5.5.3.3.1 Nitrocellulose (Alternative method). To provide good heat conduction to the solvent, place a sufficient quantity of glycerin on the flask bottom and on the surface of the heat source to produce a continuous film. Add 10 ml of ethyl alcohol to the thimble and residue from 4.5.5.3.1 and extract with acetone using the method in 4.5.5.3.1. After extraction dry the residue remaining at 100 ± 2 Degrees C for one hour. Cool in a desiccator (1/2 hour min) weigh to the nearest 0.2 mg (Weight D). Evaporate the acetone extract to dryness and the inert atmosphere throughout this test. Reflux the solution for five (5) minutes. Add to the flask, via the condenser, 25 ml of 0.7N ferrous amonium sulfate (prepared per MIL-STD-286, Method 604.1) and 10 ml concentrated hydrochloric acid. Reflux for thirty (30) minutes more to obtain a yellow liquid in which the specimen is completely disintegrated. With the inert gas still running, cool in a water bath to room temperature. Add 5 ml of 20% ammoniumthiocyanate solution (MIL-STD-286, Method 601.1). Perform a blank titration on the reagents. Calculate the percent NC as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

$$\% \text{ NC} = \frac{46.69N}{E} \times \frac{(V-B)}{W} \times 100$$

Where:

V = Volume titanious chloride used for sample, ml
B = Volume titanious chloride used for blank, ml
W = Weight of dried sample, ml
N = Normality of titanious chloride
E = Percent nitrogen in the nitrocellulose

4.5.5.3.4 Talc content (ash test). The specimen of approximately 1 - 1.5 grams shall be taken from the same case body for the above testing and weighed to within 0.2 mg. in a tared porcelain crucible. Cover the crucible. The specimen shall then be ignited at 500 Degrees C in a muffle furnace. The crucible shall be cooled at room temperature and then weighed. Heat until all evidence of carbon is gone (no black residue), or for one hour. The increase in weight of the crucible shall be calculated on a total volatile - free basis to the percent of talc content.

4.5.5.3.5 Kraft, resin and additives. Calculate the percent kraft, resin and additives as follows:

$$\% \text{ Kraft} + \% \text{ resin} + \% \text{ additives} = 100 - (\% \text{ NC} + \% \text{ DPA} + \% \text{ Talc})$$


4.5.5.3.6 Report the total methylene chloride extractables $\frac{w - C \times 100}{W}$ and the total acetone extractables $\frac{(C - D) \times 100}{W}$

4.5.6 Tensile strength. Two specimens shall be prepared from each wrapped body. The specimens shall be taken from the center of the wall of the body. Test specimens shall be taken 180 Degrees apart. The specimens shall have a one-inch gage length and width, but wall thickness shall fall within the tolerance specified on the applicable drawing. The test specimens shall be preconditioned for a minimum of 4 hours at 23 plus or minus ($\pm$) 2 Degrees centigrade (C) at a relative humidity of 50 $\pm$ 5 percent (%). The tensile breaking strength of the specimen shall be determined in accordance with ASTM-D-638, using a cross head speed of one (1) inch per minute.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

4.5.7 Density. Six (6) specimens shall be taken from each wrapped body in accordance with Figure 2. Three (3) specimens shall be taken from each rear cap, enclosure cap and igniter container sample in accordance with Figure 3, Figure 4 and Figure 5 respectively. All the specimens shall be dried for 3 hours at 105 Degrees C or for 12 hours at 70 Degrees C. The specimen thickness shall be measured, the volume computed and the sample weighed on a calibrated scale having an accuracy of ± 0.02 g. The average density for each part shall be calculated and shall be in accordance with the applicable requirements.


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

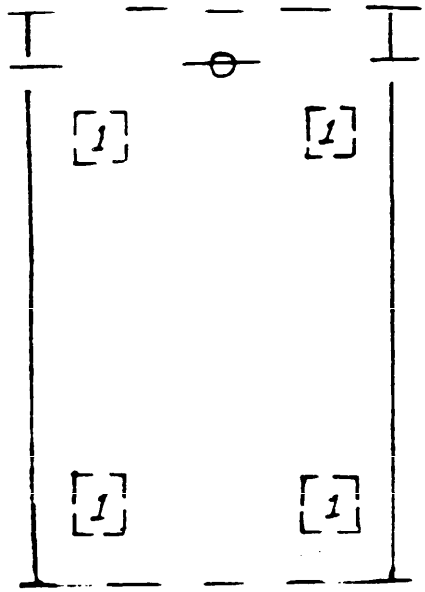

1. Three samples, 1 in. X 3 in. displaced by 120° for testing the density.
(Each from top and bottom)

FIGURE 2. Body


Source: https://assist.dla.mil -- Downloaded: 202610-26T04:30Z
Check the source to verify that this is the current version before use.

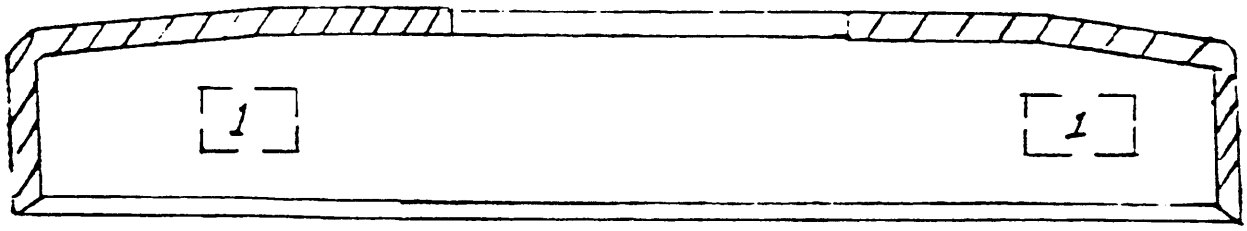

1. Three samples, 1/2 in. by 1/2 in. displaced by 120° for density test.

FIGURE 3. Rear Cap


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

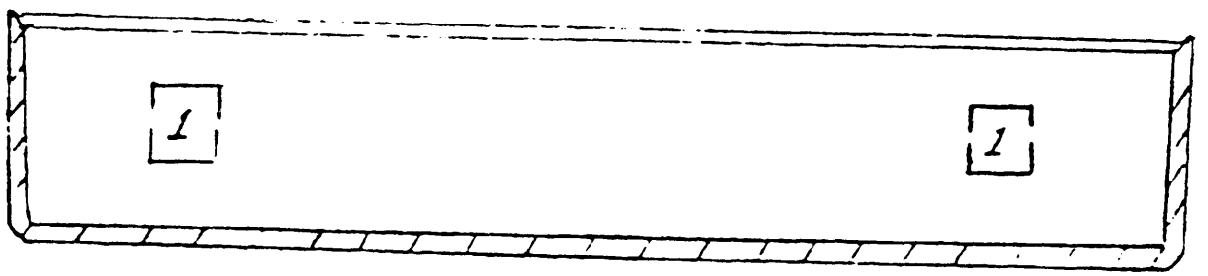

1. Three samples, 1 in. X 1 in. displaced by 120° for density test.

FIGURE 4. Closure Cap

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

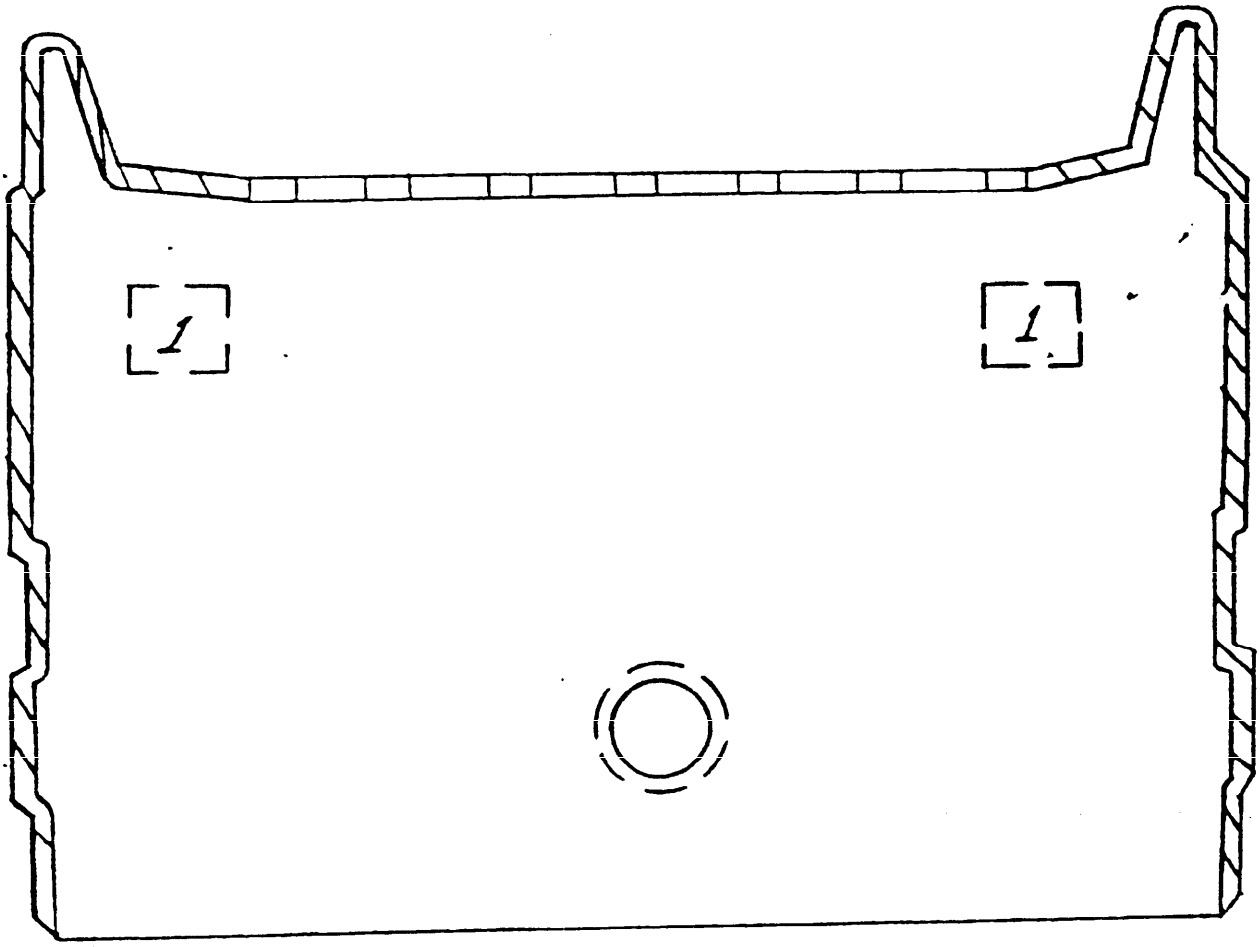

1. Three samples, 1 in. X 1 in. displaced by 120° for density test.

FIGURE 5. Igniter container

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

4.5.8 Weight. All samples shall be weighed individually, using any government approved and suitably calibrated scale capable of reading to the nearest 0.1 g. Test samples shall be preconditioned for a minimum of 4 hours at 23 ± 2 Degrees C and 50 ± 5% R.H. prior to weighing.

4.5.9 Proving ground firing. The combustible case components shall be assembled as 155mm M203A1 propelling charge with the established service charge load in accordance with MIL-C-70462. The tests shall be conducted at a Government proving ground in accordance with the applicable acceptance test procedure using M549, RA or PXR-6325 projectiles inert loaded within 0.1 pound of an as fired weight of 96.0 pounds using primer, M82 and fired in cannon M199 with 75 percent (minimum) remaining life. Firing shall be conducted with a spindle to charge base stand-off of 1 inch (plus or minus 1/4 inch). Prior to firing, all charges shall be temperature conditioned in a large conditioning box with adequate air circulation at the required temperature for a minimum of 24 hours and assurance will be made that, when fired, the charges are at the conditioning temperature. The following tolerances shall apply at all -65 Degrees F to -60 Degrees F; 145 Degrees F from 140 Degrees F to 145 Degrees F; 70 Degrees F from 68 Degrees F to 72 Degrees F. The test samples shall be fired at the temperartures indicated in Table III and any inert or burning residue shall be cause for lot rejection. Camera coverage of the weapon chamber and tube shall be provided for all test firings.

TABLE VI

Proving ground firing

Temperature	First Article	First Lot or Each New Interfix
-65 Degrees F	10	10
+70 Degrees F	10	10
+145 Degrees F	10	10

4.5.9.1 Refiring. If for any reason the proving ground considers that the test conditions have detrimentally affected the test results, the results shall be declared invalid, and a new test shall be performed.

5. PACKAGING

5.1 Packing.

5.1.1 Packing for igniter container cap and rear cap.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

5.1.1.1 Level A. The Igniter Container and Rear Cap shall be packed in accordance with drawing 9390475-1.

5.1.1.2 Level B. The Igniter Container and Rear Cap shall be packed in accordance with drawing 9390475-2.

5.1.1.3 Level C. The Igniter Container and Rear Cap shall be packed in accordance with drawing 9390469.

5.1.2 Packing for wrapped body assembly.

5.1.2.1 Level A. The Wrapped Body Assembly shall be packed in accordance with drawing 9390476-1.

5.1.2.2 Level B. The Wrapped Body Assembly shall be packed in accordance with drawing 9390476-2.

5.1.2.3 Level C. The Wrapped Body Assembly shall be packed in accordance with drawing 9390470.

5.2 Marking.

5.2.1 Marking for igniter container and rear cap.

5.2.1.1 Level A and B. Mark in accordance with drawing 9390475.

5.2.1.2 Level C. Mark in accordance with drawing 9390469.

5.2.2 Marking for wrapped body assembly.

5.2.2.1 Level A and B. Mark in accordance with drawing 9390476.

5.2.2.2 Level C. Mark in accordance with drawing 9390470.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The items covered by this specification is intended for use in M203A1 155MM Propelling Charge.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

6.2 Acquisition requirements. Acquisition documents must specify the following (see MIL-A-48078):

a. Title, number, and date of the specification.

b. Issues of DoDISS to be cited in the solicitation and if required, the specific issue of the individual documents refernced (see 2.1).

c. Provisions for submission of first article sample.

6.3 Submission of designs for approval. See 6.2.3 of MIL-A-48078. Submit equipment designs, as required to Commander, ARDEC, ATTN: AMSMC-QAR-(D), Picatinny Arsenal, NJ 07806-5001. This address will be specified on the Contract Data Requirements List, DD Form 1423 in the contract.

6.4 Submission of ammunition data cards. In addition to the normal distribution of records, when the cases are procured by the Army, one copy of all ammunition data cards shall be forwarded to each of the following:

Commander
ARDEC
ATTN: AMSMC-QAR-R (D)
SMCAR-AEE-BP
Picatinny Arsenal, NJ 07806-5000

6.5 Excessive residue. Residue is defined as excessive if it is significant enough to prevent chambering or hinder functioning of a subsequent round, or exceed 1 inch by 2 inches in size, as determined by the proving ground.

6.6 Proving ground.

6.6.1 Cleaning. Prior to each firing, the gun breech shall be thoroughly cleaned and dried.

6.6.2 Handling and storage. Special care shall be taken in the handling and storage of sample cases to prevent contamination by grease, grime, dirt, or other foreign material.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

6.6.3 First article test. The first article test is a one time qualification test for a new contractor to produce acceptable combustible cartridge cases. Also, a charge weight adjustment of using the new contractor's combustible cases against the combustible cases used in the calibration components shall be determined in the first article test. Once a contractor has demonstrated the ability to produce acceptable combustible cases and the charge weight adjustment of using the new contractor's combustible cases has been determined, the first article test may be waived by the contracting officer. The following test program shall be used for the first article test:

Table VII. First article test.

Test Phase	Temp. (Deg F)	No. of Control Rds	No. of Test Rds	Test Procedure
Sequential	145	15	60	TOP-4-2-504
Environment	-60	15	60	TOP-4-2-504
Charge weight adjustment test		see Table VIII		

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

TABLE VIII. Charge weight adjustment test.

Test Phase	Gun Tube No.	Temp (Deg F)	Sample Cal	Size Test (See Note 1)
Charge Establishment	1	70	3	9 (See Note 2)
	1	70	3	9 (See Note 3)
Uniformity	1	70	10	10 (See Note 2)
	1	70	10	10 (See Note 3)
	1	145		10 (See Note 2)
	1	145		10 (See Note 3)
	1	-65		10 (See Note 2)
	1	-65		10 (See Note 3)
	2	70	10	10 (See Note 3)
	3	70	10	10 (See Note 3)

Note 1: One new lot of M31A1E1 propellant shall be used for the charge weight adjustment test. Thirty boxes of propellant shall be randomly selected from the lot and shipped to the proving ground for charge weight adjustment test. Three gun tubes shall be used for the test. The test shall provide the two recommended charge weights. The first recommended charge weight shall be based on the established calibration combustible cases used for the test charges. The second recommended charge weights shall be based on the average of the three recommended charged weights using the new contractor's combustible cases. The difference between the first and second recommended charge weight will be used for the charge weight adjustment for the new contractor's combustible cases. The test shall be done in accordance with MIL-P-70456.

Note 2: Calibration combustible cases shall be used for the test charges.

Note 3: New contractor's combustible cases shall be used for the test charges.

6.7 Informational DPA content determinations. The tentative Method 2 for DPA content determinations is for informational purpose and cannot be used for acceptance test purpose. The informational test will be done for the first 3 production lots in addition to the normal acceptance test Method 1. All the above batch composition test results shall be submitted to Commander, ARDEC, ATTN: AMSMC-QAR-R(D), Picatinny Arsenal, NJ 07806-5000 for statistical evaluation of

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

equivalency of both methods. If the tentative Method 2 is found to be equivalent to Method 1, an ECP will be submitted for changing the tentative method to alternate method in this specification.

6.8 Submission of alternative quality conformance provisions. Unless otherwise specified in the contract, proposed alternative quality conformance provisions will be submitted by the contractor for evaluation by the technical activity responsible for preparation of this specification.

6.9 Assembly test. The rear cap and igniter container which fail the assembly test may be used again and can be assembled to different rear cap igniter container with the same interfix number. The failed rear cap and igniter container will not be considered acceptable until they pass the assembly test.

6.10 Drawings. Drawings listed in Section 2 of this specification under the heading US Army Armament Research, Development and Engineer Center (ARDEC) may also include drawings prepared by, and identified as, Edgewood Arsenal, Frankford Arsenal, Rock Island Arsenal, ARRADCOM or Picatinny Arsenal drawings. Technical data originally prepared by these activities is now under the cognizance of ARDEC.

6.11 Subject term (key word) listing.

Wrapped body
Rear cap
Closure cap
Igniter container

Custodian
Army-AR

Preparing activity:
Army-AR

(Project 1320-AC46)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER	2. DOCUMENT DATE (YYMMDD)
	MIL-C-70810 (AR)	28 May 1991

3. DOCUMENT TITLE
COMBUSTIBLE CARTRIDGE CASE ASSEMBLY PARTS NITROCELLULOSE PAPER PROCESS

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets if needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle Initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON (If applicable)	7. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY

a. NAME	b. TELEPHONE (Include Area Code)	
US ARMY ARDEC STANDARDIZATION OFFICE	(1) Commercial (201) 724-6675	(2) AUTOVON 880-6675
c. ADDRESS (Include Zip Code) ATTN: SMCAR-BAC-S PICATINNY ARSENAL, NJ 07806-5000	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340	

DD Form 1426, OCT 89 *Previous editions are obsolete.* 198/290

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:30Z
Check the source to verify that this is the current version before use.