INCH-POUND

A-A-55174

1 MARCH 1993

COMMERCIAL ITEM DESCRIPTION

COVER, BEDDING, FLAME RESISTANT

The General Services Administration has authorized the use of this Commercial Item Description in preference to Military Specification MIL-C-29126

Abstract. This Commercial Item Description covers a one size, one type, flame resistant, bedding cover intended for encasing the mattress, blankets, and pillows used on submarine bunks

Salient Characteristics. The woven or knitted cotton cloth shall be coated with polymerized or copolymerized vinyl chloride or chloroprene rubber. The slide fastener shall be aluminum and the sewing thread cotton. The cover shall be 6 feet 5 inches long, 25 inches wide, and 5-1/2 inches high. The slide fastener shall be sewn 1 inch from the top and enclose the 2 short sides and 1 long side.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Defense Personnel Support Center, Clothing and Textiles Directorate, Attn: DPSC-FSSD, 2800 South 20th Street,Philadelphia, PA 19101-8419, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A

FSC 7210

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

Material.

Cloth. The base cloth, which may be bleached or unbleached, shall be woven or knitted from 100% cotton yarn and coated with polymerized or copolymerized vinyl chloride or chloroprene rubber and shall not contain materials containing mercurial compounds or water soluble ingredients. The cloth to be coated with chloroprene rubber shall contain not more than 0.003 percent copper and 0.0015 percent manganese. A maximum of 5.0 percent styrene butadiene rubber or natural rubber may be used for masterbatch purposes. The vinyl coated cloth shall be finished with a smooth or finely embossed surface simulating the appearance of top grain leather. The surface of the rubber coated cloth shall be finished smooth. The finished coating shall be pigmented to approximate color chip Green 24449 of FED. STD. 595 except that the finish may be gloss, semi-gloss, or lusterless.

Table I - Base and Coated Cloth Requirements

Characteristic	Requirement	Test Method	
Base Cloth			
Weight, oz/sq.yd. (grams/sq m)	8 to 11 (271.2 to 372.9)	ASTM D3776 Opt C	
Weave or knit	Plain or twill	Visual	
Tape for Slide Fasteners			
Width	0.75" (+1/16" -1/32")	Visual	
Thickness	0.05"	ASTM D1777	
Coated cloth			
Weight, oz/sq.yd. (grams/sq.m)	24 to 26 (813.6 to 881.4)	ASTM D3776 Opt C	
Breaking strength, lbs. (N) - minimum			
Initial - Warp or wales	125 (556.2)	ASTM D5034	
- Filling or courses	100 (445.0)	ASTM D5034	
After Heat Aging - Warp or wales	100 (445.0)	FED STD 191-5850	5/
Filling or courses	75 (333.7)	FED STD 191-5850	
Adhesion of coating - minimum lbs/2 inch width (N/m)	10 (1750.0)	ASTM D2724	6/
Abrasion resistance - maximum double rubs	1500	ASTM D4157	2/ 9/
Flame resistance - maximum			
Flame time, seconds	2.0	FED STD 191-5903	
Char length, in (cm)	3.5 (8.9)	FED STD 191-5903	
Hydrostatic resistance - minimum lbs/sq.inch (Pa)	100 (689,400)	AATCC 127-1985	7/
Resistance to mildew	Shall not support mildew growth		
Resistance to accelerated aging (rubber coated cloth only)	Pass	FED STD 191-5852	1/
Resistance to low temperature	Shall not crack	FED STD 191-5874	8/
Resistance to oil	Pass		4/ 10/

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

Resistance to light	Pass	AATCC 16A 1990 1/
Resistance to crocking	Good	AATCC 8-1988
Resistance to blocking - maximum Scale rating	No. 2	FED STD 191-5872
Volatility, percent loss - maximum (vinyl coated cloth only)	8.0	11/ FED STD 406-6081

1/ Exposed specimens shall not become soft, tacky, stiff, or cracked when folded over a 1/8 inch diameter rod.

2/ The specimen shall fail if visible loose fibers of the base cloth are exposed in the center one inch of the abraded portion.

3/ A certificate of compliance shall be submitted and accepted for this requirement.

4/ Specimen shall show no signs of oil permeating the outside bottom of coated cloth basin.

5/ The specimens shall be exposed for 7 days at 70° C (158° F) ±2°.

6/ When the coating can be seperated from the base cloth without the aid of a solvent or adhesive, the coating may be peeled off dry.

7/ The coated side shall face the water.

8/ Specimens shall be subjected to a temperature of -18° C (0° F) ± 4° for 2 hours. Hydrostatic test is not required.

9/ Abrasion. The resistance to abrasion shall be determined as specified in ASTM test method D4157 with the following exceptions:

a. The long dimension of the specimen shall be parallel to the warp or direction of the sample.
b The tension of the specimen shall be 6 pounds (2.7 Kg)
c. The abrader shall be silicon-carbide cloth 240 grit.
d. The wear on the coating shall be observed after 1500 double rubs. The abradent shall be changed after each 250 double rubs and the test continued.
e. Three specimens shall be tested from each sample unit.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

10/ Oil resistance. An 8 by 8 inch (20.3 by 20.3 cm) specimen shall be placed on a wood frame. The inside dimension of the wood frame shall be 6 by 6 inches (15.2 by 15.2 cm) by 1 inch (2.5 cm). The coated cloth shall be inserted with the coated side up. The specimen shall be forced into the frame by a wooden block 5 3/4 by 5 3/4 inches (14.6 by 14.6 cm) by 3/4 inch (1.9 cm) with rounded corners to form a basin of uniform depth. The edges of the specimen shall be tacked to the frame and the block removed. Oil conforming to type IV of TT-S-735 shall be poured into the basin as rapidly as possible to a depth of 1/2 inch (1.3 cm). After the oil has been in the basin for four hours, the outside bottom of the specimen forming basin shall feel dry and there shall be no indication that the oil has permeated the coated cloth

11/ Volatility. The volatile loss of the coated cloth shall be determined in accordance with test method 6081 of FED-STD-406, except that two 2 by 2 inch (5.1 by 5.1 cm) specimens shall be heated at 104° C (220° F) ±4° for a period of 24 hours.

Fasteners, slide The slide fasteners to be used in the construction of the bedding cover shall be made of aluminum and shall be a non-separating, non-reversible type without lock conforming to Type style 2, size MHS of V-F-106. The width of a single tape shall be 3/4 inch (±1/16) and the thickness of tape shall be 0.050 inch maximum. The tape portion of the slide fastener shall be water-resistant and mildew-resistant treated and dyed to approximate the shade of the basic material.

Thread. The thread used in the construction of the bedding cover shall be 150 Tex (3,307 to 3,674 yards per pound), 4 ply, 100% cotton yarn with a 6.8 pounds minimum breaking strength and approximate the shade of the basic material. It shall be water-resistant and mildew-resistant treated.

TABLE II - Thread tests

Characteristic	Test method	
Fiber identification		1/
Shade match	Visual	2/
Colorfastness to:		3/ 4/
Laundering (after 3 cycles)	AATCC 61- 1986	
Light	AATCC 16- 1988	
Wet drycleaning	AATCC 132-1985	
Perspiration	AATCC 15- 1985	
Weathering	FED STD 191-5671	
Finish type		1/
Twist direction	ASTM D1423	5/
Number of plies	Visual	6/
Yards per pound	ASTM D204	7/
Breaking strength	ASTM D2256	8/

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

1/ Unless otherwise specified, a certificate of compliance shall be submitted and will be acceptable for the stated requirement.

2/ The color of the dyed thread shall match the standard sample when viewed under filtered tungsten lamps which approximate artificial daylight having a correlated color temperature of 7500 ±200K, with illumination of 100 ±20 foot candles, and shall be a good match to the standard sample under incandescent lamplight at 2300 ±200K.

3/ Two to six grams of the thread, so held together to form a unit for testing. Unless otherwise specified in the procurement document, the laundering cycle of the Launder-O-Meter or similar machine shall be 30 minutes and the temperature of the container and its contents shall be maintained at 100° ±4° F (38° ±2° C). On the color transfer cloth evaluation, only the stain on the cotton fibers of the color transfer cloth shall be evaluated.

4/ The specimens must be dried after each of the 3 laundering cycles. Unless otherwise specified, the thread shall show "good" colorfastness to laundering (after 3 cycles) light, perspiration wet drycleaning, and weathering.

5/ The direction of the final twist shall be "Z".

6/ One determination and the result reported as "pass" or "fail"

7/ In case of dispute, the length per pound of the thread shall be determined after removal of finish. The sample of thread shall be wet drycleaned in accordance with Method 5622 of FED STD 191 (disregarding references to the standard sample). Excess solvent shall be removed by wringing or centrifuging. The sample shall then be rinsed in distilled water at 120° to 160° F and dried at a temperature not exceeding 180° F. The dried sample shall then be conditioned for a minimum of 4 hours prior to evaluation for shade match.

8/ Except that the five determinations shall be made on each sample unit.

Label/marking Heat transfer markings shall be applied using a dry-heat transfer process (decalcomania) or directly applied using a black marking medium. The label inscription shall be positioned on the inside bottom half of the bedding cover adjacent to the zippered side. It shall be centered, and contain the following information:

Cover, Bedding, Flame Resistant
Contract No: DLA 100-00-0-0000 (example)
Stock No: 7210-00-000-0000 (example)
Name of Contractor:

Construction. The cover shall be 6 feet 5 inches long, 25 inches wide,

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

and 5 1/2 inches high. The slide fastener shall be sewn 1 inch from the top and enclose the 2 short sides and 1 long side. The stitches per inch for sewing the cover shall be not less than 6 nor more than 8. (see attached figures 1 and 2). All thread ends shall be trimmed to 1/4 inch maximum length.

Workmanship. After completion, the finished bedding cover shall be thoroughly cleaned, and all loose thread, lint, and foreign matter removed. The finished bedding cover shall conform to the quality established by this Commercial Item Description. The occurence of defects shall not exceed the applicable acceptable quality levels.

Product Demonstration Model. When required, offerers shall submit bedding covers of their intended production. The Product Demonstration Model will consist of two units independently developed. Product Demonstration Models will be analyzed and evaluated by the government. Evaluation criteria and basis for award are contained in the solicitation. Product Demonstration Models will be retained by the government. One (1) Product Demonstration Model approved by DPSC under the resultant contract will serve as a manufacturing standard for the corresponding production items delivered under this contract. Offerers are advised that the Product Demonstration Model does not relieve the successful offerer of his responsibility to perform in accordance with the Commercial Item Description specified above.

Quality Assurance Provisions. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the contractor may use his own or any other facilities suitable for performance of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and service conform to prescribed requirements. The supplier is responsible for assuring the product conforms to the requirements. Bedding cover lots will be inspected to determine conformance with the Commercial Item Description and the successful offerer's technical proposal as negotiated. Acceptability of bedding cover lots will be determined by the use of "Sampling Procedures and Tables for Inspection by Attributes", ANSI/ASQC Z1.4, published by the American Society for Quality Control. Sampling procedures will be designated by the Government at the time of award. The sample unit is one bedding cover. The inspection levels and the acceptable quality levels, expressed in defects per 100 units, shall be as follows:

	Inspection level	AQL's
Visual Examination	II	4.5
Dimensional Examination	S-3	1.5

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

Defects. The bedding cover shall be examined for the following defects: any hole, cut, tear, color not as specified; any spot or stain (outside); thread ends not removed; label missing, incorrect, or illegible; measurement of item not as specified. Any evidence of coating delamination, soft coating i.e. not fully cured, any brittle or excessive coating area. Any seam twisted, puckered, pleated, or open. Improper number of stitches per inch, tight or loose stitch tension. Slide fastener omitted, malformed, damaged, not type or style specified and any variance not otherwise classified herein but at variance with the product demonstration model.

Packaging Examination. The fully packaged end items shall be examined for the defects listed below. The lot size shall be expressed in units of shipping containers. The sample unit shall be one shipping container fully packaged. The inspection level shall be S-2 and the acceptable quality level (AQL), expressed in terms of defects per hundred units, shall be 1 5

Examine	Defect
Marking (exterior and interior)	Omitted; incorrect; illegible; of improper size, location, or method of application
Materials	Any component missing, damaged, or not as specified
Workmanship	Inadequate application of components, such as: incomplete closure of container flaps, loose strapping, improper taping, or inadequate stapling
Content	Number of items per container is more or less than required
	NSN shown on one or more items not as specified on shipping container
Palletization	Length, width, or height exceeds specified maximum requirements
	Pallet type not as specified
	Load not bonded as specified

Testing of the End Item The methods of testing as listed in Table I shall be followed. The requirements specified in Table I apply to the average of determinations made on a sample unit for test purposes as specified in the applicable test method. The lot size shall be expressed in units of 1 linear yard (91.4 cm). The sample unit for test purposes shall be 2 yards (183 cm), full width of finished coated fabric. The sample size shall be in accordance with Table III. The lot shall be unacceptable if one or more units fail to meet any test requirement.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

Table III - Sample size for testing

Lot size (yards)	Sample size
800 or less	2
801 through 22,000	3
22,001 and over	5

Preservation, Packing, and Marking The preservation, packing, and marking shall be as specified in the contract or order.

NOTES

Source of Government documents. Copies of Military and Federal documents are available from:

Standardization Documents Order Desk
Building 4D
700 Robbins Avenue
Philadelphia, PA 19111-5094

Rules and Regulations under the Textile Fiber Products Identification Act is available from:

Federal Trade Commission
Washington, DC 20580

Source of Non-Government documents.

ANSI/ASQC Z1.4 - Sampling Procedures and Tables for Inspection by Attributes

(Applications for copies should be addressed to American National Standards Institute, 1430 Broadway, New York, NY 10018-3308)

ASTM tests

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103)

AATCC tests

(Application for copies should be addressed to American Association of Textile Chemists and Colorists (AATCC), P. O. Box 12215, Triangle Park, NC 27709-2215)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

Custodian:
Navy - NU

Review Activity:
Navy - SH


Civil Agency Coordinating Activity
GSA-FSS


Preparing Activity:
DLA-CT

Project No. 7210-0311

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

2	SIDE
3	BOTTOM
4	EDGE
5	FASTENER, SLIDE, 10-*

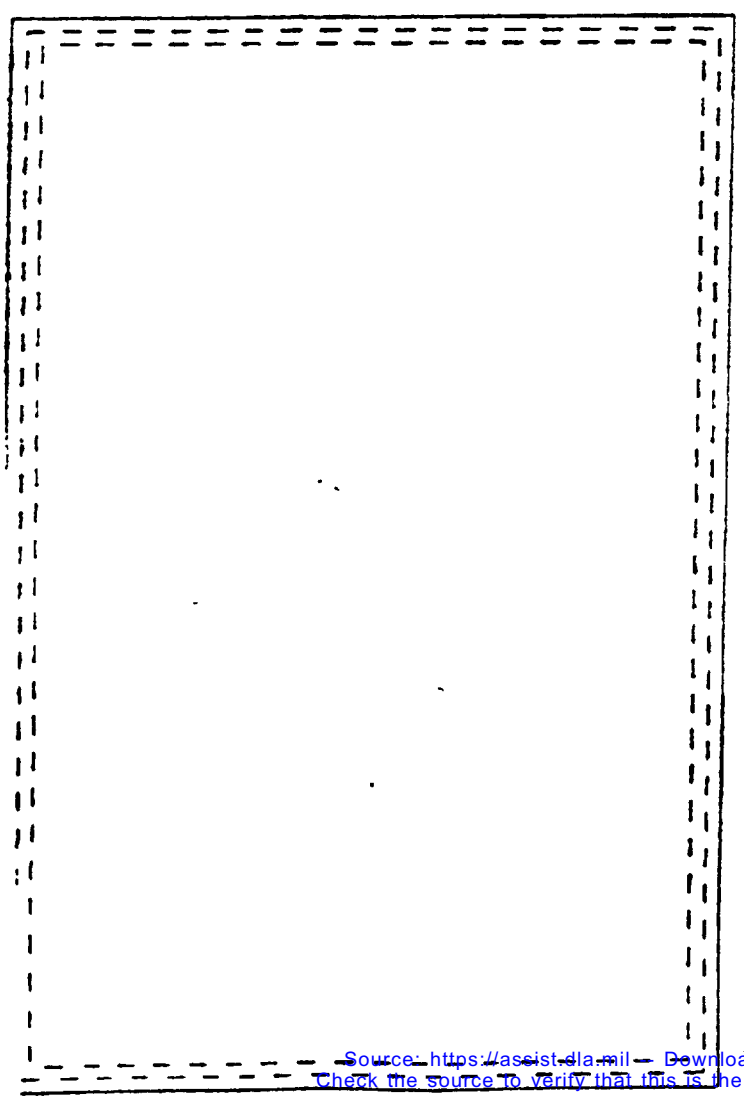

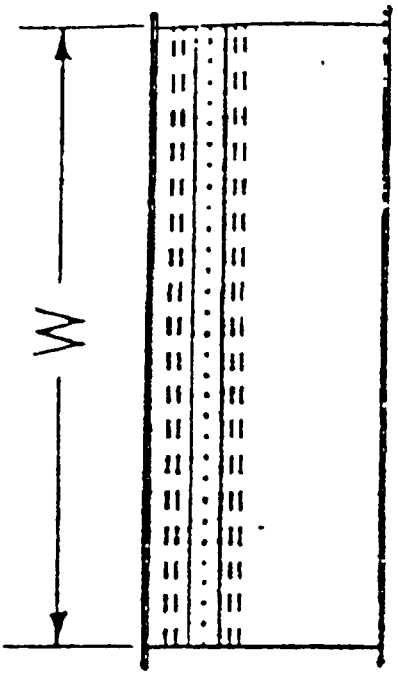

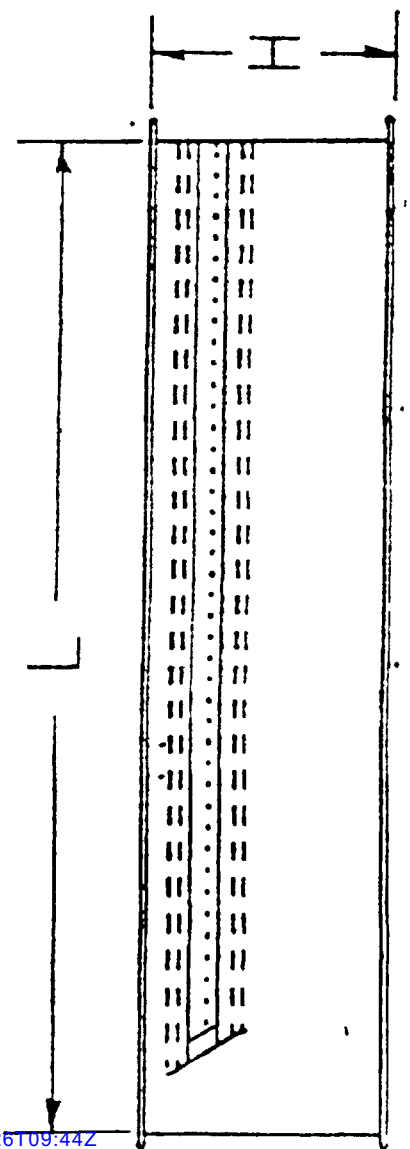


FIGURE 1 - COVER, BEDDING

Source: https://assist.dla.mil — Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

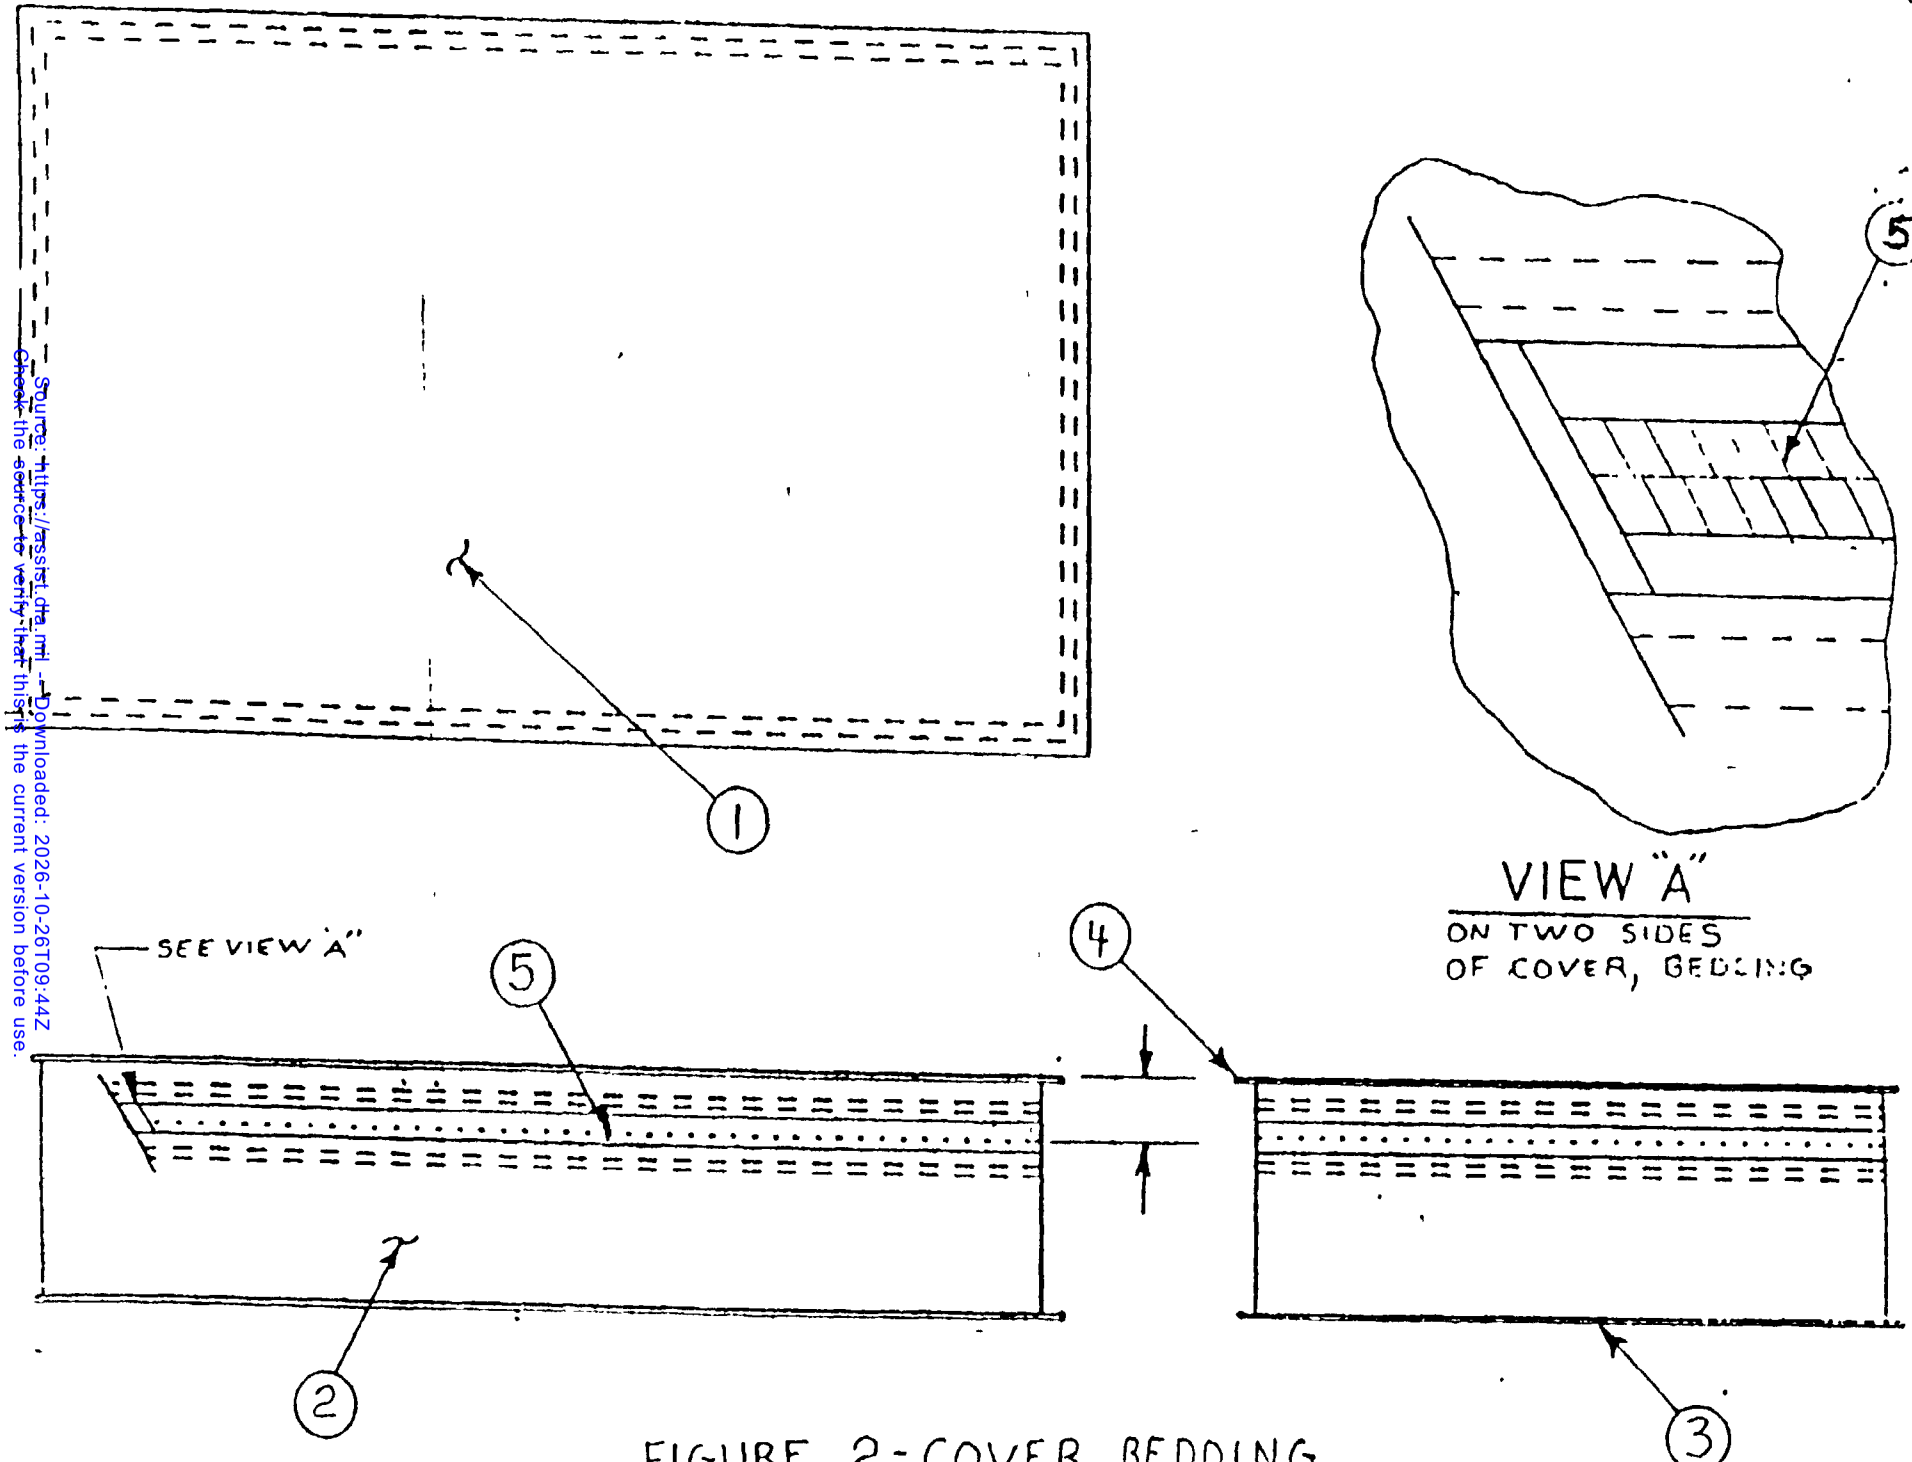


FIGURE 2 - COVER, BEDDING

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE. This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1 DOCUMENT NUMBER	2 DOCUMENT DATE (YYMMDD)
	A-A-55174	93/3/1

3 DOCUMENT TITLE

COVER, BEDDING, FLAME RESISTANT

4 NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5 REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle Initial)	b. ORGANIZATION
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON (If applicable)
	7. DATE SUBMITTED (YYMMDD)

8 PREPARING ACTIVITY

a NAME	b TELEPHONE (Include Area Code) (1) Commercial	(2) AUTOVON
DLA - CT	(215) 737-8105	(DSN) 444-8105
c ADDRESS (Include Zip Code) DEFENSE PERSONNEL SUPPORT CENTER 2800 S. 20th St. (DPSC-FSSD/Bldg. 12-3-D) Philadelphia, PA 19101-8419	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340	

Source: https://assist.dla.mil/ - Downloaded: 2026-10-26T09:44Z
Check the source to verify that this is the current version before use.