NOT MEASUREMENT SENSITIVE

TT-P-2760A
30 DECEMBER 1994
SUPERSEDING
TT-P-2760
22 OCTOBER 1990

FEDERAL SPECIFICATION

PRIMER COATING: POLYURETHANE, ELASTOMERIC, HIGH-SOLIDS

The General Services Administration has authorized the use of this federal specification by all Federal Agencies

1. SCOPE

1.1 Scope. This specification covers the requirements for two types (see 1.2.1) and two classes (see 1.2.2) of low volatile organic compound (VOC) content (see 3.4.2), solvent-borne, elastomeric, polyurethane primer coatings. These primer coatings are formulated primarily for spray application, are compatible with polyurethane topcoats, and are intended for use on aircraft and other equipment subjected to structural flexing at low temperatures. The maximum volatile organic compound (VOC) content of the admixed primer coatings is 340 grams per liter (g/l) or 2.8 pounds per gallon (lbs/gal). Unless a specific type and/or class is referenced in the contract or purchase order, TT-P-2760A, Type I, Class C is the default. Class N may not be substituted for Class C, unless authorization for its use is given by the procuring activity or engineering authority for the system or item to which the primer coating is to be applied. See 6.13 for the cross-reference of classes to previous revisions of this specification.

1.2 Classification. The primer coatings shall be of the following types and classes as specified (see 6.2):

1.2.1 Type. The primer coatings consist of the following types:

Type I - Standard pigments
Type II - Low infrared reflective pigments

1.2.2 Class. The primer coatings consist of the following classes:

Class C - Strontium chromate based corrosion inhibitors
Class N - Non-chromate based corrosion inhibitors

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Systems Standardization, Code 4.1.11B120-3, Naval Air Warfare Center Aircraft Division, Highway 547, Lakehurst, NJ 08733-5100, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 8010
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

1.3 Part numbers. Part numbers, for cataloging purposes, may be assigned in accordance with 6.7.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. The following specifications and standards form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DoDISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDERAL

QQ-A-250/4	-	Aluminum Alloy 2024, Plate and Sheet
QQ-A-250/5	-	Aluminum Alloy Alclad 2024, Plate and Sheet
QQ-A-250/12	-	Aluminum Alloy 7075, Plate and Sheet
PPP-P-1892	-	Paint, Varnish, Lacquer and Related Materials: Packaging, Packing and Marking

MILITARY

MIL-C-5541	-	Chemical Conversion Coatings on Aluminum and Aluminum Alloys
MIL-C-8514	-	Coating Compound, Metal Pretreatment, Resin-Acid
MIL-A-8625	-	Anodic Coatings, for Aluminum and Aluminum Alloys
MIL-L-23699	-	Lubricating Oil, Aircraft Turbine Engine, Synthetic Base, NATO Code Number O-156
MIL-C-38334	-	Corrosion Removing Compound, Prepaint, for Aircraft Aluminum Surfaces
MIL-R-81294	-	Remover, Paint, Epoxy, Polysulfide and Polyurethane Systems
MIL-T-81772	-	Thinner, Aircraft Coating
MIL-H-83282	-	Hydraulic Fluid, Fire Resistant, Synthetic Hydrocarbon Base, Aircraft, Metric, NATO Code Number H-537
MIL-C-83286	-	Coating, Urethane, Aliphatic Isocyanate, for Aerospace Applications
MIL-C-85285	-	Coating: Polyurethane, High-Solids

STANDARDS

FEDERAL

FED-STD-141	-	Paint, Varnish, Lacquer and Related Materials; Methods of Inspection, Sampling and Testing

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

FED-STD-313 - Material Safety Data, Transportation Data and Disposal Data for Hazardous Materials Furnished to Government Activities
FED-STD-595 - Colors Used in Government Procurement

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes

(Unless otherwise indicated, copies of federal and military specifications and standards are available from the Defense Printing Service, Standardization Documents Order Desk, Attn: DODSSP - Customer Service, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094.)

2.1.2 Other Government documents. The following other Government documents and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues are those cited in the solicitation.

CODE OF FEDERAL REGULATIONS (CFR)

DEPARTMENT OF LABOR

29 CFR 1910.1200 - Occupational Safety and Health Standards - Hazard Communications

DEPARTMENT OF TRANSPORTATION

49 CFR 171-178 - Subchapter C - Hazardous Materials Regulations

(Application of copies of the Code of Federal Regulations (CFR) should be addressed to the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.)

2.2 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are Department of Defense adopted are those listed in the issue of the DoDISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DoDISS are the issues of the documents cited in the solicitation (see 6.2).

AMERICAN NATIONAL STANDARDS INSTITUTE (ANSI)

ANSI-Z129.1 - American National Standard for the Precautionary Labeling of Hazardous Industrial Chemicals

(Application for copies should be addressed to the American National Standards Institute, Inc., 1430 Broadway, New York, NY 10018.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

ASTM-B117	-	Standard Test Method of Salt Spray (Fog) Testing
ASTM-D522	-	Mandrel Bend Test of Attached Organic Coatings
ASTM-D882	-	Standard Test Methods for Tensile Properties of Thin Plastic Sheeting
ASTM-D1200	-	Standard Test Method for Viscosity of Paints, Varnishes and Lacquers by Ford Viscosity Cup
ASTM-D1210	-	Standard Test Method for Fineness of Dispersion of Pigment - Vehicle Systems
ASTM-D1296	-	Standard Test Method for Odor of Volatile Solvents and Diluents
ASTM-D1640	-	Standard Test Method for Drying, Curing, or Film Formation of Organic Coatings at Room Temperature
ASTM-D1649	-	Standard Specification for Strontium Chromate Pigment
ASTM-D2247	-	Standard Practice for Testing Water Resistance of Coatings in 100% Relative Humidity
ASTM-D2370	-	Standard Test Method for Tensile Properties of Organic Coatings
ASTM-D2803	-	Standard Test Method for Filiform Corrosion Resistance of Organic Coatings on Metal
ASTM-D3335	-	Standard Test Method for Low Concentrations of Lead, Cadmium, and Cobalt in Paint by Atomic Absorption Spectroscopy
ASTM-D3718	-	Standard Test Method for Low Concentrations of Chromium in Paint by Atomic Absorption Spectroscopy
ASTM-D3924	-	Standard Specification for Standard Environment for Conditioning and Testing Paint, Varnish, Lacquer, and Related Materials
ASTM-D3960	-	Standard Practice for Determining Volatile Organic Compound (VOC) Content of Paints and Related Coatings
ASTM-E275	-	Standard Practice for Describing and Measuring Performance of Ultraviolet, Visible, and Near-Infrared Spectrophotometers

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Nongovernment standards and other publications are normally available from the organizations which prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Qualification. The coating furnished under this specification shall be products which are authorized by the qualification activity for listing on the applicable Qualified Products List (QPL) at the time set for award of contract (see 4.3 and 6.4). Any change in the formulation of a qualified product will necessitate its requalification. The material supplied under contract shall be identical, within manufacturing tolerances, to the product receiving qualification.

3.2 Material. Materials used to manufacture coatings supplied under this specification shall be of such a quality as to produce coatings conforming to the requirements of this specification. Chlorinated solvents are prohibited from the formulation of this coating. When tested in accordance with ASTM D3335 (see 4.6 and Table II), no component of the coating shall contain cadmium, cadmium compounds, or more than 0.06 percent (%) by weight of lead metal or lead compounds. Class N primer coating shall not contain chromium (see 3.4.1.2).

3.3 Toxicity. The manufacturer shall certify (see 6.3) that the coatings supplied under this specification have no adverse effect on the health of personnel when used for its intended purpose and with the precautions listed in 5.2.1. A Material Safety Data Sheet (MSDS) shall be prepared and submitted in accordance with FED-STD-313. The MSDS shall also meet the requirements of 29 CFR 1910.1200 (see 6.6). Questions pertinent to the effect(s) of these coatings on the health of personnel using them shall be referred by the procuring activity to the appropriate medical service, who will act as its adviser.

3.4.1 Pigments.

3.4.1.1 Class C. The pigment portion of the Class C primer coating shall contain: strontium chromate, as the corrosion inhibitor and conforming to ASTM D1649; siliceous extenders; and other pigments, as required.

3.4.1.2 Class N. The pigment portion of the Class N primer coating shall contain: non-chromate corrosion inhibitors; siliceous extenders; and other pigments, as required. When tested in accordance with ASTM D3718 (see 4.6 and Table II), the Class N primer coating shall not contain chromium.

3.4.2 Volatile organic compound (VOC) content. The maximum VOC content of the primer coating at application shall be 340 g/l (2.8 lbs/gal), when tested in accordance with ASTM D3960 (see 4.6 and Table II). The resistivity of the solvents shall be suitable for electrostatic spray application.

3.4.3 Thinner compatibility. The admixed primer coating shall be compatible with thinner conforming to MIL-T-81772, Type I (see 6.13). All

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:19Z
Check the source to verify that this is the currentversion before use.

thinners used with this coating must be "urethane grade", with a water content of less than 0.05% by weight.

3.5 Physical properties - Liquid.

3.5.1 Condition in container. The primer coating, after standing without agitation for a minimum of 14 days, shall be capable of being mixed by hand by vigorously stirring with a paddle, and, within 5 minutes, shall be smooth, homogeneous and pourable, when tested in accordance with 4.6.1. The primer coating shall be free of grit, skin, seeds, lumps, foreign contaminants, abnormal thickening or livering, and shall not exhibit pigment floatation or excessive settling that cannot be reincorporated to a smooth, homogeneous state by mixing with a hand paddle. The containers shall exhibit no deformation due to internal pressure, when examined in accordance with 4.4.3.2.

3.5.2 Storage stability. The primer coating, as packaged by the manufacturer, shall meet all requirements specified herein after storage for a minimum of one year from the date of manufacture, at a daily ambient air temperature of 35° to 115°F (1.7° to 46°C).

3.5.3 Accelerated storage stability. The primer coating, as packaged by the manufacturer, shall meet all requirements specified herein after storage for 14 days at 140° ± 5°F (60° ± 3°C), when tested in accordance with 4.6.2.

3.5.4 Color.

3.5.4.1 Type I. The color of the Type I primer coating shall be the natural color of the corrosion inhibiting pigments used, with the exception that tinting to a darker shade is permitted to improve hiding power.

3.5.4.2 Type II. The color of the Type II primer coating shall be dark green.

3.5.5 Odor. The odor of the admixed coating, wet or dry, shall be characteristic of the thinners used and shall not be obnoxious, when tested in accordance with ASTM D1296 (see 4.6 and Table II). In addition, the air-dried film shall retain no residual odor 48 hours after application.

3.5.6 Viscosity. The viscosity of the admixed primer coating shall not exceed 30 seconds through a number 4 Ford Cup, when tested in accordance with ASTM D1200 (see 4.6 and Table II).

3.5.7 Pot life. The viscosity of the admixed primer coating shall not exceed 60 seconds through a number 4 Ford Cup after storage in a closed container at room temperature for 4 hours, when tested in accordance with ASTM D1200 (see 4.6 and Table II).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

3.5.8 Fineness of grind. The fineness of grind of the primer coating shall be a minimum of 5 on the Hegman scale when tested in accordance with ASTM D1210 (see 4.6 and Table II).

3.6 Physical properties - Film.

3.6.1 Surface appearance. The admixed primer, applied to "A" test panels (see 4.5) in accordance with 4.5.1, shall not sag, run, or streak, and shall dry to a smooth, uniform surface free from grit, seeds, craters, blisters, and other irregularities after air drying for 24 hours.

3.6.2 Drying time. The admixed primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1, and tested in accordance with ASTM D1640 (see 4.6 and Table II), shall be tack-free within 5 hours and dry-hard within 8 hours.

3.6.3 Lifting. When separately applied to primer coating that has air-dried for 1, 4, and 18 hours, the polyurethane topcoat (see 4.5.2) shall exhibit no lifting or other film irregularity, when tested in accordance with 4.6.3.

3.6.4 Adhesion. The primer coating, applied to "C" test panels (see 4.5) in accordance with 4.5.1, shall not peel away from the substrate after immersion in water for 24 hours, when tested in accordance with FED-STD-141, Method 6301 (see 4.6 and Table II).

3.6.5 Flexibility. The applied primer coating shall meet the requirements of 3.6.5.1 and 3.6.5.2 before and after exposure for four hours to a temperature of 350° ± 5°F (177° ± 3°C).

3.6.5.1 Ambient flexibility. The primer coating, applied to "B" test panels (see 4.5) in accordance with 4.5.1, shall exhibit a minimum impact elongation of 60% when tested in accordance with 4.6.4.1 at 21° ± 5°C (70° ± 10°F) and 50 ± 5% relative humidity (RH).

3.6.5.2 Low-temperature flexibility. The primer coating, applied to "B" test panels (see 4.5) in accordance with 4.5.1, shall exhibit no cracking when bent over a 1/8 inch (in.) (3.2 millimeter (mm)) mandrel at -60° ± 5°F (-51° ± 3°C), in accordance with 4.6.4.2.

3.6.6 Tensile properties. A free-film of the primer coating, prepared and tested in accordance with ASTM D2370 (see 4.6 and Table II), shall have a minimum tensile strength of 2,000 lb/in^2 and a minimum elongation-at-break of 80%. The gage length shall be 3 to 5 in. (76 to 125 mm). ASTM D882 is used to determine initial grip separation and rate of elongation with respect to elongation-at-break.

3.6.7 Infrared reflectance (Type II primer coating only). The Type II primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1 shall have a maximum total reflectance (specular and diffuse) of 10%

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:19Z
Check the source to verify that this is the current version before use.

throughout the range of 450 to 2700 nanometers (nm), when tested in accordance with 4.6.5.

3.6.8 Strippability. The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1, shall have a minimum of 90% of the primer coating stripped within 60 minutes at room temperature (see 4.6) with remover conforming to MIL-R-81294, Type I, when tested in accordance with 4.6.6.

3.7 Resistance properties.

3.7.1 Water resistance. The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1 and topcoated in accordance with 4.5.2, shall withstand immersion for 4 days in distilled water maintained at 120° ± 5°F (49° ± 3°C) without exhibiting any softening, wrinkling, blistering, loss of adhesion, or other deficiency when tested in accordance with 4.6.7.

NOTE: Some strontium chromate pigments may contain soluble impurities that cause blistering in the water resistance test. Blistering of this type is acceptable.

3.7.2 Humidity resistance.

3.7.2.1 Primer coating only. The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1, and tested in accordance with ASTM D2247 at 120° ± 5°F (49° ± 3°C) and 95 ± 5% RH for a period of 30 days. The coating shall not exhibit any softening, wrinkling, blistering, loss of adhesion, or other coating deficiency.

3.7.2.2 Topcoated primer coating. The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1, shall be topcoated in accordance with 4.5.2, and tested in accordance with ASTM D2247 at 120° ± 5°F (49° ± 3°C) and 95 ± 5% RH for a period of 30 days. The coating shall not exhibit any softening, wrinkling, blistering, loss of adhesion, or other coating deficiency.

3.7.3 Fluid resistance. The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1 shall exhibit no softening, blistering, loss of adhesion or other defects after immersion for 24 hours, in accordance with 4.6.8, in the following: lubricating oil conforming to MIL-L-23699, maintained at 250° ± 5°F (121° ± 3°C); and hydraulic fluid conforming to MIL-H-83282, maintained at 150° ± 5°F (65.5° ± 3°C). Discoloration of the coating is acceptable.

3.7.4 Solvent resistance (cure). The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1, shall withstand repeated (50 passes) rubbing with a terrycloth rag soaked in methyl ethyl ketone (MEK) solvent without removal when tested in accordance with 4.6.9. Rubbing through to bare substrate constitutes failure of the primer coating to properly cure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

3.7.5 Corrosion resistance.

3.7.5.1 Salt spray.

3.7.5.1.1 Aluminum test panel. The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1 shall exhibit no blistering, lifting of the coating system, or substrate corrosion after exposure to 5% salt spray for 2000 hours when tested in accordance with 4.6.10.1.1.

3.7.5.1.2 Aluminum/graphite-epoxy test panel. The primer coating, applied to the aluminum/graphite-epoxy test panel (see Figure 1) shall exhibit no pitting greater than 0.039 in. (1.0 mm) after exposure to 5% salt spray for 500 hours, when tested in accordance with 4.6.10.1.2.

3.7.5.2 Filiform. The primer coating and topcoat, applied to "D" test panels (see 4.5) in accordance with 4.5.1 through 4.5.2, shall exhibit no filiform corrosion extending beyond 1/4 in. (6.4 mm) from the scribe lines when exposed to 12 normal (N) hydrochloric acid (HCl) for one hour and then placed in a humidity cabinet maintained at 104° ± 3°F (40° ± 1.7°C) and of 80 ± 5% RH for 1000 hours, in accordance with 4.6.10.2. The majority of the filaments shall be less than 1/8 in. (3.2 mm) in length.

3.8 Working properties.

3.8.1 Mixing and dilution. The primer coating shall blend homogeneously when mixed by a suitable mechanical mixer, and shall not separate into visually distinct layers within one hour, even when appropriately diluted (see 6.13) with thinner conforming to MIL-T-81772, Type I.

3.8.2 Application. The admixed primer coating shall be capable of being applied by conventional, airless, high volume-low pressure (HVLP), and electrostatic spray equipment. When tested after initial admix and after the admixed primer coating has been stored in a closed container maintained at room temperature (see 4.6) for four hours, in accordance with 4.6.11.1, application shall yield a smooth, uniform film with no runs or sags at a dry-film thickness of 1.5 to 2.0 mils (38 to 51 microns (μm)).

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facility suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to accept defective material.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.3).
b. Quality conformance inspection (see 4.4).

4.3 Qualification inspection. Qualification inspection shall consist of all requirements and tests specified in section 3.

4.3.1 Qualification samples. Qualification test samples shall consist of a minimum of one quart of each component of the primer coating. The material shall be furnished in containers of the Type to be used in filling contract orders. Samples shall be identified as follows and forwarded to the laboratory designated in the letter of authorization (see 6.4).

- Qualification test samples.
- Specification TT-P-2760A, Type I or II, and Class C or N (as applicable)
- PRIMER COATING: POLYURETHANE, ELASTOMERIC, HIGH-SOLIDS
- Manufacturer's name and product number
- Submitted by (name and date) for qualification testing in accordance with authorization (reference authorizing letter)

4.3.2 Test report. In addition to the qualification test samples, the manufacturer shall furnish to the qualification activity: (a) one copy of the MSDS (see 3.3); (b) a certified test report showing that the material conforms to the requirements of this specification; and (c) certification that the following chemicals were not used in the formulation of this coating: methylene chloride, trichloroethane and trichlorotrifluoroethane.

4.3.3 Retention of qualification. In order to obtain qualification of products approved for listing on the Qualified Products List (QPL), the manufacturer shall verify by certification to the qualifying activity that its product(s) comply with the requirements of this specification. Unless otherwise specified by the qualifying activity, the time of periodic verification by certification shall be in two-year intervals from the date of original qualification. The certification action shall be initiated by the qualifying activity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

4.4 Quality conformance inspection.

4.4.1 Lot formation. A lot shall consist of all coating of the same color, manufactured at one time from one batch, forming part of one contract, and submitted for acceptance. A batch shall consist of all coating material manufactured during one continuous operation.

4.4.2 Batch data. When required (see 6.2), the manufacturer shall furnish with each batch and/or lot a certified test report (see 6.3) showing that the material has satisfactorily passed the quality conformance inspection (see 4.4.3). When required (see 6.2), the manufacturer shall certify that there has been no formulation or process change from that which resulted in the production of the qualification inspection sample.

4.4.3 Examinations.

4.4.3.1 Tests. The quality conformance examination shall consist of all tests specified in section 3, with the exception of storage stability (3.5.2), accelerated storage stability (3.5.3), tensile properties (3.6.6), strippability (3.6.8), humidity resistance (3.7.2 - 3.7.2.2), and corrosion resistance (3.7.5 - 3.7.5.2). There shall be no failures. Samples for tests shall consist of one complete, unopened kit selected at random from each batch. Containers shall only be opened when being tested. Failure shall result in rejection of the batch and may justify removal of the product from the QPL (see 4.3).

4.4.3.2 Examination of packaging and marking. An examination shall be made to ensure compliance with section 5. Samples shall be selected from each lot in accordance with MIL-STD-105, inspection level S-2. The lot size for this examination shall be the number of kits fully prepared for delivery. If palletization is required (see 4.4.3.3 and 6.2), kits fully prepared for delivery shall be examined prior to being palletized. Acceptance criteria shall be as specified in the contract or purchase order (see 6.2i and 6.9). Defects are defined in the following list.

Examine	Defect
Packaging	Containers not as specified, closures not accomplished by specified or required methods or materials. Leakage or seepage of contents. Non-conforming component, component missing, damaged or otherwise defective. Rusted, bulged or distorted container.
Marking	Data, including directions for use, omitted, illegible, incorrect, incomplete, or not in accordance with contract requirements.

4.4.3.3 Visual inspection of filled containers. Samples selected at random for examination in accordance with 4.4.3.2 shall be examined for proper filling and weight, and excessive internal pressure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

4.4.3.4 Examination for palletization. If palletization is required (see 6.2h), an examination shall be made to ensure that there are no defects. Defects are as defined in the following list.

Examine	Defect
Finished dimension	Length, width or height exceeds specified maximum requirement.
Palletization	Not as specified. Pallet pattern not as specified. Interlocking of loads not as specified. Load not bonded with required straps as specified.
Weight	Exceeds maximum load limits.
Marking	Omitted, incorrect, illegible, of improper size, location, sequence or method of application.

4.4.4 Rejection and retest. Failure in any quality conformance test shall result in the rejection of that batch and shall constitute sufficient justification for removal from the qualified products list. Rejected material shall not be resubmitted for acceptance without written approval from the Commander, Naval Air Warfare Center - Aircraft Division, Code 4.3.4.1, Box 5152, Warminster, PA 18974-0591. The application for resubmission shall contain full particulars concerning previous rejections and measures taken to correct these deficiencies. Samples for retest shall be randomly selected (see 4.4.3) and forwarded to the designated testing activity.

4.5 Test panels. All test panels shall be prepared under laboratory conditions (see 4.6). With the exception of the salt-spray test (see 4.6.10.1.2), test panels shall be constructed of aluminum alloy with dimensions of 0.020 by 3.0 by 6.0 in. (0.50 by 76.2 by 152.4 mm). Alloy composition and pretreatments of test panels shall be in accordance with Table I.

TABLE I. Aluminum test panels.

Panel	Substrate	Pretreatment
A	QQ-A-250/4 (T3 temper)	MIL-C-5541, Class 1A (conversion coating)
B	QQ-A-250/4 (0 temper)	MIL-A-8625, Type I or IC (anodize)
C	QQ-A-250/5 (T3 temper)	Deoxidized 1/
D	QQ-A-250/5 (T3 temper)	MIL-C-5541, Class 1A (conversion coating)

1/ Immerse test panel for 2 minutes in corrosion removing compound conforming to MIL-C-38334, Type I, Class 1, then remove test panel and rinse with distilled water. Apply the primer coating within one hour.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:19Z
Check the source to verify that this is the current version before use.

4.5.1 Application of primer coating. When required by the test method or paragraph, the primer coating shall be prepared by:

a. Thoroughly mixing the primer coating;
b. Diluting the admixed primer coating (see 6.13), if necessary, with thinner conforming to MIL-T-81772, Type I. If dilution of the primer coating is required, do not exceed 340 g/l (2.8 lb/gal).
c. Allowing admixed coating to stand undisturbed for 30 minutes prior to use;
d. Spraying the test panels with primer coating to a dry-film thickness of 1.5 to 2.0 mils (38 to 51 μm)

When required by the test method or paragraph, apply a topcoat conforming to MIL-C-83286 or MIL-C-85285 after air drying for 2 hours, in accordance with 4.5.2. If a topcoat is not used, the primer coating shall be allowed to air dry for a minimum of 14 days, or air dry for 1 hour followed by 24 hours at 122° ± 5°F (50° ± 3°C) prior to testing.

4.5.2 Application of topcoat. When a topcoat is required by the test method or paragraph, coating conforming to MIL-C-83286 or MIL-C-85285 (untinted gloss white, FED-STD-595, color number 17925) shall be mixed and reduced with thinner, if required, conforming to MIL-T-81772, Type I, and allowed to stand for 30 minutes prior to use. Apply the coating to a dry-film thickness of 1.7 to 2.3 mils (43 to 58 μm). If applying in two coats, allow the first coat to air dry for 40 to 55 minutes prior to application of the second coat. Allow the coating to air dry for a minimum of 14 days or air dry for 1 hour followed by 24 hours at 122° ± 5°F (50° ± 3°C) prior to testing.

4.6 Test methods. The tests of this specification shall be conducted in accordance with Table II and paragraph 4.6.1 through 4.6.11.1. When directed by the test method or paragraph, test panels shall be prepared in accordance with 4.5 through 4.5.2. Unless otherwise specified in the test method or paragraph, all testing shall be conducted under laboratory test conditions in accordance with ASTM D3924 and in duplicate. Unless otherwise stated in the test method or paragraph, room temperature conditions shall be defined as 65° to 85°F (18° to 29.5°C) and 50 ± 10% RH.

TABLE II. Test methods.

Requirement paragraph	Test	Test Paragraph	Fed-STD-141 Method Number	ASTM Test Method
3.2	Lead content	--	--	D3335
3.4.1.2	Chromium (Class N only)	--	--	D3718
3.4.2	VOC	--	--	D3960

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:19Z
Check the source to verify that this is the current version before use.

TABLE II. Test methods, continued.

Requirement paragraph	Test	Test Paragraph	Fed-STD-141 Method Number	ASTM Test Method
3.5.1	Condition in container	4.6.1	--	--
3.5.2	Storage stability	--	--	--
3.5.3	Accelerated storage stability	4.6.2	--	--
3.5.5	Odor	--	--	D1296
3.5.6	Viscosity	--	--	D1200
3.5.7	Pot life	--	--	D1200
3.5.8	Fineness of grind	--	--	D1210
3.6.2	Drying time	--	--	D1640
3.6.3	Lifting	4.6.3	--	--
3.6.4	Adhesion	--	6301	--
3.6.5 and 3.6.5.1	Ambient flexibility	4.6.4.1	--	--
3.6.5 and 3.6.5.2	Low-temperature flexibility	4.6.4.2	--	--
3.6.6	Tensile properties	--	--	D2370
3.6.7	Infrared reflectance (Type II only)	4.6.5	--	--
3.6.8	Strippability	4.6.6	--	--
3.7.1	Water resistance	4.6.7	--	--
3.7.2 - 3.7.2.2	Humidity resistance	--	--	D2247
3.7.3	Fluid resistance	4.6.8	--	--
3.7.4	Solvent resistance (cure)	4.6.9	--	--

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

TABLE II. Test methods, continued.

Requirement paragraph	Test	Test Paragraph	Fed-STD-141 Method Number	ASTM Test Method
3.7.5.1	Salt-spray corrosion resistance - aluminum test panel	4.6.10.1.1	--	B117
3.7.5.1.2	Salt-spray corrosion resistance - aluminum/graphite epoxy test panel	4.6.10.1.2	--	--
3.7.5.2	Filiform corrosion resistance	4.6.10.2	--	--
3.8.2	Application	4.6.11.1	--	--

4.6.1 Condition in container. Allow the primer coating to stand without agitation for a minimum of 14 days at room temperature (see 4.6). After this period, examine container contents for conformance to 3.5.1.

4.6.2 Accelerated storage stability. A full, unopened, sealed container of each component shall be stored undisturbed for a minimum of 14 consecutive days in a location maintained at 140° ± 5°F (60° ± 3°C). At the end of the 14 day period, the containers shall be allowed to cool to room temperature (see 4.6). (During the storage period, it is advised that the unopened containers be placed in larger, vented containers to confine any splash that may occur if the lid of the unopened container is blown off by gassing.) If, upon removal, the unopened can is deformed, do not open. If it is not deformed, open the can carefully and examine its contents for conformance to 3.5.3.

4.6.3 Lifting. The primer coating shall be applied to "A" test panels (see 4.5) in accordance with 4.5.1. Topcoat shall then be applied in accordance with 4.5.2 to primer coating that air-dried for 1, 4, and 18 hours, respectively. Examine for conformance to 3.6.3.

4.6.4 Flexibility.

4.6.4.1 Ambient flexibility. The primer coating, applied to "B" test panels (see 4.5) in accordance with 4.5.1 shall be tested with a GE Universal Impact-Flexibility Tester, Model 172 (see 6.11), or equivalent. The impacter for this test weighs 3.6 lbs, and has formed on each end four convex spherical segments, each of different radii and extension. The test shall be conducted on test panels conditioned for four hours at 350° ± 5°F (177° ± 3°C).

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:19Z
Check the source to verify that this is the current version before use.

The test shall be conducted as follows:

a. Place the coated test panel, film downward, on the rubber pad at the bottom of the impacter guide.
b. Drop the impacter on the panel such that the impression of the entire rim of the impacter is made in the panel.
c. Reverse the impacter ends and drop it on the panel adjacent to the first impact area.
d. Use 10 power magnification to examine fine surface cracking and report the percent elongation, corresponding to largest spherical impression at which no cracking occurs. Examine for conformance to 3.6.5.1.

4.6.4.2 Low-temperature flexibility. The primer coating, applied to "B" test panels (see 4.5) in accordance with 4.5.1 shall be tested for coating elongation, in accordance with ASTM D522, Method "B", "Cylindrical Mandrel Test". The test shall be performed at -60° ± 5°F (-51° ± 3°C), using a 1/8 in. (3.2 mm) mandrel. After testing, the primer film shall be examined for conformance to 3.6.5.2. This test shall be repeated after the primer film has been exposed to 350° ± 5°F (177° ± 3°C) for four hours.

4.6.5 Infrared reflectance (Type II primer coating only). The Type II primer coating shall be applied to "A" test panels (see 4.5) in accordance with 4.5.1. The total reflectance (specular and diffuse) of the primer coating relative to barium sulfate shall be measured using a Perkin-Elmer LAMBDA 9 spectrophotometer, or equivalent (ASTM E275 may be used to compare performance of the equivalent unit to the LAMBDA 9), over a range of 450 to 2700 nm. Examine for conformance to 3.6.7.

4.6.6 Strippability. The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1, shall be artificially aged at 210° ± 2°F (99° ± 1°C) for 4 days. The test panels shall then be placed on a rack, coated side up, at 60° to the horizontal. In a well ventilated area maintained at room temperature (see 4.6), pour remover conforming to MIL-R-81294, Type I, along the top edge of the test panel to completely cover the coating surface. Just enough remover to cover the coating surface shall be used. After 60 minutes exposure to the remover, the loosened film shall be brushed off with a stiff, non-metallic, bristle brush while rinsing under a stream of cool water. The test panels shall then be examined for conformance to 3.6.8. The amount of primer coating removed in this manner is determined by the percentage of substrate surface area exposed.

4.6.7 Water resistance. The primer coating, applied to "A" test panels (see 4.5) in accordance with 4.5.1 and topcoated in accordance with 4.5.2 shall be completely immersed in distilled water maintained at 120° ± 5°F (49° ± 3°C) for four days. Two hours after removal from the water, the coating shall be examined for conformance to 3.7.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

4.6.8 Fluid resistance. The primer coating shall be applied to "A" test panels (see 4.5) in accordance with 4.5.1. The test panels shall then be separately immersed to half their length for 24 hours in the following liquids, contained in glass covered beakers:

a. Lubricating oil conforming to MIL-L-23699, maintained at 250° ± 5°F (121° ± 3°C);
b. Hydraulic fluid conforming to MIL-H-83282, maintained at 150° ± 5°F (65.5° ± 3°C).

After removal from the test fluids, cool the test panels to room temperature (see 4.6) and examine for conformance to 3.7.3.

4.6.9 Solvent resistance (cure). The primer coating shall be applied to "A" test panels (see 4.5) in accordance with 4.5.1. The primer coating shall then be examined for cure, as follows:

a. Soak a cotton, terrycloth rag in MEK solvent (see 6.12).
b. Rub the coating with the soaked rag for 50 passes (25 times) with firm finger pressure.
c. Examine coating for conformance to 3.7.4.

4.6.10 Corrosion resistance.

4.6.10.1 Salt spray.

4.6.10.1.1 Aluminum test panel. The primer coating shall be applied to "A" test panels (see 4.5) in accordance with 4.5.1. Two intersecting lines shall then be scribed diagonally across the surface of each panel, exposing the aluminum substrate. The test panels shall then be placed in a 5% salt-spray cabinet for 2000 hours in accordance with ASTM B117. After removal the test panels shall be examined for conformance to 3.7.5.1.1.

4.6.10.1.2 Aluminum/graphite-epoxy test panel. The primer coating shall be applied to the aluminum/graphite-epoxy test specimen (see Figure 1), in accordance with the following manner:

a. An aluminum alloy 7075 (T6 temper) plate conforming to QQ-A-250/12, dimensions of 0.125 by 6.0 by 6.0 in. (3.0 by 152.4 by 152.4 mm), shall be anodized in accordance with MIL-A-8625, Type I or IC;
b. Primer coating shall be applied to the test panel in accordance with 4.5.1;
c. Two intersecting lines shall be scribed diagonally across the surface of the plate, exposing the bare substrate;

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

d. A graphite-epoxy panel with a 0°, 90° orientation (Hercules AS4/3501-6 or equivalent) of approximately 16 plies, dimensions of 0.094 by 3.0 by 3.0 in. (2.4 by 76.0 by 76.0 mm), shall be joined to the center of the primer coated plate with four nylon fasteners.
e. Four additional lines, length of 2 in. (51 mm), shall be scribed along the edge of the panel, exposing the bare substrate of the plate.


The assembled test specimen shall then be placed in a 5% salt-spray cabinet for 500 hours in accordance with ASTM B117. After removal, examine the coating for conformance to 3.7.5.1.2.

4.6.10.2 Filiform. The primer coating shall be applied to "D" test panels (see 4.5) in accordance with 4.5.1 and topcoated in accordance with 4.5.2. Two intersecting lines shall be scribed diagonally across the surface of the test panels, exposing the bare substrate. The test panels shall then be placed vertically in a desiccator containing 12N hydrochloric acid (equivalent to American Chemical Society (ACS) reagent grade) for 1 hour. Within 5 minutes of removal from the desiccator, the test panels shall be placed in a humidity cabinet maintained at 104° ± 3°F (40° ± 1.7°C) and of 80 ± 5% RH for 1000 hours. The test panels shall then be examined for conformance to 3.7.5.2. Filiform corrosion appears as threadlike filaments initiating from the exposed substrate and spreading underneath the coating film. A general description of filiform growth appears in ASTM D2803.

4.6.11 Working properties.

4.6.11.1 Application. Using conventional, airless, HVLP (high volume, low pressure), and electrostatic spray equipment, apply the admixed primer coating to test panels to a dry film thickness of 1.5 to 2.0 mils (38 to 51 μm) in accordance with 4.5.1. Examine for conformance to 3.8.2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

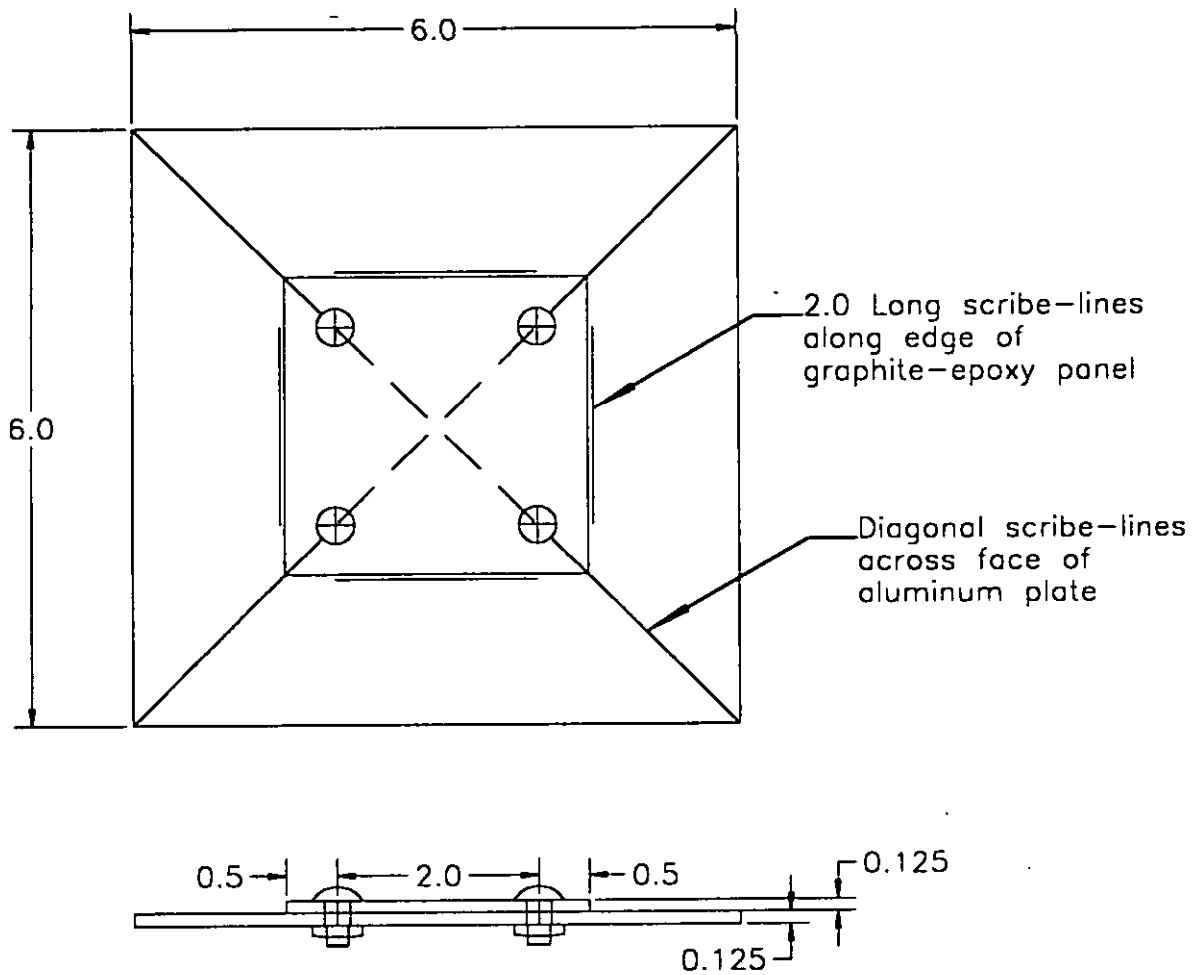

All dimensions are in inches

FIGURE 1. Aluminum/graphite - epoxy test specimen.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging and packing. The primer coatings shall be packaged, packed, and marked in accordance with PPP-P-1892. The level of preservation shall be A or C and the level of packing shall be A, B, or C, as specified (see 6.2). The size of the kit should be specified (see 6.7.1) for procurement. The size of the components in one kit need not be the same.

5.2 Marking and labeling. In addition to the marking specified in PPP-P-1892, individual cans and containers shall bear printed labels showing the following nomenclature and information:

- Specification TT-P-2760A, Type I or II and Class C or N (as applicable).
- Manufacturer's name and product number.
- Date of manufacture by month and year.
- Batch number.
- VOC content in grams/liter.
- Net contents.
- Mixing and thinning instructions.

The following is to be included on a printed sheet with each kit:

Precautions

a. The surface to be coated must be clean (free of oil, dust, etc.)

b. Spray equipment must be adequately grounded. Clean equipment immediately after use.

c. Mix only the amount of primer coating to be used within 4 hours.

d. Primer coating from one vendor, or individual component, shall never be mixed with that of another vendor.

e. Always add Component B to Component A - NEVER THE REVERSE.

f. Apply over pretreated metal. On fiberglass-reinforced plastic surfaces, application of metal pretreatment conforming to MIL-C-8514 prior to application of TT-P-2760 will facilitate stripping without damage to the fiberglass.

5.2.1 Precautionary markings - container. All unit and intermediate containers, including unit containers that serve as shipping containers shall be marked with the applicable precautionary information detailed in ANSI Z129.1 and shall be labeled in accordance with the applicable federal, state, and municipal laws, statutes, regulations, and/or ordinances. In addition to labeling specified in 49 CFR 171-178, the following labeling shall appear on each container, and on each shipping container:

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:19Z
Check the source to verify that this is the current version before use.

CAUTION

THIS COATING MATERIAL IS TOXIC AND FLAMMABLE AND
SHALL NOT BE USED IN CONFINED AREAS, WHERE THERE ARE OPEN FLAMES,
ARCING EQUIPMENT, HOT SURFACES, OR WHERE SMOKING IS PERMITTED.

USE ONLY WITH ADEQUATE VENTILATION.

AVOID BREATHING OF VAPOR.

DO NOT GET IN EYES, ON SKIN, ON CLOTHING.

IN CASE OF CONTACT WITH EYES AND/OR SKIN,
FLUSH EYES AND/OR SKIN WITH PLENTY OF WATER.
FOR EYES, GET MEDICAL ATTENTION.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but not mandatory.)

6.1 Intended use. The primer coatings covered by this specification are low VOC, corrosion-inhibitive, flexible primer coatings intended for use on the exterior surfaces of aircraft and other equipment that are subjected to structural flexing at low temperatures. Type I is for general use. Type II is for use where low infrared reflectance is required. Unless a specific type and/or class is referenced in a contract or purchase order, Type I, Class C is the default reference. The non-chromated (Class N) primer coatings are for use where federal, state, or local regulations restrict the use of chromate based materials. Class N primer coatings may only be used when authorization for its use is given by the procuring activity or the engineering authority for the system or item to which the primer coating is to be applied. For users of TT-P-2760, Class 2, "High-Solids," use Class C of this document.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification, including any amendments.
b. Classification (Type I or II, and Class C or N, as applicable) (see 1.2 and 6.7).
c. Issue of the DODISS to be cited in the solicitation, and, if required, the specific issue of individual documents referenced (see 2.1 and 2.2).
d. Data requirements (see 6.3).
e. Quantity and kit size (see 6.7.1).
f. Packaging and packing, and marking and labeling required (see 5.1, and 5.2 through 5.2.1.2).
h. Specify if palletization is required.
i. Acceptance criteria (see 6.9 and 6.10).
j. FAR clause 52.223-3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

6.3 Consideration of data requirements. The following Data Item Descriptions (DID's) must be listed, as applicable, on the Contract Data Requirements List (DD Form 1423) when this specification is applied on a contract, in order to obtain the data, except where DoD FAR Supplement 227.405-70 exempts the requirement for a DD Form 1423.

Reference Paragraph	DID Number	DID Title	Suggested Tailoring
3.3, 4.3.2, 4.4.2	DI-NDTI-80809A	Test/Inspection Reports	---

The above DID's were those cleared as of the date of this specification. The current issue of DOD 5010.12-L, Acquisition Management Systems and Data Requirements Control List (AMSDL), must be researched to ensure that only current, cleared DID's are cited on the DD Form 1423.

6.4 Qualification. With respect to products requiring qualification, awards will only be made for products which are qualified for inclusion in the applicable Qualified Products List (QPL) at the time set for award of contract, whether or not such products have actually been so listed by that date. The attention of manufacturers and suppliers is called to this requirement. Manufacturers are urged to arrange having the products that they propose to offer to the Federal Government tested for qualification in order to be eligible for award of contracts or orders for the products covered by this specification. The activity responsible for the Qualified Products List is the Commander, Naval Air Systems Command (AIR-5304), Arlington, VA 22243; however, information pertaining to qualification of products should be obtained from the Commander, Naval Air Warfare Center - Aircraft Division, Code 4.3.4.1, Box 5152, Warminster, PA 18974-0591.


6.5 Subject term (key word) listing.

Corrosion inhibitive
Flammable
Hydrochloric acid
Low infrared reflectance
Methyl ethyl ketone (MEK)
Strontium chromate

6.6 Material Safety Data Sheet (MSDS). 29 CFR 1910.1200 requires that the MSDS for each hazardous chemical used in an operation must be readily available to personnel using the material. Contracting officers will identify the activities requiring copies of the MSDS.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

6.7. Part numbers. Part numbers for cataloging purposes under this specification may be coded as follows:

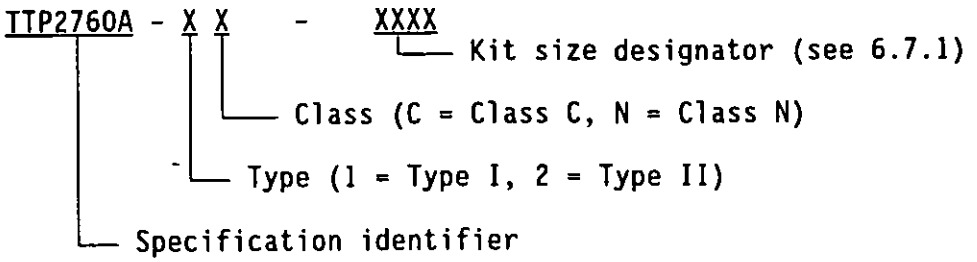

6.7.1 Kit size. The four digit kit size designation in the part number assignment is as follows:

Kit size	Kit size designator
4 pint (1.88 liter (l))	004P
4 quart (3.76 l)	004Q
4 gallon (15.14 l)	004G
20 gallon (75.7 l)	020G

6.8 Compatibility. TT-P-2760 is compatible with the following coatings: TT-P-2756, "Polyurethane Coating: Self-Priming Topcoat, Low Volatile Organic Compounds (VOC);" MIL-C-83286, "Coating, Urethane, Aliphatic Isocyanate, for Aerospace Applications;" and MIL-C-85285, "Coating: Polyurethane, High-Solids." Compatibility with other topcoats should be tested prior to use.

6.9 Acceptance criteria for packaging and marking. Previous revisions of this document specified an acceptable quality level (AQL) of 4.0 defects per hundred units, in accordance with MIL-STD-105.

6.10 Acceptance criteria for palletization. Previous revisions of this document specified an acceptable quality level (AQL) of 6.5 defects per hundred units, in accordance with MIL-STD-105.

6.11 Impact tester source. The instrument used for the test of 4.6.4 is the GE Universal Impact Tester, Model #172, available from the Paul N. Gardner Company, 316 N.E. First Street, P.O Box 10688, Pompano Beach, FL 33061-6688. The impacter for this test weighs 3.6 lbs, and has formed on each end four convex spherical segments, each of different radii and extension. There may be other instruments equivalent to this unit.

6.12 Safely handling MEK solvent. To minimize exposure to MEK solvent, it is recommended that personnel conducting the solvent resistance (cure) test (see 4.6.9) wear either butyl rubber or Teflon gloves and a half-face respirator equipped with organic vapor cartridges.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

6.13 Thinning. If it is necessary to add thinner to this coating:

a. Use only thinner conforming to MIL-T-81772, Type I;
b. In areas where air quality regulations restrict volatile emissions, do not add thinner to the primer coating if that addition will raise the VOC content to greater than 340 g/l (2.8 lbs/gal).

6.14 Cross-reference of classes from TT-P-2760 to TT-P-2760A. Class C of TT-P-2760A was Class 2 of TT-P-2760. Class N of TT-P-2760A was not covered by TT-P-2760. TT-P-2760, Classes 1 and 3, are not covered by, nor available under TT-P-2760A. Unless a specific type and/or class is referenced in the contract or purchase order, TT-P-2760A, Type I, Class C is the default. Class N may not be substituted for Class C, unless authorization for its use is given by the procuring activity or engineering authority for the system or item to which the primer coating is to be applied.

6.15 Changes from previous issues. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

MILITARY INTERESTS:

Custodians
Army - MR
Air Force - 99

Review Activities
Army - AR, MD-1, ME
Navy - CG, MC
Air Force - 11, 84

CIVIL COORDINATING ACTIVITY:

GSA - FSS (9FTE-10)

Preparing activity:
Navy - AS

DoD Project 8010-0549

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.
   NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER TT-P-2760A	2. DOCUMENT DATE (YYMMDD) 941230

3. DOCUMENT TITLE
PRIMER COATING: POLYURETHANE, ELASTOMERIC, HIGH-SOLIDS

4. NATURE OF CHANGE (*Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.*)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (*Last, First, Middle Initial*)	b. ORGANIZATION	
c. ADDRESS (*Include Zip Code*)	d. TELEPHONE (*Include Area Code*) (1) Commercial: (2) DSN: (*If Applicable*)	7. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY

a. NAME COMMANDER NAVAL AIR WARFARE CENTER AIRCRAFT DIVISION	b. TELEPHONE NUMBER (*Include Area Code*) (1) Commercial: (908) 323-7488 (2) DSN: 624-7488
c. ADDRESS (*Include Zip Code*) CODE 4.1.11.2B120-3 HIGHWAY 547 LAKEHURST, NJ 08733-5100	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office, 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 DSN 289-2340

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:19Z
Check the source to verify that this is the current version before use.

COMMANDER
NAVAL AIR WARFARE CENTER
AIRCRAFT DIVISION
CODE 4.1.11.2B120-3
HIGHWAY 547
LAKEHURST, NJ 08733-5100

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:19Z
Check the source to verify that this is the current version before use.