[METRIC]

A-A-2835
January 10, 1994

COMMERCIAL ITEM DESCRIPTION

BOXES, CONSOLIDATION, FIBERBOARD

The General Services Administration has authorized the use of this commercial item description, for all federal agencies.

1. Scope. This description covers requirements for weather-resistant, high stacking strength, double-wall, and triple-wall corrugated fiberboard boxes of special design and characteristics. These boxes are suitable for domestic and overseas consolidated shipment of aircraft parts, general supplies and equipment.

2. Salient Characteristics

A. Types

Type I - Double-wall corrugated fiberboard, weather-resistant, in accordance with ASTM D5118 and ASTM D4727, grade V11c.
Type II - Triple-wall corrugated fiberboard, weather-resistant, in accordance with ASTM D5168.

B. Styles

Style S - Sleeve (tube body) with double cover
Style T - Half-slotted body with cover (transporter)

C. First article. When specified, the contractor shall furnish sample units for first article inspection and approval. First article tests shall consist of all tests specified herein.

Beneficial comments, recommendations, additions, deletions, clarifications, etc. and any data which may improve this document should be sent to General Services Administration, Federal Supply Service, Engineering Branch, 26 Federal Plaza, New York. N.Y. 10278.

Distribution statement A: Approved for public release; distribution is unlimited.

FSC 8115

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:26Z
Check the source to verify that this is the current version before use.

D. Sleeve for style S box body. The sleeve shall be fabricated from one piece of scored fiberboard except where the volume of the box is larger than 0.043 cubic meters (15.44 cubic feet) which may be fabricated with two body (manufacturer's) joints on diagonally opposite corners. The direction of the corrugations shall be perpendicular to the open faces. Body (manufacturer's) joint shall be 50.8 mm (2") minimum in width and compressed stitched (see figure 1, detail B). Prior to stapling, the corrugations in the 50.8 mm (2") wide strip shall be completely crushed on both the body and the strip. The metal staples shall be placed on a slant across the strip and shall be spaced not more than 25.4 mm (1") apart (see figure 1, detail A).

E. Half slotted body for T boxes. The fabrication may be made with two body (manufacturer's) joints on diagonally opposite corners and shall be half slotted and the body (manufacturer's) joint shall be a minimum of 50.8 mm (2") and compressed stitched (see figure 1, detail B). The fiberboard used shall be as specified herein. The slots shall have a minimum width of 9.525 mm (3/8"). Prior to stapling, the corrugations in the 50.8 mm (2") wide strip shall be completely crushed on both the body and the strip. The metal staples shall be placed on a slant across the strip and shall be spaced not more than 25.4 mm (1") apart (see figure 1, detail A). The directions of the flutes shall be vertical in the sides and ends of the box.

F. Covers. The covers shall be made from a single piece corrugated fiberboard and cut so as to form a cover having four flanges. Corrugation direction may be either parallel or perpendicular to the length dimension of the cover. The flanges shall have a minimum width of 101.6 mm (4") and shall be so arranged that when assembled the flaps shall fasten to the outside of the flanges having the longest dimension. The corrugations in both the flap and flange overlapping areas shall be completely crush rolled to facilitate stapling with 19.05 mm (3/4") leg staples. In addition to crushing areas where flaps overlap (for stitching purposes), there shall be an additional crush 25.4 mm (1") wide on all outer edges of the flanges for style S boxes. Unless otherwise specified, covers being prepared for delivery shall not be stapled but shall be crushed, scored, and slotted (see 6.C.6 and figure 3).

G. Dimensions. The dimensions of the boxes shall be the inside measurements and shall be given in sequence of length, width, and depth. A tolerance of plus 6.35 mm (1/4") and minus zero shall be permitted in the dimensions of the assembled boxes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:26Z
Check the source to verify that this is the current version before use.

H. Regulatory requirement. The offeror/contractor is encouraged to use recovered materials to the maximum extent practicable in accordance with paragraph 23.403 of the Federal Acquisition Regulation (FAR).

3. Tests

A. Bending test. One fiberboard specimen not less than 304.8 mm (12") by 304.8 mm (12") shall be cut from a sound, undamaged, and unprinted area of each sample box in a lot. The specimens shall be conditioned in accordance with ASTM method D685. The specimens shall be scored along and across the machine direction, or corrugations, using scoring devices having the proper profiles for the type of fiberboard to be tested. There shall be no surface breaks in the board when folded 180 degrees along the score line parallel to the flute direction and 90 degrees along the score line perpendicular to the flute direction.

B. Compression strength test. A compression machine calibrated in accordance with ASTM method E4 is used. Boxes shall be conditioned in accordance with ASTM method D685. Boxes shall be assembled and empty. Double wall boxes whose volume is less than 0.184 cubic meter (6.56 cubic feet) shall be tested with a load of 1133.6 kilograms (2500 pounds); and larger double-wall boxes shall be tested with a load of 1360.50 kilograms (3000 pounds). Triple-wall boxes shall be tested with a load of 2267.50 kilograms (5000 pounds). The maximum deflection shall not be more than 50.8 mm (2").

C. Static test. Boxes shall be assembled empty and conditioned in accordance with ASTM method D685. A test load equal to 70 percent of the compression test load shall be uniformly distributed over the top of the test container. The load shall be permitted to stand in a static position for a period of 5 minutes. The maximum deflection shall not be more than 50.8 mm (2") during the 5 minute period.

4. Quality Assurance

Contractor Certification - The contractor shall certify and maintain a substantiating evidence that the product offered meets the salient characteristics of this Commercial Item Description.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:26Z
Check the source to verify that this is the current version before use.

Responsibility for Inspection - Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the contractor may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth herein, where such inspections are deemed necessary to assure that supplies and services conform to the prescribed requirements.

Each lot of boxes shall be inspected for conformance to the requirements herein. Inspection shall be in accordance with MIL-STD-105 using the sampling plans specified below.

Visual, dimensional, and sampling for end item testing - Inspection level S-2 with an Acceptable Quality level (AQL) of 2.5 percent defective. The sample unit shall be a single box.

5. Preparation for Delivery


Preservation, Packaging, Packing, Labeling and Marking shall be as specified in the contract or purchase order.

6. Notes


A. Part Identification Number

The following part identification numbering procedure is for government purposes and does not constitute a requirement for the contractor.

The below example describes a transporter double wall box in accordance with CID A-A-2835:

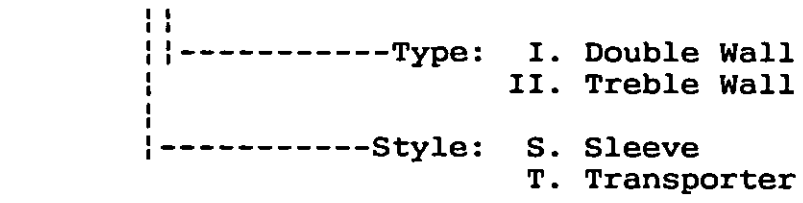


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:26Z
Check the source to verify that this is the current version before use.

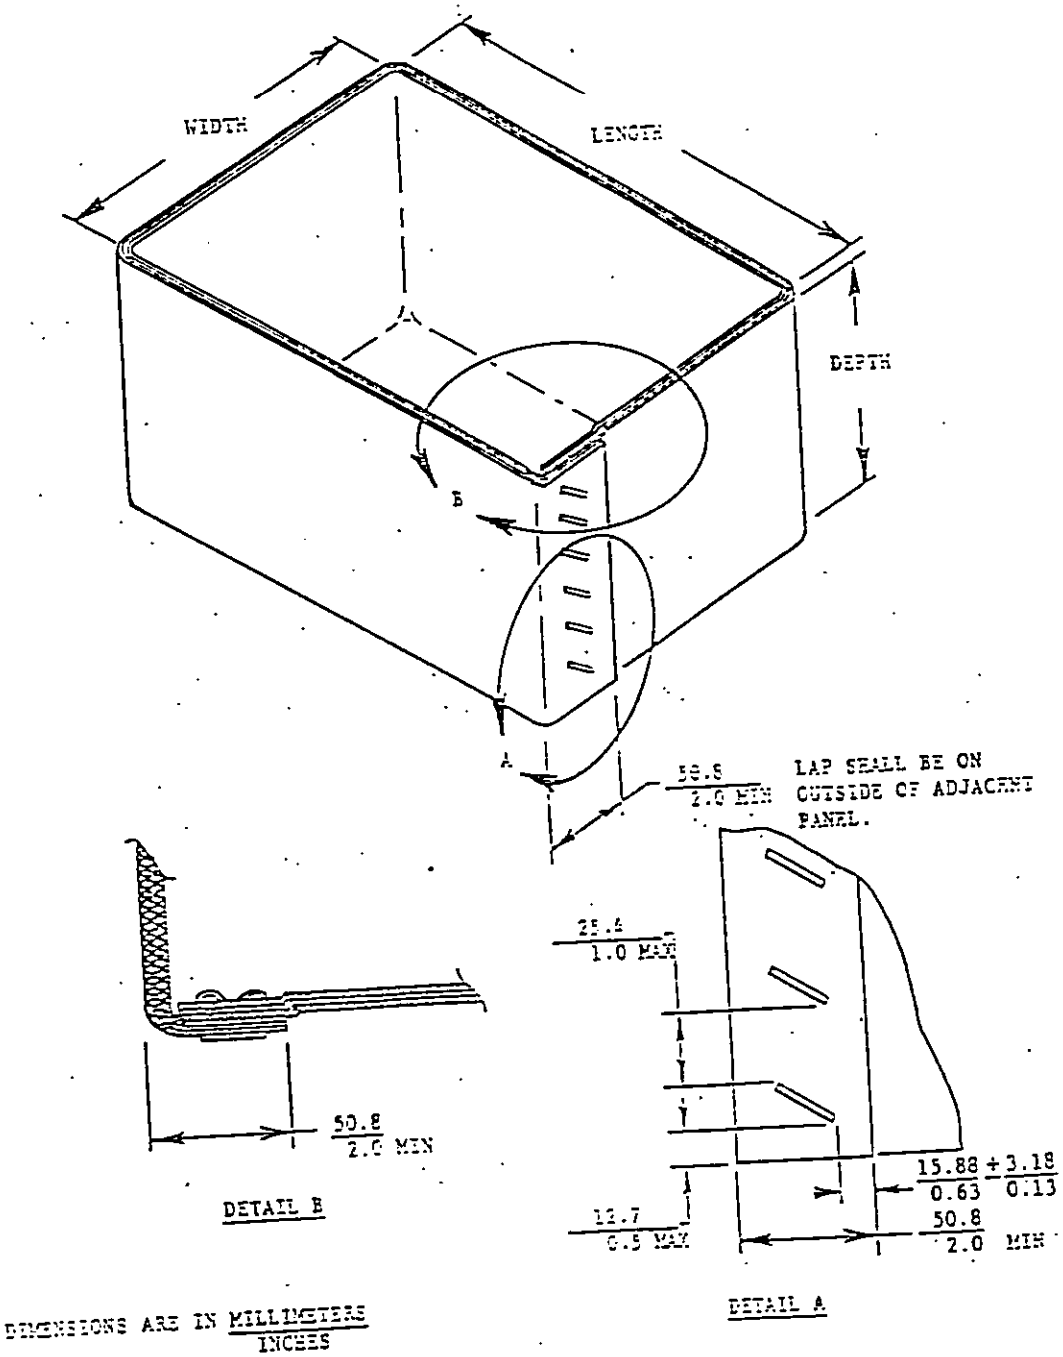

SLEEVE FOR STYLE S BOX BODY

FIGURE 1


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:26Z
Check the source to verify that this is the current version before use.

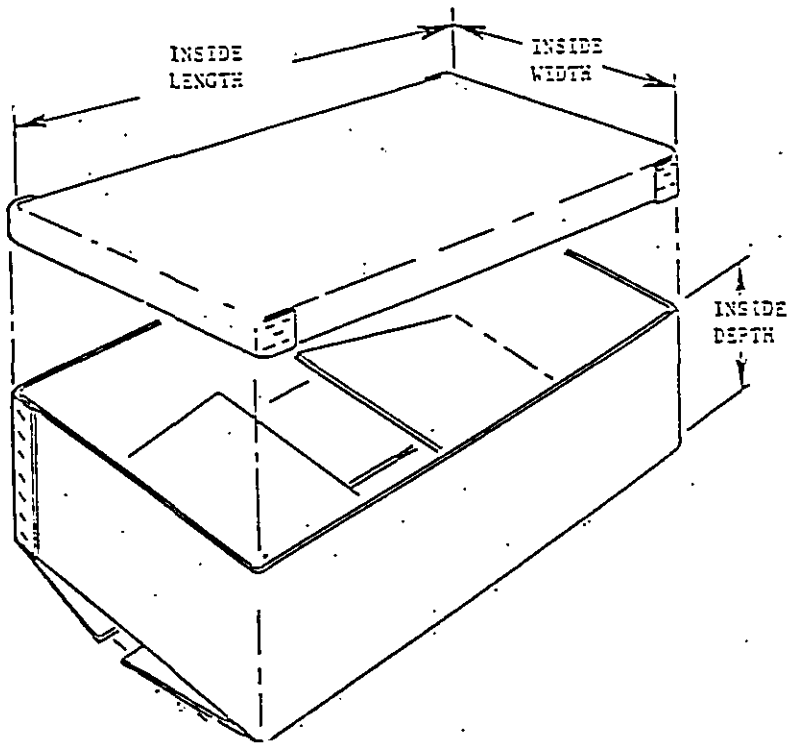


STYLE T BOX BODY W/COVER

FIGURE 2

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:26Z
Check the source to verify that this is the current version before use.

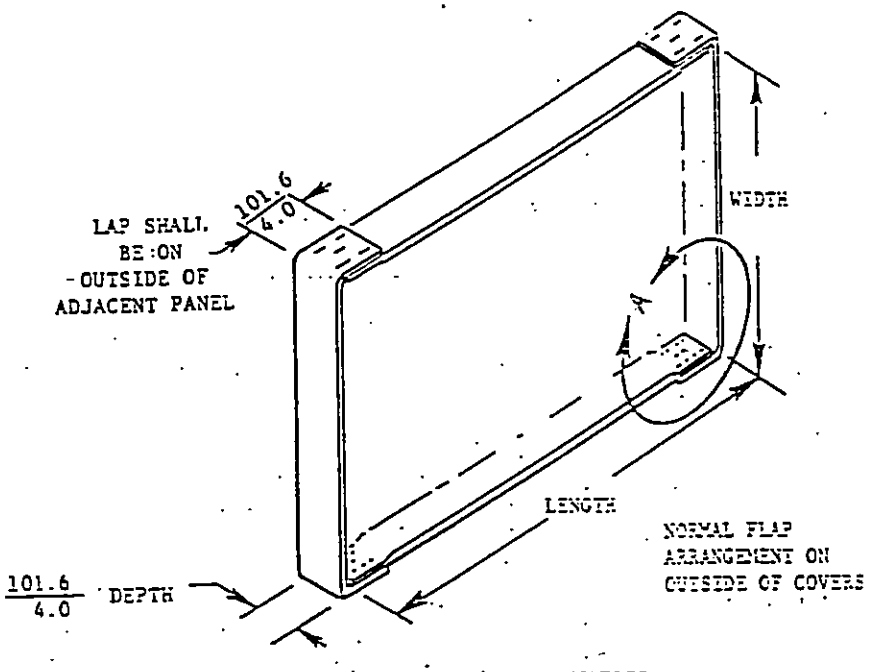

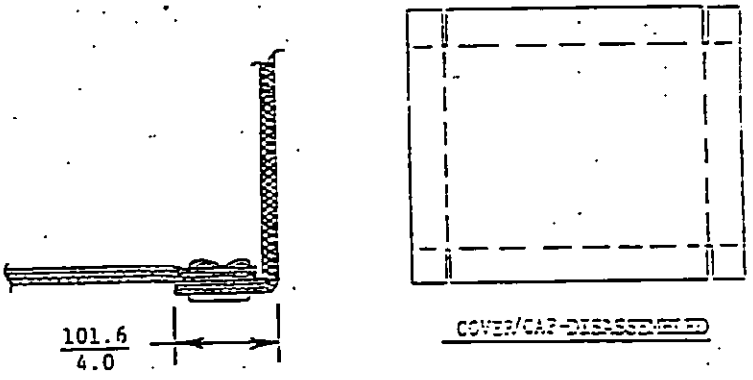

DIMENSIONS ARE IN MILLIMETERS
INCHES

COVERS AND CAPS FOR STYLE S AND T BOXES

FIGURE 3

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:26Z
Check the source to verify that this is the current version before use.

B. Application for copies of technical documents referenced herein.

The issue date in effect on date of invitation for bids or request for proposal shall apply.

1. MIL-STD-105 is available from Standardization Documents Order Desk; Building 4D; 700 Robbins Avenue; Philadelphia, PA 19111 - 5094.

2. ASTM standards are available from the American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pa 19103.

3. Federal Acquisition Regulations (FAR) are available for sale by the Superintendent of Documents, Congressional Sales Office, U.S. Government Printing Office, Washington DC 20402.

C. Ordering Data

Purchasers should select the preferred options permitted herein, and include the following information in procurement documents.

1. Title, number and date of this commercial item description.
2. Type of box (see 2.A).
3. Style of box (see 2.B).
4. Inside dimensions of box (see 2.G).
5. Quantity required.
6. Whether covers should be stapled (see 2.F).
7. When first article test sample is required (see 2.C)

No official DOD interest has been registered

Preparing Activity: GSA-FSS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:26Z
Check the source to verify that this is the current version before use.