The documentation and process conversion measures necessary to comply with this revision shall be completed by 12 May 2002.

INCH-POUND

MIL-PRF-19500/683
AMENDMENT 1
22 February 2002

PERFORMANCE SPECIFICATION

SEMICONDUCTOR DEVICE, TRANSISTOR, FIELD EFFECT, N-CHANNEL,
RADIATION HARDENED (TOTAL DOSE AND SINGLE EVENT EFFECTS)
TYPE 2N7467U2, JANTXVR, F, G, AND H AND JANSR, F, G, AND H

This amendment forms a part of MIL-PRF-19500/683, dated 9 March 2001, and is approved for use by all Departments and Agencies of the Department of Defense.

PAGE 8

4.5.2.b, delete "20 A" and substitute "16.67 A ".

4.5.2.d, delete "20 V" and substitute "10 V ".

PAGE 9

4.5.3.b, delete "20 A " and substitute "16.67 A ".

4.5.3.d, delete "20 V " and substitute "10 V ".

PAGE 10

TABLE I, subgroup 2, thermal impedance, maximum limits column, delete "0.37" and substitute "0.38".

TABLE I, subgroup 2, forward voltage, conditions column, delete "$I_D = I_{D2}$", and substitute "$I_D = I_{D1}$".

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:47Z
Check the source to verify that this is the current version before use.

TABLE III, subgroup 7, delete and substitute:

“

Subgroup 7			3 devices
SEE 2/ 3/ 4/	1080	See figure 4.	
Electrical measurements 5/		IGSS1 and IDSS1 in accordance with table I, group A, subgroup 2	
SEE irradiation		Fluence = 3E5 ± 20 percent ions/cm^2 Flux = 2E3 to 2E4 ions/cm^2/sec Temperature = 25 ± 5 °C (ION – COPPER) LET = 28 MeV-cm^2/mg Range = 40 microns Energy = 261 MeV Insitu bias conditions: VDS = 30V & VGS = -10V VDS = 25V & VGS = -15V VDS = 15V & VGS = -20V (ION – BROMINE) LET = 37 MeV-cm^2/mg Range = 37 microns Energy = 285 MeV Insitu bias conditions: VDS = 30V & VGS = -10V VDS = 22.5V & VGS = -15V VDS = 15V & VGS = -20V (ION – IODINE) LET = 60 MeV-cm^2/mg Range = 33 microns Energy = 344 MeV Insitu bias conditions: VDS = 25V & VGS = -5V VDS = 20V & VGS = -10V VDS = 15V & VGS = -15V VDS = 7.5V & VGS = -20V	
Electrical measurements 5/		IGSS1 and IDSS1 in accordance with table I, group A, subgroup 2	

1/ A separate sample for each test shall be pulled.
2/ Group E qualification of SEE testing may be performed prior to lot formation. Qualification may be extended to other performance specifications utilizing the same structurally identical die design.
3/ Device qualification to a higher level LET is sufficient to qualify all lower level LET’s.
4/ The sampling plan applies to each bias condition.
5/ Examine IGSS1 and IDSS1 before and following SEE irradiation to determine acceptability for each bias condition. Other test conditions in accordance with table I, group A, subgroup 2 herein, may be performed at the manufacturer’s option.”

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:47Z
Check the source to verify that this is the current version before use.

FIGURE 4, delete and substitute:

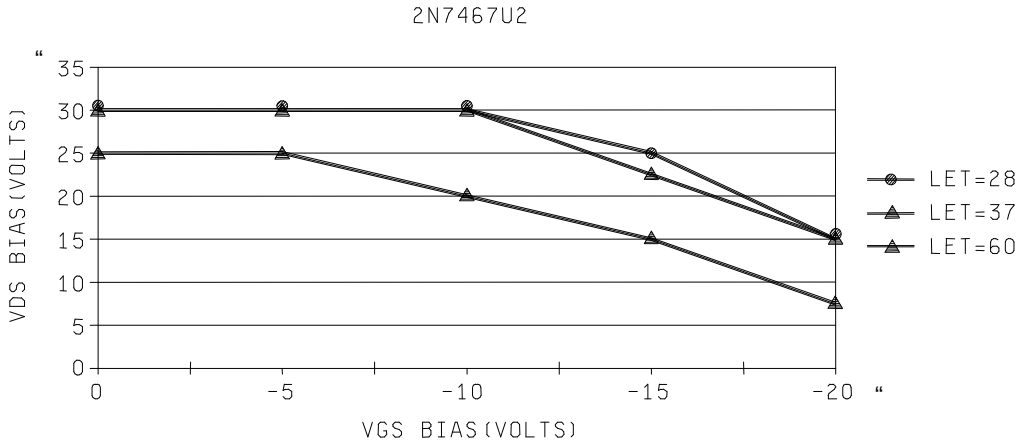

Custodians:
Army - CR
Navy - EC
Air Force - 11
NASA - NA
DLA – CC

Preparing activity:
DLA - CC

(Project 5961-2535)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:47Z
Check the source to verify that this is the current version before use.