L-T-48E
July 22, 1988
SUPERSEDING
L-T-48D
January 20, 1975

FEDERAL SPECIFICATION

TABLEWARE, PLASTIC

This specification is approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers plastic tableware suitable for use in dining halls, hospitals and in the field.

1.2 Classification. Plastic tableware shall be of the following classes, items and colors, as specified (see 6.2):

Classes:

1 - Melamine formaldehyde with alpha cellulose filler
2 - Melamine formaldehyde with fabric filler

Items:

1 - Plate, eating, dinner, round, 9 inches, with hardened surface (see fig. 1)
2 - Plate, eating, dinner, oval, 10-1/4 inches by 7-1/2 inches, with hardened surface (see fig. 2)
3 - Plate, eating, salad, round, 7 inches, with hardened surface (see fig. 3)
4 - Bowl, eating, general purpose, 17-ounce (see fig. 4)
5 - Platter, food-serving, oval, 10-1/2 inches by 15 inches, 1 inch high (see fig. 5)
7 - Tumbler, drinking, 10-ounce (see fig. 6)
8 - Cup, drinking, 1 handle, 10-ounce (see fig. 7)
10 - Bowl, food serving, fruit, 6-1/2 ounce (see fig. 8)
12 - Dish, food serving, vegetable, 1-quart (see fig. 9)
15 - Plate, eating, bread and butter (see fig. 10)
16 - Plate, eating, dinner (see fig. 11) (class 1 only)
17 - Cup, drinking, 8-ounce (see fig. 12)
18 - Saucer, cup, matching (for use with item 17) (see fig. 13)
20 - Bowl, eating, general purpose, 16-ounce (see fig. 14)
24 - Bowl, eating, fruit, 4-1/2 ounce (see fig. 15)

FSC 7350

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

Colors (see 3.6.1)

Green
Sahara Sand
Mottled Tan
Cocoa Brown

2. APPLICABLE DOCUMENTS

2.1 Government publications. The following documents of the issue in effect on the date of invitation for bids or request for proposal form a part of this specification to the extent specified herein.

Federal Specifications:

A-A-883 - Tape, Pressure Sensitive Adhesive, Masking
L-P-378 - Plastic Sheet and Strip, Thin Gauge, Polyolefin
UU-P-268 - Paper, Kraft, Wrapping
PPP-B-636 - Boxes, Shipping, Fiberboard
PPP-F-320 - Fiberboard: Corrugated and Solid, Sheet Stock (Container Grade) and Cut Shapes
PPP-T-45 - Tape, Gummed, Paper, Reinforced and Plain, For Sealing and Securing

Federal Standards:

FED-STD-123 - Marking for Shipment (Civil Agencies)
FED-STD-595 - Colors

(Activities outside the Federal Government may obtain copies of Federal specifications, standards and commercial item descriptions as outlined under General Information in the Index of Federal Specifications, Standards and Commercial Item Descriptions. The Index, which includes cumulative bimonthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.)

(Single copies of this specification and other Federal specifications, standards and commercial item descriptions required by activities outside the Federal Government for bidding purposes are available without charge from General Services Administration Business Service Centers in Boston, MA; New York, NY; Philadelphia, PA; Washington, DC; Atlanta, GA; Chicago, IL; Kansas City, MO; Fort Worth, TX; Denver, CO; San Francisco, CA; Los Angeles, CA; and Seattle, WA.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

(Federal Government activities may obtain copies of Federal standardization documents and the Index of Federal Specifications, Standards and Commercial Item Descriptions from established distribution points in their agencies.)

Military Standards:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129 - Marking for Storage and Shipment

(Copies of Military specifications, standards and drawings required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting activity.)

Other Government Documents:

U. S. DEPARTMENT OF HEALTH AND HUMAN SERVICES

Federal Food, Drug, and Cosmetic Act and Regulations Promulgated Thereunder (21 CFR Parts 170-199)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless a specific issue is identified, the issue in effect on the date of invitation for bids or request for proposal shall apply.

American Society for Testing and Materials (ASTM):

D 704 - Standard Specification for Melamine-Formaldehyde Molding Compounds

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

National Motor Freight Traffic Association, Inc., Agent:

National Motor Freight Classification

(Application for copies should be addressed to the American Trucking Associations, Inc., Tariff Order Section, 1616 P Street, N.W., Washington, DC 20036.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

National Sanitation Foundation (NSF):

Standard No. 36 - Dinnerware

Listing of Food Service Equipment

(Application for copies should be addressed to the National Sanitation Foundation, NSF Building, Ann Arbor, MI 41806.)"

Uniform Classification Committee, Agent:

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, IL 60606.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document shall take precedence. Nothing in this document, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Standard product. The tableware shall be the current standard product of the manufacturer, except for any modifications specified herein.

3.1.1 Illustrative figures. Except for items 4, 7, and 8, figures are illustrative only and are not intended to preclude any commercial design otherwise conforming to specification requirements specified herein.

3.1.2 NSF standard and certification. The tableware shall comply with the applicable requirements of NSF Standard No. 36. Prior to commencing production the contractor shall submit to the contracting officer, or his authorized representative, satisfactory evidence that the units he proposes to furnish under this specification meet the applicable requirements of NSF Standard No. 36. Acceptable evidence of meeting the applicable requirements of this standard shall be:

a. A listing in the current edition of the NSF "Listing of Food Service Equipment" or display of the NSF seal on the finished units, or

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

b. A certificate for the units issued by NSF under their one time contract evaluation certificate service, or

c. A certified test report from a recognized independent testing laboratory acceptable to GSA indicating that the units have been tested and conform to NSF Standard No. 36.

3.2 Preproduction sample. When specified (see 6.2), before production is commenced, four samples of each item of tableware shall be submitted or made available to the contracting officer or his authorized representative for approval in accordance with 4.2. The approval of the preproduction sample authorizes the commencement of production, but does not relieve the supplier of responsibility for compliance with all applicable provisions of this specification. The preproduction sample shall be manufactured in the same facilities to be used for the manufacture of the production items.

3.3 Material. The molding compound used for Class 1 and Class 2 tableware shall meet the requirements of the Federal Food, Drug, and Cosmetic Act as Amended: Title 21, CFR 177.

3.3.1 Class 1 tableware. The molding compound used for manufacturing class 1 tableware shall conform to type 1 of ASTM D 704, except that the electrical property requirements under table I shall not apply.

3.3.2 Class 2 tableware. The molding compound used for manufacturing class 2 tableware shall conform to type 12 of ASTM D 704, except that minimum flexural strength shall be 11,000 psi and the electrical property requirements under table I shall not apply.

3.3.3 Recycled material. The use of any previously cured and reground scrap material in the molding compounds is prohibited. The contractor shall furnish a certificate of compliance to the contracting officer showing that the molding compound used in the manufacture of the items complies with the requirements of 3.3. The certificate shall show the actual test values obtained on the material.

3.4 Dimensions. The dimensions of the tableware items shall be as shown on applicable figures.

3.5 Construction. All tableware items shall be molded from molding compound specified in 3.3.1 or 3.3.2 for classes 1 and 2, respectively, as specified. The tableware shall be capable of withstanding the applicable tests specified in 4.5.

3.6 Color and finish.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

3.6.1 Color. Classes 1 and 2 tableware shall be in accordance with the standard color chips of FED-STD-595. Each of the following colors shall be within its range of color numbers as shown below:

Green	No.s 24525, 24504 and 24533
Sahara sand	No.s 33717, 33711 and 23613
Mottled tan	See 3.6.1.1
Cocoa brown	See 3.6.1.2

3.6.1.1 Mottled tan. The lighter colored areas of mottled tan tableware shall be within the range of tan color numbers 20450, 21643, 22563 and 23531 of FED-STD-595. The darker colored areas shall be within the range of brown color numbers 20140, 20219, 20227 and 20313 of FED-STD-595.

3.6.1.2 Cocoa brown. The lighter colored areas of cocoa brown tableware shall be within the range of cocoa brown numbers 10219, 10233 and 10371 of FED-STD-595. The darker colored areas shall be within the range of cocoa brown color numbers 10045, 10049 and 10080 of FED-STD-595.

3.6.2 Finish. The surface of the tableware items shall have a uniformly high luster throughout, produced by molding. No surface shall be painted or otherwise treated with a protective coating or other adulterant except for items 1, 2 and 3 of class 2 tableware which shall be treated with a hardened surface that is molded into the surface of items 1, 2 and 3 in accordance with paragraph 4.5.6 (surface hardness). No machining of surfaces shall be permitted except for removal of flash at dividing line of mold. Flash or parting line after machining shall be burnished.

3.7 Uniformity. All items of tableware shall be uniform in texture, finish, gloss density, color and shade, and other properties. No particles of metal, cured resin flash, dirt or synthetic materials in the form of fabric, yarn, or thread which cause imperfections in the molded item will be permitted. Dark spots caused by dark-colored fabric materials shall be permitted on class 2 material to the extent described herein.

3.7.1 Inside surfaces of tableware (side on which food or liquid is placed), class 2. No dark spot more than 1/4 inch in largest dimension will be permitted on any class 2 tableware items. For the food-serving platter no more than 6 spots and for all other items no more than 4 spots of a size larger than 1/8 inch but smaller than 1/4 inch in largest dimension, will be permitted. For the food serving platter no more than 12 spots of any size and for all other items no more than 9 spots of any size, visible when observed at arm's length, will be permitted.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

3.8 Resistance to boiling water. Items of finished tableware shall show no cracks, chalking, changes of color, or any other defects impairing serviceability or appearance when tested as specified in 4.5.1

3.9 Resistance to boiling sulfuric acid solution. Items or test specimens cut from the tableware items shall show no chalking when tested as specified in 4.5.2.

3.10 Warpage, food serving platter. Warpage of the food serving platter shall not be greater than 0.0625 inch when measured as specified in 4.5.3.

3.11 Resistance to dry heat. Tableware shall show no cracks, color change, or blisters when tested as specified in 4.5.4.

3.12 Odor (class 2 only). Tableware items shall not have an objectionable odor and when tested as specified in 4.5.5, shall not develop an objectionable odor. The characteristic odor of phenol or formaldehyde will be cause for rejection.

3.13 Marking for identification. Tableware items shall be permanently and distinctly marked by an embossed molded-in-process marking with manufacturer's name or trademark. Marking shall be located so as not to detract from appearance of the item.

3.14 Knockout pin marks. Knockout pin marks, if hidden under normal use of item, shall not protrude more than 1/32 inch above or extend more than 1/64 inch into the surface of the item or affect stability of item when resting on a flat surface. Knockout pin marks, if not hidden under normal use of item, shall not protrude above or extend into the surface of the item more than 1/64 inch.

3.15 Workmanship. The finished tableware shall have rounded edges and shall be clean, well made and free from warpage. Tableware shall be free from any defects which may affect appearance or serviceability.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirement in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.1.2 Certificates of compliance. When certificates of compliance for component materials or test requirements are submitted, the Government reserves the right to inspect such items to determine the validity of the certification. Certificates of compliance shall be accompanied by actual test results dated not more than one year prior to the date of the start of the contract or date of purchase order.

4.2 Preproduction sample. When a preproduction sample is required it shall be examined in accordance with 4.4.1, 4.4.2 and tested in accordance with 4.5.1 through 4.5.6, as applicable.

4.3 Quality conformance inspection. Unless otherwise specified, sampling for inspection shall be performed in accordance with MIL-STD-1Ø5.

4.3.1 Lot. Unless otherwise specified (see 6.2), a lot shall consist of all tableware of the same class, item, and color submitted for inspection at the same time. The sample unit shall be one completely fabricated end item.

4.3.2 Sampling for inspection. Sampling shall be as follows:

Requirement	Level
4.4.1	I
4.4.2	S-2

4.3.3 Sampling for tests. Sampling for tests shall be in accordance with level S-2, except where otherwise indicated.

4.3.3.1 Certification. The contractor shall furnish a certificate of conformance certifying that the molding compound conforms to Title 21, CFR requirements of 3.3.

4.4 Inspection.

4.4.1 End item. Tableware shall be examined for defects listed in table I. The acceptable quality level (AQL) shall be 4.Ø for major defects and 1Ø.Ø for total defects, expressed as defects per hundred units.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

TABLE I. Classification of defects, end item

Examine	Defect	Classification Major	Minor
Tableware	Scuffed or abraded area	X	
	Scratch, dent, crack or fracture	X	
	Chalking, pinhole, or blister	X	
	Wrinkle or pit	X	
	Flow mark		X
	Shrinkage or unfilled area	X	
	Chipped or checked	X	
	Presence of mechanical oil or grease, dirt, wood shavings, metal chips or other foreign matter	X	
Knockout pin marks	Protrude more than 1/32 inch above surface of item, if mark is hidden, or more than 1/64 inch if mark is not hidden		X
	Extend more than 1/64 inch into surface of item		X
	Affect stability of the item when item is resting on flat surface	X	
Luster	Lacks luster (dull)	X	
	Not uniform luster throughout		X
Color	Not specified color	X	
	Lack of uniformity of color and shade within established tolerances		X
Spots: Class 2	Dark spots caused by material other dark-colored cotton materials		X
Inside surfaces (side in which food or liquid is placed)	Any dark spot larger than 1/4 inch in largest dimension	X	
	More than 6 dark spots on food-serving platter, 4 dark spots on all other items larger than 1/8 inch but less than 1/4 inch in largest dimension	X	
	More than 12 dark spots of any size on food-serving platter when visible at arm's length	X	
	More than 9 dark spots of any size on all other items when visible at arm's length	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

TABLE I. (Cont.)

Examine	Defect	Classification Major	Minor
Outside surfaces	Any dark spot larger than 1/4 inch in largest dimension		X
	More than 6 dark spots on food-serving platter, 4 dark spots on all other items larger than 1/8 inch but less than 1/4 inch in largest dimension		X
	More than 15 dark spots of any size on food-serving platter when visible at arm's length		X
	More than 12 dark spots of any size on all other items when visible at arm's length		X
Texture and finish	Presence of any finishing coating or orange peel	X	
	Lack of uniformity in texture and finish	X	
	NOTE: Texture may be considered as referring to the fine detail of structure, for example: A mottled effect due to the random arrangement of color areas along with lighter areas due to the cotton filler, the whole forming a pattern of normal size. In addition, an apparent matting of surface fibers becomes evident when viewed at certain angles indicating the mirror reflecting character of the surface.		
Construction Material	Not plastic	X	
	Presence of particles of metal, cured resin flash, dirt, or synthetic materials in the form of fabric, yarn or thread which cause imperfections in molded items	X	
Corners and edges	Sharp	X	
	Not "broken" and polished		X
Surfaces and curves	Not blended smoothly		X
Foot rings, as required (see drawings)	Missing	X	
	Not specified number of segments	X	
	Not smoothly blended into body		X
	Blending not started at specified points		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

TABLE I. (Cont.)

Examine	Defect	Classification Major	Classification Minor
Flashline	Not machined or burnished		X
	Insufficiently ground and burnished		X
Stacking feature (when applicable)	Stacking lugs missing	X	
	Out of position	X	
	Like units fail to stack firmly/evenly	X	
	Poor nesting resulting in restricted air circulation (for drying purposes)	X	
Handle (when required)	Missing or not in specified location	X	
Identification marking	Not permanently marked by embossed molding process		X
	Missing, illegible or incorrect		X

4.4.2 Dimensions. Tableware shall be measured dimensionally for compliance with 3.4. The acceptable quality level (AQL) shall be 1Ø.Ø, expressed in defects per hundred units.

4.4.3 Inspection for preparation and delivery. An inspection shall be made to determine whether the packaging, packing, and marking comply with the requirements of section 5 of this specification and the contract or purchase order. Examination for defects shall be in accordance with table II. For examination of interior packaging, the sample unit shall be one shipping container fully prepared for delivery. Sampling shall be in accordance with MIL-STD-1Ø5. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 with an AQL of 4.Ø defects per hundred units.

Table II
Preparation for delivery defects.

Examine	Defects
Markings	Omitted; incorrect; illegible; improper size, location, sequence, or method of application.
Material	Any component missing, damaged, or not conforming to applicable requirements stated herein.
Workmanship	Inadequate application of components such as incomplete closure of container flaps, loose strapping, or distortion of container.
Contents	Quantity of container is more or less than required. Gross weight exceeds requirements of the box specification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

4.4.4 Testing of the end item. Tableware selected in accordance with 4.3.3 shall be tested as specified in 4.5. Failure of any one item shall be cause for rejection of the lot. Unless otherwise specified, a certificate of compliance shall be allowable for all test requirements.

4.5 Tests.

4.5.1 Resistance to boiling water. Sample shall be immersed by suspending for 30 minutes in boiling water, removed and allowed to stand for 1 hour at room temperature (68 - 72 degrees Fahrenheit). This cycle shall be immediately repeated three more times. The sample shall then be allowed to stand for 12 hours in air at room temperature prior to examination. Any nonconformance to the requirements of 3.8 shall be cause for rejection of the item.

4.5.2 Resistance to sulfuric acid (see 3.9).

4.5.2.1 Platter, food serving. One platter shall be randomly selected form each lot. The platter shall be cut into four equal parts. All quarters shall be used in the test. Quarter sections shall be immersed by suspending for 10 minutes in boiling 0.8 percent (by weight) sulfuric acid, then rinsed in cold water and dried. The examination shall not include any area 1/4 inch or less from any cut (not molded) edge. Any chalking shall be cause for rejection of the item.

4.5.2.2 Other tableware items. Tableware shall be tested as specified in 4.5.2.1, except the sample shall be a complete uncut item. The examination shall include all areas of the item tested. Any chalking shall be cause for rejection of the item.

4.5.3 Warpage, food-serving platter (see 3.10).

4.5.3.1 Rim warpage. Rim warpage shall be determined by placing the platter upside down on a flat surface and holding firmly in place with a 10 pound weight, with a diameter not to exceed 5 inches, positioned at the center of the item. In this position, the item shall be sufficiently plane so that a feeler gauge of the specified maximum thickness (0.0625 inch) cannot be inserted at any point between the item and the flat surface. Any area allowing passage of the gauge shall be cause for rejection of the item.

4.5.3.2 Warpage (other than rim). Platters shall be placed upright (position of normal use on the table) on a flat surface and loaded with a 10 pound weight as specified in 4.5.3.1. In this position, the item shall be sufficiently plane so that a feeler gauge of the specified maximum thickness (0.0625 inch) cannot be inserted at any point between the item and the flat surface. Any area allowing passage of the gauge shall be cause for rejection of the item.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

4.5.4 Resistance to dry heat. Place the tableware in a circulating air oven for 8 hours at 170 degrees Fahrenheit. The specimen shall then be removed, placed in the position of use on a table and allowed to cool normally to room temperature before examination. Any nonconformance to the requirements of 3.11 shall be cause for rejection of the item.

4.5.5 Odor (class 2 only). The tableware items shall be half-filled with boiling distilled water. A plate of glass shall be immediately placed over the rim of the specimen and weighted down to obtain good contact between rim and glass. After 5 minutes the plate of glass shall be removed and the presence or absence of odor shall be determined immediately. Any nonconformance to the requirements of 3.12 shall be cause for rejection of the item.

4.5.6 Surface hardness:

4.5.6.1 Apparatus. Surface hardness tester of the design developed by the National Bureau of Standards for testing the resistance of the surface of plates to knife cutting or scratching and a stainless steel, plain edge table knife.

4.5.6.2 Specimen. The specimen shall be a minimum of 2-1/4 by 2-1/4 inches cut from the flat section of the plate.

4.5.6.3 Procedure. Sharpen the blade of the knife, being certain to wipe the blade with a clean cloth. This is to remove grit or abrasive particles resulting from the sharpening. Clamp the handle of the knife tightly in the holder after locating the tip on the crosswise centerline of the specimen with the holder midway off its stroke. The knife should be in an angle of approximately 30 degrees, and when in operation should move back and forth across the centerline of the specimen. Clamp a 3 pound weight on the blade so that its center of mass is directly above the point of contact of the knife with the surface of the specimen. The specimen shall be washed with soap and water, then rinsed with hot water, and allowed to air dry on edge. Center the specimen on the turntable. Apply 10 drops of peanut oil to the surface of the specimen, spreading it over the entire test area with a soft tissue. Slowly lower the knife onto the surface with the blade in the forward limit of the stroke, being careful to avoid abrupt contact of the blade with the test surface. Subject the specimen to 20 cycles of 100 strokes each. After each 100 strokes, resharpen, clean, and reposition the knife blade; clean test surface; and relubricate with oil. After completion of the last cycle, examine the test surface. Any evidence of deterioration or visible scratches on the upper surface of the test specimen shall be reported as a failure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

5. PREPARATION FOR DELIVERY

5.1 Packaging. Packaging shall be level A or Commercial as specified (see 6.2).

5.1.1 Level A. Tableware of like class, item and color shall be nested in quantities of 12 and securely wrapped or bagged in kraft paper having a minimum basis weight of 30 pounds conforming to UU-P-268 or plastic film conforming to L-P-378, a minimum of 1 mil thick. The package shall be secured with tape conforming to A-A-883 or PPP-T-45. Twelve items of the tableware shall be further packaged in a close-fitting box conforming to PPP-B-636, class domestic. Closure of the boxes shall be in accordance with method II of the appendix of PPP-B-636. Alternatively, tableware of like class, item and color shall be packaged in the most compact manner in a tray made from minimum 125 pound bursting strength fiberboard or paperboard. The tray shall than be completely wrapped in commercial plastic stretch film or shrink film to produce a tight package. The film shall be a minimum 0.003 inch thick.

5.1.2 Commercial. The tableware shall be packaged to insure protection during shipment and safe delivery to destination. The package and quantity per package shall be the same as that normally used by the supplier for retail distribution.

5.2 Packing. Packing shall be level A or Commercial as specified (see 6.2).

5.2.1 Level A. Twelve unit packages (144 items) of tableware of like class, item and color, except items 12 and 16, packaged as specified in 5.1, shall be packed in a close-fitting box conforming to PPP-B-636, class weather resistant, grade V3s or V2s minimum, style RSC-L. In addition to the liner, the boxes shall be provided with top and bottom pads. The material for the liner and pads shall conform to PPP-F-320, class domestic, grade 275 minimum. Boxes shall be closed method III, waterproof sealed in accordance with method V and reinforced in accordance with the appendix to PPP-B-636, except that one strap shall be applied lengthwise and one girthwise. The pack quantity for tableware of items 12 and 16 shall be four unit packages (48 items) and shall be packed as previously specified.

5.2.2 Commercial. The tableware packaged as specified in 5.1 shall be packed to comply with the National Motor Freight Classification rules and the Uniform Freight Classification rules.

5.3 Marking. In addition to marking required by the contract or purchase order, all marking shall be in accordance with 5.3.1 or 5.3.2 as specified (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

5.3.1 Civil agencies. Marking shall be in accordance with FED-STD-123.

5.3.2 Military agencies. Marking shall be in accordance with MIL-STD-129.

6. NOTES

6.1 Intended use. Tableware covered by this specification is intended to be used for the serving, dispensing, and storage of food and beverages. Class 2 material items have improved impact strength and are primarily used by the military.

6.2 Ordering data. Purchasers should select the preferred options permitted herein, and include the following information in procurement documents:

(a) Title, number, and date of this specification.
(b) Class, item, and color required (see 1.2).
(c) Whether preproduction sample is required (see 3.2)
(d) Size of lot, if different from 4.3.1.
(e) Levels of packaging and packing required (see 5.1 and 5.2).
(f) Marking required (see 5.3).

6.3 Deletions and additions. Items 11 and 13 of L-T-48D have been deleted. Items 1, 2 and 3 have been added.

MILITARY COORDINATING ACTIVITY:

Army - GL

Preparing Activity:

GSA - FSS

Custodians:

Army - GL
Navy - SA
Air Force - 99

CIVIL AGENCY COORDINATING ACTIVITIES:

HHS - NIH
VA - OSS

Review activities:

Army - MD, TS
Air Force - 84

User activities:

Navy - MC

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

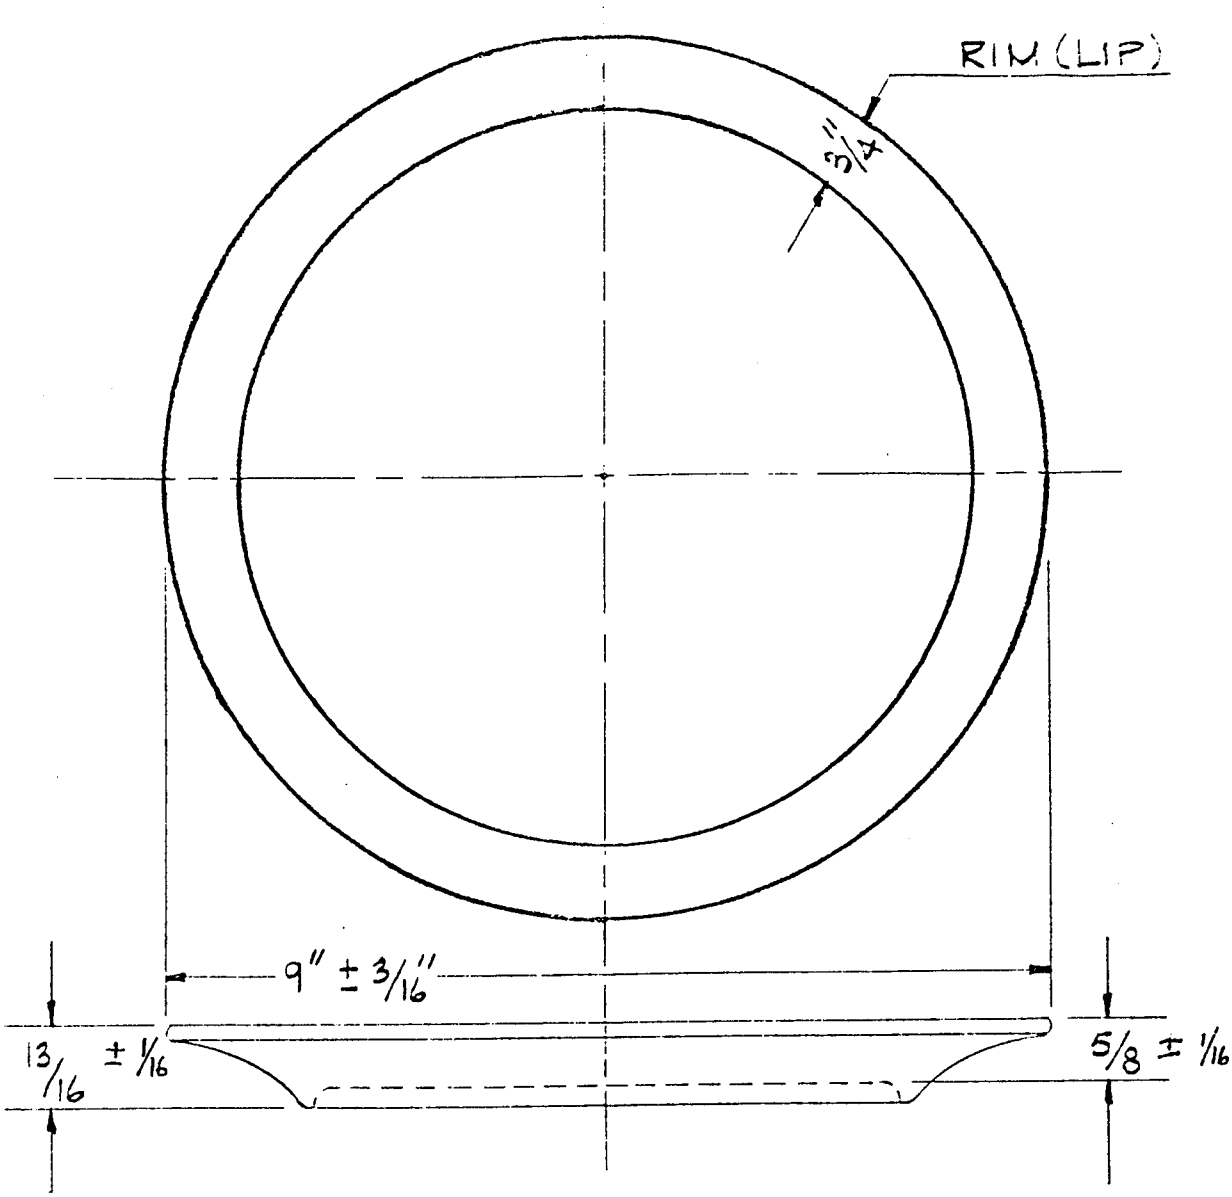


FIGURE 1 - Plate, Eating, Dinner, Round

Minimum thickness - 0.100 inch

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

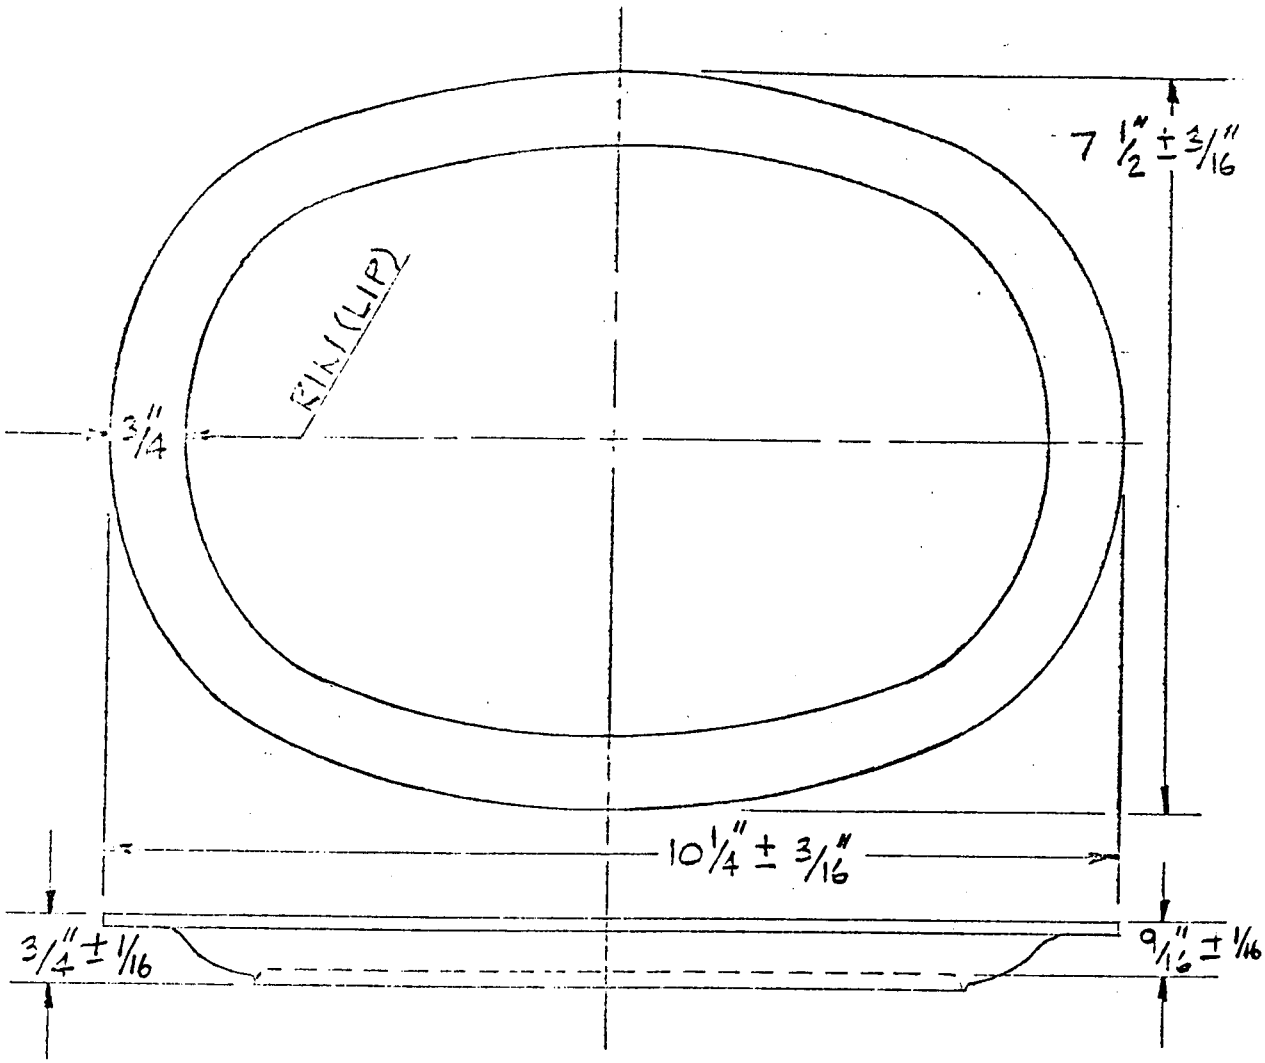


FIGURE 2 - Plate, Eating, Dinner, Oval

Minimum thickness - 0.100 inch

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

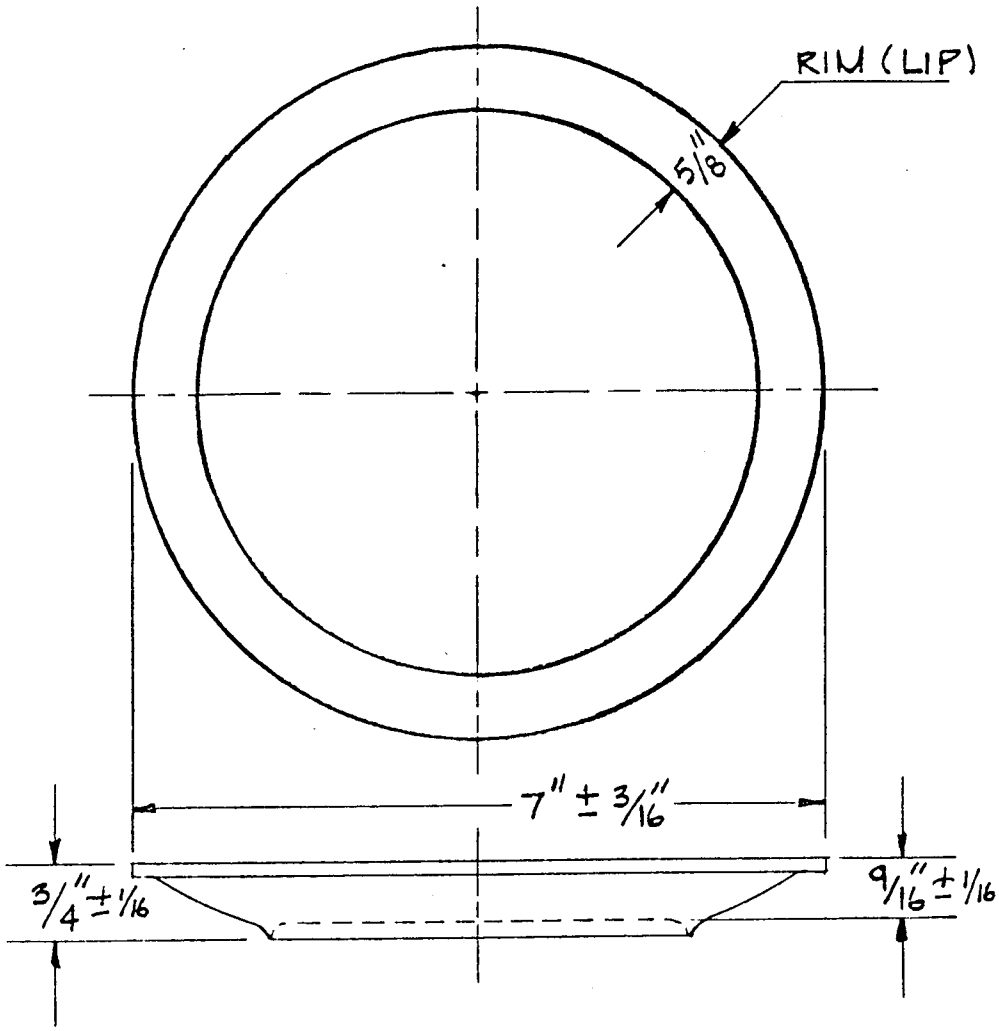


FIGURE 3 - Plate, Eating, Salad, Round

Minimum thickness - 0.100 inch

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.


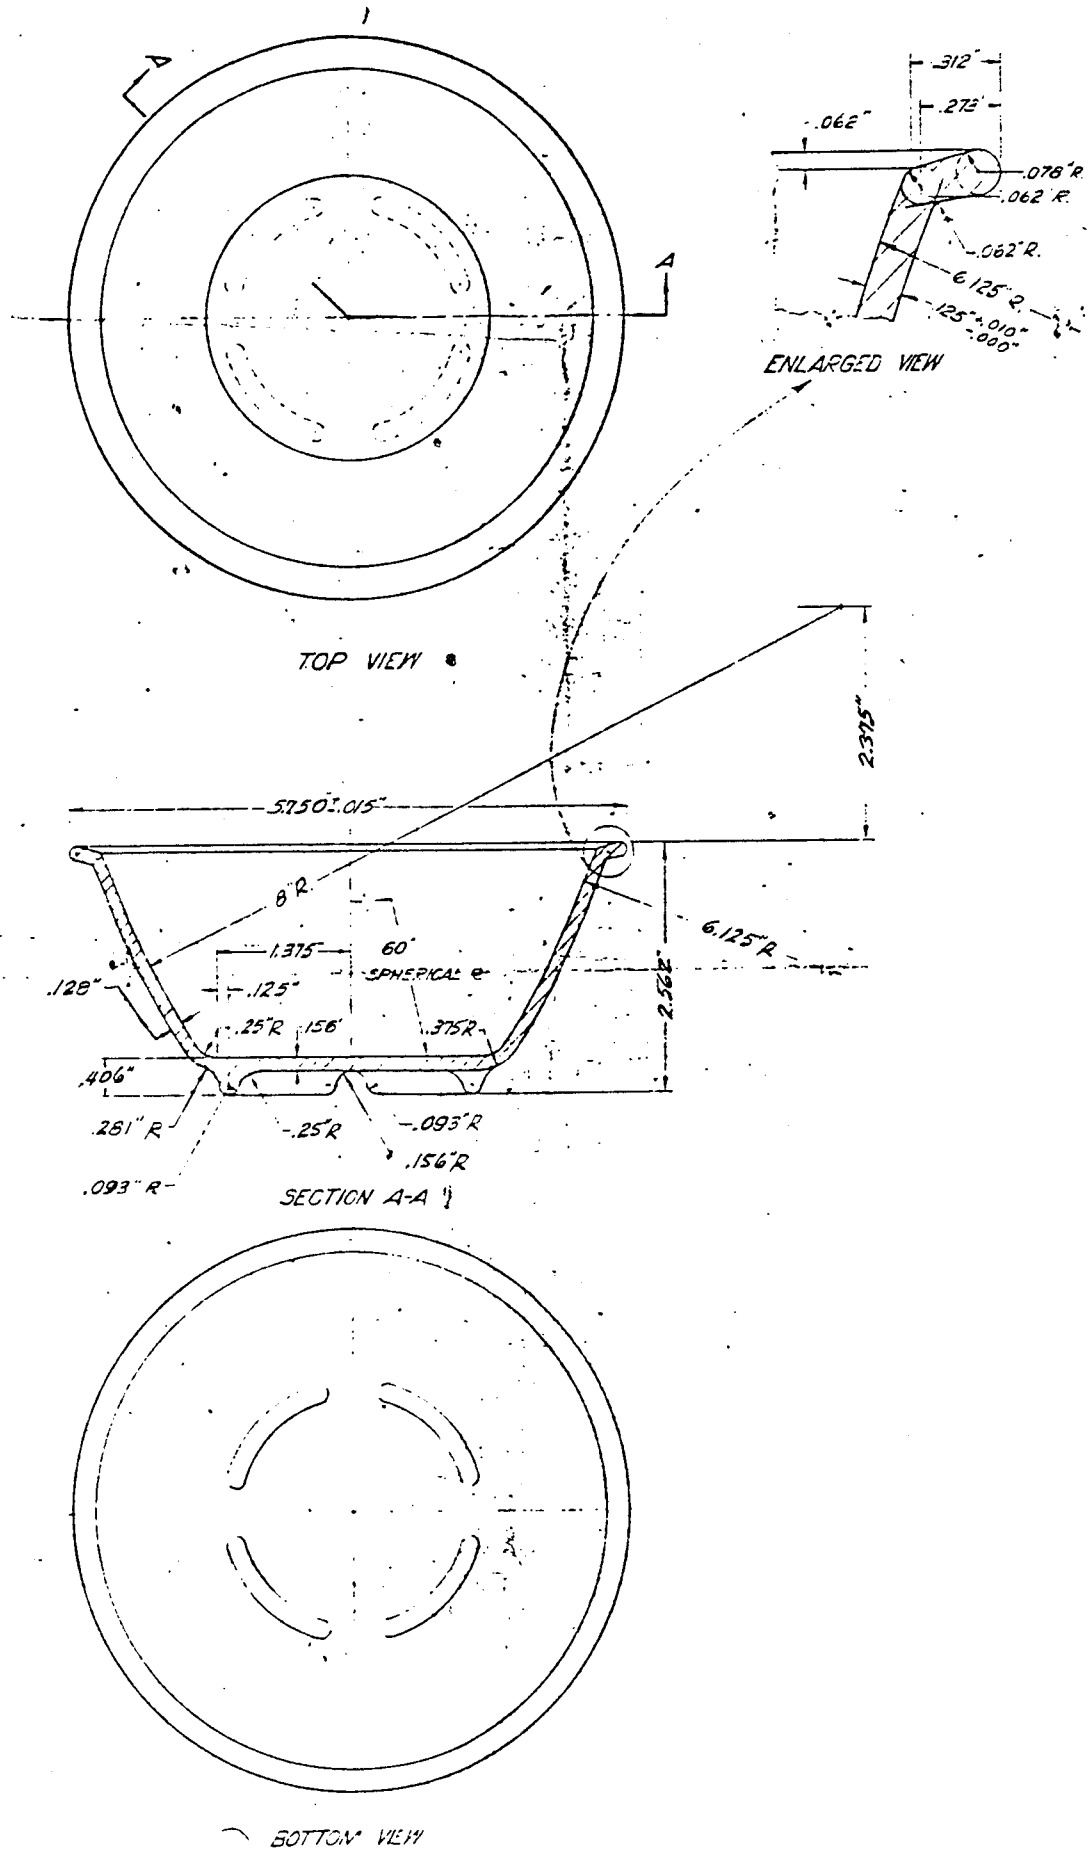


FIGURE 4 Bowl, Eating, General Putrpose, 17-ounce

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

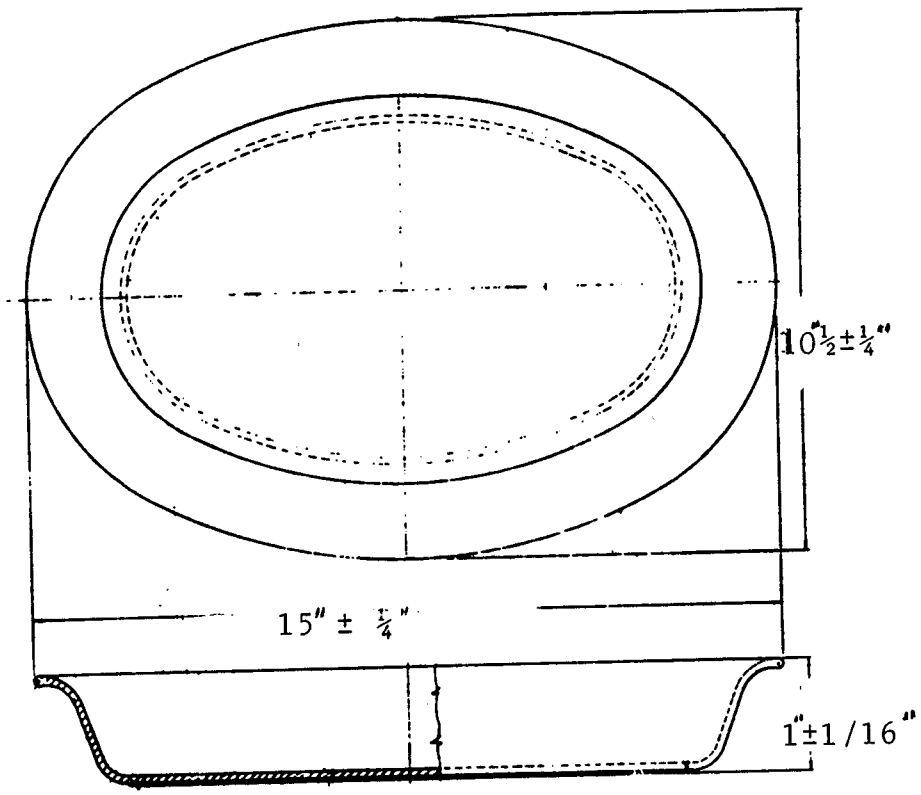

Wall thickness - 0.125"

FIGURE 5 - Platter, food-serving, oval

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

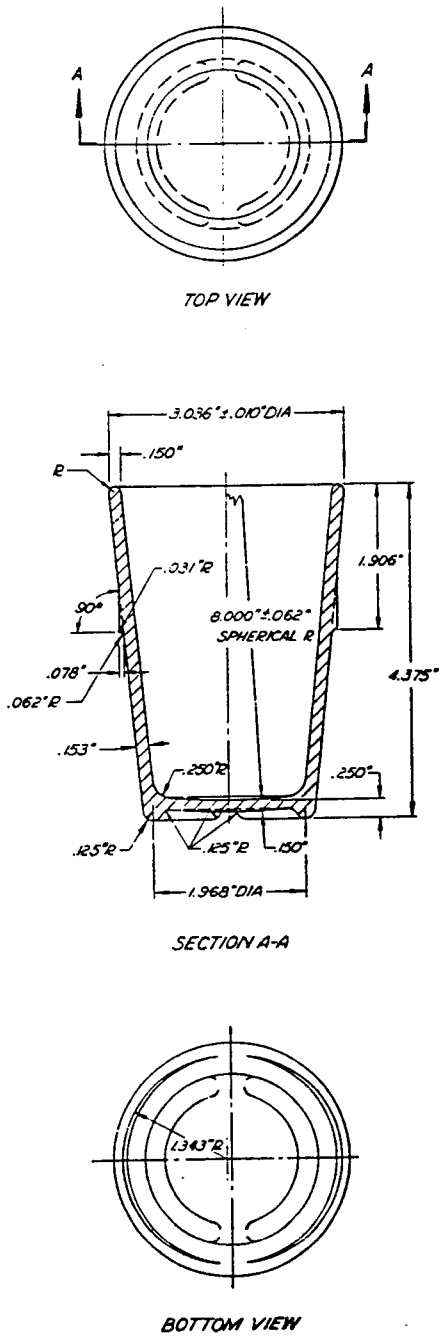


FIGURE 6 - Tumbler, drinking, 10-ounce

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.



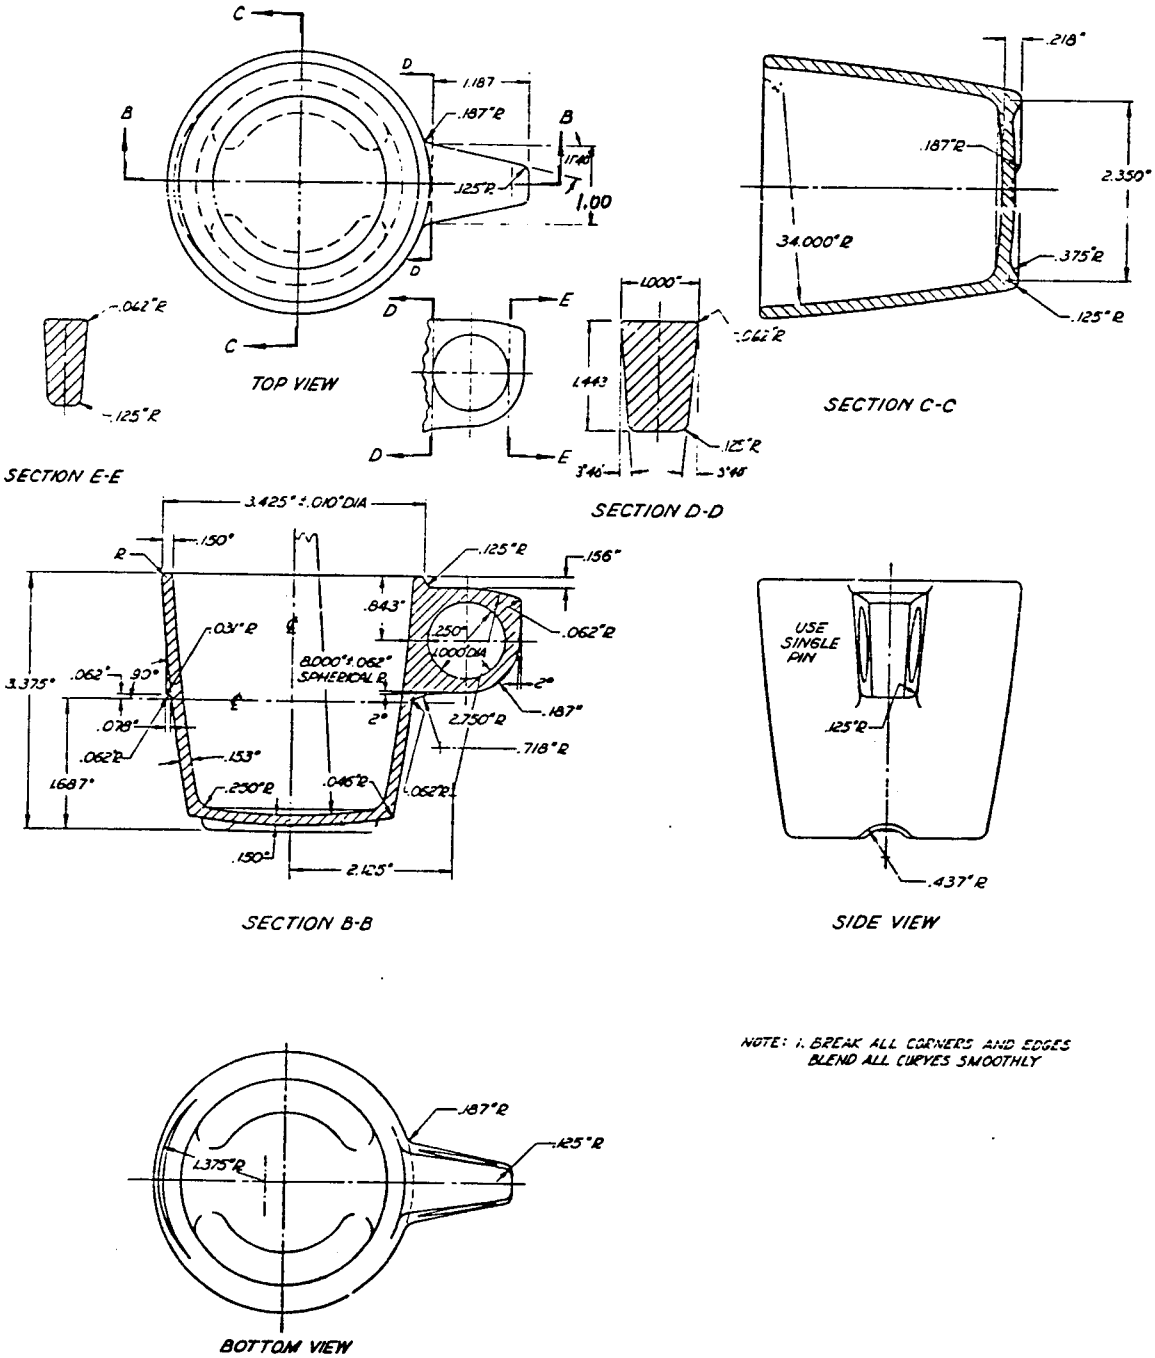


FIGURE 7 - Cup, drinking, 1-handle

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

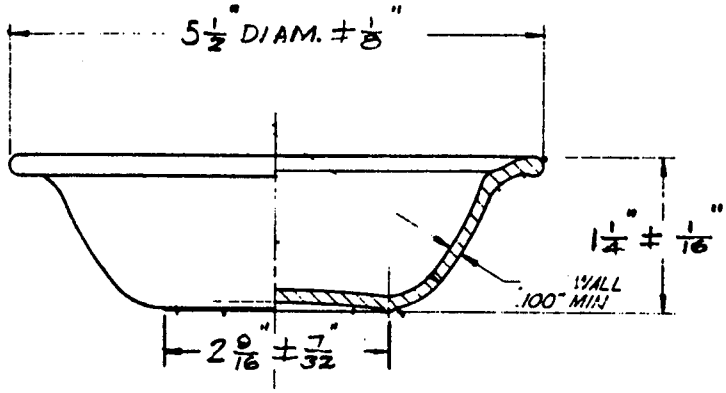

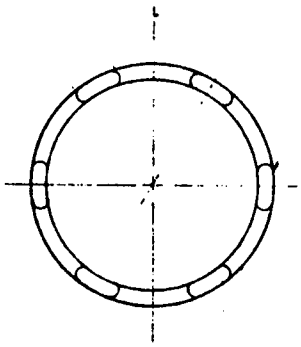


VIEW OF BOTTOM

FIGURE 8 - Bowl, Food Serving, Fruit

Capacity - 6-1/2 oz.± 1 oz.
Weight - 3 oz. minimum

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

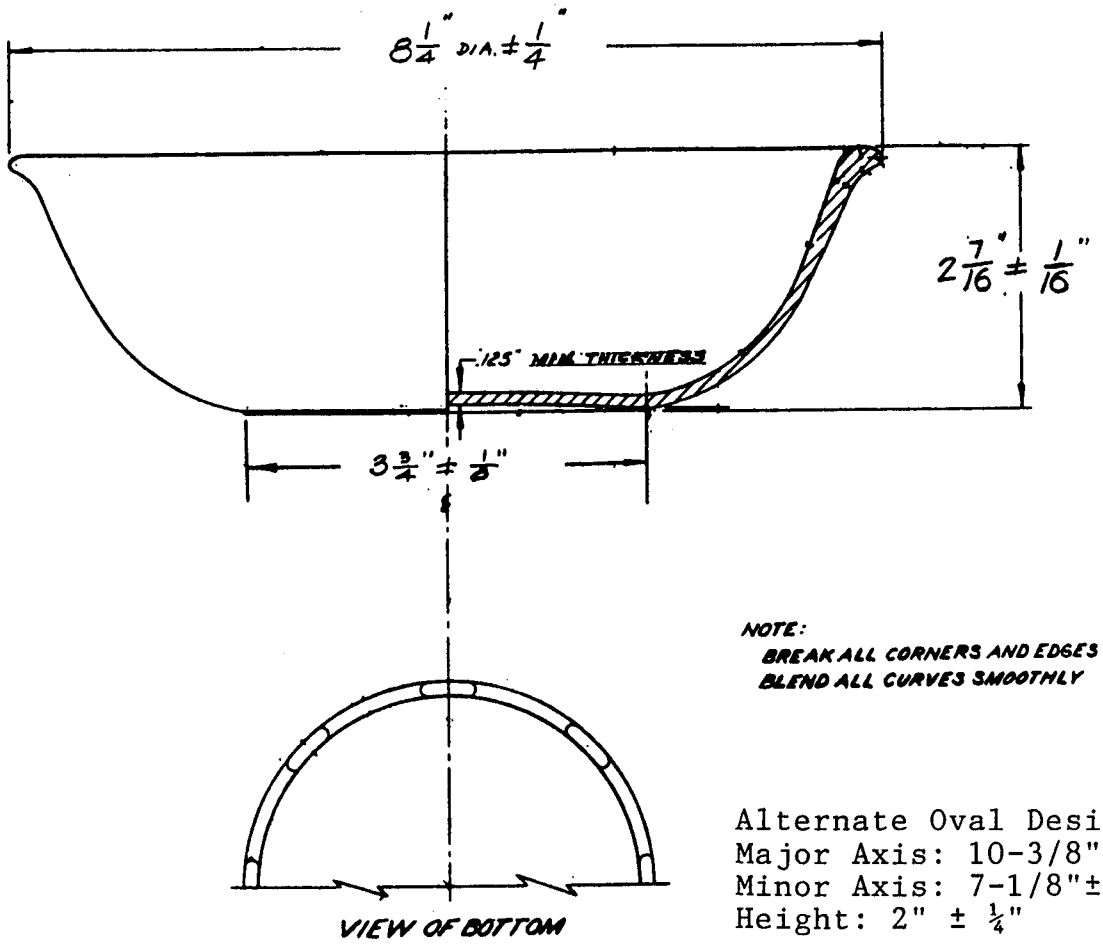

Alternate Oval Design
Major Axis: 10-3/8" ± 3/8"
Minor Axis: 7-1/8"± 5/16"
Height: 2" ± ¼"

FIGURE 9 - Dish, Food Serving, Vegetable

Capacity - 1 quart ± 3 oz.
Weight - 10 oz. minimum

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

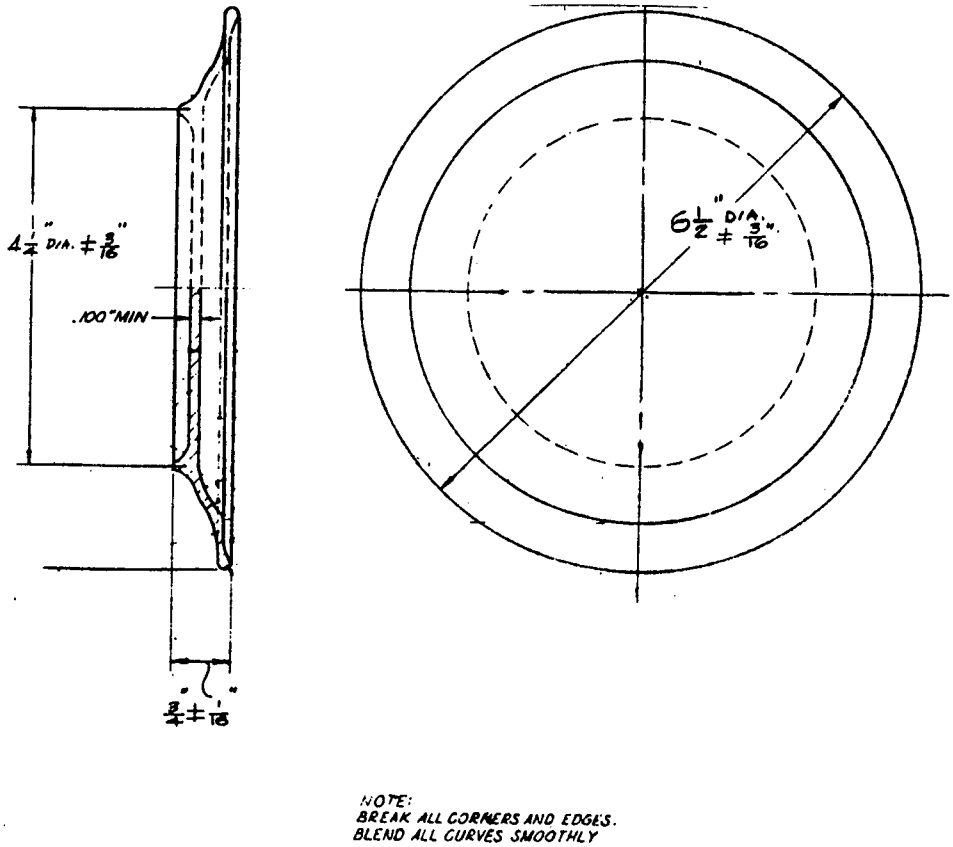


FIGURE 10 - Plate, Eating, Bread and Butter

Weight - 3 oz. minimum

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

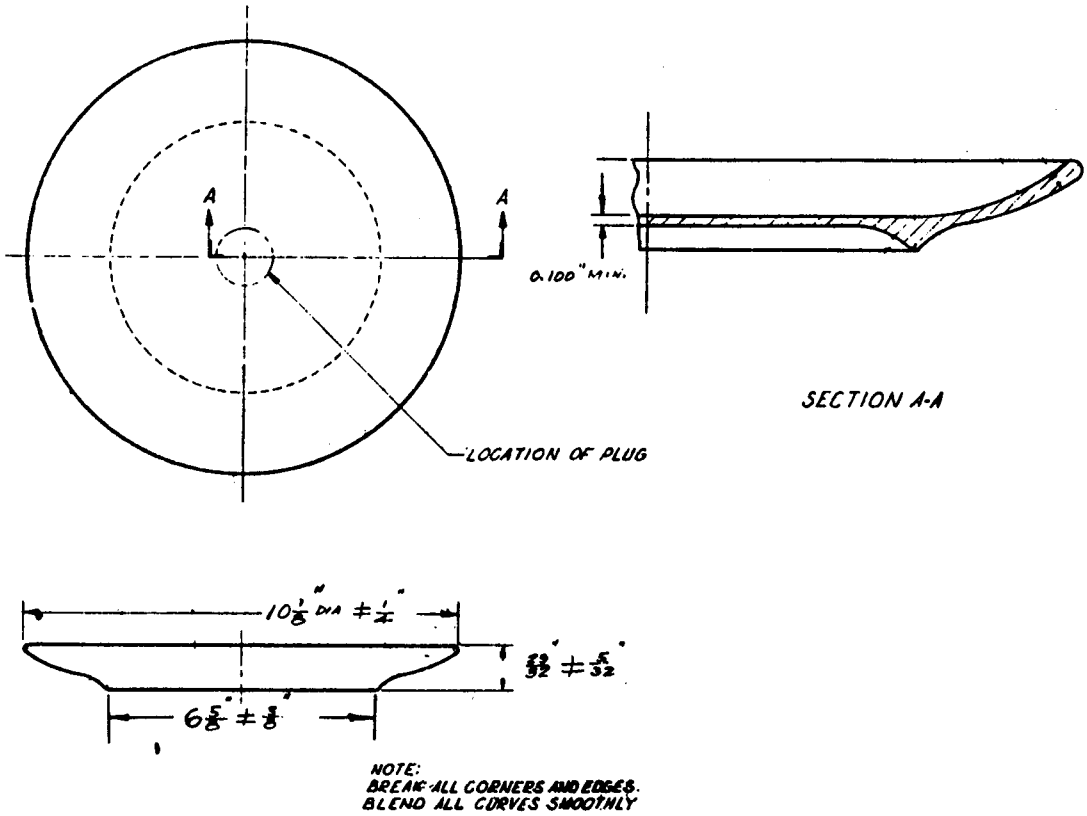


FIGURE 11 - Plate, Eating, Dinner

Weight - 9 oz. minimum

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

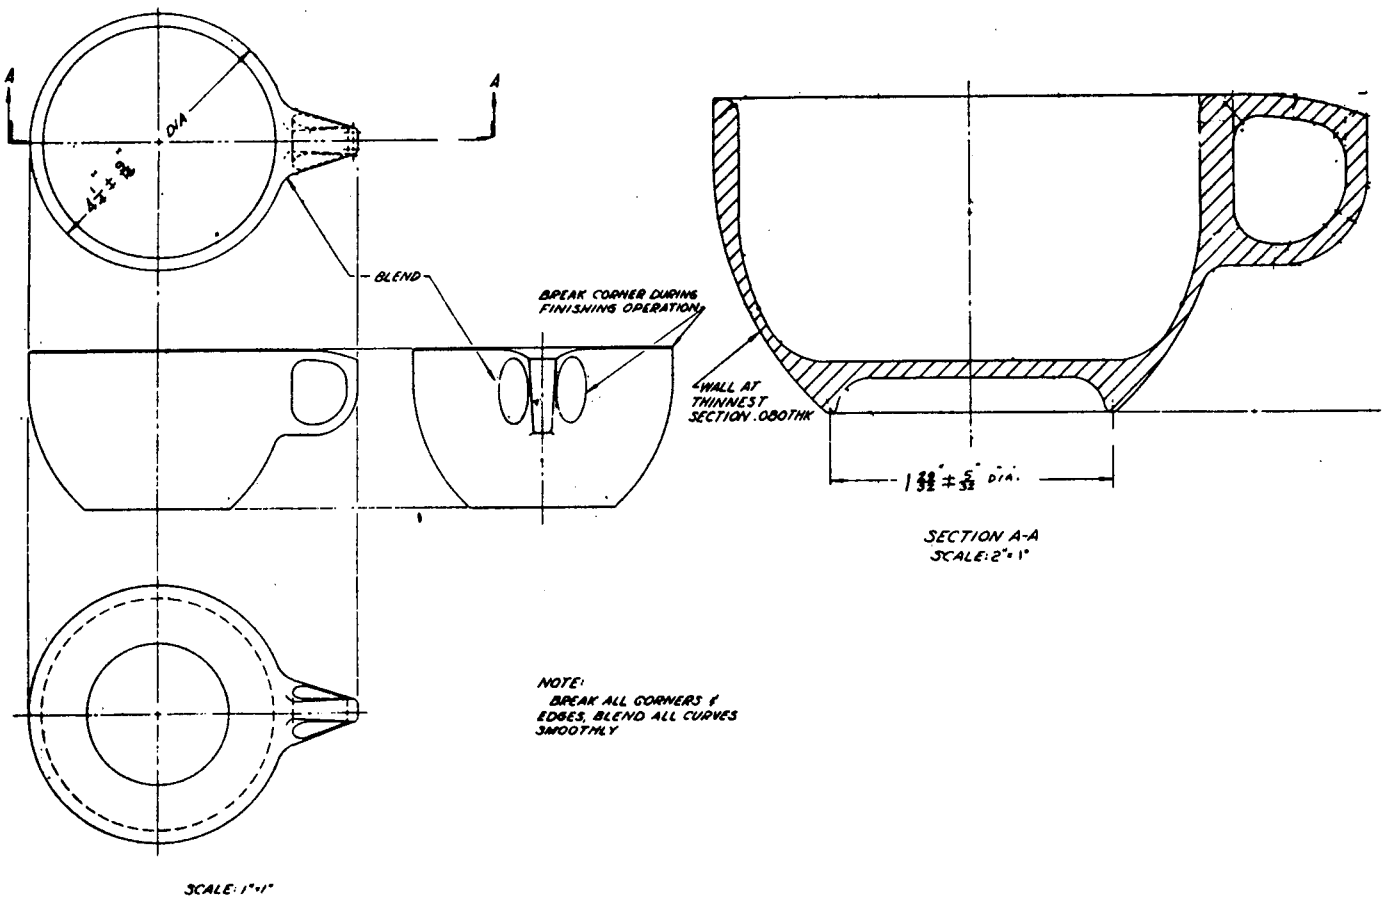


FIGURE 12 - Cup, Drinking, 8-ounce

Weight - 3-1/4 oz. minimum
Height - 2-9/32" ± 13/32"

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

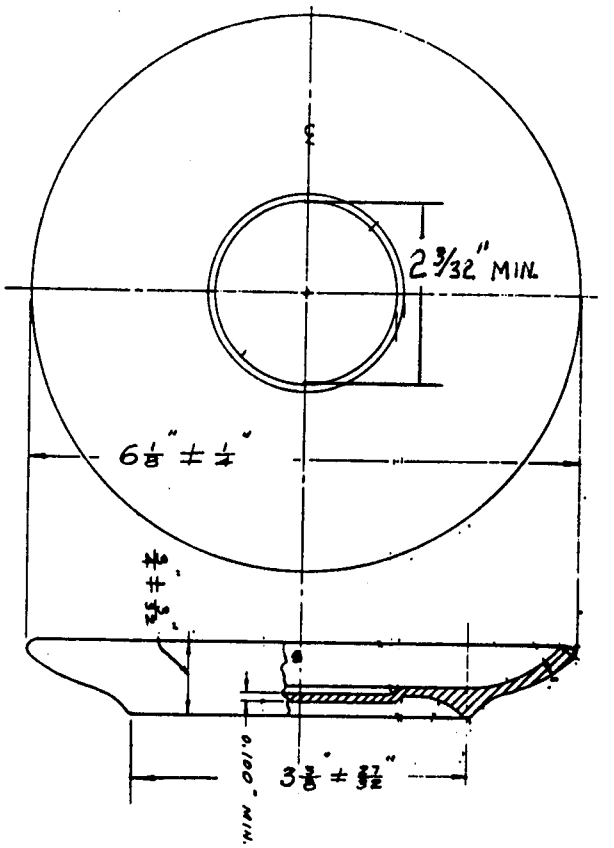


FIGURE 13 - Saucer, Cup

Weight - 3-3/8 oz. minimum

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.



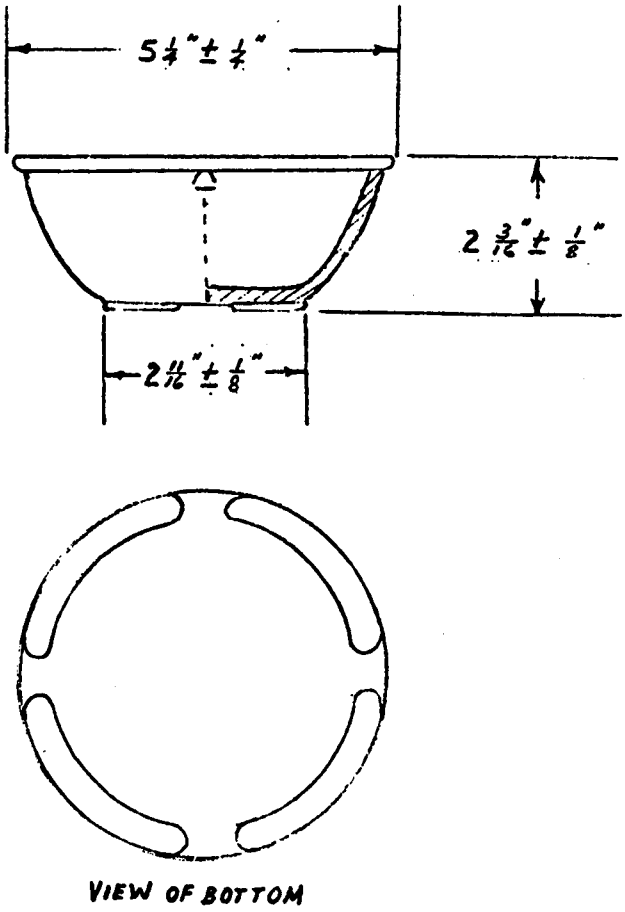


FIGURE 14 - Bowl, Eating, General Purpose, 16-ounce

Weight - 4 oz. ± 0.2 oz.
Minimum thickness - 0.090"
Note: Break all corners and edges
Blend all curves smoothly; Vented base; minimum of 3 equally spaced lugs

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.

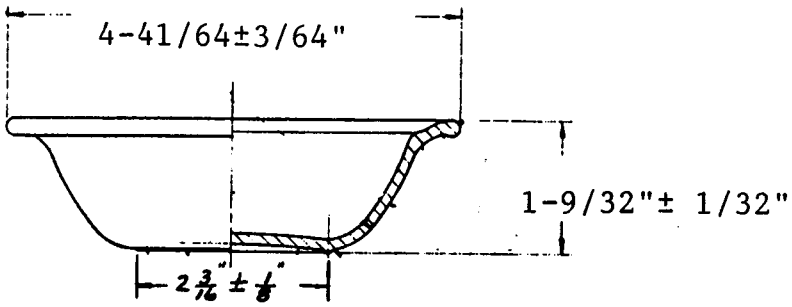

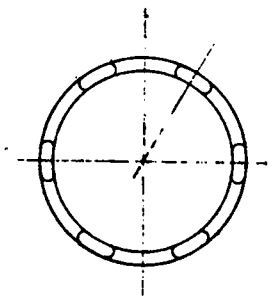

VIEW OF BOTTOM

FIGURE 15 - Bowl, Eating, Fruit, 4-1/2 ounce

Weight - 2.2 oz. ± 0.2 oz.
Minimum thickness - 0.090"

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:09Z
Check the source to verify that this is the current version before use.