RR-C-83C
January 7, 1974
SUPERSEDING
Int. Fed. Spec. RR-C-0083B
February 6, 1970
Fed. Spec. RR-C-83A
March 31, 1955

FEDERAL SPECIFICATION

CANS, MILK, STEEL TINNED

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers tinned steel milk cans used for transportation and storage purposes.

1.2 Classification.

1.2.1 Type and capacities. The milk cans shall be of one type and of the following capacities, as specified (see 6.1):

5 gallon (United States liquid measure)
10 gallon (United States liquid measure)

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Specification:

QQ-S-698 - Steel, Sheet and Strip, Low-Carbon.

Federal Standard:

Fed. Std. No. 123 - Marking for Domestic Shipment (Civilian Agencies).

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, D. C. 20402.

(Single copies of this specification and other Federal Specifications required by activities outside the Federal Government for bidding purposes are available without charge from Business Service Centers at the General Services Administration Regional Offices in Boston, New York, Washington, D.C., Atlanta, Chicago, Kansas City, MO, Fort Worth, Denver, San Francisco, Los Angeles, and Seattle, WA.

(Federal Government activities may obtain copies of Federal Specifications, Standards and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Standards:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.
MIL-STD-130 - Identification Marking of U. S. Military Property.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

FSC 8110

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:08Z
Check the source to verify that this is the current version before use.

Laws and Regulations:

21 CFR - Federal Food, Drug and Cosmetic Act and Regulations Promulgated Thereunder.

(The Code of Federal Regulations (CFR) and the Federal Register (FR) are on sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, D.C. 20402. When indicated, reprints of certain regulations may be obtained from the Federal agency responsible for the issuance thereof.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless a specific issue is identified, the issue in effect on date of invitation for bids or request for proposal shall apply.

National Motor Freight Traffic Association, Inc., Agent

National Motor Freight Classification.

(Application for copies should be addressed to the American Trucking Associations, Inc., Tariff Order Section, 1616 P Street, N.W., Washington, D.C. 20036.)

Uniform Classification Committee, Agent

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, Illinois 60606.)

3. REQUIREMENTS

3.1 Certification. Upon receipt of contract, the contractor shall, upon request, furnish the contracting officer with a certified statement that the cans furnished under this contract comply with all provisions of the Federal Food, Drug and Cosmetic Act as amended, and have been manufactured in accordance with the Food Additive Regulations promulgated under the Act.

3.2 Preproduction sample. Unless otherwise specified (see 6.1), the supplier shall furnish one complete can of each capacity specified in the contract or order as a sample for preproduction inspection in accordance with section 4. The sample may be either a preproduction item or a production item which meets the requirements of this specification. In either case, the approved sample shall be used as the standard for all production items manufactured to fulfill the terms of the contract. Approval of the preproduction sample shall not relieve the supplier of the responsibility to furnish cans in accordance with the requirements of this specification (see figure 1).

3.3 Material.

3.3.1 Sheet steel. Steel, used in the manufacture of the milk cans, shall be cold rolled commercial quality conforming to QQ-S-698 suitable for hot dip tinning; free from laminations, blisters, slivers, rolled-in scale, open seams, pits, ragged edges, holes, turned-down corners and any other defects affecting appearance or which may affect the serviceability.

3.3.2 Tin. The tin used for hot tinned process shall be not less than 98.00 percent pure tin.

3.4 Construction.

3.4.1 Can. The can shall be constructed of steel specified in 3.3.1. The bowl neck and breast shall be seamless drawn shell. The body shall be rolled from a flat sheet and resistance welded. The bottom shall be a shallow drawn shell. These three parts shall be resistance welded together, forming the container. The breast shall be reinforced with a resistance-welded metal hoop made of not less than 1-1/4-inches wide by 0.1045-inch thick, beveled-edge steel. The hoop shall be installed at the junction of the breast and the body, before or during the tinning operation. The use of special formed sections as bottom reinforcement is permissible. The sections shall be not less than 0.093-inch to 0.1875 by 2-1/8 inches for 5-gallon cans and 0.115 to 0.240-inch by 2-7/16-inches for 10-gallon cans, resistance-welded to form a hoop.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:08Z
Check the source to verify that this is the current version before use.

3.4.2 Handles. Each can shall be equipped with two stamped steel upright handles not less than 0.054-inch thick. The handles shall have a grip not less than 3 inches wide inside; shaped to permit the hand to be easily inserted, and without cutting or squeezing of the hand when the can is filled with liquid. The handles shall be welded to the breast of the can diametrically opposite each other and within the over-all diameter of the breast and bottom hoops. The handles shall withstand tests specified in 4.5.1.

3.4.3 Cover. Each can shall be equipped with a friction type umbrella cover made of a drawn steel cup securely spot welded, seam welded or fused during the tinning operation to a beaded (roll or light) top rim collar. Two holes approximately 1/4-inch diameter shall be punched directly opposite each other in the rim or collar. The finished cover shall fit snugly into the can.

3.4.4 Thickness. The cans shall be made of sheet steel having minimum thicknesses shown in figure 1.

3.4.5 Dimensions. Minimum dimensions for the cans shall be as specified in figure 1.

3.4.6 Weight. Minimum weights, for cans of each capacity, shall be as specified in figure 1.

3.5 Finish. The completely assembled can shall be tinned by the hot dip process. Covers shall be coated by the hot dip tinning process. Tin used in the process shall be as specified in 3.3.2. The entire inside and outside of the can and cover shall be uniformly coated with tin a minimum thickness of 0.001-inch. The tinned surface of the can and cover shall be free from bare or imperfectly coated spots, excessive scratches, serious abrasions or other defects affecting appearance or serviceability.

3.6 Marking for identification. The cans shall be marked in accordance with MIL-STD-130, except as follows: The can cylinder shall have die stamped prior to tinning, the letters "U.S.", the manufacturer's code, month and year, and date of fabrication.

3.7 Workmanship. The finished can shall be clean, well made and free from any defects which may affect the appearance or serviceability.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.2 Preproduction inspection. Preproduction inspection shall be applied to the samples when required in accordance with 3.2. Failure of the sample to pass the examination or one or more preproduction tests shall be cause for rejection. Unless otherwise specified (see 6.1), preproduction inspection shall consist of the examination in 4.4 and all tests in 4.5.

4.3 Sampling.

4.3.1 Lot. A lot shall consist of all cans submitted for inspection at the same time.

4.3.2 Sampling for tests. Each lot shall be sampled for the tests in 4.5.1, 4.5.4, 4.5.5 and 4.5.6 in accordance with level S-2 in MIL-STD-105. The AQL for tests shall be 4.0 percent defective.

4.3.3 Visual examination of end item. Sampling for this examination shall be according to level S-2 in MIL-STD-105. The AQL for defects shall be 4.0 percent defective.

4.4 Examination. Cans selected in accordance with 4.3.3 shall be examined for construction, materials, components and workmanship to determine compliance with the requirements of this specification. Any deviations from these requirements shall be cause for rejection.

4.5 Testing.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:08Z
Check the source to verify that this is the current version before use.

4.5.1 Test for handles. Handles shall show no signs of bending, breaking, or distortion when the load specified below is placed in or on the can and the can lifted by each handle.

Can capacity	Test load in pounds
5 gallon	80
10 gallon	160

The handles, located on the breast of the can, shall not interfere when rolling in a horizontal position on a flat surface.

4.5.2 Rigidity test. One can, as specified in 3.2, of each capacity, shall be filled with water to the capacity line shown in figure 1, and the cover replaced, securely. The can shall be dropped six times from a height of two feet onto a flat concrete, stone or brick floor, on angle, approximately 30 degrees from the vertical. Opening of seams, breaking of any part, cover dropping off or leakage, will constitute failure to meet specification requirements.

4.5.3 Test for leakage. After the rigidity test, the filled can shall be allowed to stand, with the cover off, for a period of six hours. Any sign of leakage will be failure to meet specification requirements.

4.5.4 Stability test. Covered cans, filled with water to capacity line as shown in figure 1, shall not tip over or spill the contents when placed in an upright position on a flat inclined plane, which forms an angle of 30 (plus or minus 5) degrees with the horizontal.

4.5.5 Cover test. The cover cup shall fit snug into the neck of the can to prevent spilling of liquid contents, when the filled can is filled as specified in 4.5.4.

4.5.6 Capacity test. Capacity shall be determined by measuring the liquid contents with a standard measure to the capacity line shown in figure 1.

5. PREPARATION FOR DELIVERY

5.1 Packaging. Unless otherwise specified, commercial packaging is acceptable under this specification.

5.2 Packing. Packing shall be level A, B or C, as specified (see 6.1).

5.2.1 Level A and B. The cover of each milk can shall be secured, by passing an annealed wire, minimum 20-gage, through the opening of one handle retainer on the body of the can, through the holes of the cover down through the handle retainer on the opposite side of the can, twisting the two ends of the wire tightly together, removing any slack and turning the twisted ends formed, down parallel with the wiring.

5.2.2 Level C. The cans shall be packed to insure carrier acceptance and safe delivery at destination at lowest rates, in containers complying with the Uniform Freight Classification or National Motor Freight Classification, as applicable.

5.3 Marking. In addition to any special markings required in the procurement documents, marking for identification and shipment shall be in accordance with Fed. Std. No. 123 for civil agencies or MIL-STD-129 for military agencies, as applicable.

6. NOTES

6.1 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number and date of this specification.
(b) Capacity of can required (see 1.2).
(c) When preproduction sample is not required (see 3.2).
(d) Selection of applicable level of packing required (see 5.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:08Z
Check the source to verify that this is the current version before use.

MILITARY INTERESTS:

Custodians:
None


Review Activities:
DOD waives coordination

CIVIL AGENCY COORDINATING ACTIVITIES

USDA-APS
VA-DMS

Preparing Activity:

GSA-PSS

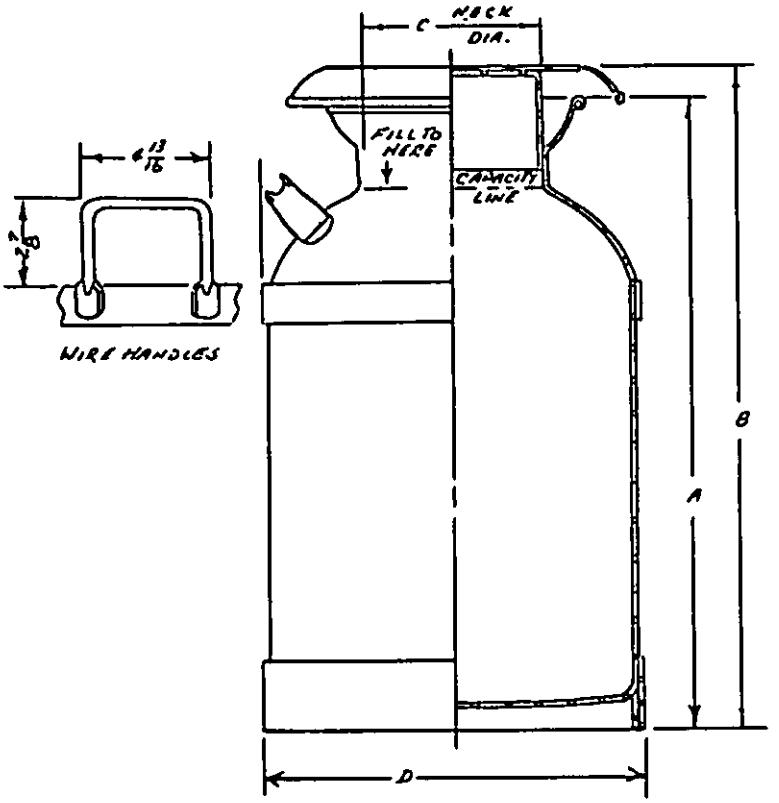

DETAIL	10 GAL	5 GAL
COVER RING	.059	.059
COVER CUP	.047	.047
BREAST	.047	.047
CYLINDER	.047	.035
BOTTOM	.059	.059
HANDLES	.059	5/16 DIA
BREAST HOOP	.105"	.105"
BOTTOM HOOP	.089	.089
BREAST WIRE	NO. 10	NO. 10

MIN. DIM.	10 GAL.	5 GAL.
A	23 1/2	19 7/8
B	24 1/2	20 1/8
C	7 1/4	7 1/2
D	13	10 1/2
WT.	25 lbs.	16 lbs.

FIGURE 1.

Orders for this publication are to be placed with General Services Administration, acting as an agent for the Superintendent of Documents. See section 2 of this specification to obtain extra copies and other documents referenced herein. Price 10 cents each.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:08Z
Check the source to verify that this is the current version before use.