MIL-C-8956A

2 December 1970

Superseding
MIL-C-8956(ASG)
1 July 1967

MILITARY SPECIFICATION

CLAMPS, LOOP, TUBE SUPPORT

This specification is mandatory for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope - This specification covers tube support loop clamps.

1.2 Classification - Clamps shall be of the following types and classes (see 6.2):

Type	Class	Description
I	A	Plain, aluminum alloy, 300° F
I	B	Plain, corrosion-resistant steel, 1,200° F
II	A	Fuel-weather-resistant cushion, aluminum alloy, 212° F
II	B	Fuel-weather-resistant cushion, corrosion-resistant steel, 212° F
III	B	Intermediate temperature, fluid-resistant cushion, corrosion-resistant steel, 500°F
IV	B	High temperature cushion, corrosion-resistant steel, 1,200° F
V	A	Polytetrafluoroethylene cushion, aluminum alloy, 300° F
V	B	Polytetrafluoroethylene cushion, corrosion resistant steel, 450° F

FSC 5340

Source: https://assist.dla.mil -- Downloaded: 202610-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 The following documents, of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

SPECIFICATIONS

Federal

L-P-403	Plastic Molding Material, Polytetrafluoroethylene (TFE Fluorocarbon)
L-P-410	Plastic, Polyamide (Nylon), Rigid, Rods, Tubes, Flats, Molded and Cast Parts
QQ-A-250/5	Aluminum Alloy, Alclad 2024, Plate and Sheet
ZZ-R-765	Rubber, Silicone, Low-and High-Temperature and Tear Resistant
PPP-B-566	Boxes, Folding, Paperboard
PPP-B-576	Box, Wood, Cleated, Veneer, Paper Overlaid
PPP-B-585	Box,Wood, Wirebound
PPP-B-591	Box, Fiberboard, Wood-Cleated
PPP-B-601	Box, Wood, Cleated-Plywood
PPP-B-621	Box, Wood, Nailed and Lock Corner
PPP-B-636	Box, Fiberboard
PPP-B-640	Box, Fiberboard, Corrugated, Triple-Wall
PPP-B-665	Box, Paperboard, Metal Stayed (Including Stay Material)
PPP-B-676	Box,Setup

Military

MIL-P-116	Preservation, Methods of
MIL-E-5272	Environmental Testing, Aeronautical and Associated Equipment, General Specification for
MIL-H-5606	Hydraulic Fluid, Petroleum Base, Aircraft, Missile, and Ordnance
* MIL-T-5624	Turbine Fuel, Aviation, Grades JP-4 and JP-5
MIL-H-6088	Heat Treatment of Aluminum Alloys
MIL-S-6721	Steel, Corrosion - and Heat-Resistant (Chemically Stabilized) Plate, Sheet and Strip
MIL-T-6845	Tubing, Steel, Corrosion-Resisting (304), Aerospace Vehicle Hydraulic System, 1/8 Hard Condition
MIL-S-6855	Synthetic Rubber Sheets, Strips, Molded or Extruded Shapes
MIL-L-7808	Lubricating Oil, Aircraft Turbine Engine, Synthetic Base
MIL-G-23652	Gasket and Packing Material, Petroleum and Phosphate Ester, Fluid Resistant

Source: https://assist.dla.mil -- Downloaded: 202610-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Military (Cont)

MIL-L-23699	Lubricating Oil, Aircraft Turbine Engines, Synthetic Base
MIL-M-24041	Molding and Potting Compound, Chemically Cured, Polyurethane (Polyether-Based)
MIL-R-25897	Rubber, High-Temperature, Fluid-Resistant

STANDARDS

Federal

FED. TEST METHOD STD. NO. 406	Plastics: Method of Testing
FED. TEST METHOD STD. NO. 601	Rubber: Sampling and Testing

Military

MIL-STD-105	Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	Marking for Shipment and Storage
MIL-STD-831	Test Reports, Preparation of
MS21103	Clamp, Plain, Support, Loop, Aircraft, Type I, Class A and B
MS21104	Clamp, Loop, Cushioned, Wedge, Fuel-Weather Resistant 212°F, Type II, Class A and B
MS21105	Clamp, Loop, Cushioned, Wedge, Fluid Resistant, 500°F, CRES, Type III, Class B
MS21106	Clamp, Loop, Cushioned, 1200°F, CRES, Type IV, Class B
MS21122	Clamp, Loop, Cushioned, Wedge, Polytetrafluoroethylene, Type V, Class A and B

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

3. REQUIREMENTS

* 3.1 First article - Before production is commenced, a sample of the completely fabricated Clamp shall be submitted or made available to the contracting officer or his authorized representative for approval in accordance with 4.3. The approval of the first article sample authorizes commencement of production but does not relieve the supplier of responsibility for compliance with all applicable provisions of this specification. The first article sample shall be manufactured in the same facilities to be used for the manufacture of the production item.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

3.2 Materials -

3.2.1 Band material -

3.2.1.1 Class A - Class A clamp bands shall be formed from annealed aluminum alloy conforming to QQ-A-250/5 and subsequently heat treated to T4 temper in accordance with MIL-H-6088. Recladding of edges and ends is not required.

3.2.1.2 Class B - Class B clamp bands shall be formed from MIL-S-6721 corrosion-resistant steel in the annealed state.

3.2.2 Cushioning materials -

3.2.2.1 Type II - Cushioning material for the type II fuel/weather-resistant clamps shall be an elastomer or other nonmetallic material. The elastomers shall conform to class 1 grade 50 of MIL-S-6855. The nonmetallic cushioning material shall conform to L-P-410, weather-resistant, wear-resistant, heat-stabilized polyhexamethylene adipamide or type I of MIL-M-24041.

3.2.2.2 Type III - Cushioning material for the type III intermediate temperature fluid-resistant clamps shall be an elastomer or other nonmetallic material conforming to MIL-G-23652 or MIL-R-25897.

3.2.2.3 Type IV - Cushioning material for the type IV high temperature clamps shall be stainless steel.

3.2.2.4 Type V - Cushioning material for the type V clamp shall be polytetrafluoroethylene extruded from material conforming to L-P-403.

3.3 Design and construction - The sizes and dimensions shall be as specified on MS21103 through MS21106, MS21122, or other applicable military standards (see 6.2). Clamps shall be formed through a minimum of 270 degrees of the mandrel circumference. Normal spring-back of the clamp from this formed condition will be acceptable.

3.4 Finish - All surfaces shall have a smooth finish and be free from burrs and sharp edges. The inside edges of the clamp band shall be rolled or provided with a radius to eliminate sharp edges which would cut the clamp cushion or mark tubing.

3.5 Identification of product - Each clamp shall be marked with the complete MS part number in accordance with the applicable drawings. The manufacturer's identification shall be placed in some convenient location of the clamp.

3.6 Workmanship - Clamps shall be of uniform quality and free from burrs or slivers or other defects which might affect their service.

Source: https://assist.dla.mil -- Downloaded: 202610-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

3.6.1 The slitting operation shall be performed in a manner that minimizes the tearing of the clad protection at the edge of the strips.

3.6.2 Rerolling shall be performed, following the slitting operation, to remove twist and camber.

* 3.7 Performance - The clamps shall meet the performance requirements specified in section 4 when subjected to the applicable tests.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection - Unless otherwise specified * in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Classification of inspections - The inspection of clamps shall be classified as follows:

*	(a) First article inspection	(4.3)
	(b) Quality conformance inspection	(4.4)

4.3 First article inspection - When specified (see 6.2), and * as soon as practicable after award of contract or order, first article samples shall be separately packaged and forwarded to testing activity to be indicated by preparing activity.

* 4.3.1 Clamps - Four clamps, of each type and class specified on the contract or order (see 6.2), shall be subjected to the examinations specified in 4.6.1.1.

* 4.3.2 Cushioning material - Cushioning material test specimens shall consist of the following. Samples shall be subjected to the applicable tests specified in 4.6.2.2.

(a)	Elastomers:	12 pieces 6 by 6 inches by 0.075 inch platen sheets 1 piece 6 by 6 inches by 0.030 platen sheet 6 pieces 3 inches long of clamp cushion 4 disks 1.129 ± 0.001 by 0.5 ± 0.005 inch
(b)	Plastics or other nonmetallic:	12 pieces 10 by 10 inches by 0.125 inch platen sheets 6 pieces 3 inches long of clamp cushion

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Samples shall be identified with the name of the manufacturer and the manufacturer's production code or compound number. The manufacturer shall certify that the sample specimens are identical in composition and state of cure to the material supplied on the clamps.

* * 4.3.3 Identification of samples - Unless otherwise specified, as soon as practicable after award of contract or order, first article samples shall be separately packaged and forwarded as specified in the contract or order (see 6.2). Samples shall be plainly identified by securely attached durable tags marked with the following information:

Samples for first article inspection
MIL-C-8956
CLAMP, LOOP, TUBE SUPPORT
MS Part Number
Manufacturer's part number
Name of manufacturer

4.4 Quality conformance inspections.- Quality conformance inspections shall consist of sampling plans A and B (see 4.4.2 and 4.4.3).

4.4.1 Inspection lot - An inspection lot shall consist of all clamps of a particular size, type, and class and made under essentially the same conditions and presented for acceptance at the same time.

4.4.2 Sampling plan A -

4.4.2.1 Sampling procedure - A random sample shall be selected from each inspection lot in accordance with MIL-STD-105, inspection level II, of table titled "Sample size code letters" for ordinary inspection. The acceptable quality level (AQL) shall be as specified in table I.

TABLE I. Classification of defects, sampling plan A

Inspection	AQL (percent defective)	
	Major	Minor
Examination of product.	1.0	4.0
(a) Dimensions:		
(1) Loop diameter (max.)	X	
(2) Width (min.)	X	
(3) Thickness (min.)	X	
(4) Centerline of loop to centerline of screw hole (min.)	X	
(5) All other dimensions		X
(b) Materials	X	
(c) Workmanship and marking		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

4.4.2.2 Inspections - The sampling plan A inspection shall consist of examination of product, as described under 4.6.1.1.

4.4.3 Sampling plan B -

4.4.3.1 Sampling procedure - A random sample shall be selected from each inspection lot in accordance with MIL-STD-105, inspection level S-2, acceptance number zero. Samples of cushioning material shall consist of one 6- by 6- by 0.075 - inch platen sheet molded from the sample lot. In addition, four compression set disks shall be cut from material molded from the sample lot.

* 4.4.3.2 Inspections - The sampling plan B inspection shall consist of the closure test (4.6.2.1.3) for clamps. The cushioning material shall be tested for conformance to original properties, hardness, tensile strength, and specific gravity (see 4.6.2.2.1).

4.4.4 Resubmitted inspection lots - The resubmitted lots requirement of MIL-STD-105 shall apply, except that a resubmitted inspection lot shall be inspected by the contractor under supervision of the procuring activity using tightened inspection. If the original acceptance number was zero, a sample size represented by the next higher sample size code letter shall be chosen with the acceptance number remaining zero. Before an inspection lot is resubmitted, full particulars concerning the cause of previous rejection and the action taken to correct the defects found in the inspection lot shall be furnished by the contractor to the procuring activity.

4.5 Test conditions -

4.5.1 Cushion material specimens - The number, form, and dimensions of specimens shall be as specified in the applicable test method.

4.5.2 Atmospheric conditions - Unless otherwise specified, all tests shall be performed at an ambient room termperature of 20° to 30° C (68° to 86° F), 30 to 80 percent relative humidity, and a barometric pressure of 24 to 31 inches of mercury. The test area shall be free from drafts.

4.6 Inspectiom methods -

4.6.1 Examinations -

* 4.6.1.1 Examination of product - Clamps, both before and after testing, shall be carefully examined to determine compliance with the requirements of this specification and applicable standards with respect to materials, workmanship, form, marking, and dimensions. Any variations beyond the dimensions, plus allowable tolerances, shall be classified as a major or minor defect, as indicated in table I.

Source: https://assist.dla.mil -- Downloaded: 202610-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

4.6.1.2 Examination of preservation, packaging, packing, and marking - Preparation for delivery shall be examined for conformance to section 5.

4.6.2 Tests -

4.6.2.1 Clamp tests -

4.6.2.1.1 Vibration - Three clamps of each representative type, and class as shown in table II shall be installed as shown on figure 1, securing a tube of appropriate size on a metal plate securely mounted on a vibration table and vibrated in accordance with the requirements of Procedure XIV of MIL-E-5272. Tests shall be performed as specified in table II. Tubing shall conform to MIL-T-6845 or equivalent and shall contain hydraulic fluid per MIL-H-5606 or water. After vibration under the conditions of table II, the clamps and cushions shall be removed and visually inspected. Deterioration, fraying, cracking of clamp welds, damage to tubing, or separation of cushion material from clamp band shall be cause for rejection.

TABLE II. Vibration requirements

Temperature	Type II, classes A and B	Type III, class B	Type IV, class B	Type V, class A	Type V, class B
Low	-65°F	-65°F	-65°F	-65°F	-65°F
Room	70°F	70°F	70°F	70°F	70°F
High	212°F	500°F	1,200°F	300°F	450°F

4.6.2.1.2 Corrosion - Two clamps each of the representative sizes of each type and class, except for type I, shall be subjected to salt spray test Procedure I of MIL-E-5272.


* 4.6.2.1.3 Closure - Four clamps shall be installed on a bar having a diameter equal to the nominal tube outside diameter within ±.001 inch. The gap (G) between the clamp legs, at the attachment screw holes shall meet within specified tolerance limits; the holes shall be in alignment within 0.01 inch and the clamps shall be flat within 0.008 inch through the clamp width and circumference.

4.6.2.2 Cushion material tests -

4.6.2.2.1 Original properties - The original properties of the cushion material, tensile strength, specific gravity, and hardness shall be determined in accordance with the Federal Test Method Standards and Method numbers specified in MIL-G-23652, MIL-R-25897, MIL-S-6855, L-P-410, MIL-M-240.1 (type I), or L-P-403, as applicable.

Source: https://assist.dla.mil -- Downloaded: 202610-17T11:46Z
Check the source to verify that this is the currentversion before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

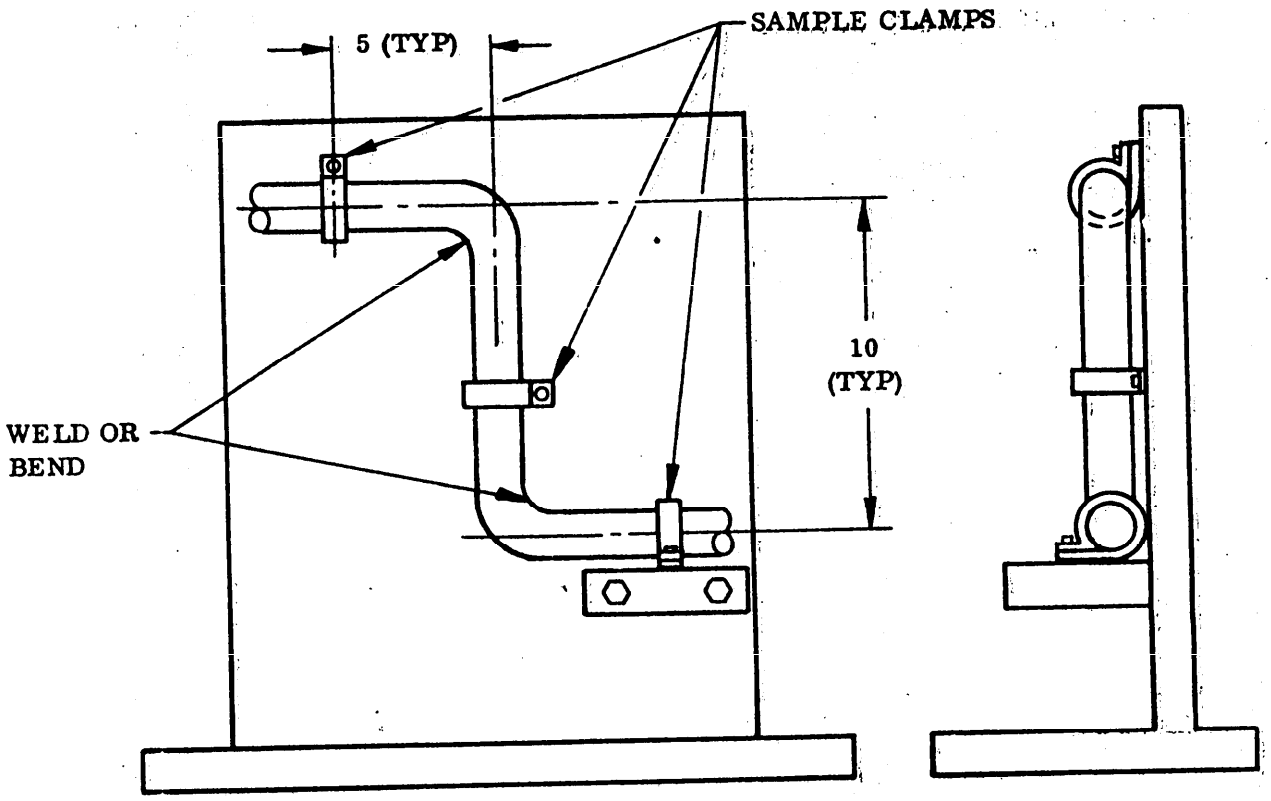

DIMENSIONS IN INCHES
TOLERANCES ±0.06

FIGURE 1. Vibration test jig

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

4.6.2.2.2 Heat aging - Three samples of the cushion material conforming to the dimensions of the tensile test specimen and two samples of the shape used on the clamp, 3 inches in length, shall be subjected to the heat-aging temperature and exposure time as specified in the applicable specifications (see 4.6.2.2.1). Tensile and hardness tests on the heat-aged tensile specimens shall be made as specified in 4.6.2.2.1. The two 3-inch-long samples shall be bent in an 180-degree arc around a round rod with a diameter twice the cushion material thickness, without breaking or cracking the material.

4.6.2.2.3 Brittleness - Two samples of the cushion material of the configuration used on the clamp, 3 inches in length, shall be subjected to the time-temperature requirements as specified in the spplicable specification. The specimens shall be bent in an 180-degree arch around a round rod with a diameter twice the cushion material thickness, without breaking or cracking the material.

4.6.2.2.4 Weathering - Three samples of the elastomeric cushion material, 0.030 inch thick in the shape of the tensile specimens shall be tested in accordance with Federal Test Method Standard No. 601, Method No. 7311. Specimens shall be stretched to 10 percent elongation. The stretched samples shall be exposed for 100 hours in the weathering unit and then subjected to the tensile test specified in MIL-S-6855.

4.6.2.2.5 Tear resistance - Three cushion material samples shall be tested in accordance with Method 4211 of Federal Test Method Standard No. 601 or Method 1121 of Federal Test Method Standard No. 406, as applicable.

4.6.2.2.6 Compression set - Only elastomeric material shall be subjected to the compression set test in accordance with Method 3311 of Federal Test Method Standard No. 601.

4.6.2.2.7 Fluid immersion - The type III samples, as follows, shall be immersed in an aromatic fuel, type JP-4 of MIL-T-5624, or MIL-L-23699 oil, or equivalent:

(a) Three samples of cushion material conforming dimensionally to the tensile specimens
(b) Two samples of cushion material 1 by 2 inches that are used to measure volumetric expansion
(c) Two samples of the clamp cushion 3 inches long to be used in the bending test
(d) Two samples of cushion material 1 by 2 inches shall be immersed in a nonaromatic fuel

Source: https://assist.dla.mil -- Downloaded: 202640-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

The ratio of test fluid to test material shall be approximately 40 ml./gm. Test containers shall be glass and tightly stoppered to maintain an airtight seal for the duration of the test. At the end of the test period, the samples shall be removed from the fluid, immediately blotted dry and tested, to the sub-paragraphs (b), (c) and (d). The clamp cushion test samples, following the dry-out period, shall be subjected to the flat bend test where they are bent in an 180-degree arc over a rod with a diameter twice the cushion thickness.

4.6.2.2.8 Oil resistance - Type II cushion specimens shall be tested for 168 hours in MIL-H-5606 oil at 180°F, and in MIL-L-7808 and MIL-L-23699 oils at 212°F. Type III cushion specimens shall be tested for 168 hours in MIL-L-7808 and MIL-L-23699 oils at 350°F. Each oil test shall be performed in new oil. Tests shall be performed in either an aluminum block or oil bath. Aging of specimens shall be performed in clean 39-mm. (OD) by 300-mm. pyrex glass test tubes fitted with two-hole cork stoppers. Each stopper shall be fitted with two lengths of 8-mm. pyrex glass tubing (chimneys), one 3 inches in length, the other 5 inches in length. The 3-inch chimney shall extend through and 1/2 inch above the top of the stopper. The 5-inch chimney shall extend through and 3-1/2 inches above the top of the stopper. The test tubes shall be inserted into the aluminum block or oil bath in such a manner that the fluid level in the test tubes shall be approximately 1-5/8 inches above the heating unit of the aluminum block or the surface of the oil bath. This distance shall not be measured from the top of the aluminum block or covering of the oil bath. Four dumbbell specimens shall be tested. Only two specimens shall be aged in a single test tube, one each shall be suspended at depths of 1 inch and 2 inches below the surface of the fluid. For each test, 140 ml. of oil shall be used. The measurement of specimen depth in the fluid shall be made between the top edge of the specimen and the fluid level. Care shall be taken to prevent contact of specimens with each other or the wall of the test tube. After aging and prior to physical property determinations, the specimens shall be removed from the hot fluid and cooled 30 minutes in fresh fluid. Tensile strength tests shall be performed as specified in 4.6.2.2.1. Volume change shall be determined in accordance with Fed. Test Method Std. No. 601, Method 6211. Hardness change shall be measured in accordance with Fed. Test Method Std. No. 601, Method 3021.

5. PREPARATION FOR DELIVERY

* 5.1 Preservation and packaging - Shall be Level A or C as specified (see 6.2).

* 5.1.1 Level A - Clamps shall be preserved and packaged in accordance with Method III of MIL-P-116. Unless otherwise specified clamp of one size, type and class shall be packaged in multiples of 10, with a maximum of 100 per package. Unit containers shall conform to Specification PPP-B-566, PPP-B-665, PPP-B-676 or PPP-B-636. Box closures shall be in accordance with the appendix to the applicable box specifications.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

* 5.1.2 Level C - Preservation and packaging shall be sufficient to afford physical protection against damage during shipment from the supply source to the first receiving activity for immediate use. This level may conform to the supplier's commercial practice when such meets the requirement of this level.

* 5.2. Packing - Shall be level A, B or C as specified (see 6.2.).

* 5.2.1. Levels A and B - Clamps packaged as described in 5.1 shall be packed in boxes conforming to any one of the following specifications for the level specified.

SPECIFICATION	TYPE OR CLASS	
	LEVEL A	LEVEL B
PPP-B-576	Class 2	Class 1
PPP-B-585	Class 2 or 3	Class 1
PPP-B-591	Class 2	Class 1
PPP-B-601	Overseas	domestic
PPP-B-621	Class 2	Class 1
PPP-B-636	Weather resistant	domestic
PPP-B-640	Class 2	Class 1

Boxes shall be closed strapped or banded in accordance with the applicable box specification or appendix thereto for the level specified. Gross weight of wood, wood cleated, and triple wall boxes shall not exceed 200 lbs. Gross weight of PPP-B-636 boxes shall not exceed the weight limitation of the box specification.

* 5.2.2 Level C - clamps packaged as specified in 5.1 shall be packed in a manner to insure carrier acceptance and safe delivery at destinations. Containers shall conform to the applicable rules and regulations applicable to the mode of transportation.

5.3 Marking - Marking of interior packages and exterior shipping containers shall be in accordance with MIL-STD-129.

6. NOTES

6.1 Intended use - The clamps are intended for use on rigid tubing, or loose, insulated electrical cables. Plain clamps are intended for use where lowest bonding resistance is required; cushioned clamps may be used within the temperature classifications established. Where practicable, clamps shall be used to connect similar materials.

* 6.2 Ordering data - Procurement documents should specify:

(a) Title, number, and date of this specification.
(b) Type and class of clamp by MS part number.
(c) Data requirements, and where first article samples are to be forwarded (see 4.3.1, 4.3.3, and 4.3.4).

Source: https://assist.dla.mil -- Downloaded: 202610-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

(d) Quantity
(e) Selection of applicable levels of preservation packaging and packing required (see section 5).

* 6.2.1 Contracts or orders should specify the following provisions for first article inspection.

* 6.2.1.1 Whether first article inspection is required - When a contractor is in continuous production of the clamps from contract to contract, consideration should be given to waive the first article inspections. If inspection is required, indicate:

(a) Where the first article inspection is to be conducted (at the contractor's plant or Government or commercial laboratory).

(b) That the approval of first article samples or the waiving of the first article inspection shall not relieve the contractor of his obligation to fulfill all other requirements of the specification and contract.

* 6.3 Data - For the information of Contractors and Contracting Officers, any of the data specified in (a) subparagraphs below, (b) applicable documents listed in Section 2 of this specification, or (c) referenced lower-tier documents need not be prepared for the Government and shall not be furnished to the Government unless specified in the contract or order. The data to be furnished shall be listed on DD Form 1423 (Contractor Data Requirements List), which shall be attached to and made a part of the contract or order.

* 6.3.1 First article data - When first article samples are submitted (see 6.2), they should be accompanied by a certified inspection report in accordance with MIL-STD-831 showing that the manufacturer's product satisfactorily conforms to this specification. The test report shall include, as a minimum, the following:

(a) Report of all inspections graphically presented when possible, together with a detailed statement indicating compliance or extent of noncompliance with all requirements of this specification and applicable military standard referring specifically to paragraph numbers. Wherever a requirement is considered to be not applicable, the report should so state.

(b) Dated drawing which completely describes the manufactures product by specifying all dimensions, including dimensions of the clamp in the closed position, and tolerances, types of material selected, and heat treatment. The manufacturer's part number for each size shall be included on the drawing.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

(c) Diagrams of inspection set-ups. A complete description of inspection equipment and inspection procedures.

(d) Reproducible outline and description of inspection conditions. Where inspections specified in this specification are not considered applicable, the reason, and the substituted inspection should be clearly described.

(e) Copies of inspection log sheets.

(f) Photographs when available.

* 6.4 Marginal indicia - The margins of this specification are marked to indicate where changes, deletions, or additions to the previous issue have been made. This is done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Figures are not so marked. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content as written, irrespective of the marginal notations and relationship to the last previous issue.

Custodians:
Navy - AS
Air Force - 82
Army - AV

Reviewer activities:
Navy - AS
Air Force - 82
Army - AV

Preparing activity:
Navy - AS

Project No. 5340-0879

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 22-R255

INSTRUCTIONS: This sheet is to be filled out by personnel, either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments and suggestions submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or serve to amend contractual requirements.

SPECIFICATION

MIL-C-8956A, CLAMPS, LOOP, TUBE SUPPORT

ORGANIZATION

CITY AND STATE

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO *(If "yes", in what way?)*

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity - Optional)*

DATE

DD FORM 1 JAN 64 1426

REPLACES EDITION OF 1 OCT 64 WHICH MAY BE USED.

Source: https://assist.dla.mil -- Downloaded: 202610-17T11:46Z
Check the source to verify that this is the currentversion before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T11:46Z
Check the source to verify that this is the current version before use.