MILITARY SPECIFICATION

VISORS, SHATTER RESISTANT

This amendment forms a part of Military Specification MIL-V-85374(AS), dated 13 December 1979.

PAGE 1

2.1 SPECIFICATIONS: - MILITARY

Delete the following:

"MIL-V-22272 Visor, Protective, Helmet"

PAGE 8

4.3.1, line 12: Delete "Code 4041" and substitute "Code 6021".

PAGE 9

4.6.1.3, lines 1, 2, 3, 4: Delete second and fourth sentence.

PAGE 15

4.6.8, Delete and substitute the following:

"4.6.8 Abrasion Resistance. The haze and luminous transmittance of the coated specimens shall be determined before and after the abrasion test as specified in FED-STD-406, Method 3022. The abrasion test shall be performed by rubbing with a specially standardized eraser mounted as illustrated in figure 3 and held approximately normal to the visor. The device and eraser material indicated in figure 3 shall be used for this test. The eraser shall be rubbed across the surface of the coated visor from one point to another, over the same path, for 20 complete cycles with a force of 2.0 to 2.5 pounds continuously applied. Whenever possible, rubs of about 1 inch length are preferred. After rubbing has been completed, the lens shall be thoroughly cleaned to remove dirt, film, fingermarks and grease marks using a mild detergent and water followed by drying with a soft cloth or lens tissue. The visor shall meet the requirements specified in 3.4.7."

FSC 8475

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:44Z
Check the source to verify that this is the current version before use.

PAGE 15

4.6.9, Delete and substitute the following:

"4.6.9 Adhesion Test Method. The specimens shall be subjected to humidity tests as specified in MIL-STD-810, Method 507, for 120 hours (five cycles). Immediately upon removal from the humidity chamber, the samples shall be dried with a cotton cloth and then subject to the adhesion test. A test tape (3M 670, 202, 218, 232 or equivalent), with an adhesion rating of 40 ounces per inch of width, shall be firmly applied to the front surface of the visor.

The area covered shall be 2 square inches. The tape is then removed using a snapping motion applied $90^{o}$ to the specimen. Two trials at separate locations shall be made using this method. The visor shall meet the requirements specified in 3.4.8."

PAGE 16

4.6.12, line 2: Delete "Figure 3" and substitute "Figure 4".

Following page 16: Add new Figure 3.


PAGE 17

Change "Figure 3" to "Figure 4".

Preparing Activity
Navy (AS)
(Project No. 8475-N168)



Source: https://assist.dla.mil - Downloaded: 2026-10-23T10:44Z
Check the source to verify that this is the current version before use.

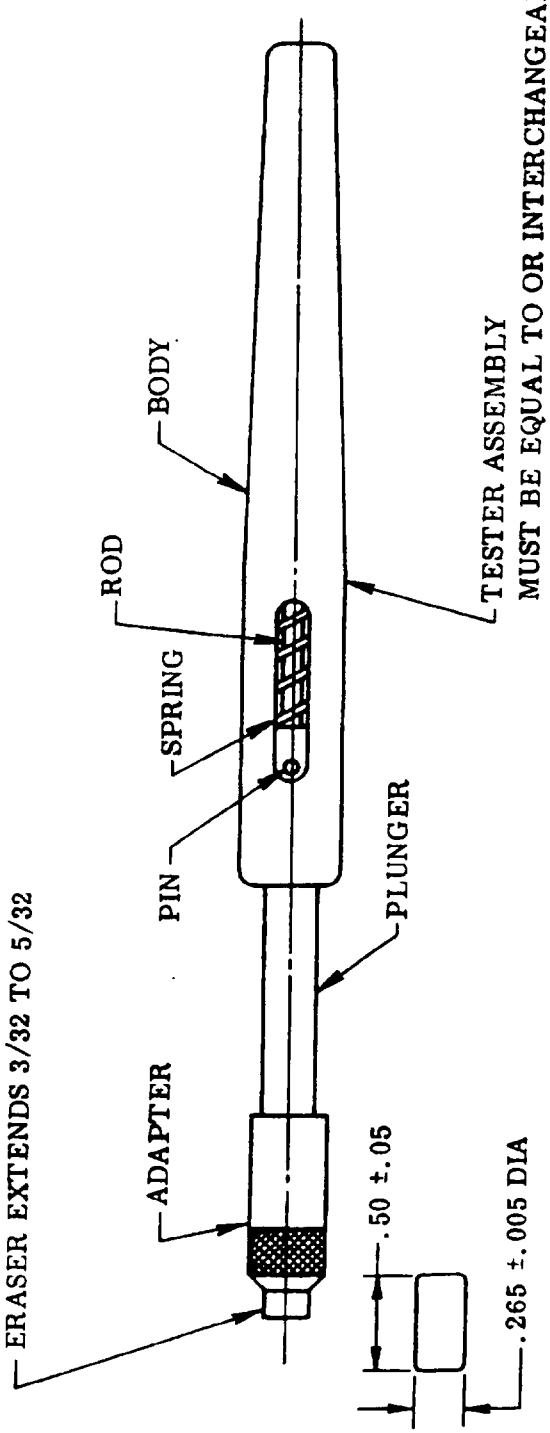


APPROVED PICATINNY ARSENAL ABRASIVE
PLUG NO. 1. OR ROCK ISLAND ARSENAL RUBBER
LABORATORY FORMULA A15-C-2F
SOURCE OF SUPPLY: PICATINNY ARSENAL

Figure 3. Eraser Abrasion Tester Assembly and Eraser Plug

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:44Z
Check the source to verify that this is the current version before use.