INCH-POUND

MMM-A-260D
17 February 2026
SUPERSEDING
MMM-A-260C
May 10, 1984

FEDERAL SPECIFICATION

ADHESIVE, WATER-RESISTANT, (FOR SEALING WATERPROOFED PAPER)

This specification was approved by the Commissioner, Federal Supply Services, General Services Administration, for the use of all Federal agencies.

1. SCOPE

1.1 Scope. This specification covers water-resistant adhesive intended for application to the seams in the manufacture and in the closure of waterproofed paper bags, wrappers, and case liners.

1.2 Classification.

1.2.1 Types, grades, and classes. The adhesive covered by this specification shall be of the following types, grades, and classes as specified, (see 6.2):

1.2.1.1 Types.

Type I - For application by machine.

Type II - For hand application, by brushing.

1.2.1.2 Grades.

Grade A - For subsistence items.

Grade B - For other than subsistence items.

Comments, suggestions, or questions on this document should be addressed to: Director, U.S. Army DEVCOM, Army Research Laboratory, Army Research Directorate, Specifications and Standards Office, Attn: FCDD-RLA-M, Aberdeen Proving Ground, MD 21005-5069. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil/.

AMSC N/A FSC 8040

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

1.2.1.3 Classes.

Class 1 - Solvent-based adhesive (see 3.10).

Class 2 - Water-emulsion adhesive.

Class 3 - Hot melt adhesive.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the contract or purchase order.

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-129	-	Marking for Shipment and Storage
MIL-STD-1916	-	DoD Preferred Methods for Acceptance of Product

(Copies of these documents are available online at https://quicksearch.dla.mil/.)

2.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

FEDERAL SPECIFICATIONS

PPP-B-1055	-	Barrier Material, Waterproof, Flexible

FEDERAL STANDARDS

FED-STD-123	-	Marking for Shipment (Civilian Agencies).
FED-STD-313	-	Material Safety Data, Transportation Data, and Disposal Data for Hazardous Materials Furnished to Government Activities.

(Copies of this document are available online at https://quicksearch.dla.mil/).

2.3 Non-Government publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the contract or purchase order.

THE AMERICAN NATIONAL STANDARDS INSTITUTE

ANSI/ASQ Z1.4	-	Sampling Procedures and Tables for Inspection by Attributes

(Copies of these documents are available online at https://ansi.org/).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

ASTM INTERNATIONAL

ASTM D3951 - Standard Practice for Commercial Packaging

(Copies of these documents are available online at https://www.astm.org/).

2.4 Order of precedence. Unless otherwise noted herein or within the contract or purchase order, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Fungi resistance. When specifically designated in the applicable contract or purchase order, the adhesive shall be resistant to the growth of fungi. NOTE: fungi resistance is not a default requirement and must be deliberately requested as part of the contract or purchase order. Test procedures and specific requirements shall be specified by the procuring activity (see 6.2).

3.2 Low temperature flexibility. The adhesive bond shall not separate from the paper nor fracture when tested as specified in 4.4.1.

3.3 Resistance to water penetration. The adhesive bond shall resist water penetration for a period of eight hours when tested as specified in 4.4.2.

3.4 Adhesion after subjection to heat. The adhesive bond shall not shear under a tension of less than 7.5 pounds (2.8 kg) when specimens are prepared from the adhesive and barrier material, conditioned at elevated temperature, and tested at room temperature in accordance with 4.4.3.

3.5 Initial tack (type II only). The adhesive shall develop sufficient adherence (tack) within 105 seconds plus 6 seconds of the time of application to sustain a suspended load of 3.5 oz (100 grams) for a period of 60 seconds when tested as specified in 4.4.4.

3.6 Resistance to flow. The dried adhesive film shall show no separation of adhesive from the barrier material or adhesive flow when tested and examined after subjection to heat as specified in 4.4.3.2.

3.7 Stability.

3.7.1 Resistance to elevated temperature degradation. The adhesive shall conform to 3.3 and 3.5 when tested as specified in 4.4.5.1.

3.7.2 Resistance to low temperature degradation. The adhesive shall conform to 3,3 and 3.5 when tested as specified in 4.4.5.2.

3.8 Consistency (classes 1 and 2).

3.8.1 Consistency, as received.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

3.8.1.1 Type I. Type I adhesive shall have a consistency such that it may be applied satisfactorily by means of commercially available bag and liner sealing equipment. Adhesive so applied shall not exhibit stringiness when machine transfer surfaces are separated; shall not build up excessively on machine parts, and shall not foam. Compliance shall be determined visually, using standard available commercial sealing equipment, or as otherwise specified by the procuring activity (see 6.2).

3.8.1.2 Type II. Type II adhesive shall have a consistency such that it may be applied easily and satisfactorily by hand brushing. Compliance shall be determined in preparing the test specimens of 4.4.3 or as otherwise specified in the contract or by the procuring activity.

3.8.2 Consistency after subjection to stability test conditions. After subjection to the procedures of 4.4.5.1 and 4.4.5.2, the adhesive shall comply with the requirements for consistency of 3.8.1, as applicable to the type under test. Compliance shall be determined in accordance with that paragraph.

3.9 Toxicity. The adhesive shall have no adverse effect on the health of personnel as applicators or consumers. The manufacturer shall furnish the contracting officer with a certificate stating that the adhesive contains no known toxic material.

3.10 Condition in container. The adhesives supplied in liquid form shall be free from lumps, skins, foreign matter, settling, separation, and all other evidence of nonuniformity. It shall be capable of being made homogeneous without mechanical stirring. The hot melt adhesive shall be solid, free from foreign matter and, when melted for application, shall be smooth and homogeneous.

3.11 Shelf storage life. When stored as specified in 4.4.6, the adhesive shall meet the requirements specified in 3.2, 3,5, 3.8.1, and 3.10.

3.12 Materials. Recycled and/or reclaimed materials shall be used to the maximum extent possible without adversely affecting the final product.

3.13 Safety Data Sheets (SDS). The manufacturer shall comply with the requirements as specified in the OSHA Brief:

(http://www.osha.gov/dsg/hazcom/osha-brief.html

And, as specified in Appendix D of 29 CFR 1910.1200 see:

(https://www.osha.gov/laws-regs/regulations/standardnumber/1910/1910.1200AppD).

A SDS shall be prepared for the adhesive product in accordance with FED-STD-313 and forwarded to the qualifying activity (see 6.4.3). The SDS shall be included with each shipment (see 5.1) of the material covered by this specification and submitted to pertinent Government agencies as stated in FED-STD-313.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.2 Sampling.

4.2.1 Lot. For purposes of sampling, a lot shall consist of all adhesive of one type, grade, and class, manufactured as one batch, and offered for acceptance at one time, by one contractor.

4.2.2 Sampling for inspection of filled containers. Following MIL-STD-1916 guidance, a random sample of filled containers shall be taken from each lot in accordance with ANSI/ASQ Z1.4 at inspection level I and acceptance quality level (AQL) equal to 2.5 percent defective to verify compliance with all stipulations of the specification regarding fill, closure, marking, and other requirements not involving tests.

examination in accordance with MIL-STD-1916 and surveyed in accordance with level I of ANSI/ASQ Z1.4.

4.2.3 Sampling for lot acceptance tests. From each inspection lot, a one half gallon (1.9 liter) sample shall be taken at random, from each of two containers (or a sufficient quantity of randomly selected smaller containers) so as to obtain two one half gallon (1.9 liter) samples, for use in testing.

4.3 Inspection.

4.3.1 Inspection of filled containers. Each sample filled container selected in accordance with 4.2.2 shall be examined for defects of the container and the closure, for evidence of leakage, and for non-compliance with marking requirements. Each sample filled container shall also be weighed to determine the compliance with requirements for amount of contents. Any container in the sample having one or more defects, or under the required fill, shall be rejected, and if the number of defective containers exceeds the acceptance number for the appropriate sampling plan of MIL-STD-1916 (see 4.2.2), the lot represented shall be rejected. Rejected lots may be submitted for acceptance, in accordance with the requirements of MIL-STD-1916 for resubmission, using tightened inspection for such reinspection.

4.3.2 Lot acceptance tests. The sample specimens selected in accordance with 4.2.3 shall be subjected separately to the tests of 4.4. If specimens taken from either adhesive sample fail one or more of the tests, the lot represented shall be rejected.

4.4 Test procedures.

4.4.1 Low temperature flexibility.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

4.4.1.1 Material. Barrier material conforming to class L-4, of PPP-B-1055 shall be used in type I adhesive tests and type II class 1 adhesives tests for low temperature flexibility, and class L-2 material of PPP-B-1055 shall be used in type II classes 2 and 3 adhesive tests for that property. Tests made using class L-4 material shall be made by bending (flexing) the two test specimens so that the crepe direction is perpendicular to the seam length. All tests made using class L-2 material shall be made with the adhesive applied to the untreated surface, and bonded to the treated surface.

4.4.1.2 Preparation of test specimens. Barrier material samples conforming to 4.4.1.1 shall be cut into 8.0 by 2.5 inch (20.3 x 6.4 centimeter) pieces. The adhesive shall be applied in a smooth continuous film, in the thickness recommended by the manufacturer, and in a width of one inch along the 8-inch (2.0 centimeter) edge of one of the cut pieces of barrier material, and allowed to stand for approximately 30 seconds (except that class 3 - hot melt adhesives shall be allowed to stand for no longer than 5 seconds). Then an uncoated similar piece of barrier material shall be placed against the adhesive coated piece so that all edges coincide. The adhered (bonded) area of the assembly shall be immediately subjected.to a uniform pressure of 0.5 psi (3.5×10^3 Pa) for 24 hours while in an atmosphere of 73° ± 2°F (22.7° ± 1.1°C). At the end of that period, the pressure shall be removed, and the assembly allowed to set for an additional 24 hours at the above temperature and a relative humidity of 50 ± 5 percent. One inch (2.5 centimeters) shall then be cut from each end of the assembly perpendicular to the seam and discarded. The remainder shall be cut in two, so that two specimens, each 3.0 by 2.5 inches (7.6 by 6.4 centimeters) remain for testing.


4.4.1.3 Test procedure. Specimens prepared as in 4.4.1.2 shall be conditioned at 0° ± 2°F (-17 ± 1.1°C) for a period of 2 hours, and then bent immediately through 180 degrees over a 3/4-inch (1.9 centimeter) diameter mandrel, previously conditioned and maintained at the same temperature. The bending (flexing) shall be performed so that the length of seam is perpendicular to the mandrel and made at the above temperature. The specimen shall then be turned over, without changing the direction of the seam and the 180 degree bending repeated with the opposite face of the specimen against the mandrel, and then the specimen returned to its original position. Each bending operation shall be performed in not less than 3 seconds nor more than 5 seconds, with a maximum time interval of 5 seconds between the two operations. The adhesive bond shall be carefully examined visually for separation from the paper and for fracture. If such is in evidence, it shall be indication of failure to meet the requirement for low temperature flexibility. If the specimens are satisfactory when so examined, they shall be conditioned for 2 hours at 73° ± 2°F (22.7° ± 1.1°C) and then used as specimens for the water penetration test of 4.4.2.

4.4.2 Water penetration.

4.4.2.1 Preparation of specimens. Specimens meeting the requirements and test of 4.4.1 for low temperature flexibility shall be opened to form 3 by 3 inch (7.6 x 7.6 centimeter) specimens each having a 1 inch (2.5 centimeter) fin seam. The creased material shall be inspected visually to avoid the use of pinholed or split specimens which would affect the permeability of the material. A dry indicator reagent which changes color due to the permeation of moisture (see 4.4.2.3), shall be sprinkled evenly over approximately 2 inch (5.0 centimeter) square area in the center of the 3 by 3 inch (7.6 x 7.6 centimeter) flat surface of the T-shaped specimen. Care shall be taken to apply the reagent as evenly as practicable since bunching or piling of the reagent may cause erratic results. Place a 2 inch (5.0 centimeter) watch glass over the reagent and in the approximate center of the surface of the specimen, figure la. Brush away the reagent outside the watch glass and seal


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

the watch glass to the test specimen using a mixture of equal weights of beeswax and rosin. The outer 0.25 inch (.64 centimeters) of the 3inch (7.6 centimeter) edges shall be coated, both sides with the wax mixture, but no wax applied to the cut edges of the adhesive seam, figure lb.

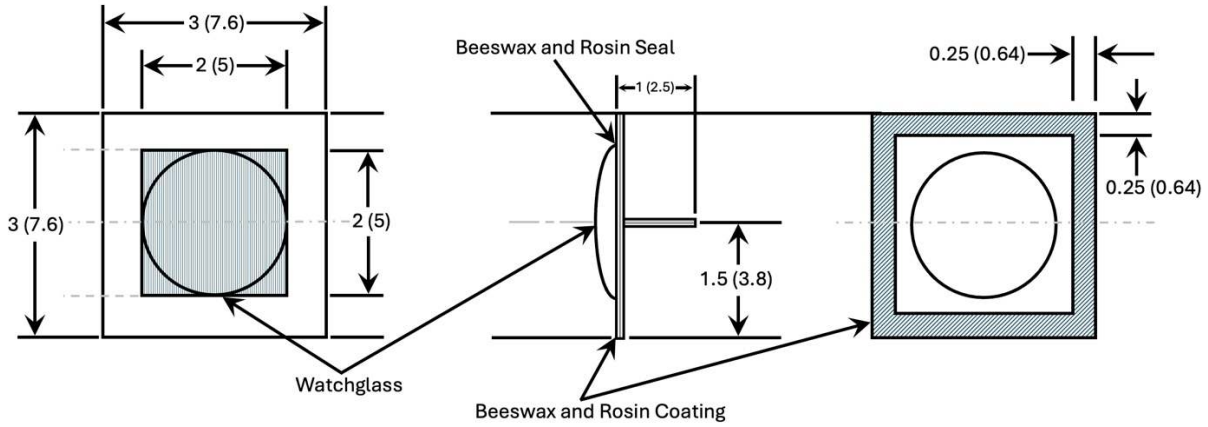

a. PREPARATION OF SPECIMEN b. APPLICATION OF SEALANT

Notes
1/ Numbers in inches
2/ Bracketed numbers in centimeters

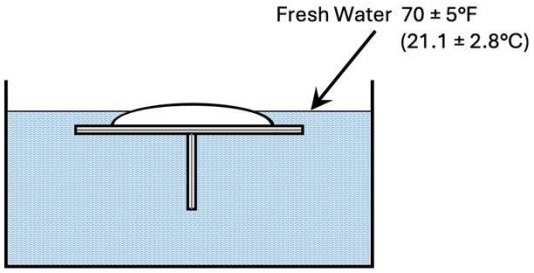

c. FLOATING OF SPECIMEN

FIGURE 1. Water Penetration Test.

4.4.2.2 Test procedure. The specimens prepared as in 4,4.2.1 shall then be floated on fresh tap water maintained at 70 ± 5°F (21.1 ± 2.8°C) with the fin seam down, figure lc. The test shall be conducted using both of the PPP-B-1055 materials (L-4 and L-2). The time required to cause a definite development of color to appear in the indicator shall be noted and recorded as the penetration time.

4.4.2.3 Dry indicator. The dry indicator for use in the above test shall be composed of cane sugar, soluble starch, and methyl violet, prepared as follows:

a. Grind each ingredient separately until it passes through a No. 100 U.S. Standard sieve and completely dry it in a desiccator over calcium chloride before making the mixture. When dry, mix the following proportion by weight:

Sugar	45
Soluble starch	5
Methyl violet	1

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

b. Mix the ingredients above by sieving repeatedly through a U.S. Standard No. 60 sieve until the mixture is uniform. Keep the prepared indicator in a closed desiccator until ready for testing.

4.4.3 Adhesion after subjection to heat.

4.4.3.1 Specimen preparation. Two pieces, each 12 by 4 inches (30.5 x 10.7 centimeters) with the 4 inch (10.2 centimeter) dimension in the direction of the greater tensile strength, shall be cut from a barrier material conforming to class L-4 of PPP-B-1055. The adhesive shall be applied in a smooth continuous film, of the thickness recommended by the manufacturer, over a one inch (2.5 centimeter) width of the untreated face along a 12-inch (30.5 centimeter) edge of each of the pieces, and shall be allowed to set for approximately 30 seconds, except that hot melt adhesives shall be allowed to set for a maximum of 5 seconds. The adhesive coated section of each piece forming an assembly measuring 7 by 12 inches (17.8 x 30.5 centimeters), with a 1 by 12 inch (2.5 x 30.5 centimeter) adhesive bonded lap joint shall be joined. The bonded area shall immediately be subjected to a uniform pressure of 0.5 psi (3.5×10^3 Pa) for 24 hours. The pressure shall then be removed, and the assembly shall be allowed to stand for an additional 24 hours. The assembly shall then be cut perpendicular to the bond into twelve 1 inch (2.5 centimeters) wide specimens, using a suitable paper cutter.

4.4.3.2 Procedure. The 12 bonded specimens prepared as specified in 4.4.3.1 shall be suspended within an air circulating oven or cabinet maintained at 140° ± 2°F (60° ± 1.1°C) for 240 hours; then removed and conditioned for 24 hours at 73 ± 2°F (22.7° ± 1.1°C). Specimens subjected to the above shall then be examined for evidence of adhesive flow and separation by visual means as required in 3.6, and if satisfactory immediately subjected to tension in a tensile testing machine. One end of each specimen shall be centered and tightened individually in the flat jaws of a suitable tension testing machine. The jaws shall be separated at a constant rate chosen to cause either the imposition of a load of 7.5 pounds (3.4 kgs.) or breakage of the specimen before that load has been reached, within 5 to 15 seconds after starting the grip motion. If tension recorded for any specimen fails to reach 7.5 pounds (3.4 kgs.) at the point of bond separation, the test shall be repeated using double the number of specimens, prepared as before. If any specimen fails to meet the 7.5 pound (3.4 kg.) requirement for adhesive bond strength on retest, the adhesive lot represented shall be rejected. If the barrier material portion of any specimen breaks at less than 7.5 pounds (3.4 kgs.) tension, and the adhesive bond is not broken, 12 additional specimens shall be prepared as above, using a suitable brand of class L-4 barrier material, as specified in PPP-B-1055, of sufficient strength that tensile failure will not occur at less than 7.5 pounds (3.4 kgs.) tension, when tested as described.

4.4.4 Initial tack (type II only). Separate tests shall be made using class L-4 material for type II, class 1 adhesives and class L-2 material for type II, classes 2 and 3 adhesives (see 4.4.1.1) at a temperature of 73 ± 2°F (22.7° ± 1.1°C) and 50 ± 5 percent relative humidity. Specimens of the barrier material (bottom adherend) shall be securely placed onto the top side of a tiltable table as shown in Figure 2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

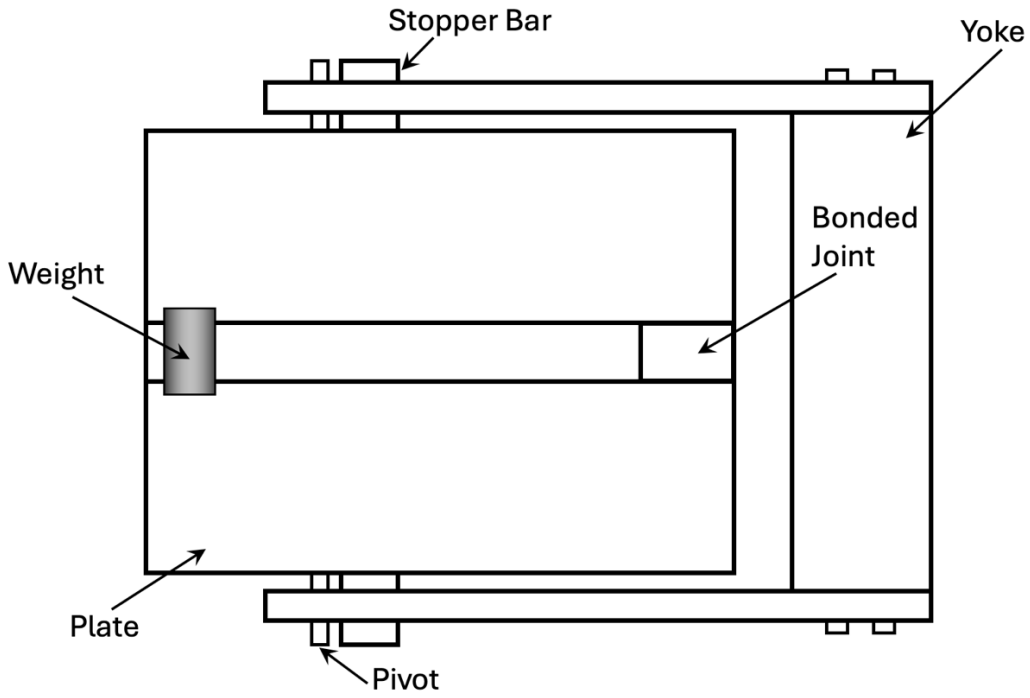


FIGURE 2. Tiltable Table, Top View Plate Horizontal.

A one inch (2.5 centimeter) wide strip of barrier material, the top adherend, shall have a 3.5 oz (100 gram) weight applied to one end so that the total length including the weight is equal to the length of the bottom adherend.

To the top and bottom adherends shall be carefully applied, a film of adhesive covered by this specification in the thickness recommended by the manufacturer, in a section of each to provide a lap shear specimen having a lap 1 inch (2.5 centimeters) wide by 1 1/2 inches (5.1 centimeters) long, figure 2. The adhesive film shall be allowed to air dry for 30 seconds (except that class 3, hot melt adhesives shall be subjected to the next operation within 10 seconds of adhesive film coating the material), the time being determined from the forming of the surface of the adhesive to be bonded, which shall be no more than 15 seconds after the start of the adhesive application operation. Simultaneous with this, the 1 inch (2.5 centimeter) wide strip, the top adherend, shall be wet in the same manner as the bottom adherend. The top adherend shall be placed onto the bottom adherend so that a lap shear specimen is formed, figure 2, with only the specification adhesive between them. The crepe direction of the barrier material shall be in the direction of the test weight, and a pressure, recommended by the manufacturer, be applied to the setting joint. Sixty seconds after applying the adherends together (80 seconds for class 3 hot melt adhesives) the pressure shall be removed and the tiltable table rotated into the vertical position, figure 3. This operation shall be accomplished within 6 seconds.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

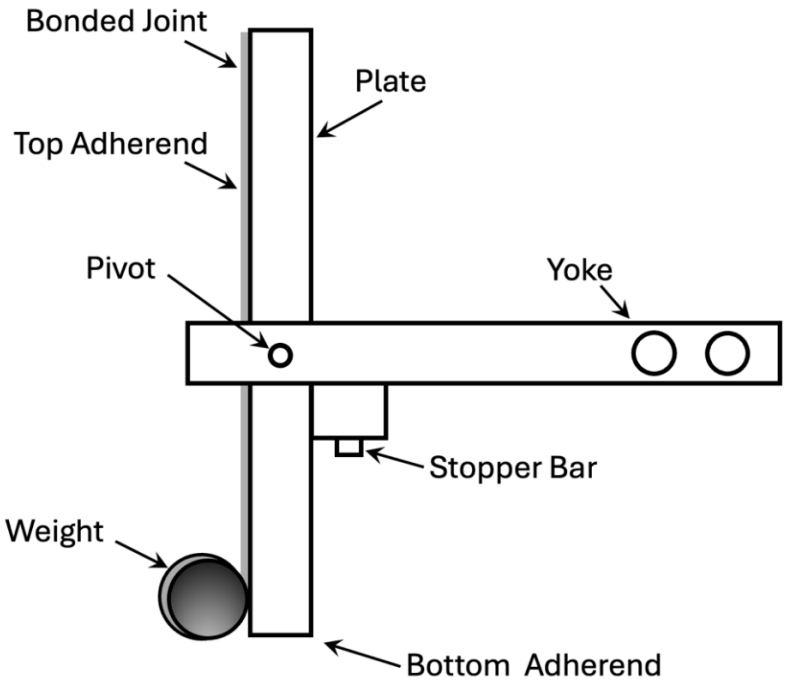


FIGURE 3. Tiltable Table, Side View with Plate Rotated into Vertical.

A series of 10 lap shear specimens using each of the above barrier materials shall be so tested. A minimum of 9 of the 10 specimens shall be so tested without separation of the top adherend from the assembly, in order to comply with the requirement for initial tack.

4.4.5 Stability.

4.4.5.1 Resistance to elevated temperature degradation. Approximately one pint (470 cubic centimeters) of the adhesive shall be placed in a wide mouth jar or glass container and sealed and then placed in a circulating air oven or temperature cabinet for a period of two weeks at 140 ± 2°F (60° ± 1.1°C). After completion of that time interval, the container shall be removed, allowed to cool to 73° ± 2°F (22.7° ± 1.1°C), and subjected to the tests of 4.4.2 and 4.4.4. In addition, the consistency of the adhesive shall conform to that required in 3.8, when tested as required in that paragraph.

4.4.5.2 Resistance to low temperature degradation. Approximately one pint (470 cubic centimeters) of the adhesive shall be placed in a wide mouth jar or glass container, sealed and then placed in a temperature cabinet maintained at 0 ± 2°F (-17 ± 1.1°C) for a period of 16 hours. The container and contents shall then be allowed to stand for a period of 8 hours at 73° ± 2°F (22.7 ± 1.1°C). The above cycle shall be repeated for a total of 3 times. Following the final 8 hours at 73 ± 2°F (22.7 ± 1.1°C), the adhesive sample shall be subjected to the tests of 4.4.2 and 4.4.4. In addition, the consistency of the adhesive shall conform to that required in 3.8 when tested as required in that paragraph.

4.4.6 Shelf storage life. One quart of the adhesive shall be sealed tightly in a glass or metal container, stored for eighteen (18) months at 23 ± 1°C (73.5 ± 2°F) and 50 percent relative humidity, and tested or examined for compliance with 3.11. The supplier may certify that their formulation meets the requirements of 3.11.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or purchase order (see 6.2). When packaging of materiel components is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

5.1.1 Shipping and marking notes. Due to the substantial passage of time since the last revision of this specification, additional packaging and marking information for shipment that may be helpful including past definitions and procedures are included in 6.3 and its sections therein. This legacy content will be deleted in the next revision or amendment to this specification.

5.2 Markings. Containers of adhesive shall include labels that identify the specification number, type, grade, and class so that traceability of the lot can be verified and a SDS (see 3.13) shall be included.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The adhesive is intended primarily for use in seam bonding and closure of waterproof paper bags, wraps, and case liners. It may however be used in other applications where its properties are desired and are applicable.

6.2 Ordering data. Purchasers should select the preferred options permitted herein, and include the following information in procurement documents:

a. Title, number, and date of this specification.
b. Type, grade, and class of adhesive required (see 1.2).
c. Unit quantities of adhesive required. The adhesive should be purchased by volume, the standard being one U.S. Gallon (231 cubic inches) (3.8 liters) at 60°F (15.5°C), or parts thereof.
d. Levels of packaging and packing required (see 5.1 and 5.2)
e. Requirements for fungi resistance and tests if applicable (see 3.1).
f. Preparation of SDS in accordance with FED-STD-313 for the adhesive and inclusion of SDS with shipment of material (see 3.13).
g. Any additional marking or other requirements.

6.3 Legacy marking notes. Due to the substantial passage of time since the prior revision of this specification, select additional packaging and marking information from MMM-A-260C are included as a courtesy in this section.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

6.3.1 Civil agencies. In addition to any special marking required by the contract or order, marking of shipping containers should be in accordance with Fed, Std. No. 123. In addition, the following should appear on each container.

a. Date of manufacture.

b. Type, grade, and class furnished.

c. Manufacturer's batch number or code.

d. Weight of adhesive and tare weight of container.

e. Caution Notice "STORE IN A COOL PLACE - KEEP FROM FREEZING."

f. Warning Notice, when adhesive does not meet the requirements for Grade A, for subsistence items, "WARNING: THIS ADHESIVE IS NOT TO BE USED ON CASE LINERS FOR SUBSISTENCE ITEMS,"

g. Federal stock number.

h. Date of first reinspection (Insert date eighteen months after date of manufacture for liquid adhesives, and 36 months after date of manufacture for hot melt adhesives).

6.3.2 Military activities. In addition to marking required by the contract or purchase order, marking of shipping containers shall be in accordance with the requirements of MIL-STD-129. In addition, the information required under a., b., c., e., and f., in paragraph 5.3,1 above should appear on each container.

6.4 SDS. Contracting officers should identify those activities requiring copies of a completed SDS, (see 3.13 and 5.2) when implemented, prepared in accordance with FED-STD-313. The pertinent Government mailing addresses for submission of data are listed in FED-STD-313.

6.5 Supersession data. This specification includes requirements from Military Specification MIL-A-140A, dated November 23, 1951, and from Federal Specification O-A-166 (GSA-FSS), dated January 18, 1962. Due to the extreme age of these cancelled prior documents, users are advised that backwards compatibility may no longer be possible.

6.6 Subject term (key word) listing.

Adhesion	Maps	Preservative
Barrier	Parchment	Water repellant

6.6 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.

CONCLUDING MATERIAL

Custodians:
Army - MR
Navy - AS

Preparing activity:
ARMY - MR

(Project 8040-2025-004)

Review activities:
Army - EA, GL, SM
Navy - MC, OS, YD
DLA - SS
Other DoD - DS

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil/.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:47Z
Check the source to verify that this is the current version before use.