FED. SUP CLASS
2620

NOTE: ALL DIMENSIONS ARE IN INCHES

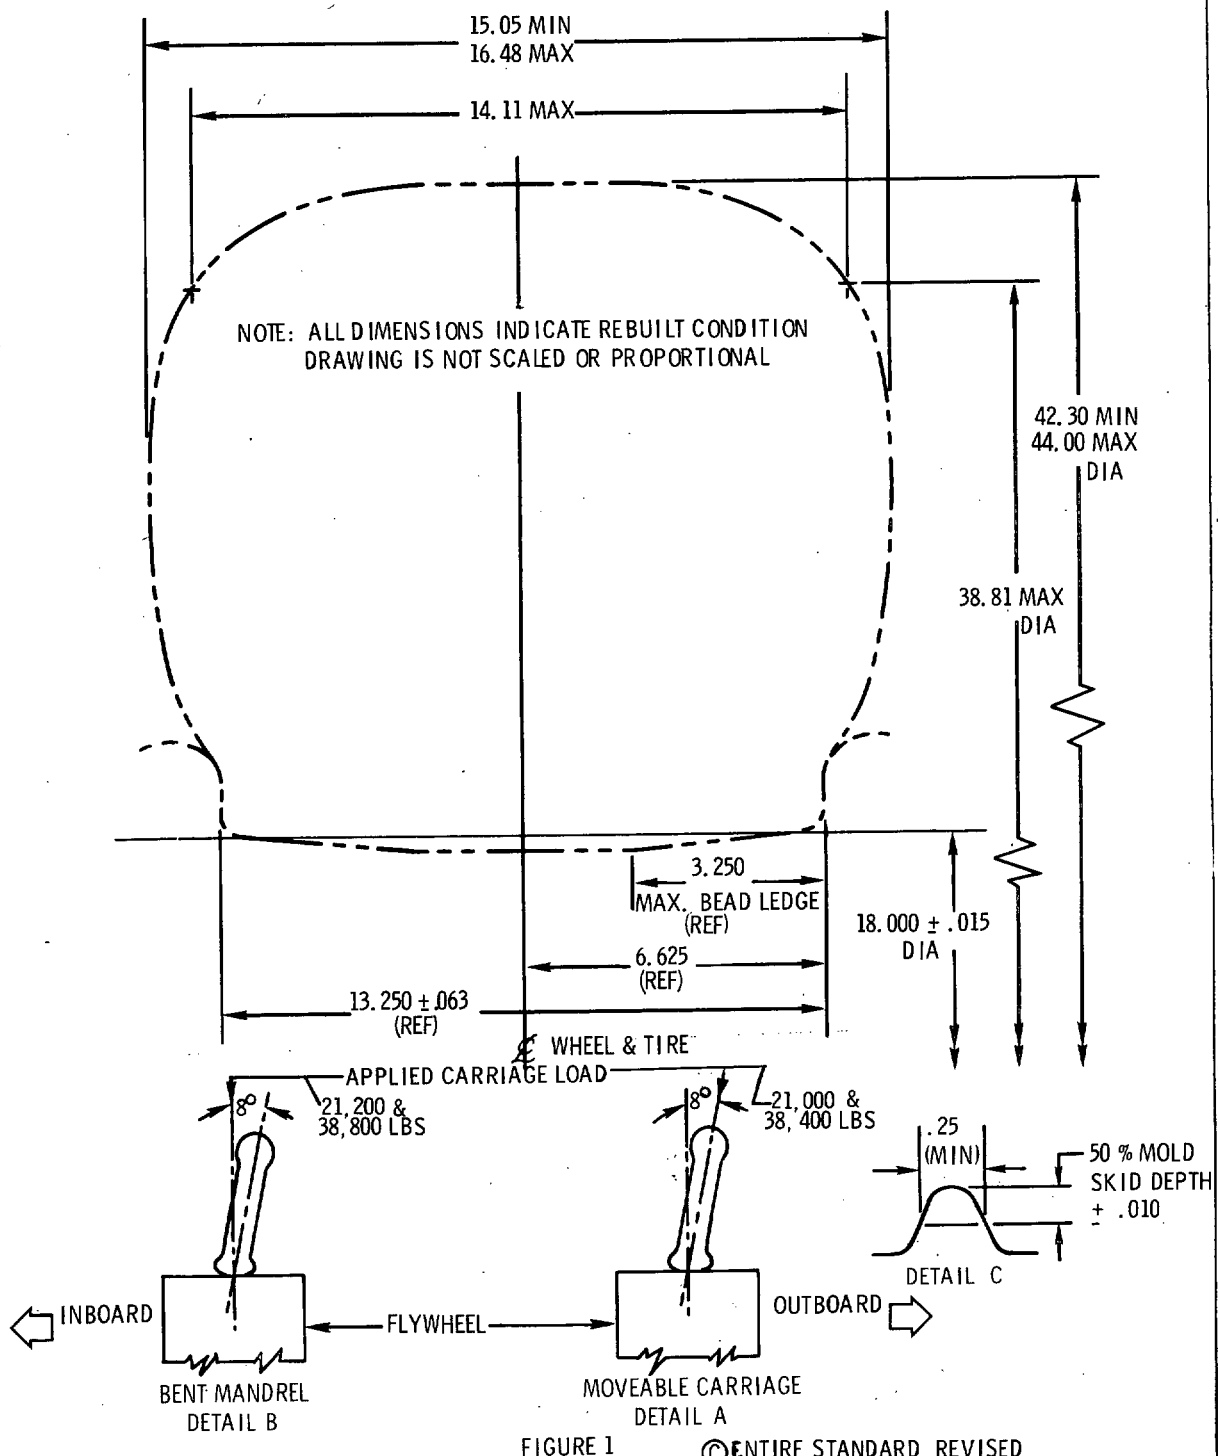


FIGURE 1

©ENTIRE STANDARD REVISED

APPROVED 21 DEC 1970 REVISED (A) 28 JUNE 1973 (B) 1 APRIL 1978 (C) 30 MARCH 1981

P.A. 99 Other Cust	TITLE TIRE - PNEUMATIC REBUILT, TYPE VII 44 X 16, 28 PR	MILITARY STANDARD MS27815 (USAF)
PROCUREMENT SPECIFICATION MIL - R - 7726	SUPERSEDES: AF DWG NO. 64F1847	SHEET 1 OF 2

DD FORM 1 SEP 63 672-1 (Limited coordination) EDITION OF 1 SEP 57 MAY BE USED

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T16:52Z
Check the source to verify that this is the current version before use.

FED. SUP CLASS
2620

GENERAL NOTES

1. ANY DEVIATIONS FROM GIVEN DIMENSIONS MUST BE AUTHORIZED BY WRITTEN APPROVAL OF THE PROCURING AGENCY. DIMENSIONS CALLED OUT ARE AFTER REBUILDING.

2. REFERENCE TO ANY SPECIFICATION HEREIN SHOULD BE CONSTRUED AS REFERENCE TO THE ISSUE IN EFFECT ON THE DATE OF INVITATION FOR BIDS.

3. WHERE CONFLICT EXISTS BETWEEN THIS STANDARD AND ANY CIVIL REGULATION OR OTHER MILITARY SPECIFICATIONS THE REQUIREMENTS OF THIS STANDARD SHALL APPLY.

4. THE QUALITY ASSURANCE SHALL BE IN ACCORDANCE WITH THE REQUIREMENTS OF MIL-R-7726.

REBUILT TIRE NOTES

1. THE REBUILT TUBELESS TIRE SHALL CONFORM TO THE APPLICABLE MILITARY REQUIREMENTS: MIL-R-7726, AND FAA REQUIREMENTS TSO C62B, CAR 4b and CAM 18.30-9(b)(3).

SIZE	PLY RATING	MAX STATIC LOAD (LBS)	INFLATION PRESSURE PSI (RATED)	BEAD WIDTH (MAX IN)	WEIGHT (LBS MAX)	STATIC UNBALANCE OZ IN MAX	TREAD	MOLD SKID DEPTH (MIN IN)
44x16	28	38,400	185	3.25	186	50	See Note 3	0.38

THE TIRE SHALL SATISFACTORILY WITHSTAND 80 CYCLES EACH OF TESTS 1A, 1B, $1C_1$ AND $1C_2$ (TOTAL, 320 CYCLES). THE FIRST 40 CYCLES OF 1A, 1B, $1C_1$ AND $1C_2$ SHALL BE RUN AT 38% DEFLECTION.

1A-TAXI TAKE-OFF. THE TIRE SHALL BE LANDED AGAINST A STATIONARY FLYWHEEL AT THE MAXIMUM STATIC LOAD. THE FLYWHEEL SHALL THEN BE ACCELERATED UNIFORMLY TO 40 MPH AND MAINTAINED AT THIS VELOCITY UNTIL A TAXI ROLL DISTANCE OF 15,000 FT ± 200 FT HAS BEEN COVERED. THE FLYWHEEL SHALL THEN BE DECELERATED TO ZERO MPH AND IMMEDIATELY ACCELERATED AT 9FT/SEC/SEC AVERAGE (SIMULATING TAKE-OFF) TO 200 MPH. DURING THE ACCELERATION, THE LOADS SHALL BE MAINTAINED AT THE MAX STATIC LOAD FOR THE FIRST 10 SEC AND THEN DECREASED LINEARLY WITH TIME TO ZERO LOAD DURING AN ADDITIONAL 22 TO 23 SECONDS. THE TOTAL DISTANCE TRAVELED ON THE TAXI AND TAKE-OFF CYCLE IS APPROXIMATELY 14,800 FT (2.8 MILES).

1B-LANDING TAXI. THE TIRE SHALL BE LANDED AGAINST A FLYWHEEL ROTATING AT A PERIPHERAL SPEED OF 138 MPH. THE FLYWHEEL SHALL BE DECELERATED AT AN AVERAGE RATE OF 8.0 FT/SEC/SEC FROM 138 MPH TO 20 MPH. THE LOAD SHALL BE INCREASED LINEARLY TO 30,500 POUNDS DURING THE INITIAL 3 TO 4 SECONDS AFTER LANDING AND MAINTAINED CONSTANT UNTIL A TOTAL ROLL DISTANCE OF 2,500 FT HAS BEEN COVERED. THE FLYWHEEL SHALL THEN BE ACCELERATED TO 30 MPH AND THE LOAD SHALL REMAIN CONSTANT UNTIL THE TIRE HAS BEEN ROLLED AN ADDITIONAL 15,000 FEET ± 200 FEET.

1C-TAXI TURNS. CONDUCT TAXI-TURN CYCLES IN ACCORDANCE WITH THE "MOVABLE CARRIAGE" PROCEDURE FIG 1 DET. A. IF THIS CAPABILITY DOES NOT EXIST, AN ACCEPTABLE ALTERNATE IS THE "BENT MANDREL" PROCEDURE DETAIL B.

$1C_1$-TAXI OUTBOARD CAMBER. THE FLYWHEEL SHALL BE ACCELERATED TO 40 MPH AND THIS SPEED MAINTAINED THROUGHOUT THE CYCLE. LAND THE TIRE AGAINST THE ROTATING FLYWHEEL IN A POSITION OF 8° OUTBOARD CAMBER. INCREASE THE CARRIAGE LOAD LINEARLY TO 21,000 LBS FOR DET A (21,200 LBS FOR DETAIL B) DURING THE FIRST 1.5 SECONDS, FURTHER INCREASE THE LOAD TO 38,400 LBS FOR DET A (38,800 LBS FOR DET B) WITHIN 2.5 TO 3.0 SECONDS AFTER LANDING AND MAINTAIN THE LOAD UNTIL A DISTANCE OF 1630 FEET HAS BEEN COVERED.

$1C_2$-TAXI AND INBOARD CAMBER TEST. THE TEST IS IDENTICAL TO C_1 EXCEPT THE ANGLE OF CAMBER IS 8° INBOARD

2. THE QUALIFICATION TEST INFLATION PRESSURE SHALL BE IN ACCORDANCE WITH THE FOLLOWING TABLE FOR THE RESPECTIVE FLYWHEEL DIAMETER USED TO CONDUCT THE CYCLE(S).

FLYWHEEL DIAMETER	INFLATION PRESSURE
84	230
96	224
120	212

3. THE TREAD PATTERN SHALL HAVE A MINIMUM OF FOUR AND A MAXIMUM OF SEVEN GROOVES. THESE GROOVES SHALL BE CONTINUOUS AND CIRCUMFERENTIAL. IF THE TREAD PATTERN HAS FIVE OR MORE GROOVES THE TWO OUTER GROOVES MAY BE OF PARTIAL SKID DEPTH. ALL OTHER GROOVES SHALL BE A MINIMUM OF THE SKID DEPTH SPECIFIED ABOVE. (MINIMUM OF 80% OF THE ACTUAL SKID MOLD DEPTH). A MINIMUM OF FOUR GROOVES SHALL BE WITHIN THE CONTACT AREA TAKEN AT 60% OF THE MAXIMUM STATIC LOAD AT RATED INFLATION PRESSURE. THE MOLD GROOVE WIDTH SHALL BE A MINIMUM OF 0.25 INCHES MEASURED AS SHOWN IN DETAIL C. THE MAXIMUM CENTER RIB WIDTH OF THE UNINFLATED TIRE SHALL NOT EXCEED 3.0 INCH. ALL OF THE ABOVE SHALL BE REPORTED IN THE QUALIFICATION TEST REPORT.

4. THE REBUILT TIRE MAY BE CONSTRUCTED WITH A FABRIC REINFORCED TREAD FEATURE TO OBTAIN MAXIMUM RELIABILITY AND RETENTION OF THE TREAD TO THE CARCASS.

APPROVED 21 DEC 1970 REVISED © FOR CHANGES SEE SHEET 1 & 2

This military standard is approved for use by Code 99, (Department of the Air Force) and is available for use by all departments and agencies of the Department of Defense.

P.A. 99 Other Cust	TITLE: TIRE - PNEUMATIC REBUILT, TYPE VII 44 X 16, 28 PR	MILITARY STANDARD MS27815 (USAF)
PROCUREMENT SPECIFICATION: MIL-R-7726	SUPERSEDES: AF DWG. NO. 64F1847	SHEET 2 OF 2

DD FORM 1 SEP 63 672-1 (Limited coordination) EDITION OF [illegible] MAY BE USED.

Source: https://assist.dla.mil - Downloaded: 2026-10-23T16:52Z
Check the source to verify that this is the current version before use.

☆ U.S. GOVERNMENT PRINTING OFFICE: 1981—703-023/3264 2-1