AA-H-001895B (GSA-FSS)
January 1, 1980
SUPERSEDING
Int. Fed. Spec. AA-H-001895A
July 14, 1978

INTERIM FEDERAL SPECIFICATION

HOUSEHOLD FURNITURE, WOOD, TRADITIONAL

This Interim Federal Specification was developed by the National Furniture Center, General Services Administration, Federal Supply Service, Washington, DC 20406, based upon currently available technical information. It is recommended that Federal agencies use it in procurement and forward recommendations for changes to the preparing activity at the address shown above.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers minimum requirements for wood household furniture items of commercial design and is of a quality required by the Government for use in Federal installations such as homes and quarters provided certain Government personnel.

1.2 Classification.

1.2.1 Groups, items, and sizes. The furniture shall be of the following groups, items, and sizes. All dimensions are overall (excluding glides) and are in inches (see 6.2).

GROUP A - Bedroom.

Item 1 - Headboard with frame (figure 1).
Size 1 - Single - 39 wide, 39-1/2 high.
Size 2 - Double - 54 wide, 39-1/2 high.

Item 1A - Metal bed frame.

Item 2 - Dresser.
Size 1 - Single (figure 2) - 42 wide, 20 deep, 32 high (four-drawer).
Size 2 - Double (figure 3) - 54 wide, 20 deep, 32 high (six-drawer).
Size 3 - Triple (figure 4) - 68 wide, 20 deep, 32 high (nine-drawer).

Item 3 - Chest.
Size 1 - Three-drawer (figure 5) - 36 wide, 20 deep, 32 high.
Size 2 - Six-drawer (figure 6) - 36 wide, 20 deep, 45 high.

Item 4 - Night stand (one-drawer) (figure 7) - 22 wide, 14 deep, 24 high.

Item 5 - Mirror (wooden frame).
Size 1 - (figure 2) - 26 by 36.
Size 2 - (figure 3) - 30 by 44.

GROUP B - Dining room.

Item 1 - Hutch (figure 8), with shelves, two wooden doors in center, side areas open, 54 wide by 15-3/8 deep by 46 high.

Item 2 - Buffet (figure 8), five drawers, two cupboard doors with adjustable shelves, center drawer divided for silver, 54 wide by 20 deep by 32 high.

Item 3 - Server (figure 9), one silver drawer with four dividers, lower area two cupboard doors with one adjustable shelf, 36 wide by 20 deep by 32 high.

Item 4 - Oval extension table (figure 10), 54 long by 42 wide by 29-1/2 high (without leaves), 90 long by 42 wide by 29-1/2 high (with leaves).

Item 5 - Chair (side) without arms (figure 11), 20 wide, 21-3/4 deep, 37-1/2 high.

Item 6 - Chair (host) with arms (figure 11), 21-3/4 wide, 21-3/4 deep, 37-1/2 high.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

GROUP C - Occasional tables.

Item 1 - Coffee (oval) (figure 12) - 46 long by 26 wide by 17 high.

Item 2 - End (rectangular) (figure 13) - 28 long by 20 wide by 21 high.

Item 3 - Lamp (square) (figure 13) - 28 long by 28 wide by 21 high.

Item 4 - Pivot top (figure 14) - 36 wide by 18 deep by 30-3/8 high (closed); 36 wide by 36 deep by 29-1/2 high (open).

GROUP D - Utility.

Item 1 - Bookcase (figure 15), open with two adjustable shelves, 42 wide by 13-1/2 deep by 32 high.

Item 2 - Desk (figure 16), double pedestal with center drawer plus two storage and one file drawer each side, 48 wide by 24 deep by 29-1/2 high.

2. APPLICABLE DOCUMENTS

2.1 The following documents, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Specifications:

L-P-386 - Plastic Material, Cellular, Urethane (Flexible).
L-P-508 - Plastic Sheets, Laminated, Decorative and Nondecorative.
CCC-C-00540 - Cloth, Upholstery.

Federal Standards:

Fed. Test Method Std. No. 191 - Textile Test Methods.

(Activities outside the Federal Government may obtain copies of Federal specifications, standards and commercial item descriptions, as outlined under General Information in the Index of Federal Specifications, Standards, and Commercial Item Descriptions. The Index, which includes cumulative bimonthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.

(Single copies of this specification, other Federal specifications, and commercial item descriptions required by activities outside the Federal Government for bidding purposes are available without charge from General Services Administration, Business Service Centers in Boston; New York; Philadelphia; Washington, DC; Atlanta; Chicago; Kansas City, MO; Fort Worth; Houston; Denver; Los Angeles; San Francisco; and Seattle, WA.

(Federal Government activities may obtain copies of Federal specifications, standards, commercial item descriptions, and the index of Federal Specifications, Standards, and Commercial Item Descriptions from established distribution points in their agencies.)

Military Standards:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless a specific issue is identified, the issue in effect on date of invitation for bids or request for proposal shall apply.

U.S. Department of Commerce Publications:

Product Standard PS-58 - Basic Hardboard.
Product Standard PS-51 - Hardwood and Decorative Plywood.

(Copies are for sale by the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

American Society for Testing and Materials (ASTM) Standards:

D 905 - Standard Method of Test for Strength Properties of Adhesives in Shear by Compression Loading.
D 3597 - Standard Specification for Woven Upholstery Fabrics - Plain, Tufted or Flocked.

(Copies may be obtained from the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

National Particleboard Association Publications:

NPA 4 - Standard for Medium Density Fiberboard.

(Copies may be obtained from National Particleboard Association, 2306 Perkins Place, Silver Spring, MD 20910).

American National Standards Institute (ANSI) Standards:

ANSI A208.1-1979 - Mat-Formed Wood Particleboard.

(Copies may be obtained from the American National Standards Institute, 1430 Broadway, New York, NY 10018 or National Particleboard Association, 2306 Perkins Place, Silver Spring, MD 20910.)

National Motor Freight Traffic Association, Inc., Agent:

National Motor Freight Classification.

(Application for copies should be addressed to the American Trucking Associations, Inc., Traffic Department, 1616 P Street, N.W., Washington, DC 20036.)

Uniform Classification Committee, Agent:

Uniform Freight Classification.

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, IL 60606.)

3. REQUIREMENTS

3.1 Materials. Materials used in construction and assembly shall conform to the following paragraphs. The manufacturer shall utilize recovered material to the maximum extent practicable.

3.1.2 Adhesives. Adhesives shall meet requirements in table I.

TABLE I. Adhesives

Application	Kind of adhesives
All glue blocks, assembly joints, glued laminated stock, and edge joining of lumber-core panels and plastic laminate to core.	Any adhesive that will develop an average block shear strength of not less than 2,800 lb/in^2 when tested as specified in 4.4.3.
All plywood gluing, edge joining of plys, cross banding, and edge banding.	Any adhesive that will meet the test requirements of the type II bond or better, as described in PS-51.

3.1.3 Dowels. Dowels shall be of maple, birch, or beech dried to a moisture content of from 3 to 5 percent. They shall be longitudinally or spirally grooved and shall have beveled ends. Diameter and length shall be as large as practicable to insure maximum strength of joined members.

3.1.4 Upholstery fabric. Fabric color shall be as specified by the contracting officer (see 6.2(c)). Unless otherwise specified in 6.2(c), the fabric shall conform to type VII of CCC-C-00540 with the following exceptions:

It shall be 100 percent flat nylon plain weave.
Weight shall be 17 oz minimum (see 3.8 of CCC-C-00540).
Fabric shall meet the test requirements in 4.4.4.

3.1.5 Padding.

3.1.5.1 Polyurethane. Polyurethane shall conform to the requirements of type II, class 4 of L-P-386.

3.1.6 Hardware. Hardware shall conform to the following requirements and shall have a minimum of one coat of baked-on clear synthetic enamel or lacquer. Hardware pieces are specified in both the text and in the figures.

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:41Z
Check the source to verify that this is the currentversion before use.

3.1.6.1 Drawer and door knobs. Drawer knobs shall be metal, disc shaped provincial style, 1-1/8-inch diameter and shall have an antique bronze finish. Door knobs shall be key style pulls with escutcheon and shall have an antique bronze finish (see 6.4). Knobs shall be attached with trim screws.

3.1.6.2 Pulls. The pulls used on the drawers shall be metal, provincial style with an antique bronze finish. The bail shall be 3-1/4 inches wide with an appropriate back plate (see 6.4). Pulls shall be attached with trim screws.

3.1.6.2.1 Door catches. Door catches shall be plastic housed magnetic type or plastic intermembering type with a pull of 6 to 8 lb. Catches and strike plates shall be dark brown or antique bronze finished.

3.1.6.3 Ferrules. Ferrules shall be provincial style with escutcheon pin as shown in the appropriate figures. Two types are required (see 6.4).

3.1.6.4 Table lock. The table locking rod shall be a minimum of 14 inches long (see 6.4).

3.1.6.5 Table eveners. The table eveners shall keep the intermembering top and leaves even when they are joined (see 6.4).

3.1.6.6 Glides. Glides shall be single prong, stainless steel or nylon and shall be as large as the leg or base permits. The prong shall be not less than 3/4 inch in length and securely fastened to the base of the glide so that it will not be easily detached.

3.1.6.7 Hinges. Butt hinges, used on the hutch, buffet, and server doors, shall be 2-1/2 inches long, five knuckle, antique bronze plated steel. Each hinge shall be fully mortised and secured with six brass-plated screws.

Hinges used on the pivot top table shall be concealed type with 180° opening. They shall be brass with steel linkages. Each hinge shall be secured with four toe screws (see 6.4).

3.1.6.8 Adjustable shelf hardware. Bookcase shall have shelf standards and supports. The standards and supports shall be cold-rolled steel or anodized aluminum with antique bronze finish. The standards shall be 5/8 inch wide, slotted every 1/2 inch, and numbered every inch. Standards shall be surface mounted securely with brass-plated screws. The supports shall lock into the standards.

The adjustable shelves in the hutch, buffet, and server shall rest on heavy-duty brass or bronze-plated steel supports. Each support shall have a minimum 7/32-inch diameter by 3/8-inch long stem and a minimum 1/2-inch wide support area. These supports shall be inserted into holes bored in the side and partition panels. Shelves shall have three positions for vertical adjustment, spaced 1-1/2 inches apart O.C.

3.1.6.9 Center drawer-guiding system. System shall consist of two components: female guide and male guide. Components shall interlock.

The following systems are acceptable:

Female guide	Male guide
1. Wood full length channel and plastic back bearing (see 6.4).	T-shaped wooden guide.
2. Plastic channel (see 6.4).	T-shaped wooden guide.
3. Steel, channel formed, 22-gage minimum.	T-shaped wooden guide or steel, channel formed, 22-gage minimum.

Female guide attachment.

1. Wood channel shall be glued to the bottom, reinforced with glue blocks, and stapled to the drawer front and back. Plastic back bearing shall be secured to the drawer back with three screws or three staples.
2. Plastic channel shall be secured to the drawer back with three staples and to the front with one staple minimum.
3. Metal channel. Back tab shall be fastened to the rear of the drawer back with three staples or three screws and to the front with one staple minimum.

Male guide shall be screwed to the front and back frame rails.

All guide parts shall be securely attached with no play.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

3.1.6.10 Table extension slides. Slides shall be either:

Wood, 2-3/8 inches thick, six-section, minimum 30 inches long, and open to 38 inches, or
Steel, six-section and open to 38 inches (see 6.4).

3.1.6.11 Attachment plates for hutch and buffet. Two attachment plates and eight adhesive-backed, mar-resistant pads shall be packed with each hutch. Mounting instructions shall be provided with these parts. The attachment plates shall be 2 inches long, minimum, by 3/4 inch wide by .027 inch thick minimum if plate has reinforcing formation or .074 inch thick minimum if plate is flat. Each plate shall be secured with minimum 3/4 x No. 6 tapping screws.

3.1.7 Particleboard. Particleboard used shall meet or exceed the requirements for grade 1-M-2 in ANSI A208.1-1979 with the following exception: Panels 7/8 inch thick or less shall have a minimum average screw-holding capacity of 285 lb face, 235 lb edge.

Thickness shall be as specified herein. Moisture content shall not exceed 9 percent at time of laminating.

3.1.8 Lacquer. Minimum solids: cold application 21 percent, hot application 30 percent. Lacquer used in wood finish system shall meet the tests in 4.4.1.

3.1.9 Mirror, glass. Mirror glass shall be mirror quality plate glass, 1/4 inch thick ± 1/64 inch). Silvering, copper plate, and protective paint shall conform to best commercial practice. Reflected image shall be distortion free.

3.1.10 Wood.

3.1.10.1 Wood species. Woods permitted are those listed in table II.

TABLE II. Wood species

Exposed veneer 1/	Exposed solid parts 1/ 2/	Interior drawer parts 2/	Unexposed solid and plywood parts
Mahogany (Khaya or Swietenia)	Andiroba (carapa guianensis)	Andiroba (carapa guianensis)	Andiroba (carapa guianensis)
	Cherry	Ash (white)	Ash (white)
	Mahogany (Khaya or Swietenia)	Beech	Beech
	Walnut	Birch	Birch
		Mahogany (Khaya or Swietenia)	Hackberry
		Maple	Mahogany (Khaya or Swietenia)
		Oak	Maple
		Sweetgum	Oak
			Poplar
			Sweetgum

1/ Includes exposed interior surfaces such as door backs, shelves, and interior panels.
2/ Only one specie may be used in any one unit.

3.1.10.2 Solid wood requirements. Wood used for exposed parts, including drawer parts, shall be bright, well sanded, and free from brashness, discolorations, worm holes, splits, shake, or other defects which affect the appearance or which may affect the serviceability of the finished product. Wood used in unexposed parts may contain small defects such as pin-knots, sapwood, or mineral streaks provided they do not affect the strength of the part.

3.1.10.3 Wood seasoning. All wood, including veneers, shall be uniformly kiln dried to a 5- to 8-percent moisture content. After drying, it shall be held in temperature and humidity controlled storage for a sufficient time to ensure uniform moisture distribution among the individual parts. After gluing and before planing and sanding for crossbands, lumber cores shall be permitted to cure out to ensure uniform distribution of glue joint moisture and to minimize sunken joints, spring back, and stresses.

3.1.10.4 Hardwood plywood. All hardwood plywood shall be constructed in accordance with PS-51 and as specified herein. Glue bond shall be type II or better. All good grade (1) face veneers shall be edge glued. Wood used in plywood construction shall conform to 3.1.10.1. When edge banding is specified, it shall be minimum 5/16-inch thick wood of the same species used for other exposed parts of the unit. Banding shall be lap or butt-joined at the corners. The core and edge banding assembly shall be dressed to a uniform thickness before the application of the crossbands, face, and back veneers. Veneers and cores shall be as specified in table III.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

TABLE III. Hardwood plywood requirements

Face veneers	Back veneers	Crossbands and/or veneer core	Lumber core	Particle board core
Panels exposed to view in normal use positions including exposed interior surfaces.				
1/32 inch minimum (before sanding) Good grade (1) 1/ (See 3.1.10.5)	1/32 inch minimum (before sanding) Sound grade (2)	1/24 inch minimum. Sound grade (2)	Sound grade	See 3.1.7.
Interior drawer parts, case backs, and slip seat panels				
1/28 inch minimum (before sanding) Sound grade (2)	1/28 inch minimum (before sanding) Sound grade (2)	Sound grade (2)	N.A.	N.A.
Dust panels				
1/24 inch minimum Utility grade (3)	1/24 inch minimum Utility grade (3)	Utility grade (3)	N.A.	N.A.

1/ Exposed interior surfaces shall have Sound grade(2) veneer minimum.

3.1.10.5 Good grade(1) veneer requirements. Face veneers shall be book matched for figure and color. Veneer strips shall be minimum 3-1/2 inches wide. There shall be no patches or imperfections except that if there are pin knots, there shall be no more than two on any 36-inch long section of veneer.

3.1.11 Laminated plastic. The decorative face sheets for the top panels of all items shall conform to style D, type I, class 1. of L-P-508, and the thickness shall be 0.050 inch. The plastic laminate shall match the reference panel FSS-L-01006 (see 6.3). The backing sheet shall be style ND, type IV, minimum thickness 0.030 inch as specified in L-P-508.

Alternatively, the following low pressure backing sheet shall be used: Wood fiber mat, 0.041 ± .004 inch thick, manufactured by a continuous process, impregnated with resin, such as urea formaldehyde, modified with crosslinking resins such as acrylic or vinyl acetate, and having a dry resin to dry fiber percentage of 32.6 percent ± 5 percent (see 6.5). Grain direction of backing sheet shall be the same as the decorative face sheet.

3.1.12 Hardboard. Hardboard shall conform to class 1. SIS of PS-58. Hardboard used for drawer bottoms shall be printed with an oak grain on the smooth face.

3.2 Construction details. The construction details, as shown in figures 17 - 40 and described in the following paragraphs, are the minimum acceptable to the Government. In any case where there is a conflict between the text of the specification and the figures, the text shall prevail.

Construction detail reference

Item	Figure number
Headboard	18
Dressers	17, 19, 20, 21
Chest	17, 20, 21, 22, 23
Mirror	24
Night stand	26, 27
Hutch	28
Buffet	17, 21, 25, 26, 29
Server	17, 21, 25, 26, 29
Oval extension table	30, 31, 32
Chairs	33, 34
Coffee table	32, 35
End/lamp tables	36
Pivot top table	37
Bookcase	38, 39
Desk	40
Bed frame, metal	41

3.2.1 Joinery. Joinery shall be mortise and tenon, tongue and grooved or doweled (see 3.1.3). Even though one joint type is visually illustrated in the drawings, you may use one of the other joint types specified above, provided the final assembly is rigid and durable. Joints shall be true, and all wood parts shall be accurately, neatly, and smoothly milled. Joints subject to stress shall be reinforced with rubbed-in-place glue blocks and/or screws as applicable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

Miter joints of aprons, bases, or other similar joints shall be glued and clamp nailed.

Mortises or grooves for rails, panels, and dust bottoms shall be 1/2 inch deep minimum except for drawer bottoms which shall be 1/4 inch deep minimum.

Tenons shall be not less than one-third the thickness of the rails or panels but not less than 1/4 inch thick.

3.2.1.1 Tolerances. Where tolerances are not specified, the following tolerances will be permitted:

Overall dimensions: plus, minus 1/8 inch.
Solid wood part dimensions: plus 1/16 inch, minus 1/32 inch.
Plywood part dimensions for 3/20-inch thick plywood or thicker; plus 1/16 inch, minus 1/32 inch.
Mirror glass size: plus, minus 1/16 inch.

3.2.2 Direction of grain. The grain pattern on the top shall run parallel to the length; the pattern on all edges and bandings shall run the length and width of the panel. The pattern on the side panels and the doors shall run vertically. Grain on the drawer fronts shall be horizontal. Shelf grain shall run lengthwise. The hutch back shall be one piece with vertical grain.

3.2.3 Gluing. All structural joints shall be thoroughly glued (see 3.1.2). Nails, brads, or staples will not be permitted on outside frames. A 6d barbed or cement coated nail driven through the tenon into the case frame or post will be permitted, provided the head does not show when the furniture is in its use position. Excess glue shall be neatly cleaned from exposed surfaces.

3.2.4 Legs and posts. Legs and posts shall be of one piece solid wood or glued-up of two full length pieces with the joint line on the side of the post. All wood used for built-up parts shall be carefully matched for grain and color. All legs or base support members, except the headboard, shall have glides (3.1.6.6).

3.2.5 Drawers and drawer bearer frames.

3.2.5.1 Drawers.

TABLE IV. Drawer components (dimensions in inches)

	Front	Sides and back		Bottom	
Material	Minimum 5-ply hardwood plywood 1/ 2/ with decorative moulding (see figures).	Solid wood or	minimum 5-ply veneer core plywood	3-ply or oak printed plywood	hardboard
Reference	3.1.10.4	3.1.10.2	3.1.10.4	3.1.10.4	3.1.12
Thickness	3/4	7/16		3/20 min.	3/16 min.

1/ Core material may alternatively be medium density fiberboard conforming to NPA-4.
2/ When a nonlumber core is used, the top edge of the drawer front shall be banded (3.1.10.4).

Drawer sides shall be neatly multifinger dovetailed and glued to the drawer front and back. Drawer sides, front, and back shall be grooved to receive the bottom. In lieu of grooving the back, the back may be cut off, up to an additional 1/4 inch, to permit insertion of an overlapping bottom. The bottom shall be reinforced with not less than six rubbed glue blocks (eight if drawer is over 15 inches wide). Narrow crown staples, spaced 3 inches apart maximum, may be used in lieu of glue blocks. Staples shall be driven flush.

The drawer sides and back shall be not more than 1/4 inch less in height than the drawer opening. The drawer back may be 1/8 inch less in height than the sides to allow for adjusting the drawers in the case. The top edges of the drawer sides and back shall be either rounded or sanded smooth with the edges eased. Space between the back of the drawer and the case back shall not exceed 3 inches, except for occassional tables when it shall not exceed 9-1/2 inches. A 1/16- to 3/32-inch clearance shall be maintained around the perimeter of the drawer fronts.

The top edge and ends of drawer fronts shall be slightly beveled or offset to prevent sticking and to allow free sliding of the drawer as soon as it is opened. A female guide shall be securely attached to the center of the drawer bottom (3.1.6.9). Drawers shall not be racked and shall operate smoothly without binding or excessive side play. With drawers two-thirds out, drop shall not exceed 5/16 inch.

Drawer pulls (3.1.6.1 and 3.1.6.2) shall be neatly installed as shown in the figures.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

3.2.5.2 Drawer bearer frames and top frames. The drawer bearer (dust panel) frame and top frame shall consist of a front rail, back rail, and side rails. An intermediate rail is required in frames under drawers over 34 inches wide or under double drawers. Rails shall be 3/4 inch thick by 1 1/2 inches wide. Intermediate rail under double drawer shall be 3/4 inch thick by 3 inches wide. Frames shall be mortise and tenoned or double doweled together.

Front and back rails of frames shall be either double doweled or mortised and tenoned into the ends. These joints shall then be toe screwed.

All drawer bearer frames (except under knee hole drawer in desk and under drawers in occasional tables) shall have a dust bottom let into the rails on all four sides with minimum play.

Dust bottom shall be either:

1. Three-ply hardwood plywood (3.1.10.4), minimum 3/2 inch thick or
2. Hardboard (3.1.12), minimum 3/16 inch thick.

The male portion of the center drawer-guiding system (3.1.6.9) shall be securely screwed to the drawer bearer frame. Tack glides shall be used on the front rail for drawer to ride on. Stop blocks (two per drawer) shall be glued and screwed to the frames to prevent the drawer from hitting the back of the case.

3.2.6 Doors. Doors shall be 3/4-inch-thick, minimum five-ply hardwood plywood (3.1.10.4) with decorative moulding (see figures). Core material may alternatively be medium density fiberboard conforming to NPA-4. When a nonlumber core is used, the top edge and both side edges of the door shall be banded (3.1.10.4).

Hinges (3.1.6.7), catches (3.1.6.2.1) and knobs (3.1.6.1) shall be neatly and securely installed as shown in the figures.

The free edges of the doors shall be slightly beveled to prevent sticking. A 1/16- to 3/32-inch clearance shall be maintained around the perimeters of the doors.

3.2.7 Tops. Tops shall have a decorative plastic laminate face with backing sheet (3.1.11) securely bonded to a 3/4-inch-thick particleboard core (3.1.7). Tops shall be self-edged. Case tops shall be securely fastened to the case with tapping screws. Table tops shall be securely fastened to the table aprons with tapping screws or steel fasteners. The sag or warp in the tops of all units, except the extension table, shall not exceed 1/8 inch.

3.2.8 Table, extension. Extension table shall have three 12-inch leaves without aprons. The leaves and top sections shall have four dowels per joint with matching holes to assure accurate alignment. Leaf joints shall be flush on top and edges. Table eveners (3.1.6.5), table lock (3.1.6.4), and extension slides (3.1.6.10) shall be attached to the top with tapping screws.

The table shall be tested as specified in 4.4.2.1 with no loosening of parts or impairment of operating efficiency after testing. Before and after testing, the total sag in table top, with all leaves installed, shall not exceed 1/4 inch.

3.2.9 Case ends, partitions, and bottom panel of hutch and server. These panels shall be 3/4-inch-thick, minimum five-ply hardwood plywood (3.1.10.4). Exposed edges of nonlumber core panels, visible in normal use position, shall be banded as specified in 3.1.10.4.

3.2.10 Table aprons. The aprons shall be 3/4-inch-thick, solid wood (3.1.10.1 and 3.1.10.2) or five-ply hardwood plywood (3.1.10.4). Curved aprons shall be steam bent solid wood, horizontal laminated stock, or minimum nine-ply hardwood plywood. The aprons shall be slotted for steel fasteners or bored for tapping screws as applicable.

3.2.11 Case backs. Case backs of night stand, hutch, buffet, server, and bookcase shall be minimum 3/20-inch, three-ply hardwood plywood (3.1.10.4). The case backs of all other units, except desks, shall be either 3/20-inch, three-ply hardwood plywood or 3/16-inch hardboard (3.1.12). All case backs, except desk, shall be one-piece construction.

The ends of all cases shall be rabbeted to receive the backs. Tops shall be rabbeted or may extend over the case back. The case back shall be attached to the case (including drawer frame rails, fixed shelves, and partitions) with pneumatically driven staples spaced a minimum of 3 inches apart.

3.2.11.1 Desk back. The desk back shall be minimum 3/4-inch-thick, five-ply plywood (3.1.10.4). Pedestal and center section back panels shall each be one piece construction with molding overlayed as shown in figure 16.

3.2.12 Shelves. Shelves shall be 3/4-inch-thick, minimum five-ply hardwood plywood (3.1.10.4). When a nonlumber core is used, the front edge shall be wood banded (3.1.10.4). All adjustable shelves, except those in the bookcase, shall be routed 1/8 inch deep where shelf rests on the shelf support to prevent movement.

3.2.13 Beds.

3.2.13.1 Headboards. Headboards shall be 3/4-inch-thick, minimum five-ply hardwood plywood (3.1.10.4) and solid wood (3.1.10.1). See figures 1 and 18.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

3.2.13.2 Metal bed frame. The unit shall consist of a frame and four legs, each equipped with glides. See figures 1 and 41. Glides shall be:

1. All high impact plastic, 2-3/4-inch diameter, minimum or
2. Brass or nickel plated steel stem and base with high impact plastic insert, 2-inch diameter, minimum.

Glides shall have a stem designed to prevent their dropping out of the socket.

Frame shall be adjustable to accommodate standard 3' 3" and 4' 6" boxsprings. Three types of frame construction are acceptable. The first two types are illustrated and described in figure 41. The third type is a channel construction with outward extending, plastic covered, boxspring retaining tabs. The only allowable source for the channel type frame is listed in 6.4.

All sharp edges and corners shall be eliminated. Frames shall be smooth and free of rust, scale, oil, dirt, or other foreign matter. Frames shall be painted with either a baking or air dry enamel. Plated bolts, nuts, and lockwashers, for attaching headboard to frame, shall be supplied with the frame.

3.2.14 Chairs, dining room. Chair frame shall be solid wood (3.1.10.1). See figures 11, 33, and 34 for construction details.

3.2.14.1 Slip seats. Slip seats shall have a 3/8-inch thick minimum, veneer core, plywood base (3.1.10.4). Four 1/2-inch diameter vent holes shall be bored in the seat panel. The plywood bottom face shall be walnut stained and sealer coated.

The top of the plywood panel shall be covered with a layer of 1-1/2-inch-thick, minimum, polyurethane (3.1.5.1). Alternatively the polyurethane shall be form molded to the panel. After molding, the polyurethane shall be 1-1/2 inches thick minimum. Upholstery fabric (3.1.4) shall then be neatly applied over the foam and securely fastened to the bottom.

Slotted or phillips screws shall be used for attaching the slip seats to the frame.

3.2.15 Mirror. Mirror glass shall be as specified in 3.1.9. Wood frame shall be constructed as described in 3.2.1 and figure 24. Mirror back shall be three-ply hardwood plywood (3.1.10.4), 3/20 inch thick minimum, or hardboard (3.1.12), 3/16 inch thick minimum. The mirror backs shall be closely fitted and tightly secured to the frame.

All dresser mirrors shall be equipped with provision for attaching to the case and for hanging. Attaching means shall include a tilting device which is securely attached to the back of the mirror. Pilot holes shall be drilled in the dresser case back to accept tilting device.

3.3 Plastic laminate and wood finish.

3.3.1 Plastic laminate. Plastic laminate shall match GSA Standard sample (walnut tone on mahogany) FSS-L-01006 (6.3) for color and appearance.

3.3.2 Finish, exposed wood parts, and surfaces. (Includes exposed interior surfaces such as door backs, top and bottom faces of shelves, and interior compartments.) All surfaces exposed to view in normal use shall be sanded smooth and finished. Exposed wood finish shall match standard sample FSS-L-01006 (6.3) for color and appearance. The two side edges of the drawer fronts shall be filled and finished to match, as closely as possible, the top edge. The side and back edges of the adjustable shelves shall be stained and sealed. The natural grain of the wood shall not be clouded by the finishing materials. Bleaching agents or materials shall not be used. The application of materials drying time, sanding, cleaning, and rubbing shall be controlled to produce items of uniform finish without sags, runs, orange peel, or other defects detrimental to a smooth quality appearance. Final finish shall be satin.

3.3.2.1 Recommended procedure for finishing exposed wood surfaces.

1. Sap stain to equalize color.
2. Apply selected stain to produce color specified.
3. Wash coat with adhesive sealer.
4. Scuff sand, using sandpaper grit of fineness needed to produce proper surface.
5. Fill to degree necessary to match standard sample.
6. Seal with adhesive type sealer.
7. Sand, using sandpaper grit of fineness needed to produce proper surface.
8. Shade to tie-in color variation, if necessary.
9. Top coat with lacquer (two coats). The materials and final finish shall be of a quality to meet the tests in 4.4.1.
10. Rub with material necessary for final finish to conform to standard sample.

NOTE: Operation number 8 may be performed where shown or after operation number 5.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

3.3.3 Finish, unexposed parts, and surfaces. All unexposed interior and exterior parts and surfaces, including the drawer interior and exterior surfaces, drawer bearer sections, and drawer guides, shall be machined smooth and cleaned. Then they shall be treated by either method 1 or method 2 as specified below:

Method 1, sealer and lacquer. Unexposed parts and surfaces shall receive one coat of lacquer sealer and one coat of lacquer (3.1.8). The drawer guides shall be rubbed with paraffin, or dipped in a paraffin solution.

Method 2, chemical treatment. Unexposed parts and surfaces shall be given a moisture-retarding and lubricating treatment (see 6.4). The entire surfaces or the unexposed parts of the drawers shall be submerged in the moisture-retarding solution for not less than 3 minutes. The drawers shall be allowed to drain before insertion into the furniture cases, and all surplus of the solution shall be thoroughly wiped from finished surfaces to insure a clean, smooth finish and free sliding drawer operation.

Alternatively, the solution may be applied by spraying a heavy wet coat, then oven dried for not less than 30 minutes at a temperature of not less than 120° F.

3.4 Identification marking. Each item shall be permanently and clearly marked with contrasting, indelible ink in an inconspicuous place, with the Federal Stock Number, contract number, this specification number, the month and year of manufacture, and the manufacturer's name or trademark.

3.5 Workmanship. A high degree of craftmanship, with care in fabrication and quality control, shall be exercised in order to produce items of furniture suitable for use in a home. The methods of construction, veneering joinery, assembly, the care used in the fitting and installing drawers with regards to clearances and ease of operation, and the appearance of the furniture in general shall be in accordance with the minimum requirements of this specification. Each unit of furniture shall be free from any defects that affect appearance or which may affect serviceability during a reasonable lifetime of the furniture.

4. QUALITY ASSURANCE PROVISIONS

4.1 Inspection provisions. Details of the preproduction sample requirement are contained in the solicitation. In addition, approval of the preproduction sample authorizes the commencement of production, but does not relieve the contractor of responsibility from conformance with all other applicable provisions of this specification. Inspection requirements are stated in GSA form 1424, paragraph 5. All examination and testing shall be in accordance with section 4 of this specification.

4.2 Sampling for inspection and acceptance. Sampling for inspection and acceptance shall be performed in accordance with the provisions set forth in MIL-STD-105, except where otherwise indicated.

4.3 Inspection levels and acceptable quality levels (AQL's). Inspection levels and acceptable quality levels expressed in percent defective shall be as shown in table V.

TABLE V. Acceptable quality levels in accordance with MIL-STD-105

For examination in	Inspection level	AQL's	
		Major	Total
4.3.1	II	4	10.0
4.3.2	II		4.0
4.3.3	S-2		4.0

4.3.1 Visual examination. Examination of the end item(s) shall be in accordance with the classification of defects specified in table VI and acceptable quality levels (AQL's) specified in 4.3 herein. The lot size shall be all units of the same type offered for inspection at one time. The sample unit for this examination shall be one complete item.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

TABLE VI. Classification of end item defects

Examine	Defects	Classification	
		Major	Minor
Finish and appearance of exposed wood parts visible in normal use position.	Does not match standard reference panel with respect to color.	X	
	Discoloration (bleeding) over 1 in^2.		X
	Spotted, affecting appearance.		X
	Light or dark colored area affecting appearance.		X
	Area of no lacquer film over 1 in^2 in area.	X	
	Glue stain or glue line clearly showing, affecting appearance.		X
	Excess glue not removed.		X
	Finish peeling, flaking, blistered, cracked, checked, or wrinkled.	X	
	Finish cut or rubbed through to wood.		X
	Open grain. Finish material not filling pores.		X
	Orange peel, affecting appearance.		X
	Damage or scratch, less than 1 inch long, or 1 inch square.		X
	Damage or scratch over 1 inch square or 1 inch long.	X	
	Edges of drawer fronts not filled and finished as required.	X	
	Finish tacky, i.e., not completely dry.		X
	Rough or gritty surface or foreign matter embedded in finish.	X	
	Light colored edge not touched up.		X
	Burn-in or repairs not neatly accomplished.		X
	Unstained (white) wood visible when item is in normal use position.	X	
	Not polished where required.		X
Finish of exterior wood parts not visible in normal use.	Finish not as specified.	X	
	Finish not applied where required.	X	
Finish of interior and concealed wood surfaces.	Top edge of drawer front or door scratched, bruised, or not finished same as exterior wood surfaces.		X
	Buffet and server compartments or drawer interiors are rough.	X	
	Stain or sealer coat omitted from bottom edge of drawer.	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

TABLE VI. Classification of end item defects (Cont'd)

Examine	Defects	Classification	
		Major	Minor
Finish of hardware.	Does not match standard finish.	X	
	Component tarnished or stained, affecting appearance.		X
	Rusted or corroded.	X	
	Not coated with protective finish.	X	
Quality of solid wood or built-up stock on exposed and unexposed surfaces.	Species of wood not as specified.	X	
	Component not fabricated of one solid piece of wood where required.		X
	More than one species of wood used for exposed wood components of any one item.		X
	Direction of grain not as specified.		X
	Check or split over 1 inch in length..	X	
	Wood warped, affecting appearance or serviceability.	X	
	Loosened grain or shake on exposed surface.	X	
	Loosened grain or shake on unexposed surface.	X	
	Honeycomb.	X	
	Loose or unsound knot.	X	
	Hole on exterior exposed surface.	X	
	Glue line in builtup stock open over 1 inch in length.	X	
	Glued up pieces uneven in builtup stock	X	
	Wave of uneven sanding.		X
	Machine mark on exposed surface, affecting appearance.		X
	Any mineral streak on exposed surface over 1/8 inch by 4 inches or 1/4 inch by 2 inches.	X	
	Wood chipped or splintered on exposed surface of drawer interior.	X	
	Any manufacturing defect or defect native to the wood filled in with plastic wood or other filler material.		X
Quality of plywood.	Species of wood not as specified.	X	
	Construction not as specified.	X	
	Number of plys not as specified.	X	
	Veneer delaminated.	X	
	Telegraphing of core or cross bands on exposed surface.	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

TABLE VI. Classification of end item defects (Cont'd)

Examine	Defects	Classification	
		Major	Minor
Quality of particleboard.	Not material specified.	X	
Quality of laminated plastic.	Not material specified.	X	
	Color or grain character of face sheet does not match reference panel.	X	
	Face or backing sheet missing.	X	
	Top surface not proper finish.		X
	Sheet containing area of no adhesion.	X	
	Face sheet damaged, dented, cracked, marred, or discolored.	X	
	Scratch or nick in face sheet, affecting appearance.		X
	Evidence of telegraphing lumber-core grain.		X
Quality of hardboard.	Not material specified.	X	
Construction, assembly, and attachment of unexposed and exposed parts.	Not as specified or not as shown on drawings or figures.	X	
	Component not size or shape specified.	X	
	Component not type or design specified.	X	
	Component not assembled as specified.	X	
	Component missing.	X	
	Component loose or insecurely fastened where rigidity is required.	X	
	Component out of alignment or out of square affecting serviceability.	X	
	Poor fit of component to mating part.	X	
	Wood component not glued as specified.	X	
	Solid wood used in place of veneer or vice versa.		X
	Wood component damaged or not properly machined.		X
	Edges not "eased off" where required.		X
	Any loose or unsound glued joint.	X	
	Wood joint not as specified.	X	
	Glue joint open over 1/16 inch on exposed part.	X	
	Over 1/4-inch sag in extension table top.	X	
	Top panels warped over 1/8 inch in width or length.	X	
	Top sag over 1/8 inch in any piece except extension table.	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

TABLE VI. Classification of end item defects (Cont'd)

Examine	Defects	Classification	
		Major	Minor
Upholstery and padding.	Not material specified.	X	
	Color not as specified.	X	
	Stained, streaked, spotted, faded, affecting appearance.	X	
Upholstery workmanship.	Not securely and neatly attached.	X	
Steel frame assemblies.	Not steel specified, not rigid, cross members not perpendicular to vertical members, gaps in joints.	X	
Welding	Missing, not sound (broken, cracked, burnt, poor adhesion).	X	
	Not ground smooth, pits not filled.		X
Screws, lockwashers, and rivets.	Screws and lockwashers not metal plated; threads stripped on more than one screw, lockwasher, screw, or rivet missing.		X
Enamel finish.	Poor adhesion, i.e. blistered, checked, peeling; tacky (not dry to touch); color separation, stain, not smooth and uniform, runs, sags, foreign matter in coating, area of thin coating or abrasion.	X	
	Color not compatible as required.		X
	Scratch through to base metal, bare spots, rust under coating.	X	
Miscellaneous hardware.	Part(s) missing, type, wrong location, not securely attached.		X
Identification marking.	Missing, incorrect, or illegible.		X
	Text incomplete.		X
	Marking in wrong location.		X

4.3.2 Dimensional examination. Inspection shall be made for compliance with dimensions specified. Any dimension not within tolerance specified shall be classified as a defect (see 4.3 herein).

4.3.3 Examination of preparation for delivery. An examination shall be made to determine compliance with requirements of section 5. The sample unit shall be one shipping container, identical to each unit being shipped, fully prepared for delivery. Sampling shall be in accordance with MIL-STD-105 (see 4.3).

4.4 Tests.

4.4.1 Tests for lacquer and finish system. All the following tests, except U.V. test, shall be made on completely finished wood panels produced in accordance with the production procedures used in producing the furniture.

4.4.1.1 Alcohol. Age panel one week. Place 0.5 ml of 100-proof (50-percent) grain neutral spirits on the aged panel and trap for 2 hours with a watch glass. Remove glass and allow to evaporate. Light polishing of the area with a soft cloth must remove any whitening or spotting that developed.

4.4.1.2 Boiling water. Age panel one week. Pour 25 ml of boiling water on the leveled panel and allow to cool at room temperature. Dry the surface. After drying, there must be no graying or spotting.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

4.4.1.3 Cold check. Age panel one week. Follow ASTM D 1211 test procedure. After exposure to 10 cycles, there shall be no checking or cracking. True lacquer checking normally is one or more wavy or straight lines which cross the grain and do not appear related to grain structure. When a panel displays veneer checks, checks running parallel to the grain or glue line failure, the panel shall be disregarded and another panel tested.

4.4.1.4 Cold print. Age panel 48 hours. A 2- by 2-inch (approximately) piece of duck material (canvas), 8.25 oz/yd^2, minimum count 60 by 58 yarns per inch, shall be placed on the panel. Place a 1-lb weight on the material for 24 hours at 75° F. Bottom (contact surface) of the weight shall be flat and have a 1.128-inch diameter (1 in^2). After the weight is removed, light polishing with a soft cloth and liquid polish must remove any imprint.

4.4.1.5 Hot print. Follow cold print test procedure with the following exceptions:

(a) Weight is 1/2 lb instead of 1 lb.
(b) Temperature during test is 110° F instead of 75° F.

4.4.1.6 Ultraviolet light resistance. Spray one-half of a 6- by 9-inch white porcelain panel with two coats of the lacquer to be tested. Allow panel to air dry for at least 18 hours. Place panel 12 inches from a carbon arc lamp enclosed by a Corex D glass globe, and expose for 24 hours. After exposure, spray the other half of the panel in the same manner and allow to air dry for at least 4 hours. Compare the two finishes. There shall be no more than a slight darkening of the arc lamp exposed film.

4.4.1.7 Toughness and adhesion. The test for toughness and adhesion shall be made by using Bell Hardness Tester, Model No. 1001 (see 6.5) in accordance with manufacturer's instructions. The panel shall be marred both parallel and perpendicular to the grain. The resulting indentation shall show no whitening which is evidence of film separation. The film shall conform to the contour of the indentation and shall not crack in a brittle manner in or along the indentation.

4.4.2 Test for extension table. The sample to be tested shall be one complete table in the lot being offered.

4.4.2.1 Procedure. Place an assembled table with all leaves in place, on a flat surface. Extend a piece of thread lengthwise from one end of the table top to the other. Draw thread tightly and secure at both ends. Measure deflection in table top at center of table. Place a 150-lb load in the center of the table for 30 minutes. Remove load. Check to see that the thread is still tight. Measure deflection again. Table shall meet test requirements in 3.2.8.

4.4.3 Test for adhesives.

TABLE VII. Test for adhesives

Component	Characteristic	Requirement reference	Test method
Adhesive	Block shear test	3.1.2	ASTM D 905 1/

1/ Disregard a test specimen if:
a. It fails at less than 2,800 psi; and
b. It has 50 percent or more wood failure.

Rerun test if:
a. Average shear strength is less than 2,800 psi; or
b. There is a 10 percent or greater difference between high and low test specimen values; or
c. One or more samples fails at 2800 psi or more.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

4.4.4 Tests for upholstery fabric.

TABLE VIII

Characteristic	Requirement	Test method 1/
Breaking strength (load), lb, minimum		
Warp	180	5100
Filling	110	5100
Tearing strength, lb, minimum		
Warp	18	ANSI/ASTM D 3597
Filling	22	ANSI/ASTM D 3597
Surface abrasion, cycles (double rubs), minimum, oscillatory cylinder method	15,000	ANSI/ASTM D 3597
Seam efficiency	2/	5110

1/ Methods 5100 and 5110 are included in Federal Test Method Standard No. 191.
2/ Nylon thread of a size comparable to that specified in CCC-C-00540 may be used to test for the seam efficiency requirements of CCC-C-00540.

5. PREPARATION FOR DELIVERY

5.1 Packaging (commercial). The furniture described herein shall be packaged in accordance with normal commercial practice. The complete package shall be designed to protect the particular item against damage during multiple shipments, handling, and storage.

5.2 Packing (commercial). The furniture described herein, packaged as specified in 5.1, shall be packed in containers to insure delivery at destination; provide for redistribution by the initial receiving activity; and be acceptable by common carrier under the National Motor Freight Classification and Uniform Freight Classification.

5.3 Marking. Marking shall be as specified in the contract or purchase order and shall include all applicable package identification information and precautionary marking required by the National Motor Freight Classification and Uniform Freight Classification for items of furniture.

6. NOTES

6.1 Intended use. This line of furniture is intended for use in family housing.

6.2 Ordering data. Purchasers should select any desired options offered herein and procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) Group, item, and size(see 1.2.1).
(c) Color of upholstery material and, if other than specified, the type of material required (see 3.1.4).

6.3 Standard sample. A sample plastic laminate panel (walnut or mahogany: FSS-L-01006) may be obtained from:

National Furniture Center
Engineering Branch
GSA-FSS
Washington, DC 20406

A list of manufacturers (and their product numbers) who make an approved match to FSS-L-01006 is in the invitation to bid. Using one of the approved laminates does not relieve the contractor of the responsibility of ensuring that the laminated plastic is a proper match for pattern/color to the standard plastic laminate panel.

6.4 The following manufacturers are known sources of supply for the item indicated:

3.1.6.1 Drawer knob with escutcheon.
Keeler Brass Co. #3573-K11615, or equal
Grand Rapids, Michigan 49502

Bassick Sack Division #DC 19962-S805108, or equal
Stewart-Warner Corporation
Winston-Salem, North Carolina 27105

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:41Z
Check the source to verify that this is the currentversion before use.

Door-key style pull with escutcheon.
Keeler Brass Co. #N518-K13131, or equal.

Bassick Sack Division #DC 25037V-S80510E, or equal.

3.1.6.2 Drawer pull with bail.
Keeler Brass Co. #163 H334, or equal.
Bassick Sack Division #DC 40105-S2253-K, or equal.

3.1.6.3 Ferrules (all units except dining table).
Keeler Brass Co. #K897, or equal.

Bassick Sack Division #DC17229, or equal.

3.1.6.4 Ferrules (dining table).

Keeler Brass Co. #K8188, or equal.

3.1.6.4 Table lock.
National Lock Co. #6J-2975H, or equal
Rockford, Illinois 61101

3.1.6.5 Table eveners.
Southern Tool Co. #801, or equal
P.O. Box 4508
Winston-Salem, North Carolina 27107

3.1.6.7 Hinges. (Concealed type.)
Selby Furniture Hardward Co.
#16542 or equal
17 E. 22 St.
New York, NY 10010

3.1.6.9 Center drawer guiding system.
Plastic back bearing - Ronthor R-40-28, or equa.
Plastic channel - Ronthor R-40-29, or equal
Ronthor, a Division of Evans Products Company
Route 46
Little Falls, NJ 07424

3.1.6.10 Table extension slides.
Jefferson Woodworking Co.
1316 W. Hill St.
Louisville, KY 40210

B. Walter Co. Inc.
P.O. Box 278
Wabash, IN 46992

3.1.11 Laminated plastic
(alternate backing sheet)
Gator-Ply
International Paper Company
Statesville, NC 28677

3.2.13.2 Metal bedframe.
Angle frame - Harvard Mfg. Co.
24300 Solon Rd.
Bedford Heights, OH 44146

Leggett and Platt, Inc.
Metal Bed Rail Div.
P.O. Box 140
Linwood, NC 27299

Channel frame - Beauti-Glide/Seymour Div. of
Lear Siegler
Chestnut & Ninth Streets
Seymour, IN 47274

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

3.3.2 Finish, unexposed parts and surfaces
Method 2, chemical treatment - Nelsonite No. 15CO2
Nelsonite Chemical Products, Inc.
776 Leonard St., N.E.
Grand Rapids, Michigan 49503

6.5 Bell Laboratories Hardness Tester. Information about the Bell Laboratories Hardness Tester, Model No. 100i may be obtained from:

U.S. Testing Company, Inc.
Instrument Marketing Division
1415 Park Avenue
Hoboken, NJ 07030

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:41Z
Check the source to verify that this is the currentversion before use.

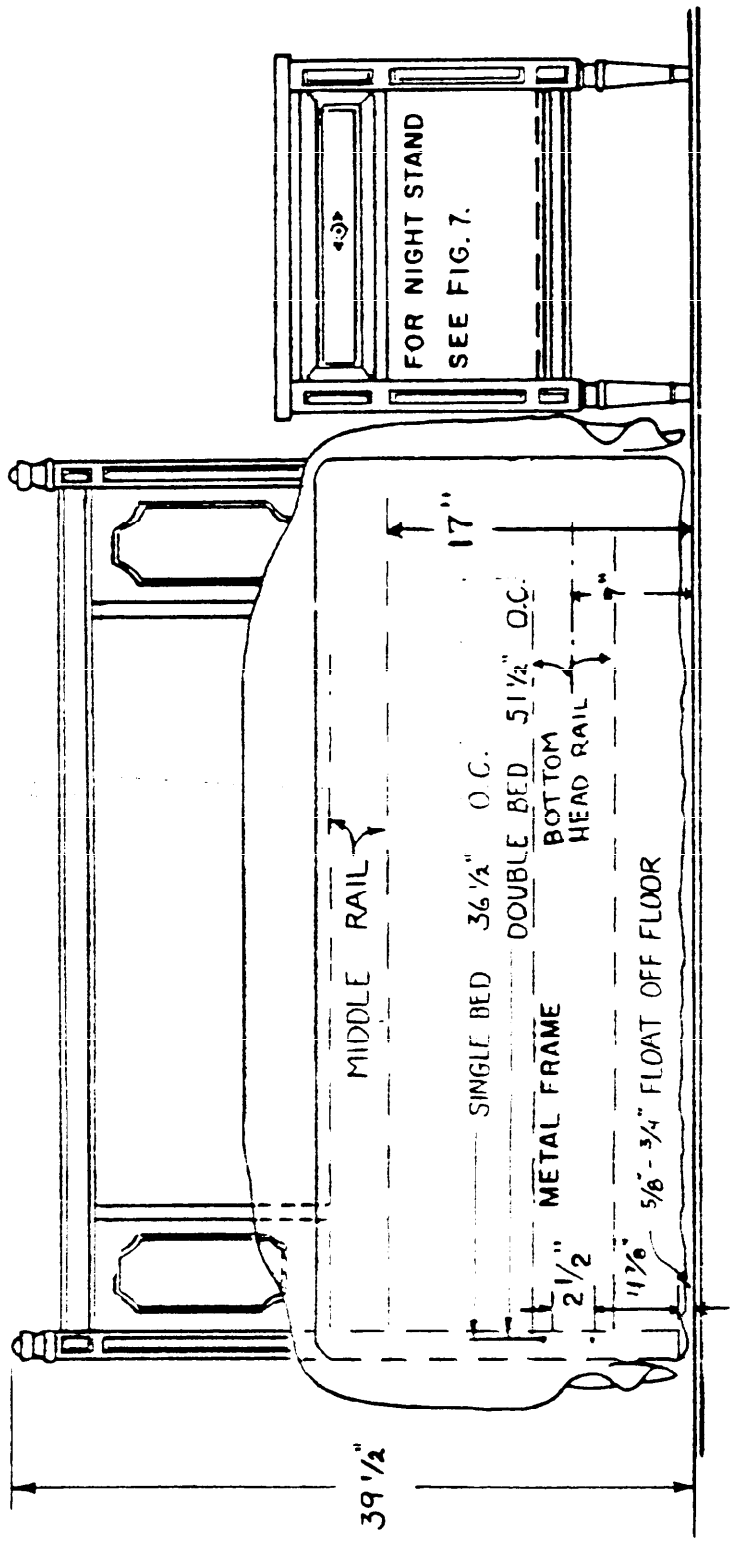


Figure 1. Headboard W/Frame

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the currentversion before use.


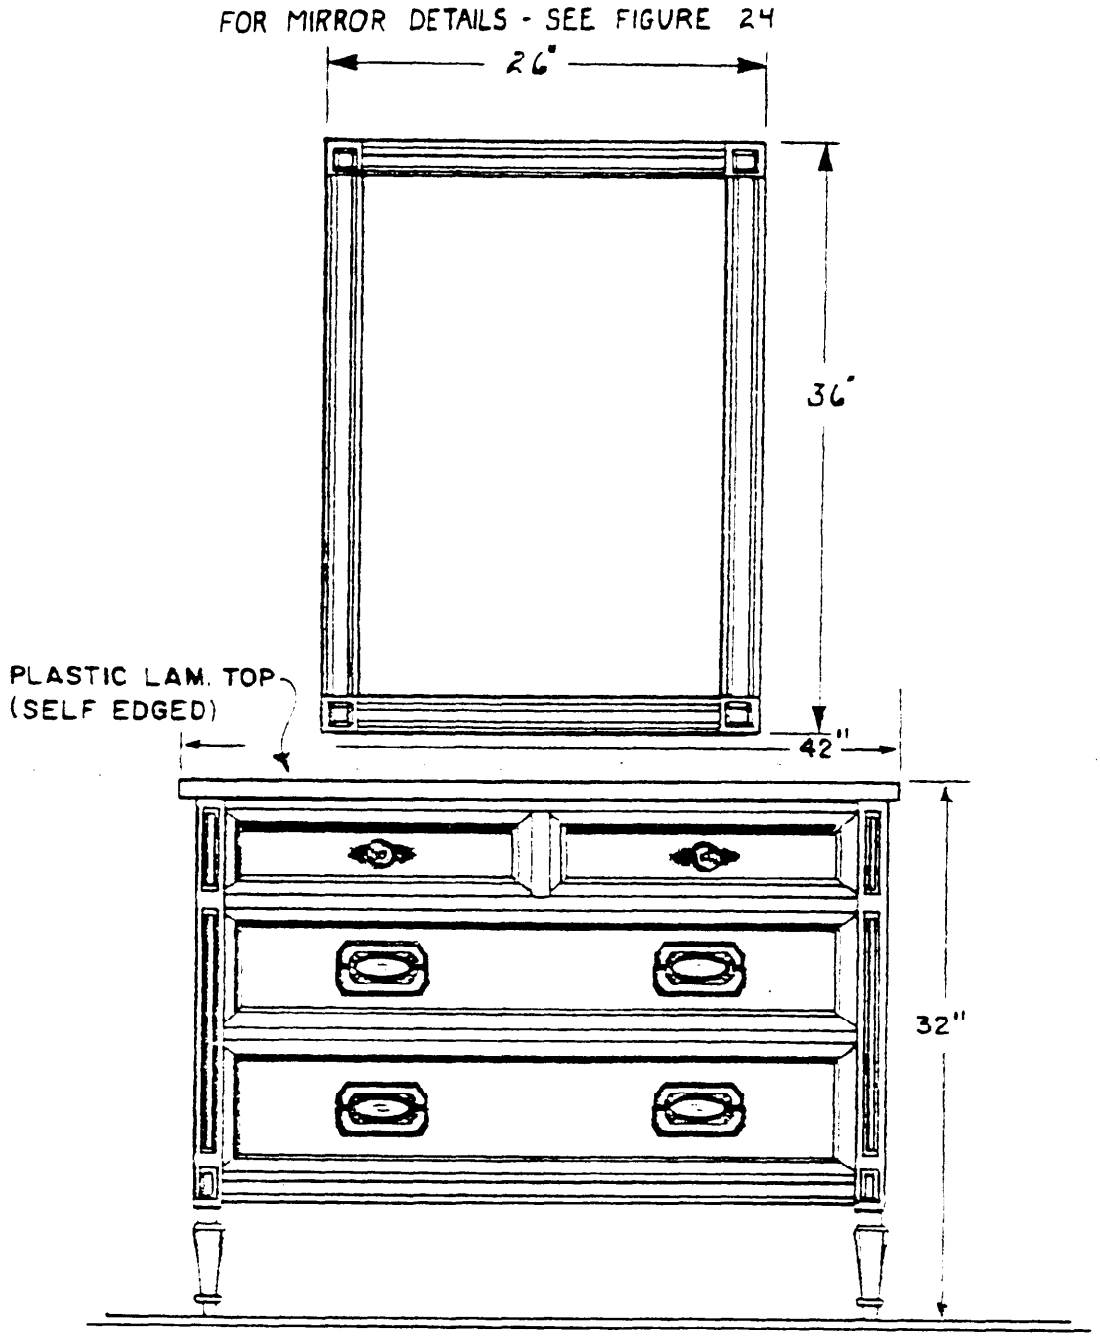


Figure 2. Single Dresser W/Size 1 Mirror


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

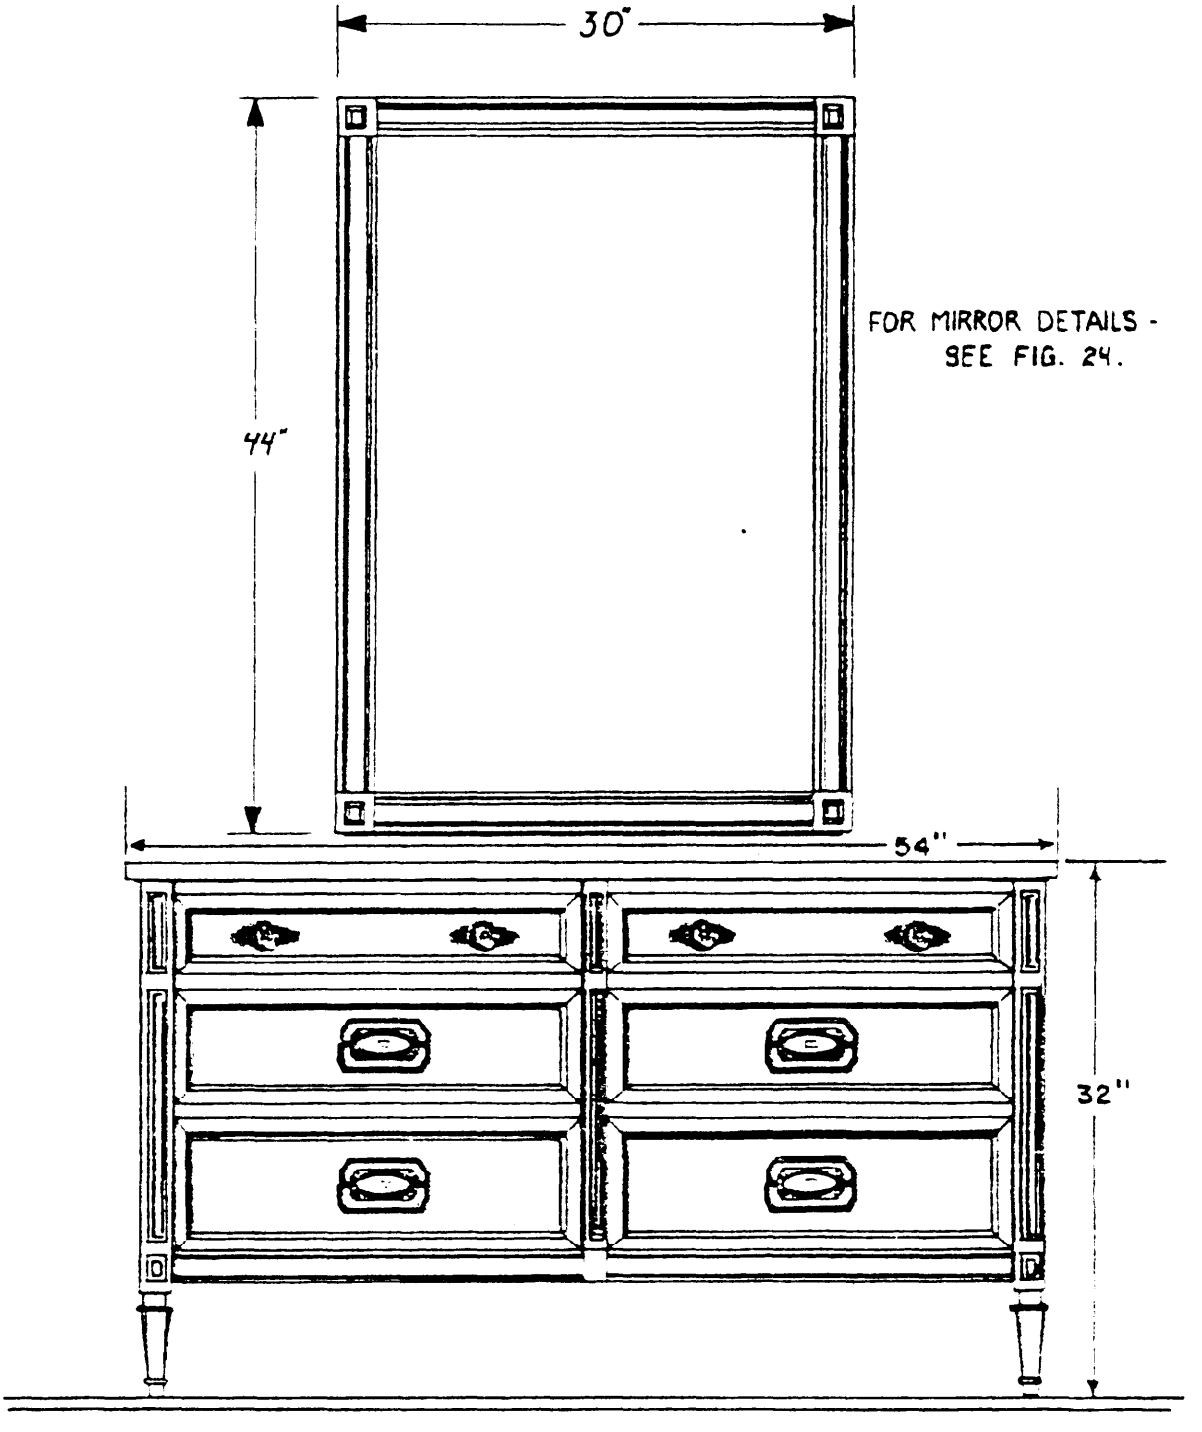

FOR DRESSER DETAILS - SEE FIGURES 17, 19, 20, 21.

Figure 3. Double Dresser W/Size 2 Mirror

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

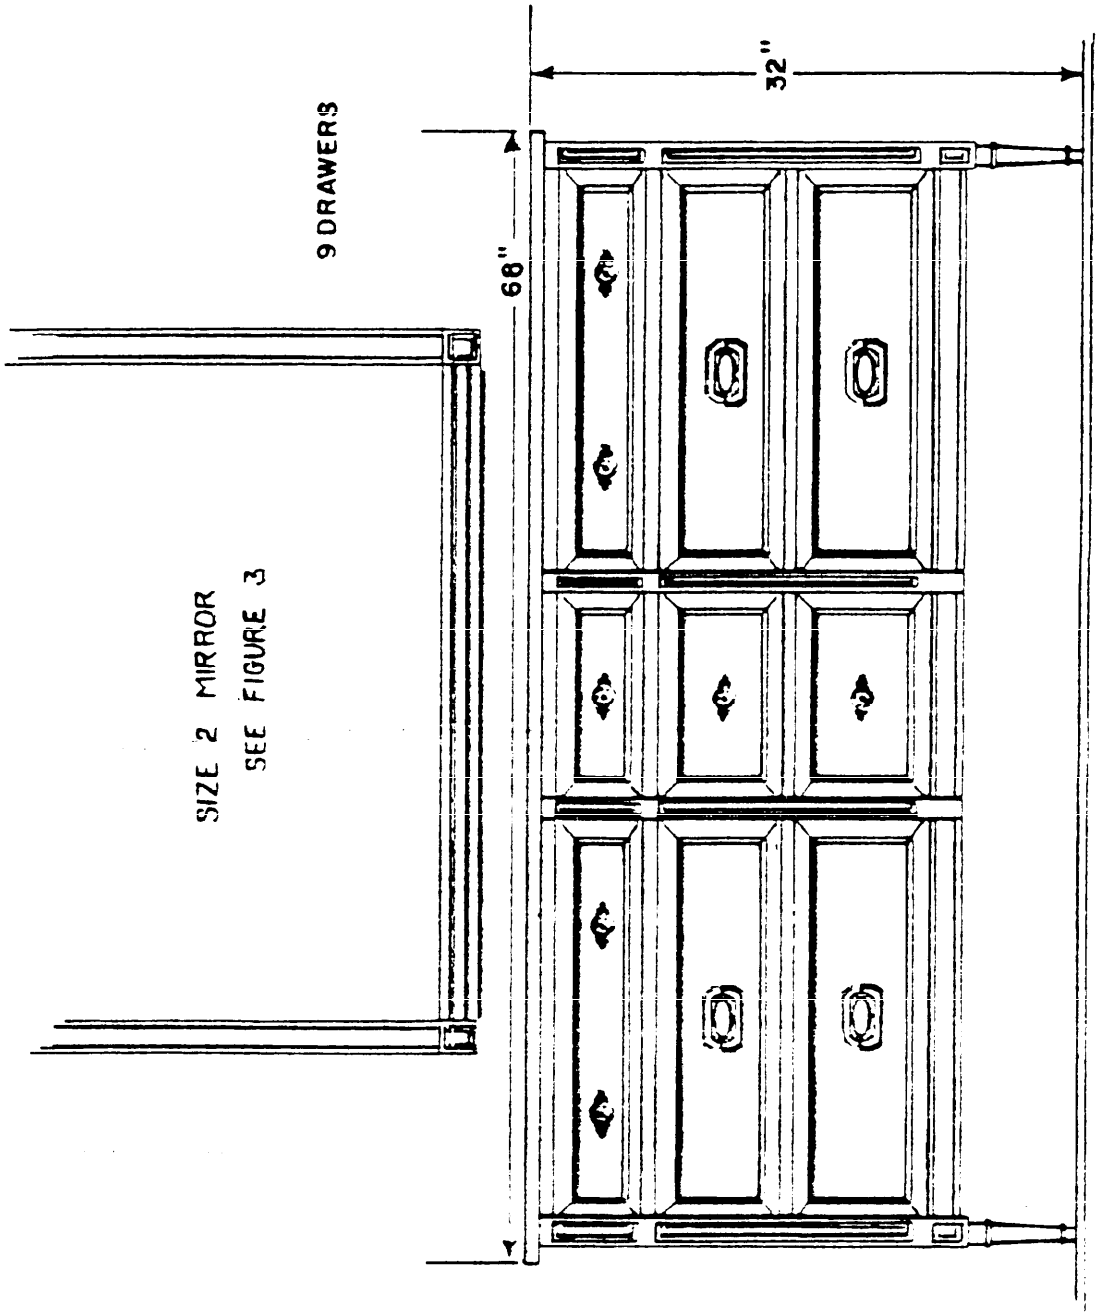

FOR DRESSER DETAILS - SEE FIGS. 17, 19, 20, 21.

Figure 4. Triple Dresser

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the currentversion before use.


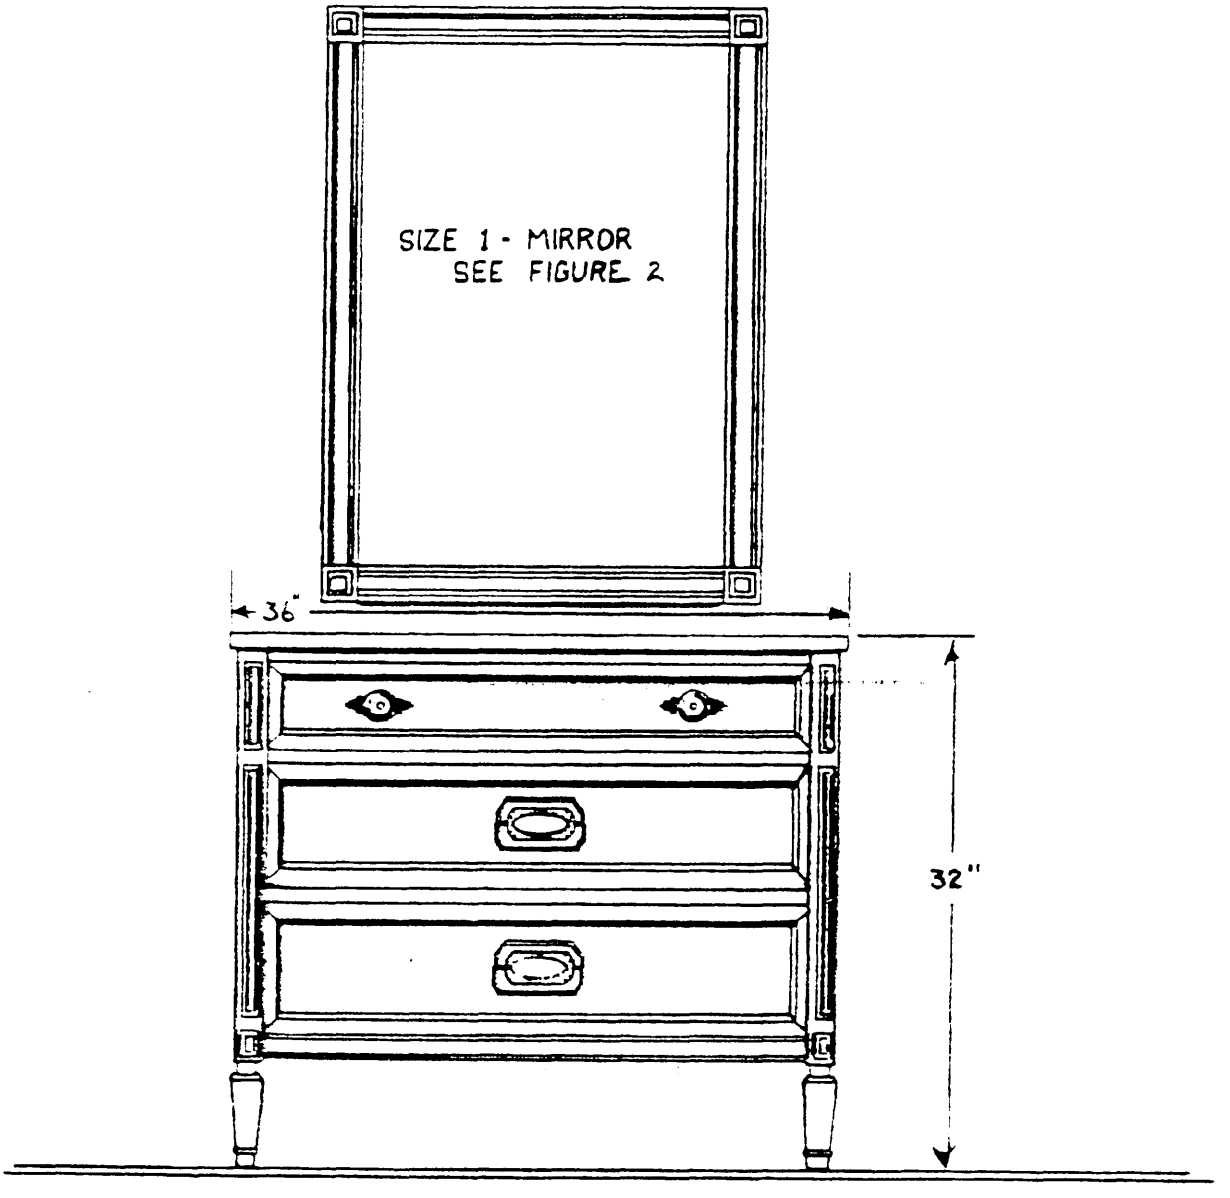


Figure 5. 3 Drawer Chest


Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

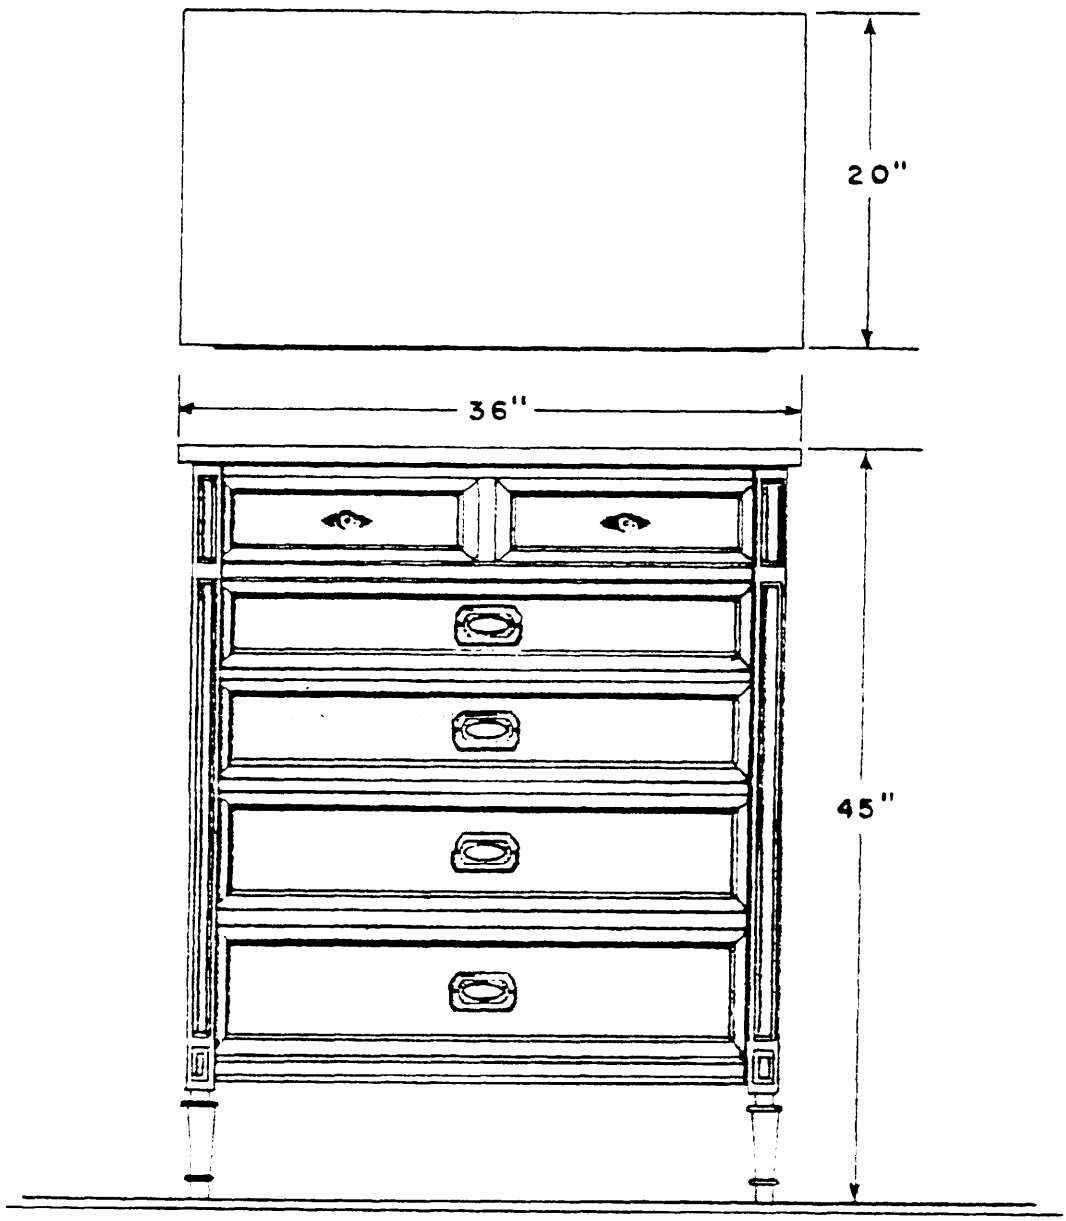

FOR CHEST DETAILS - SEE FIGS. 17, 20, 21, 22, 23.

Figure 6. 6 Drawer Chest

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

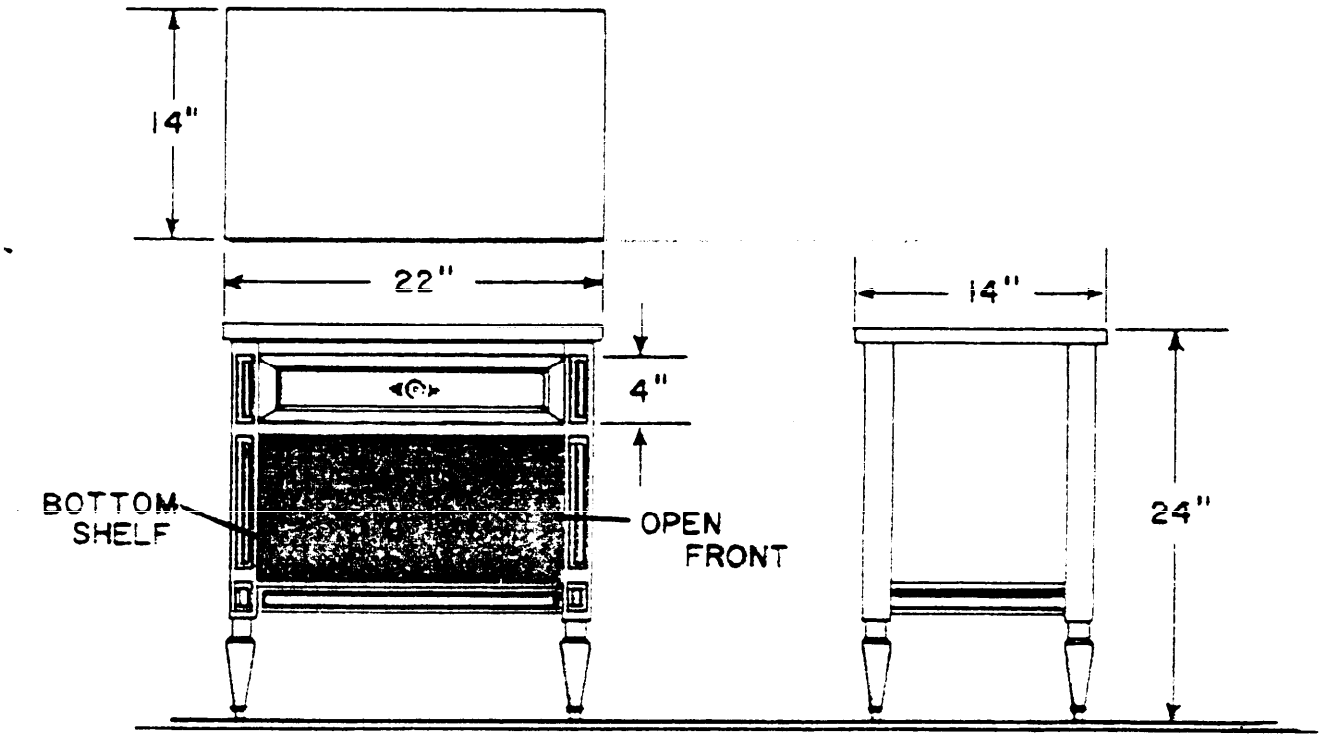

FOR NIGHT STAND DETAILS - SEE FIGS. 26, 27.

Figure 7. Night Stand

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.


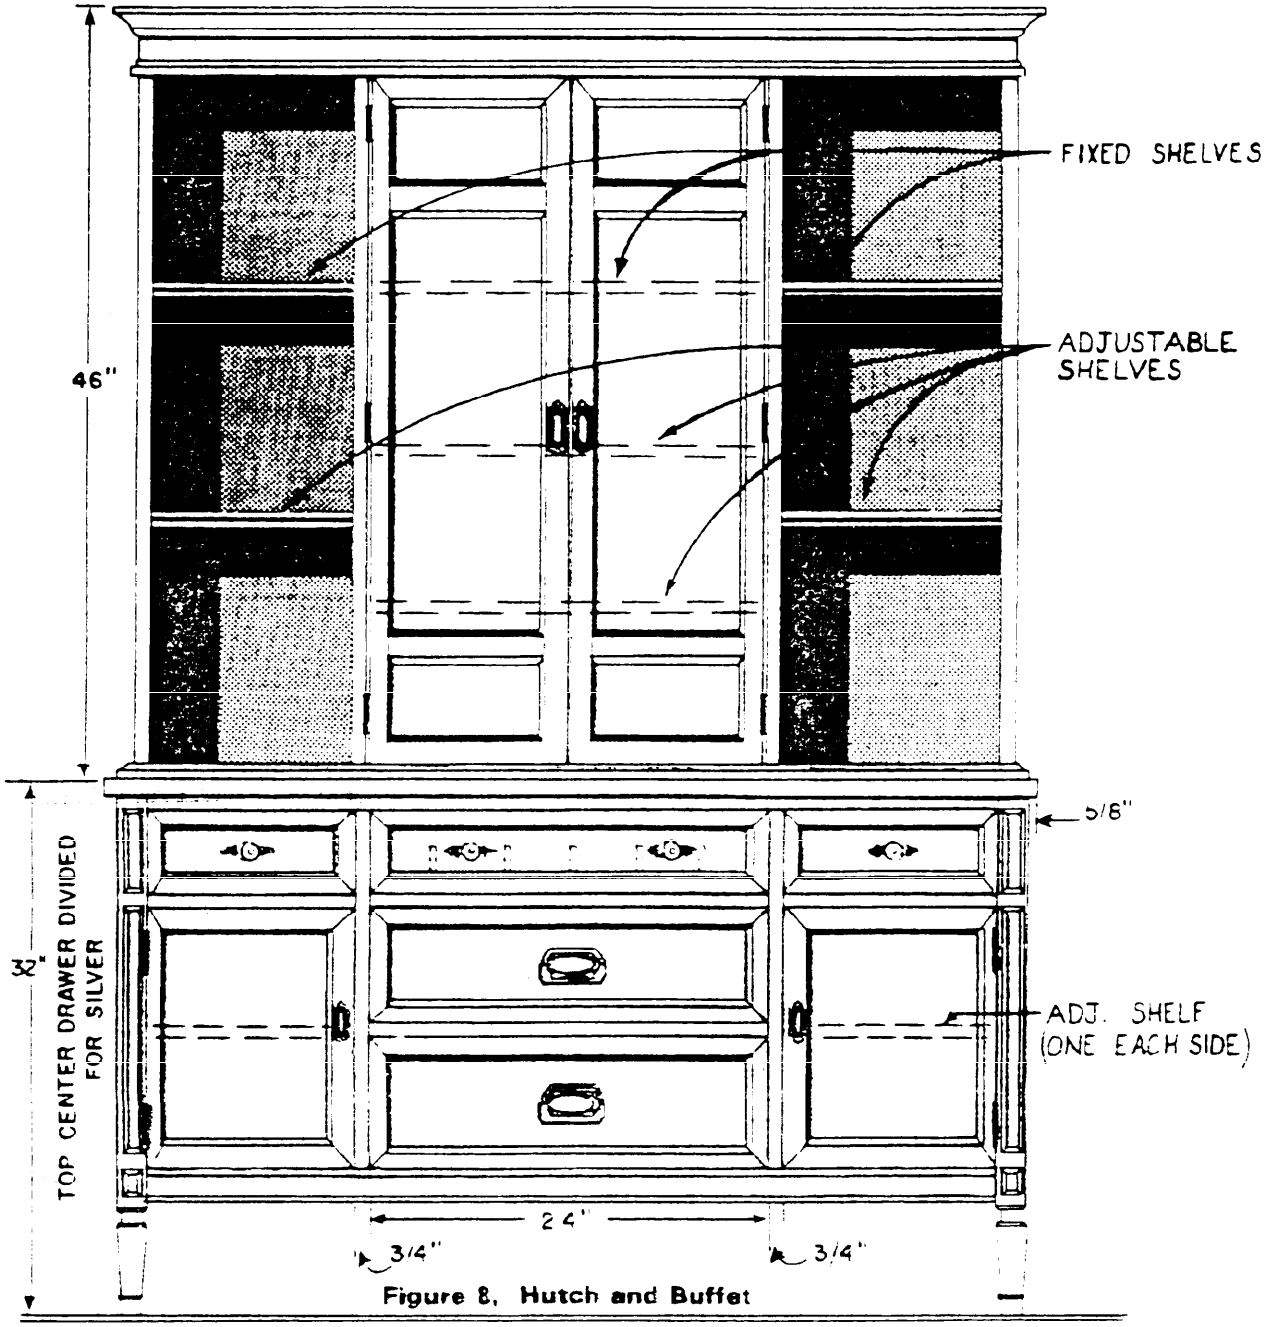


Figure 8. Hutch and Buffet

FOR HUTCH DETAILS - SEE FIG. 28.
FOR BUFFET DETAILS - SEE FIGS. 17, 21, 25, 26, 29.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

have a fillet weld with a throat depth (shortest distance from the root to the face) of not less than

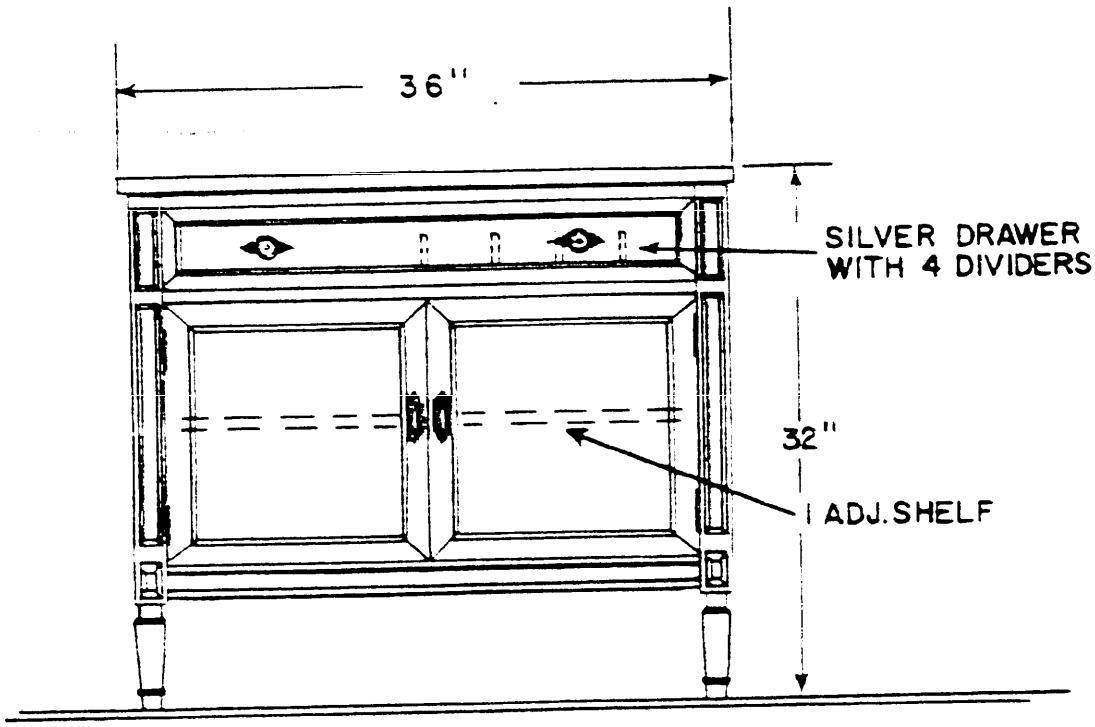

FOR SERVER DETAILS SEE FIGS. 17, 21, 25, 26, 29.

Figure 9. SERVER

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

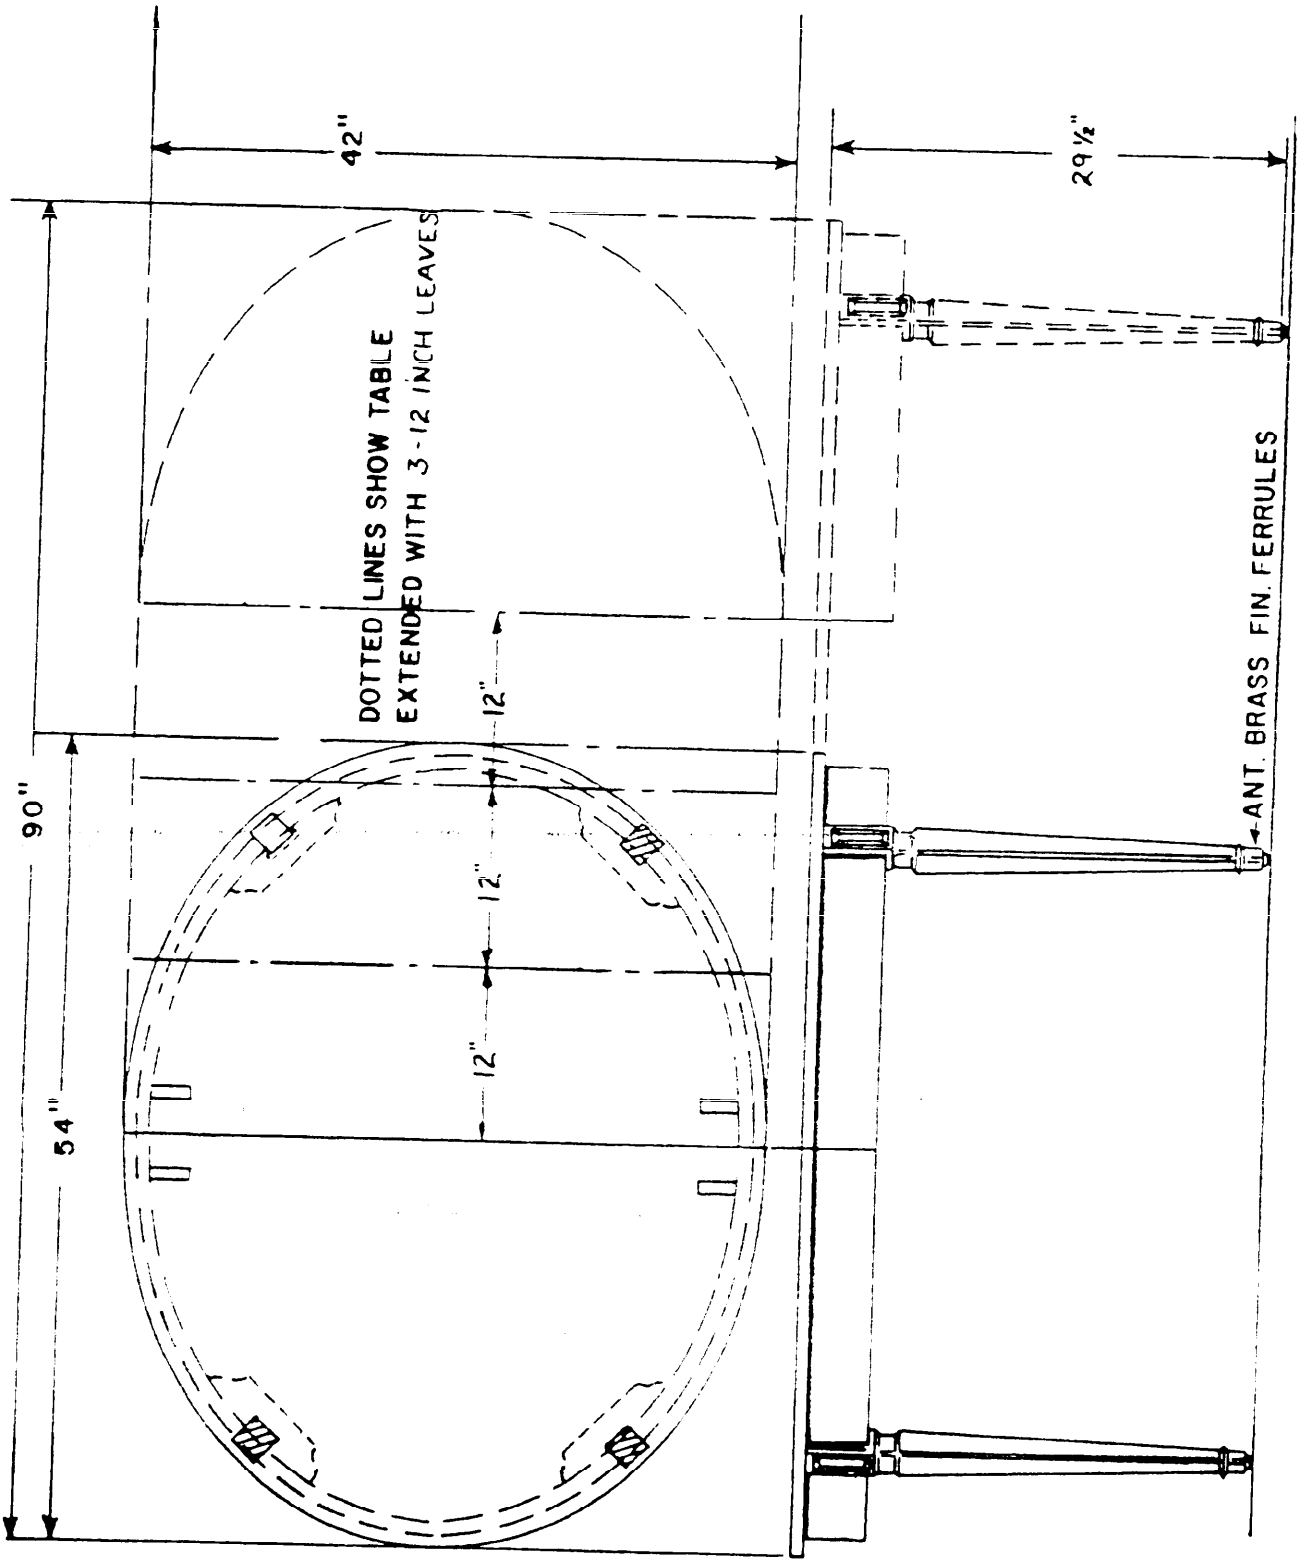


Figure 10. OVAL EXTENSION TABLE

FOR TABLE DETAILS SEE FIGS. 30, 31, 32.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

NOTES:
ARMS SHALL BE GLUED AND SCREWED OR GLUED AND DOWELED TO THE BACK POSTS.
SCREW HOLES SHALL BE PLUGGED WITH FLUSH OR BUTTON TYPE PLUGS ON EXPOSED PARTS.


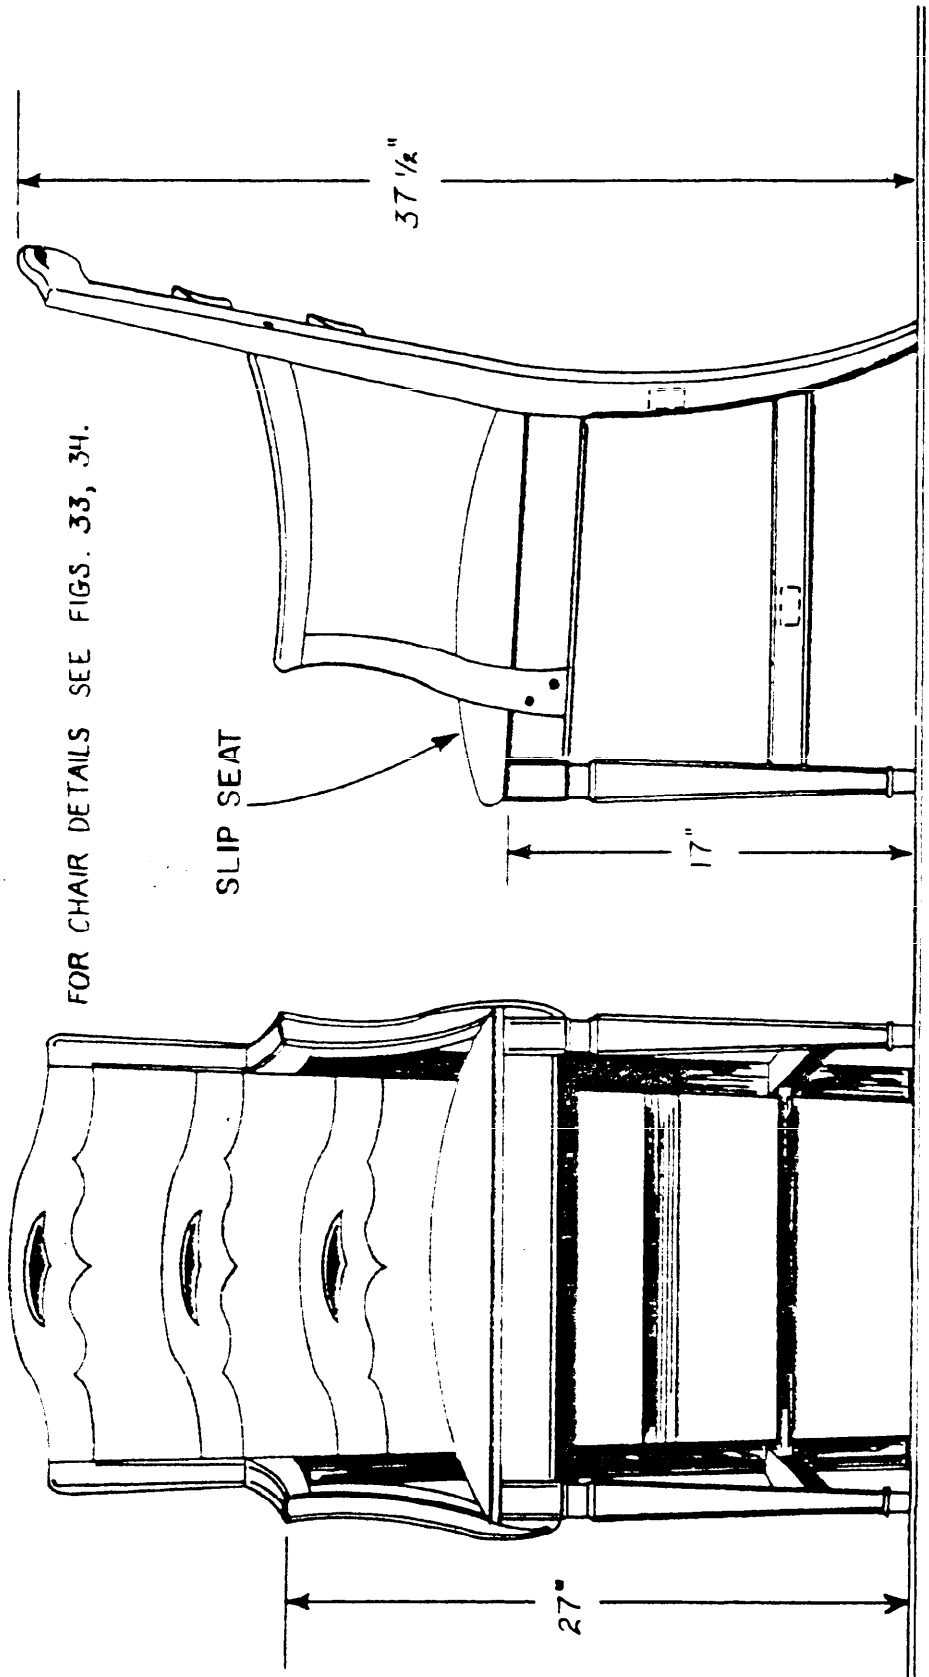


Figure 11. SIDE/HOST CHAIR

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

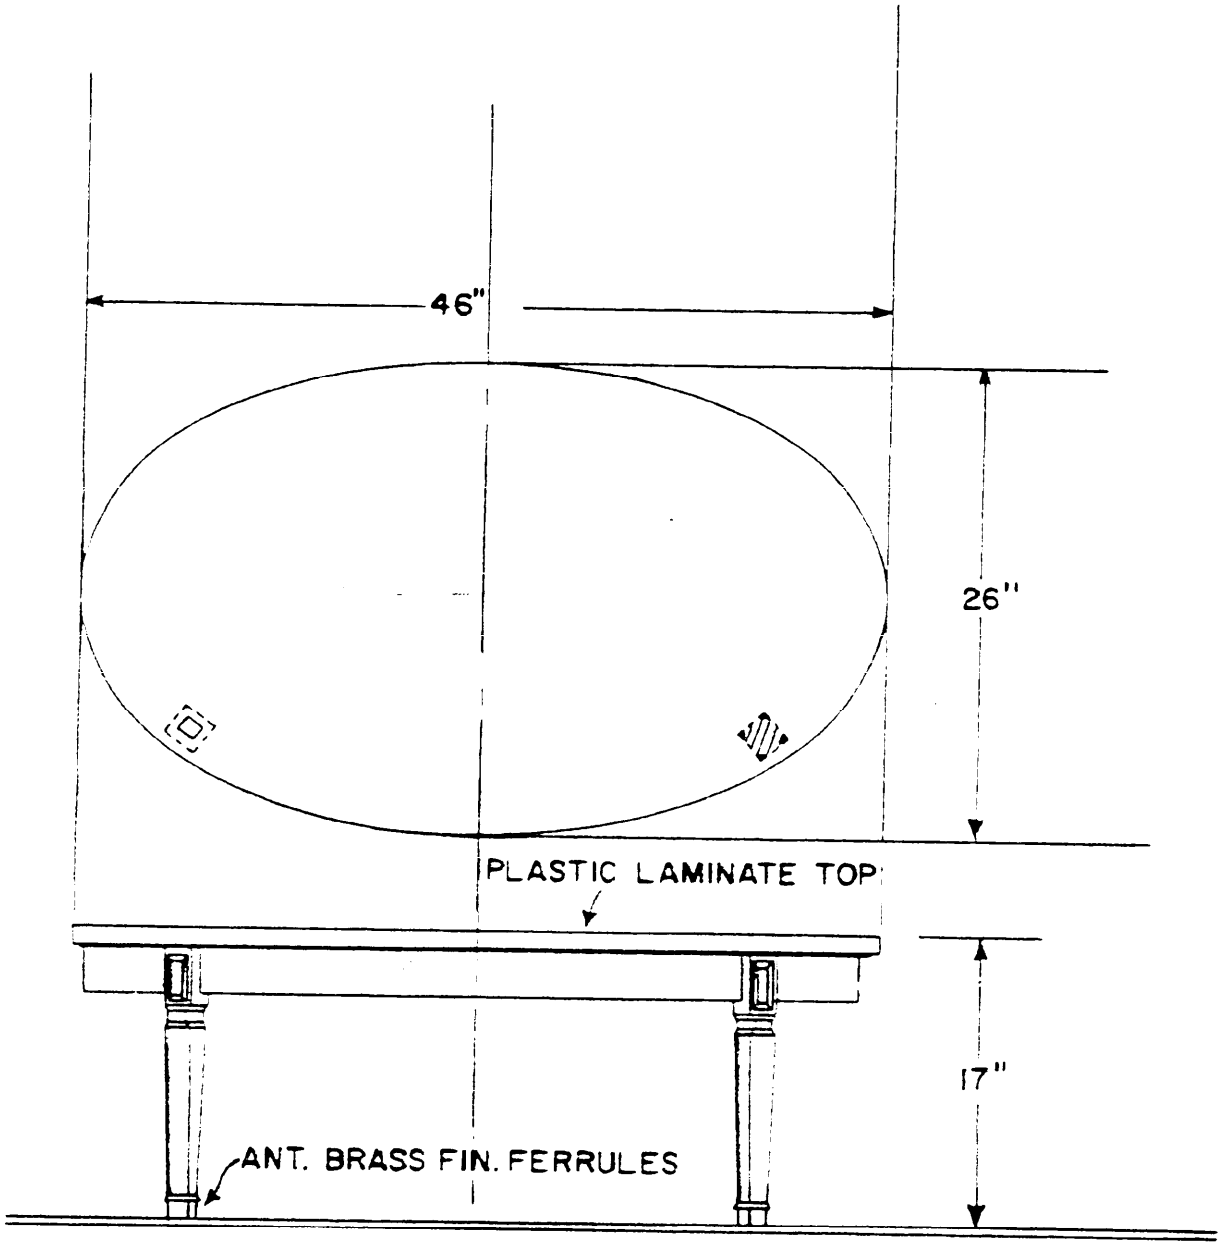

FOR TABLE DETAILS SEE FIGS. 32, 35.

Figure 12. Oval Coffee Table

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

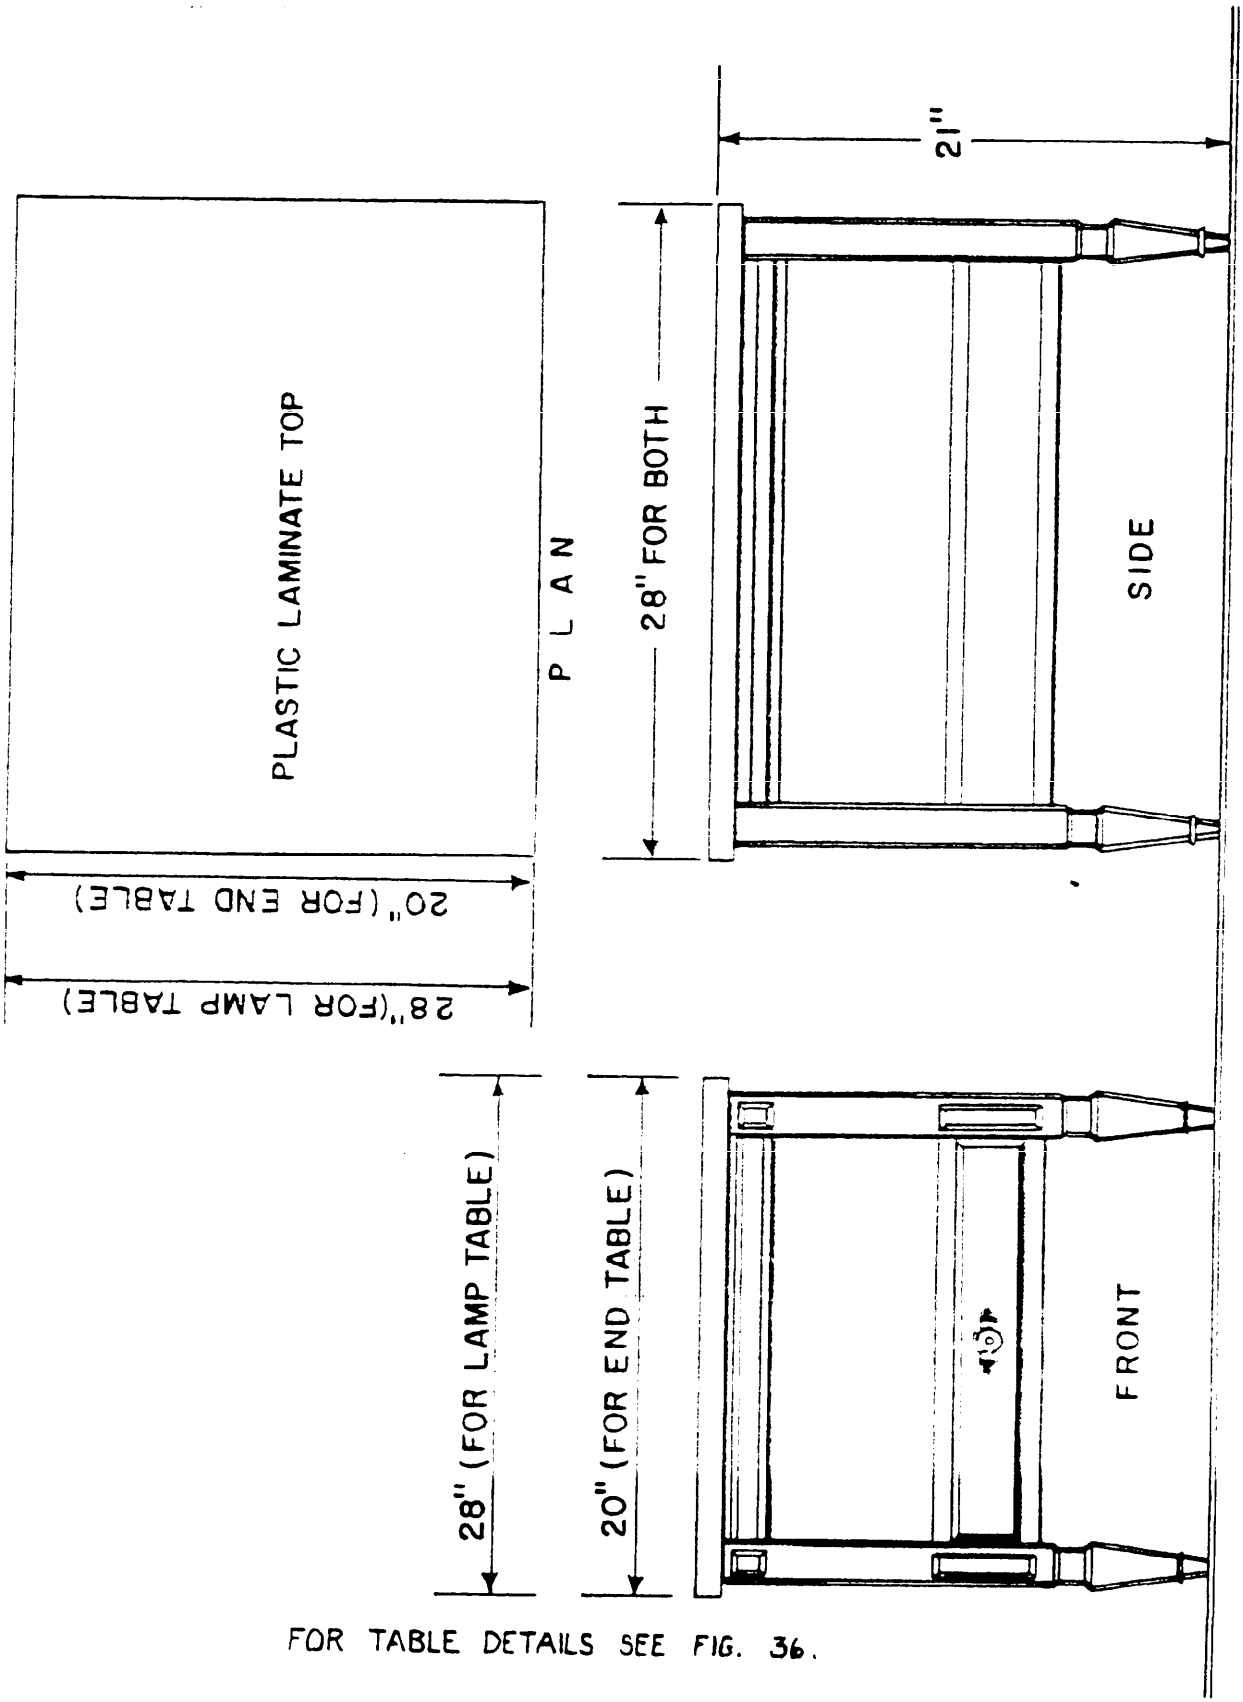


Figure 13. End/Lamp Table

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.


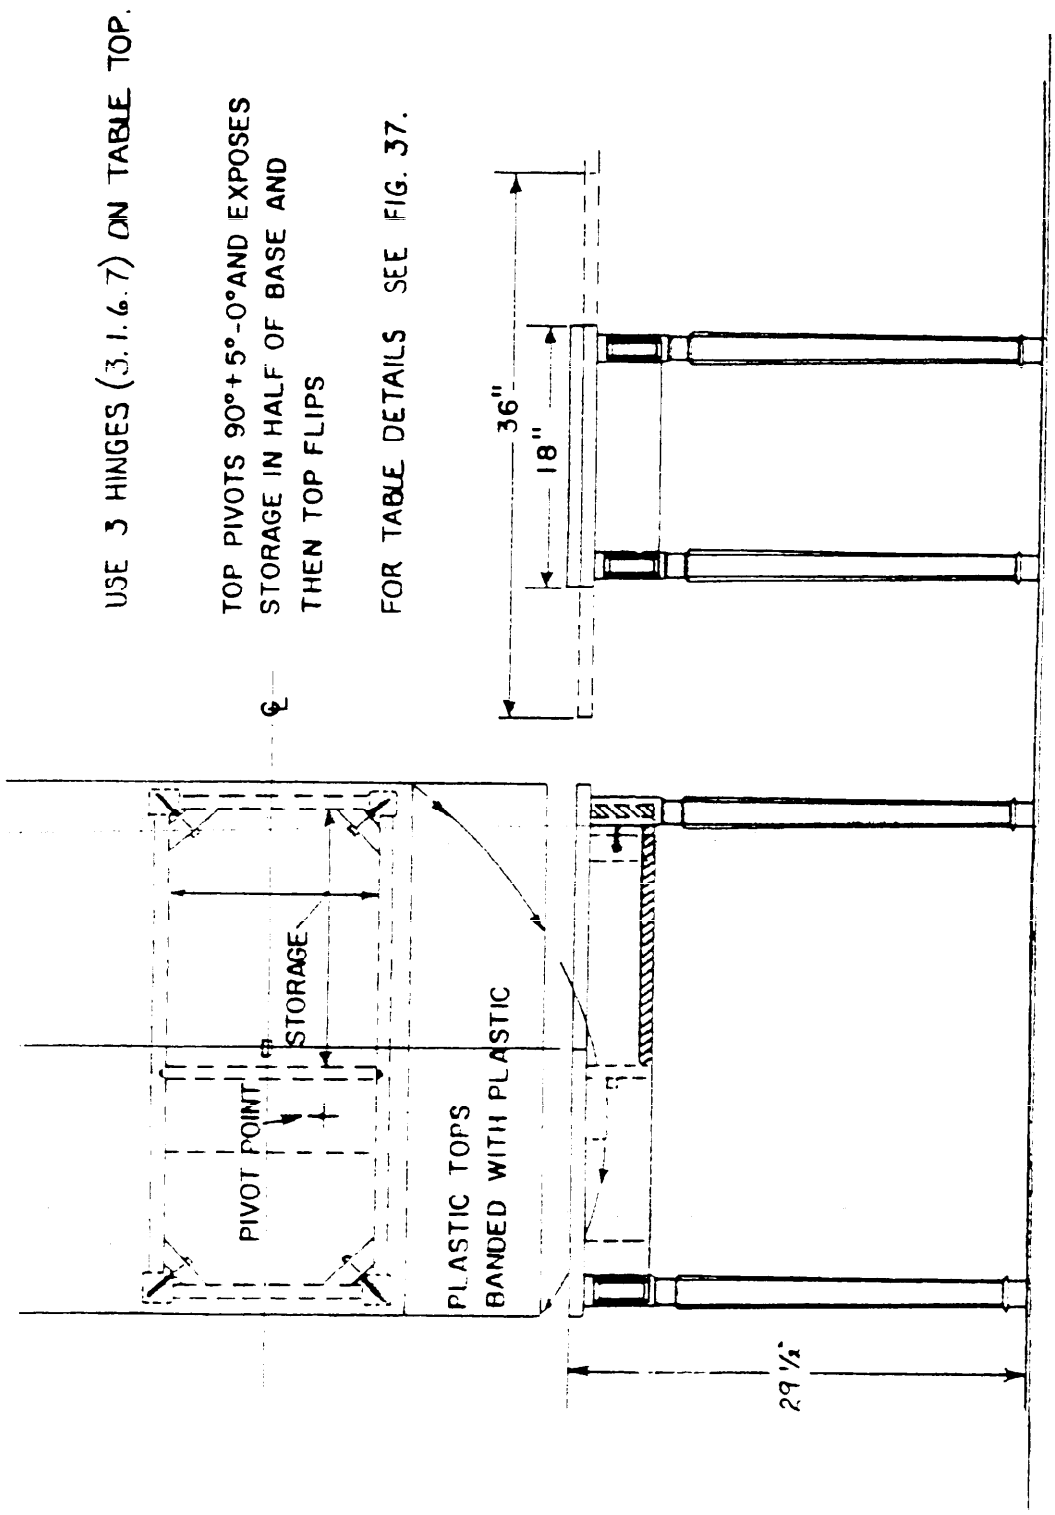



Figure 14. Pivot Top Table

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

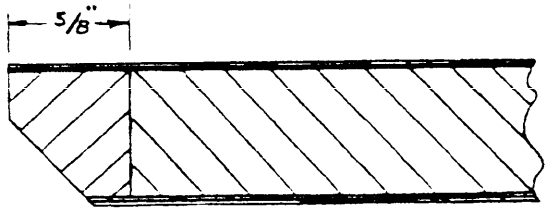

DETAIL A SHELF FRONT

NOT TO SCALE

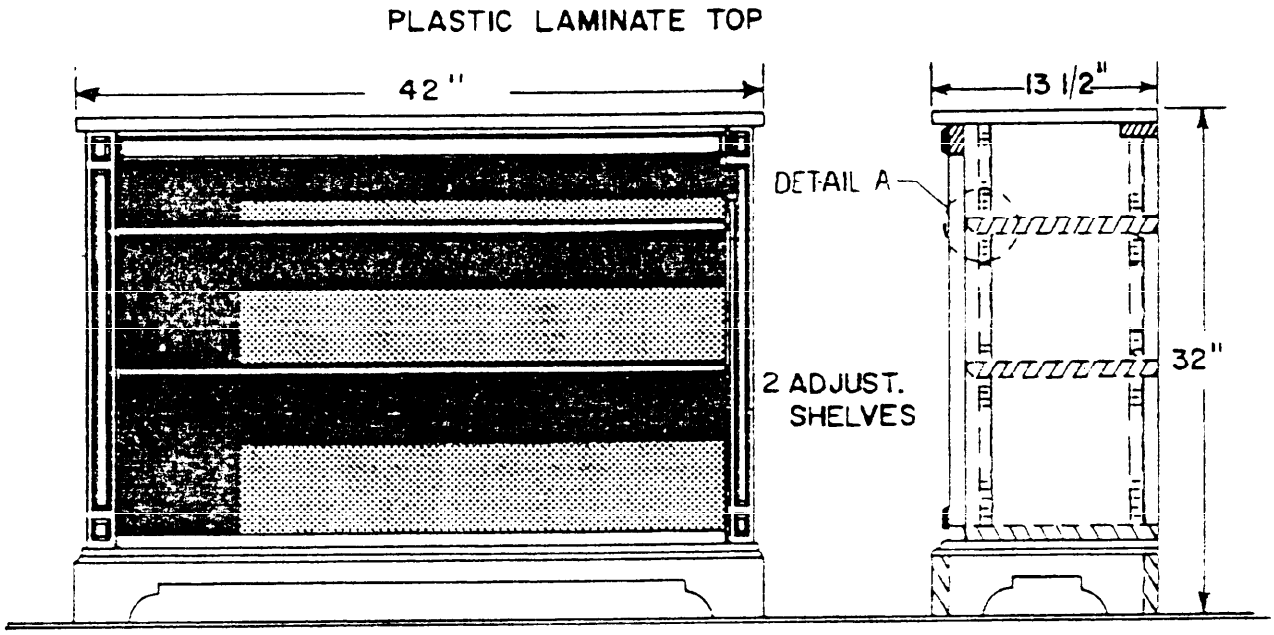

FOR BOOKCASE DETAILS SEE FIGS. 38, 39.

Figure 15. Bookcase

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

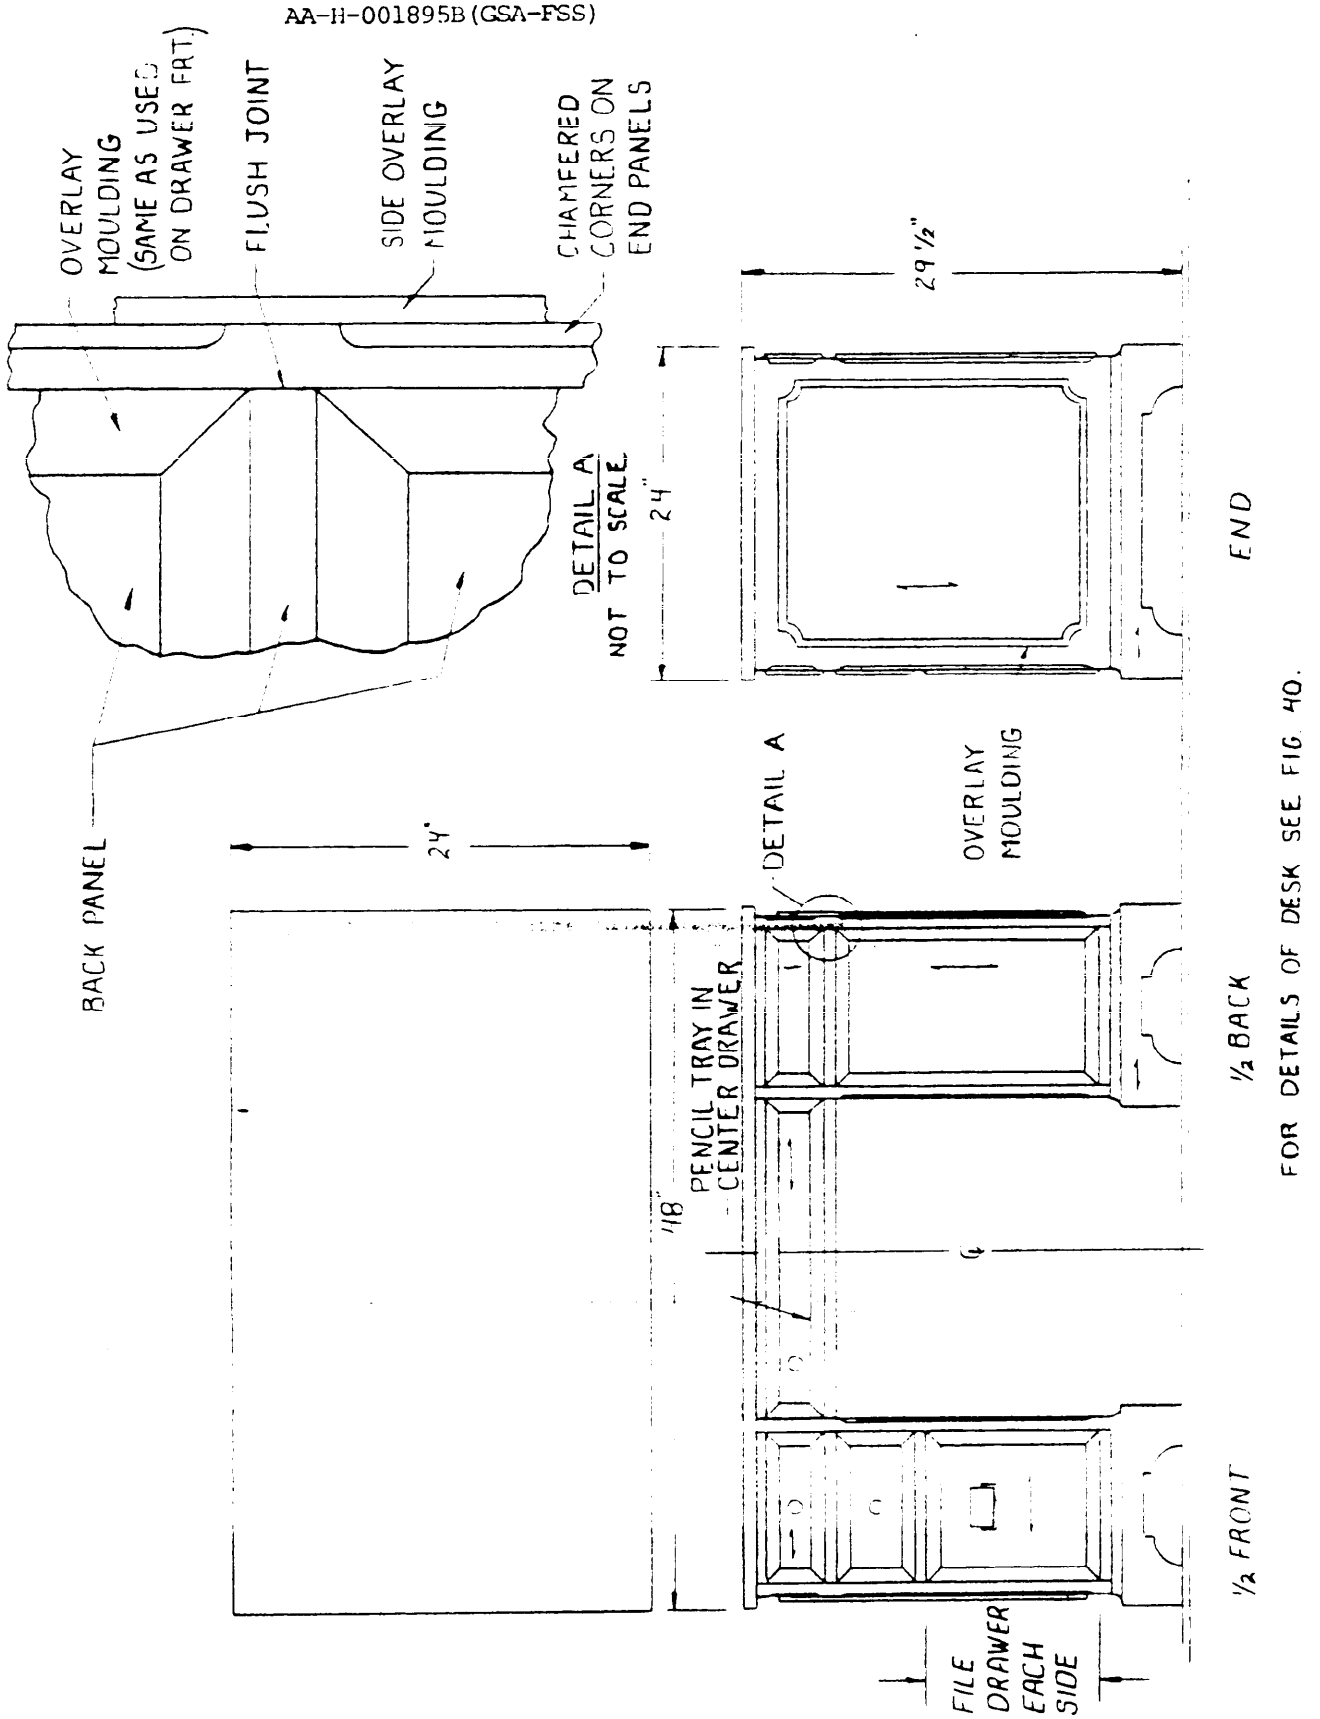


FIGURE 16. DESK

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

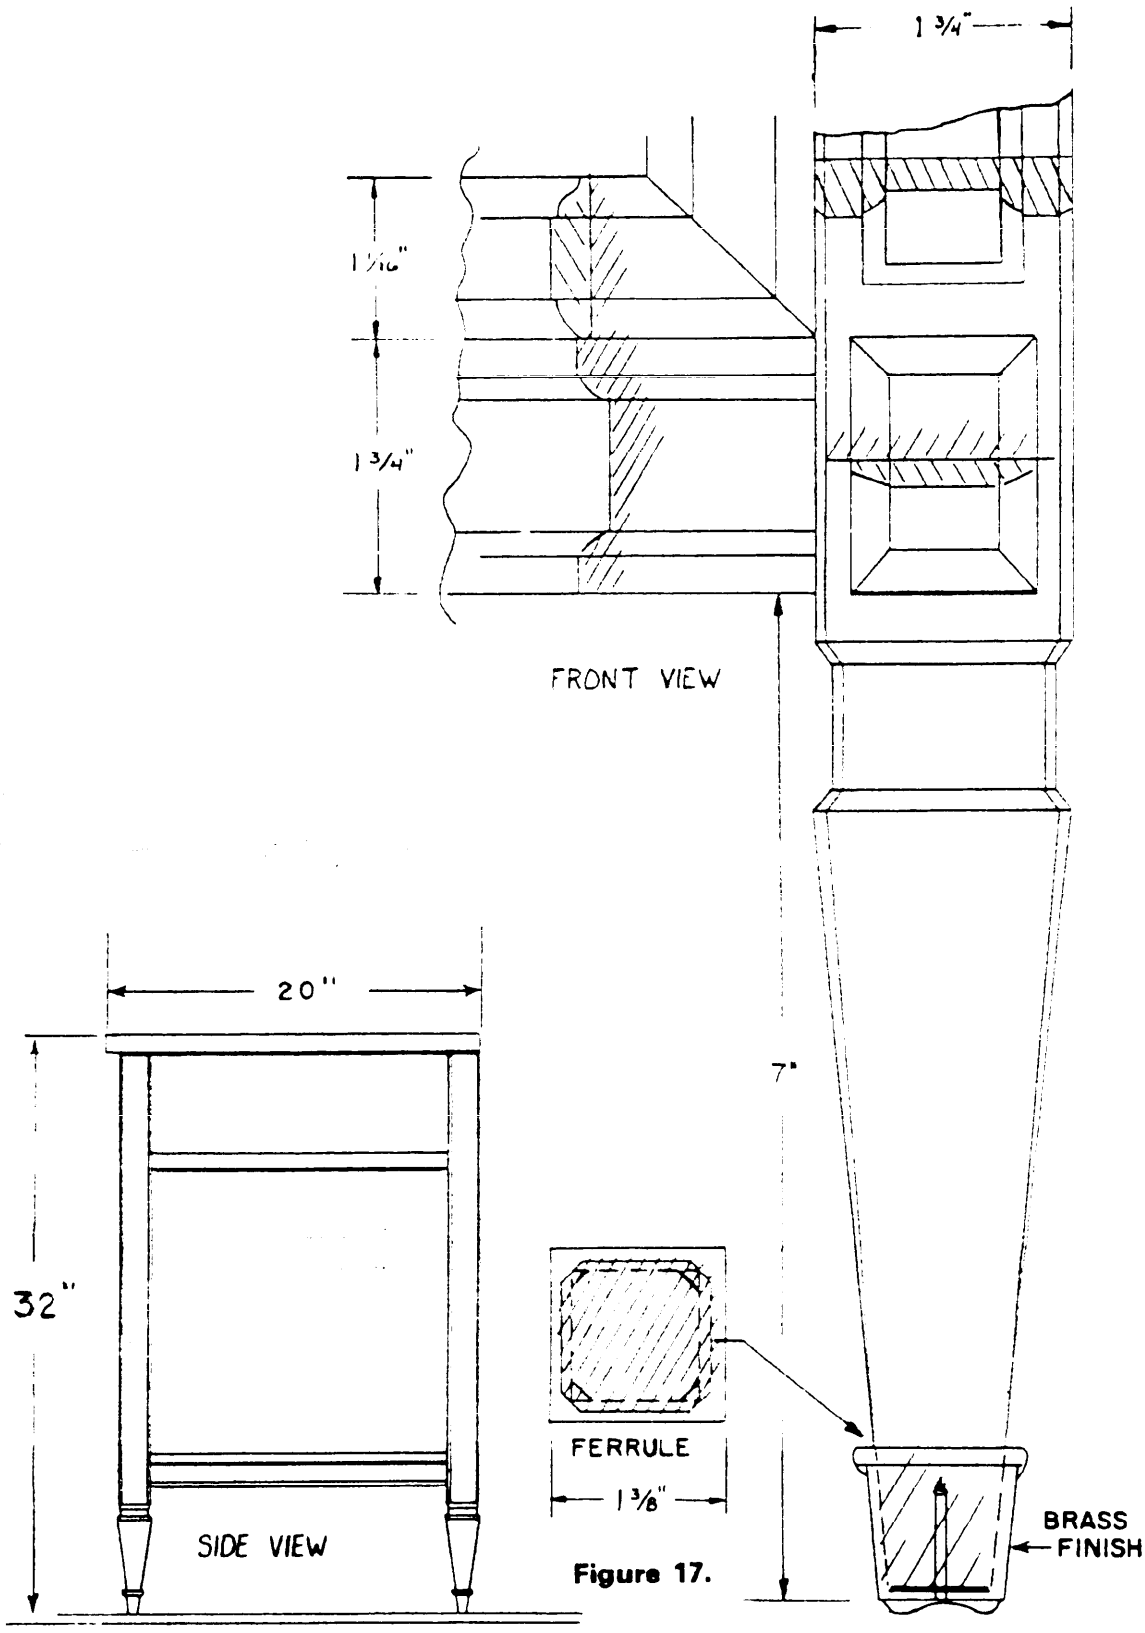


Figure 17.

NOT TO SCALE
TYPICAL OF DRESSERS, CHESTS, BUFFET, AND SERVER

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.


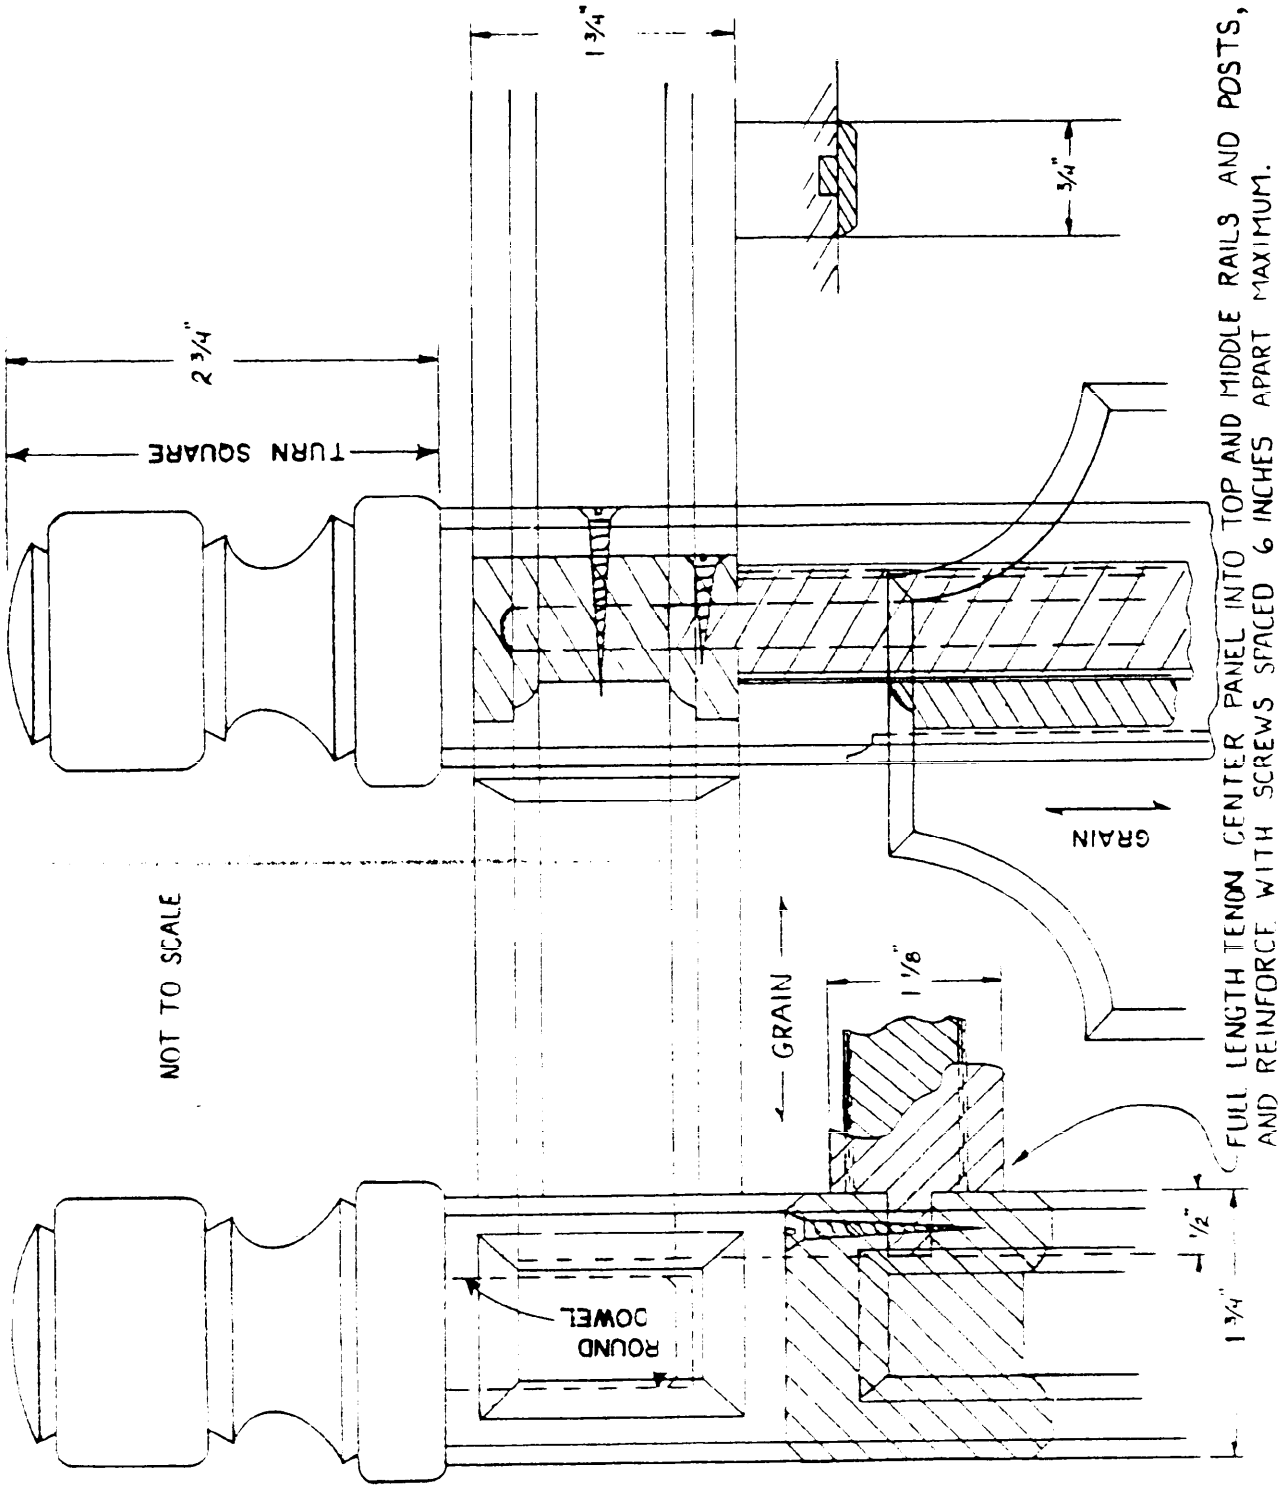


Figure 18. HEADBOARD DETAILS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

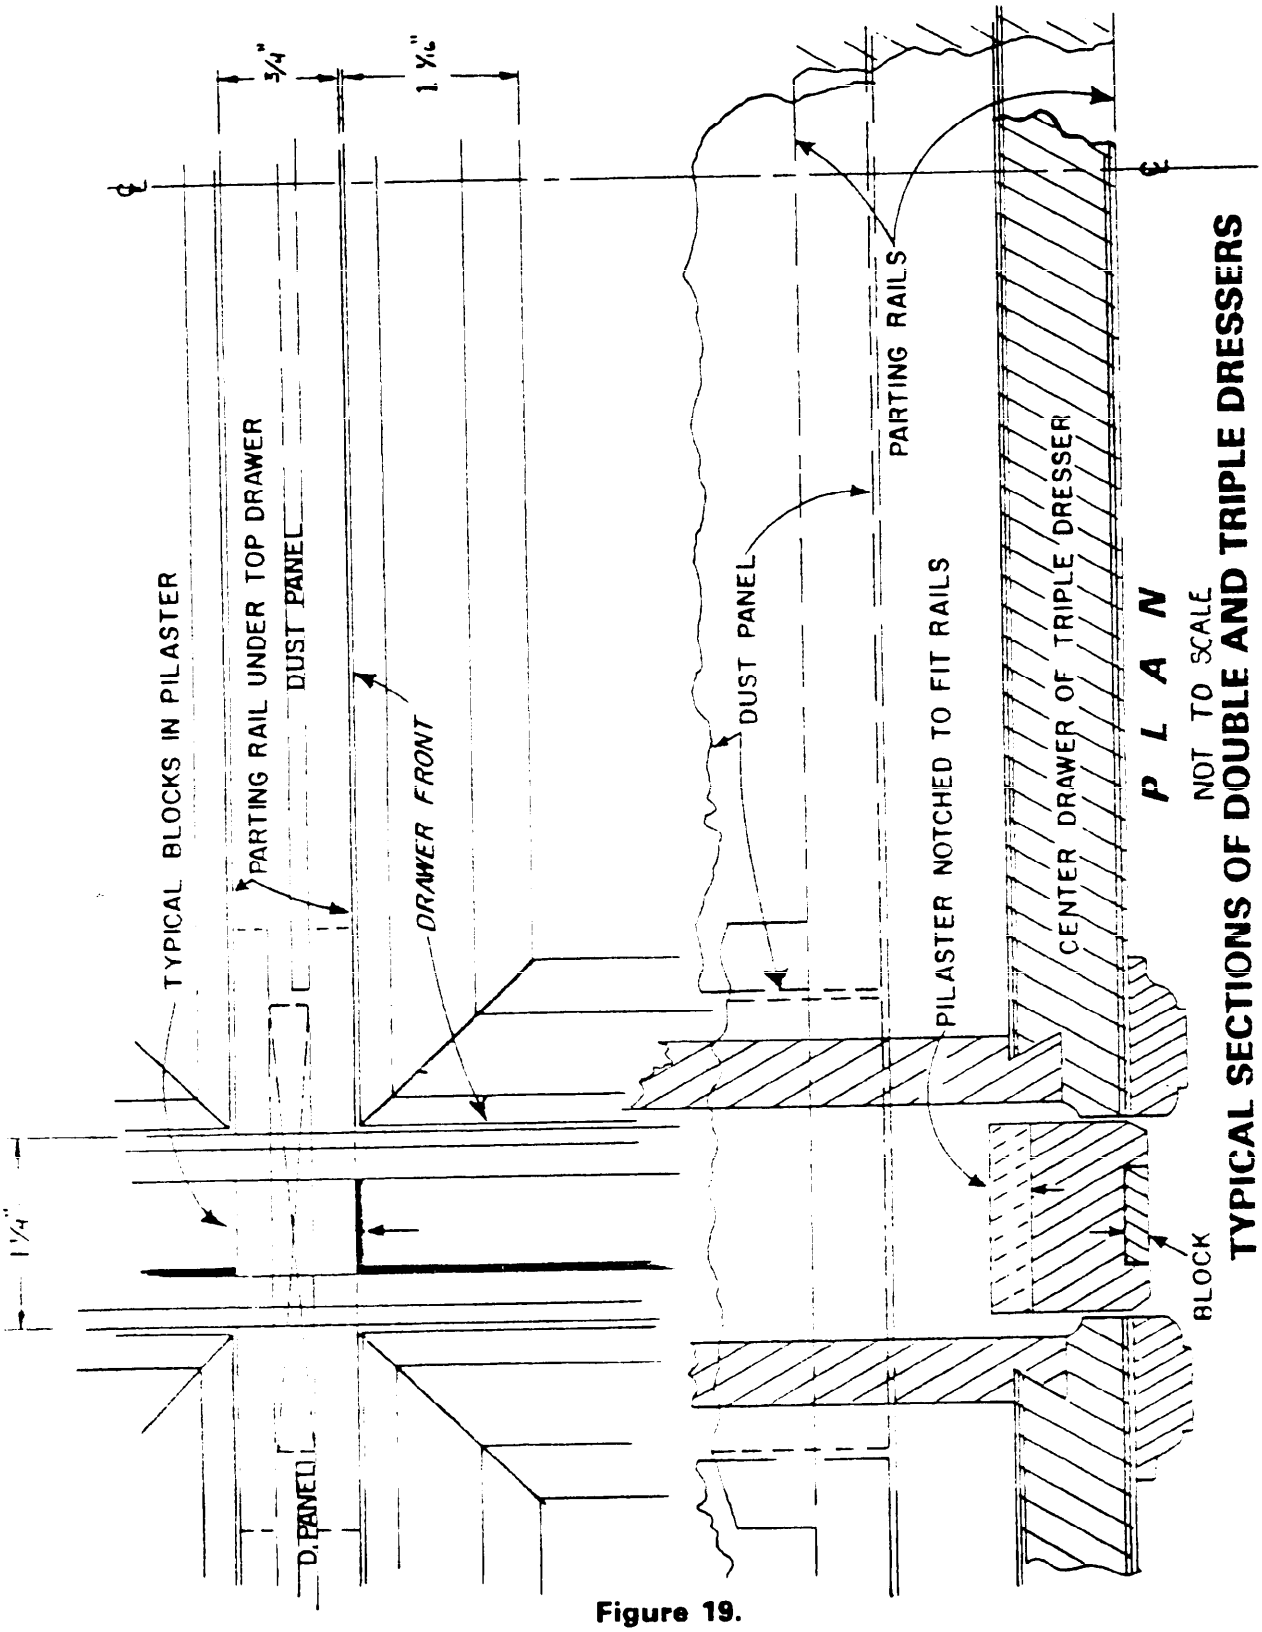

TYPICAL SECTIONS OF DOUBLE AND TRIPLE DRESSERS

Figure 19.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.


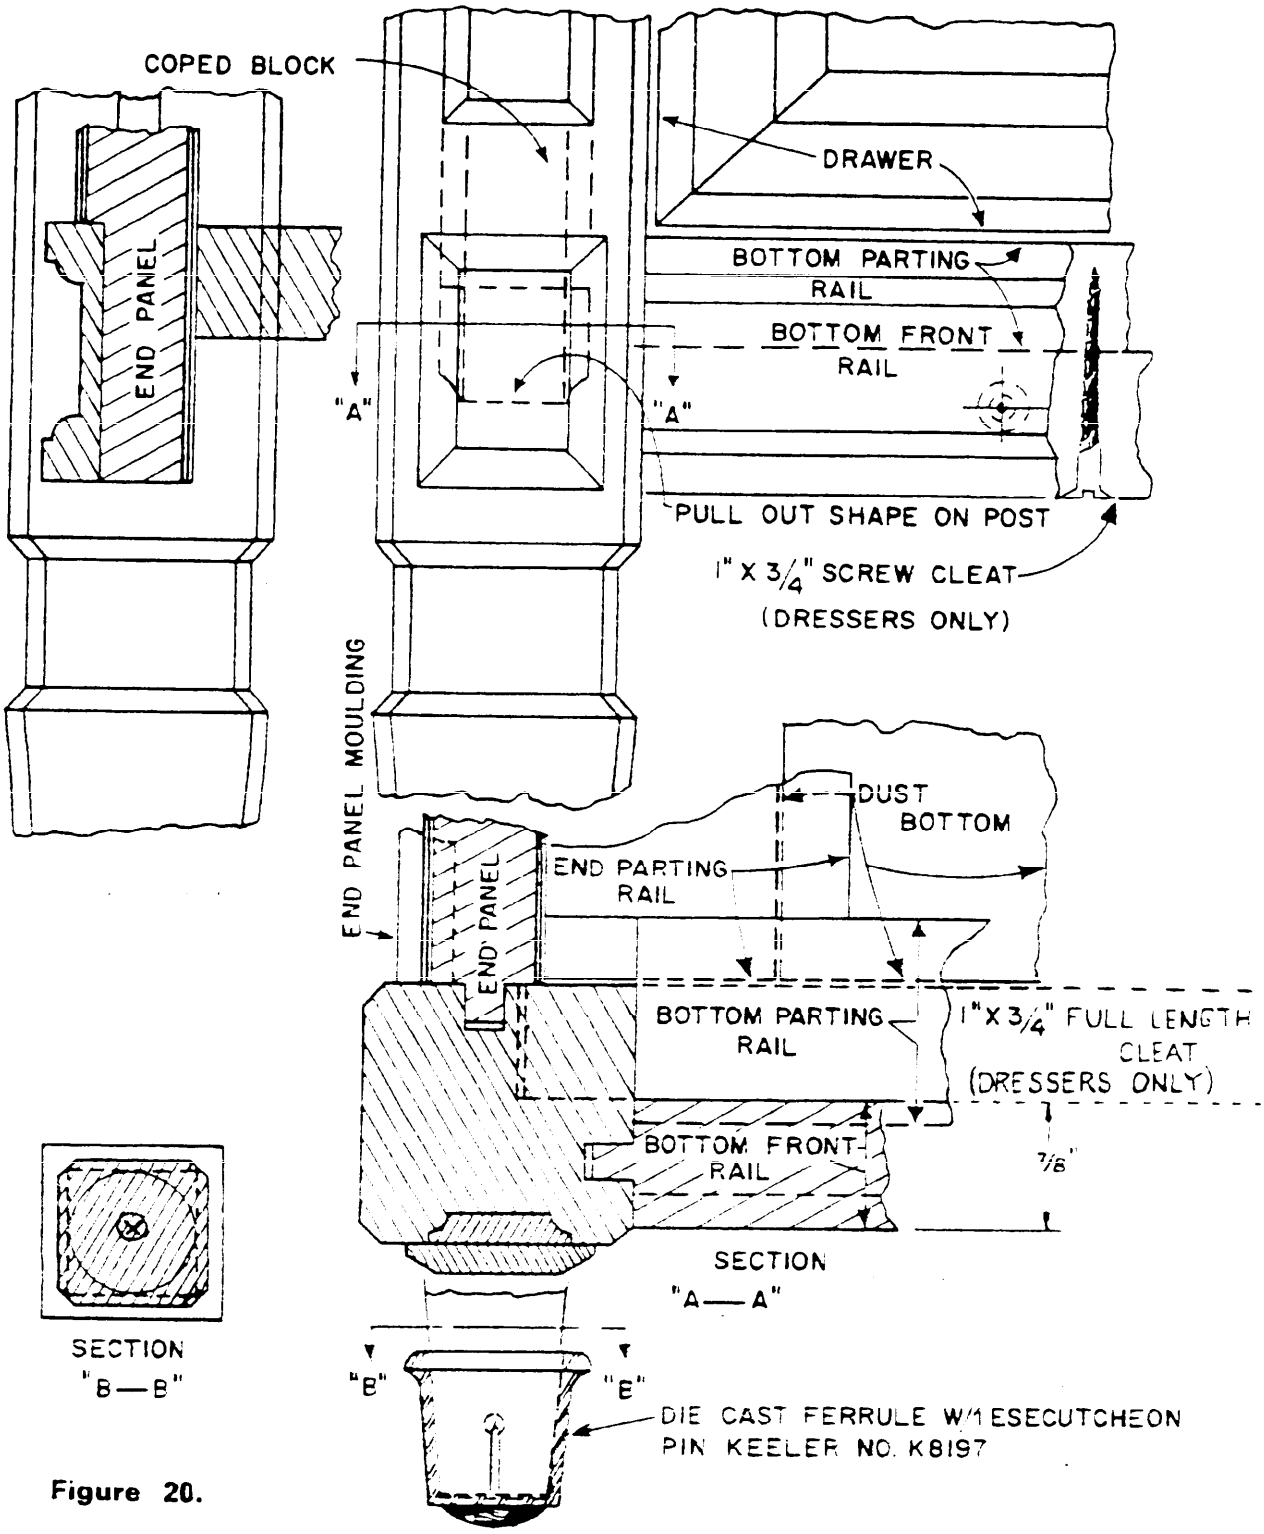


Figure 20.

TYPICAL SECTIONS OF DRESSER AND CHEST

NOT TO SCALE


Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the currentversion before use.

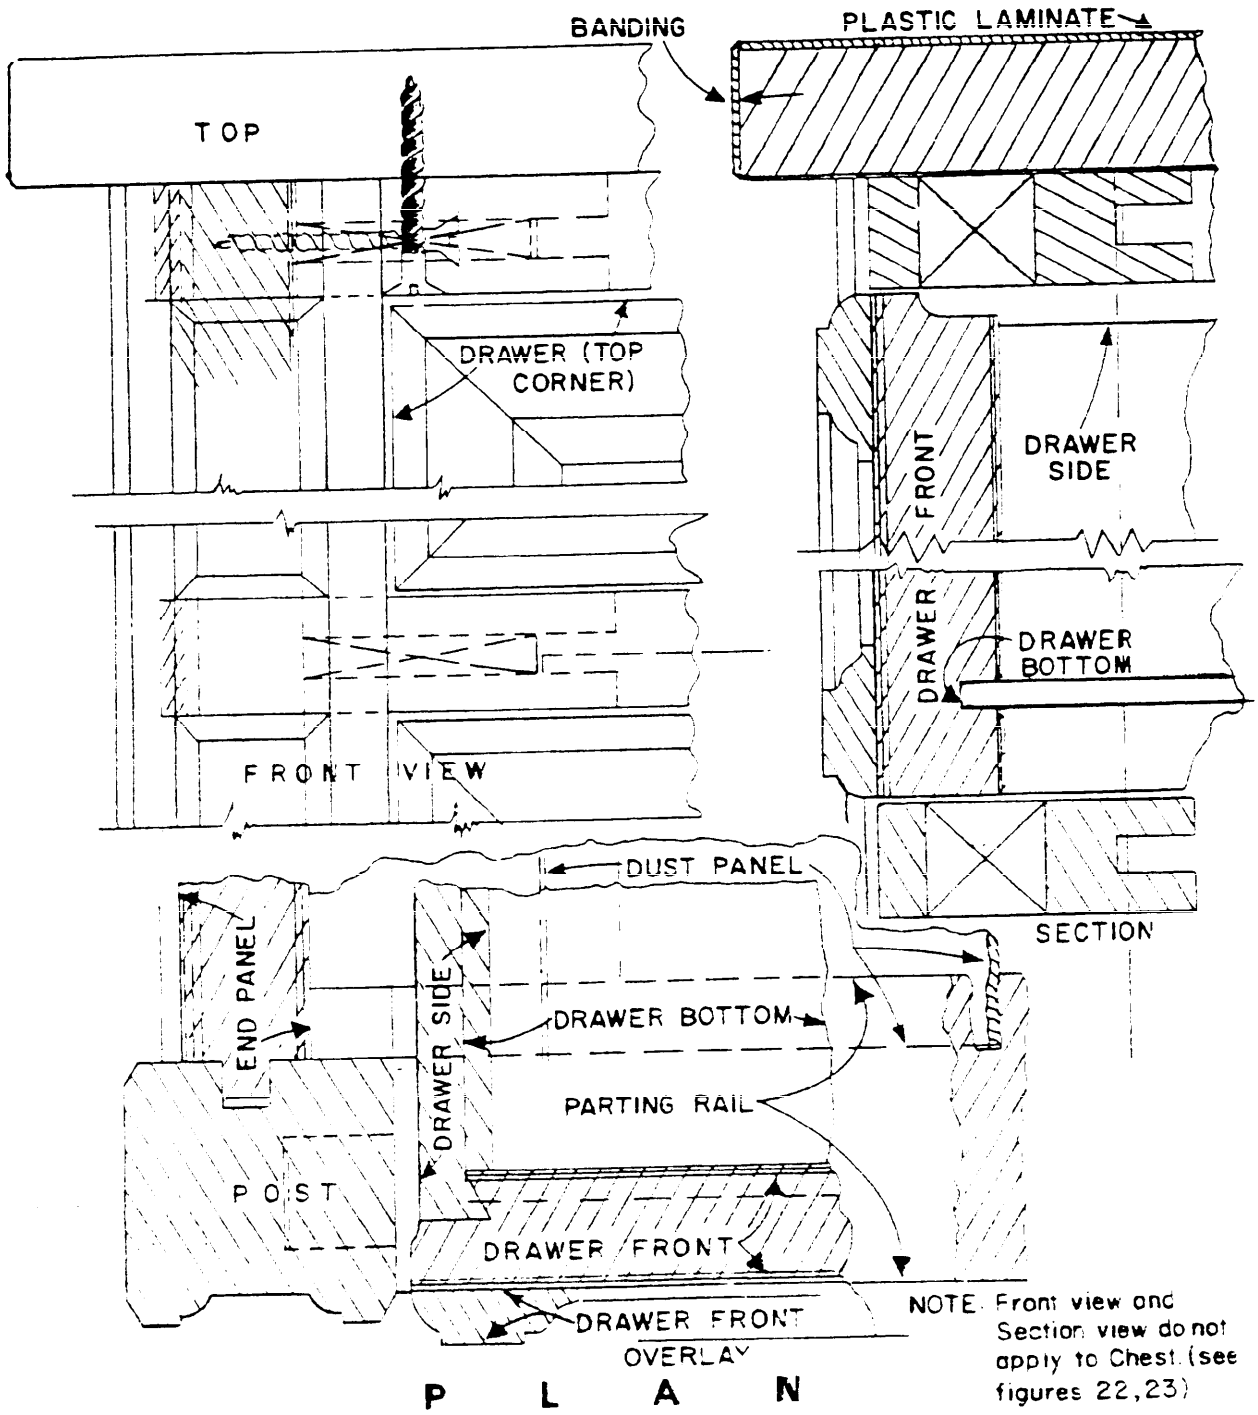

TYPICAL SECTIONS OF DRESSERS, CHEST, BUFFET AND SERVER

Figure 21. NOT TO SCALE


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

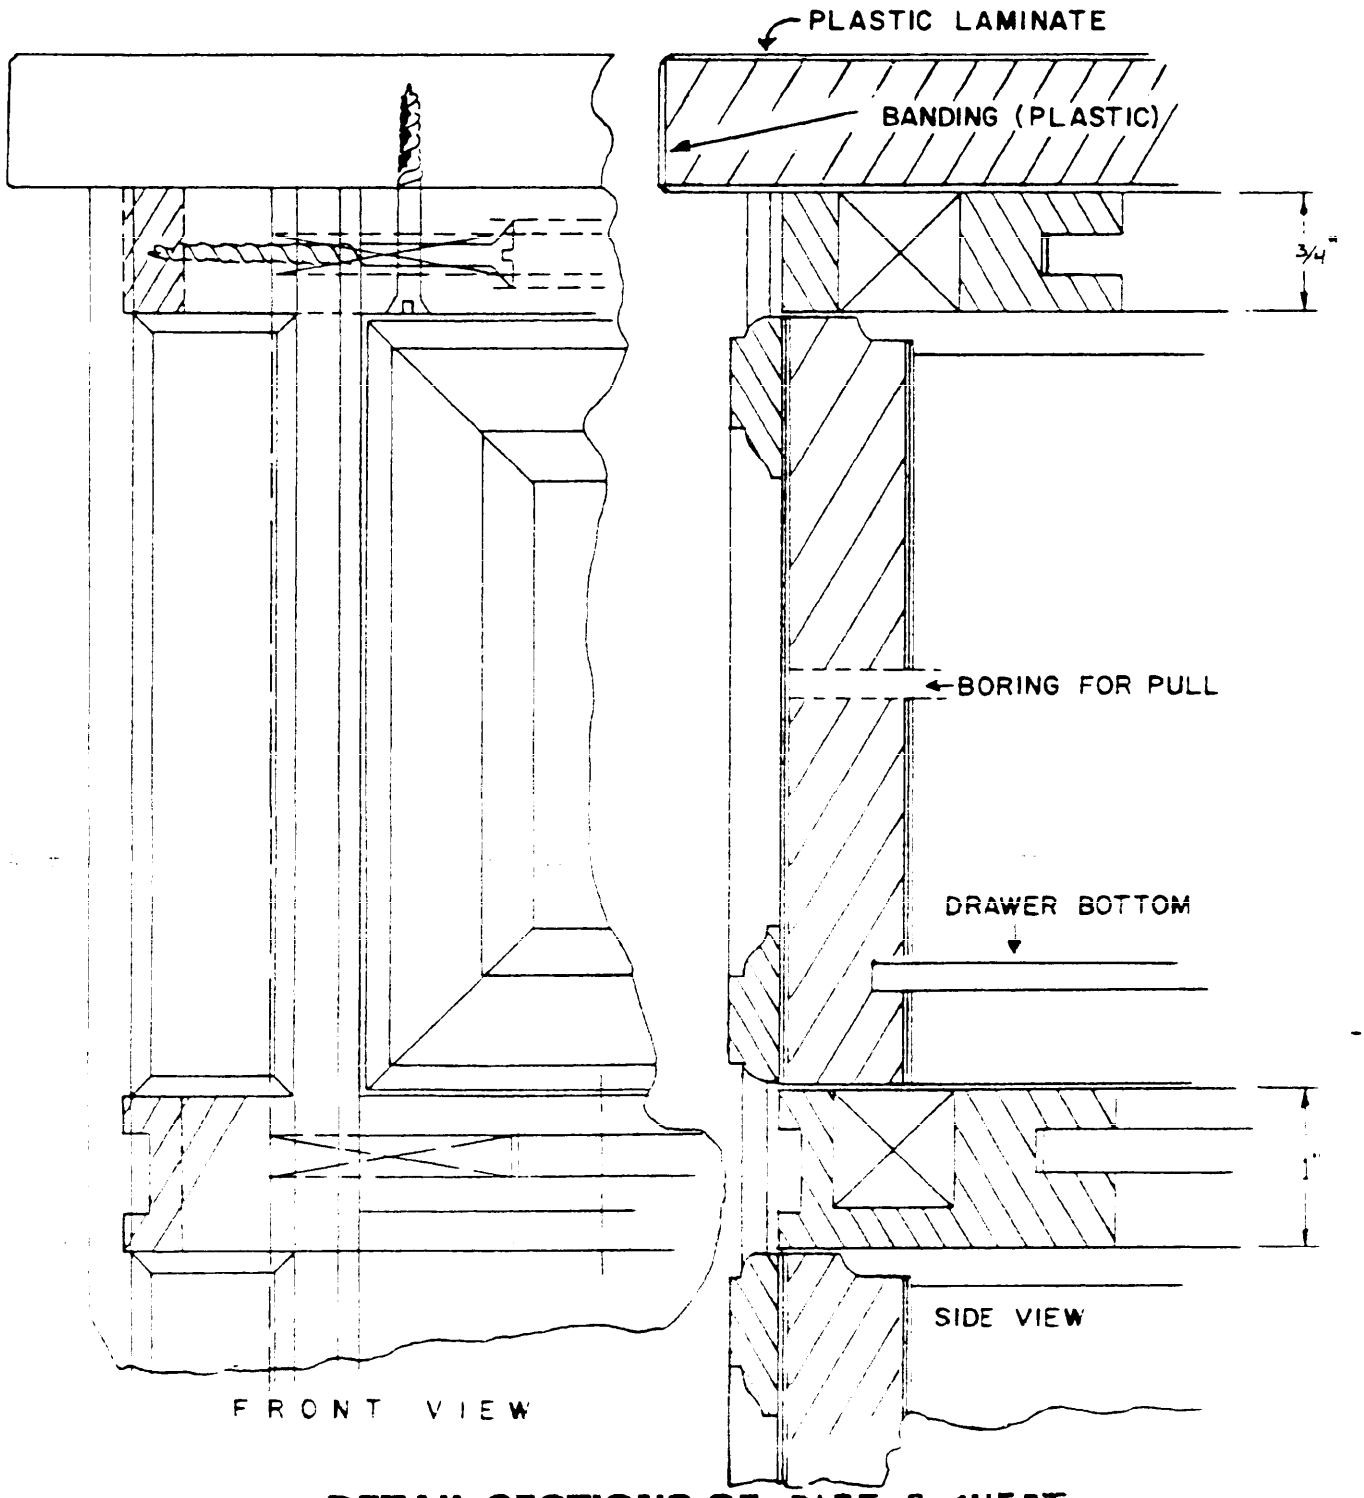

DETAIL SECTIONS OF SIZE 2 CHEST

Figure 22. NOT TO SCALE

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

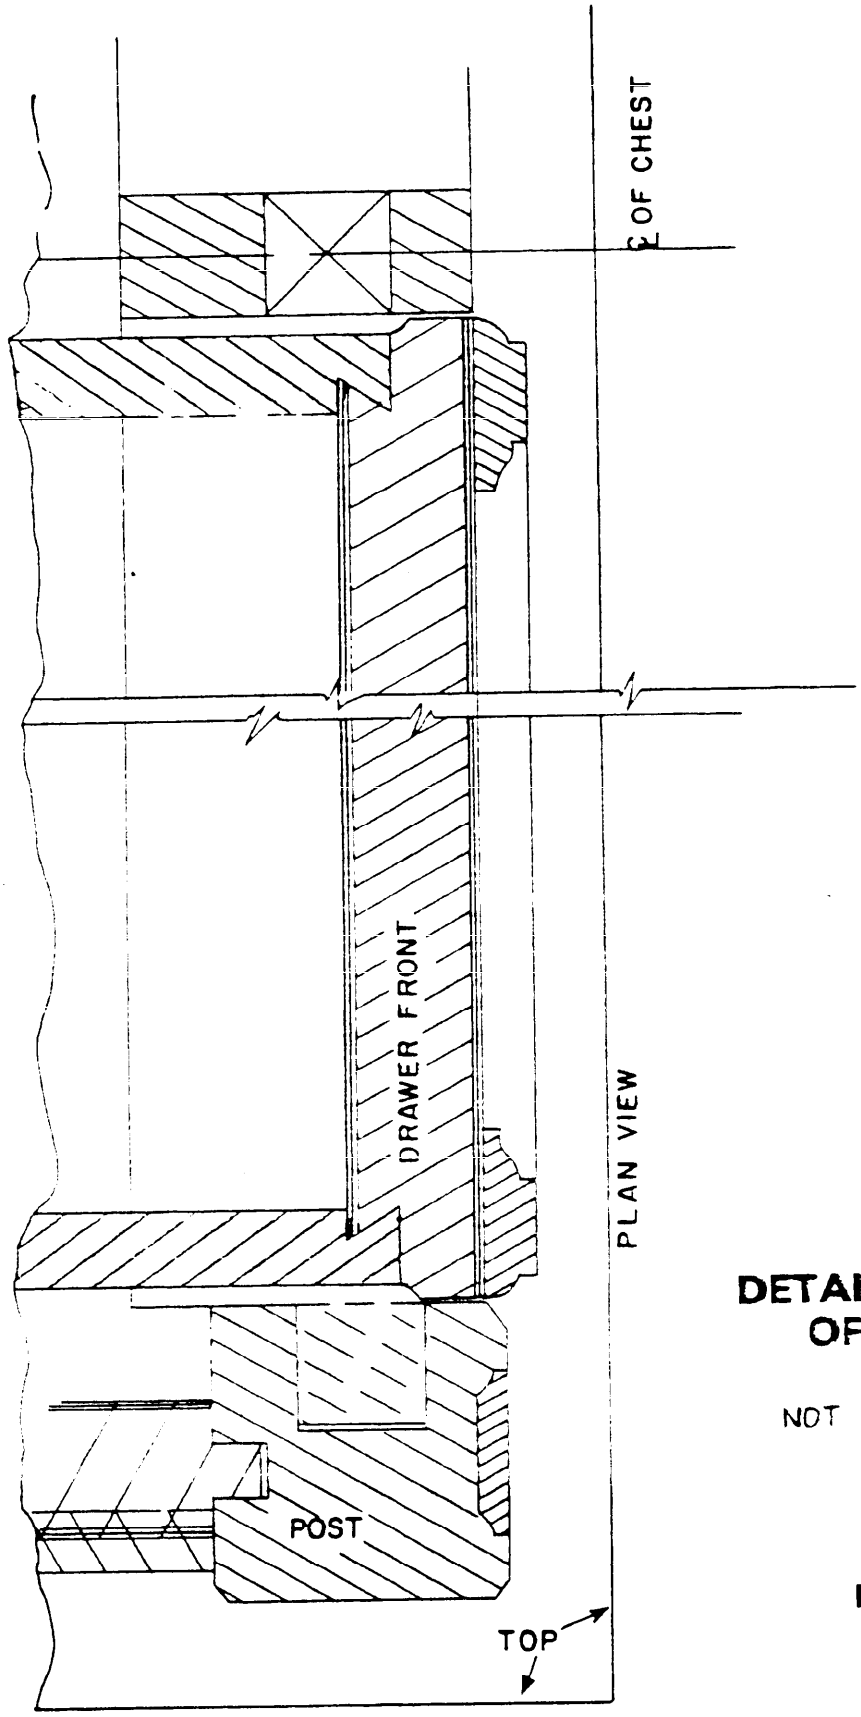


DETAIL SECTION OF CHEST

NOT TO SCALE

Figure 23.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

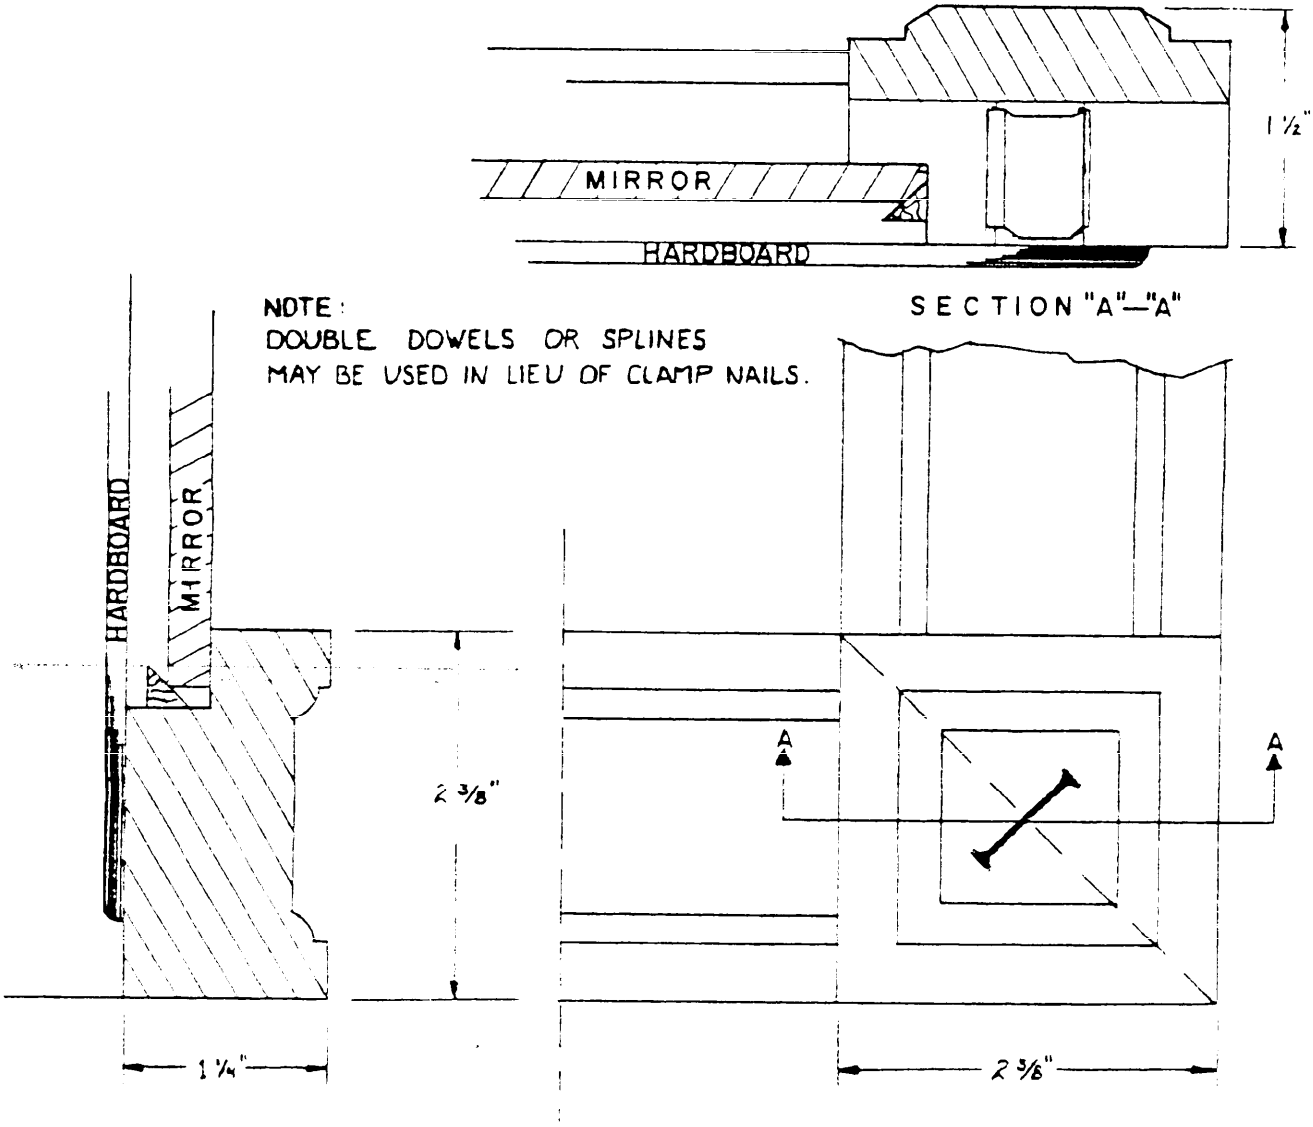


NOT TO SCALE

TYPICAL SECTIONS OF MIRRORS

Figure 24.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

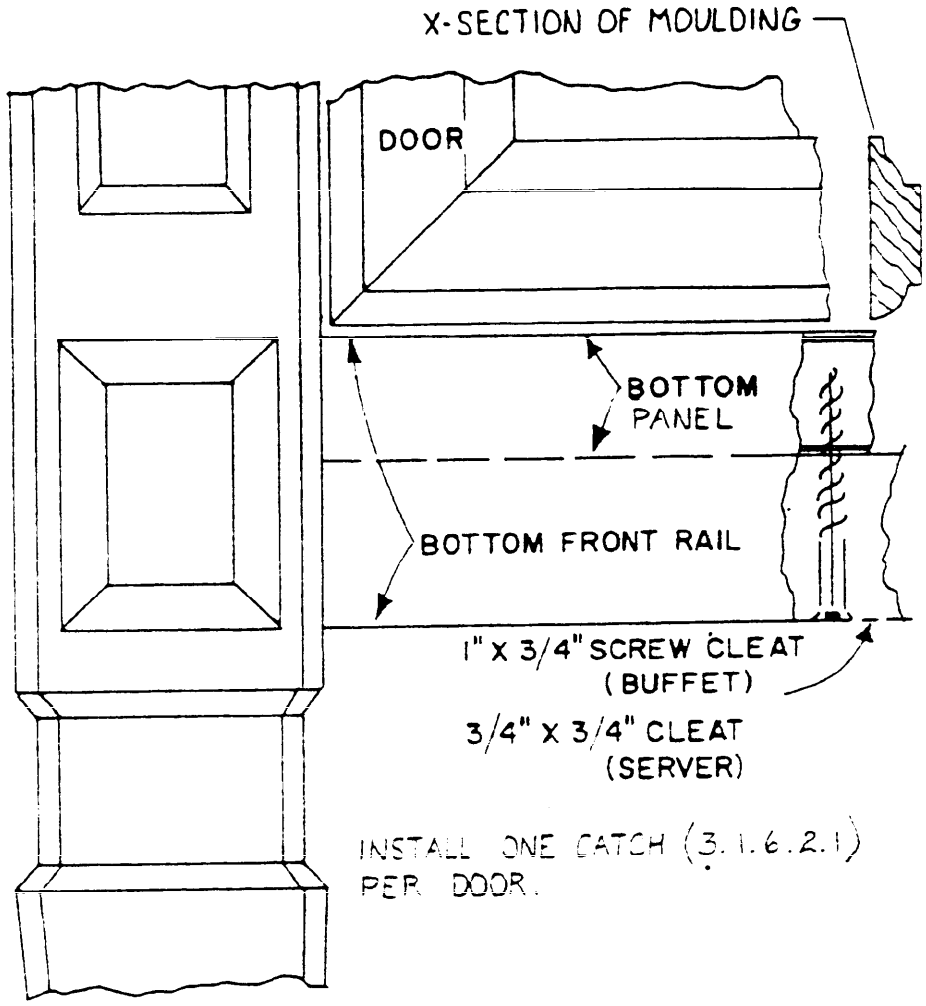


NOT TO SCALE

BUFFET AND SERVER

Figure 25.


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

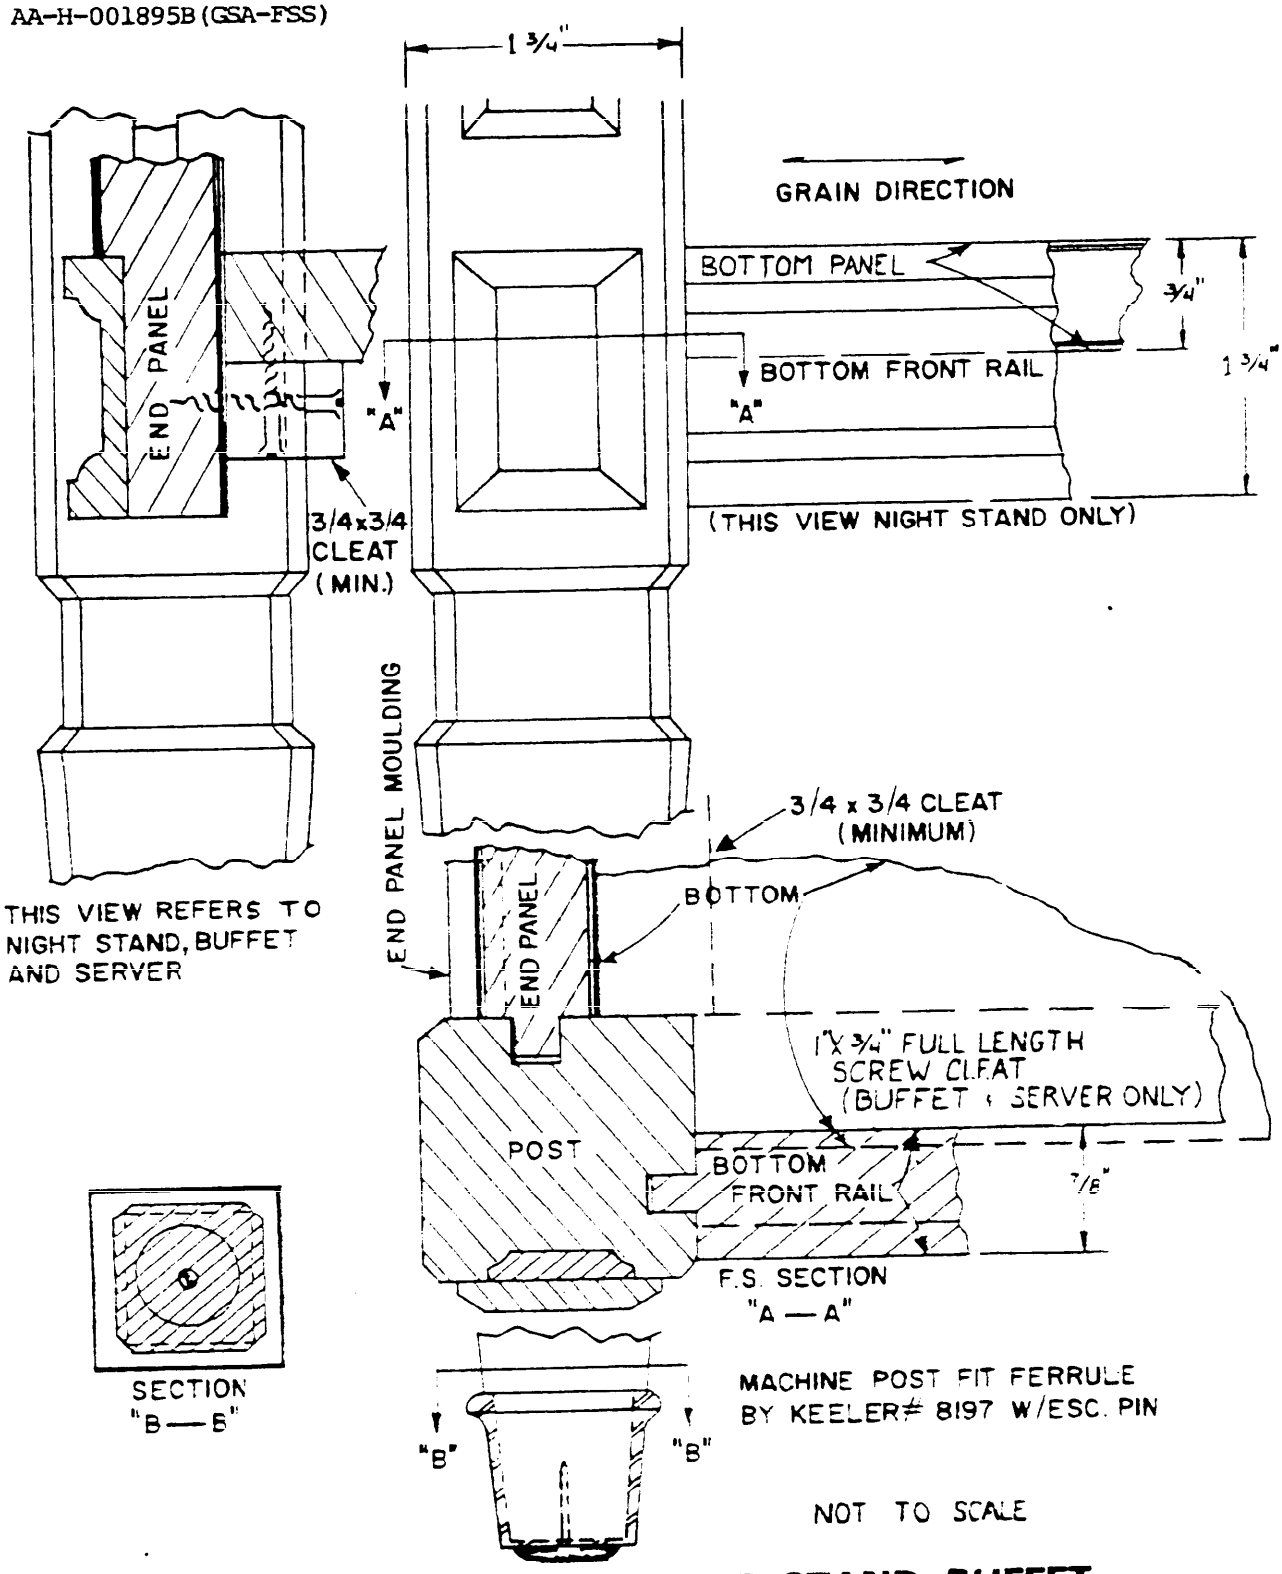

TYPICAL SECTIONS OF NIGHT STAND, BUFFET AND SERVER

Figure 26.


Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

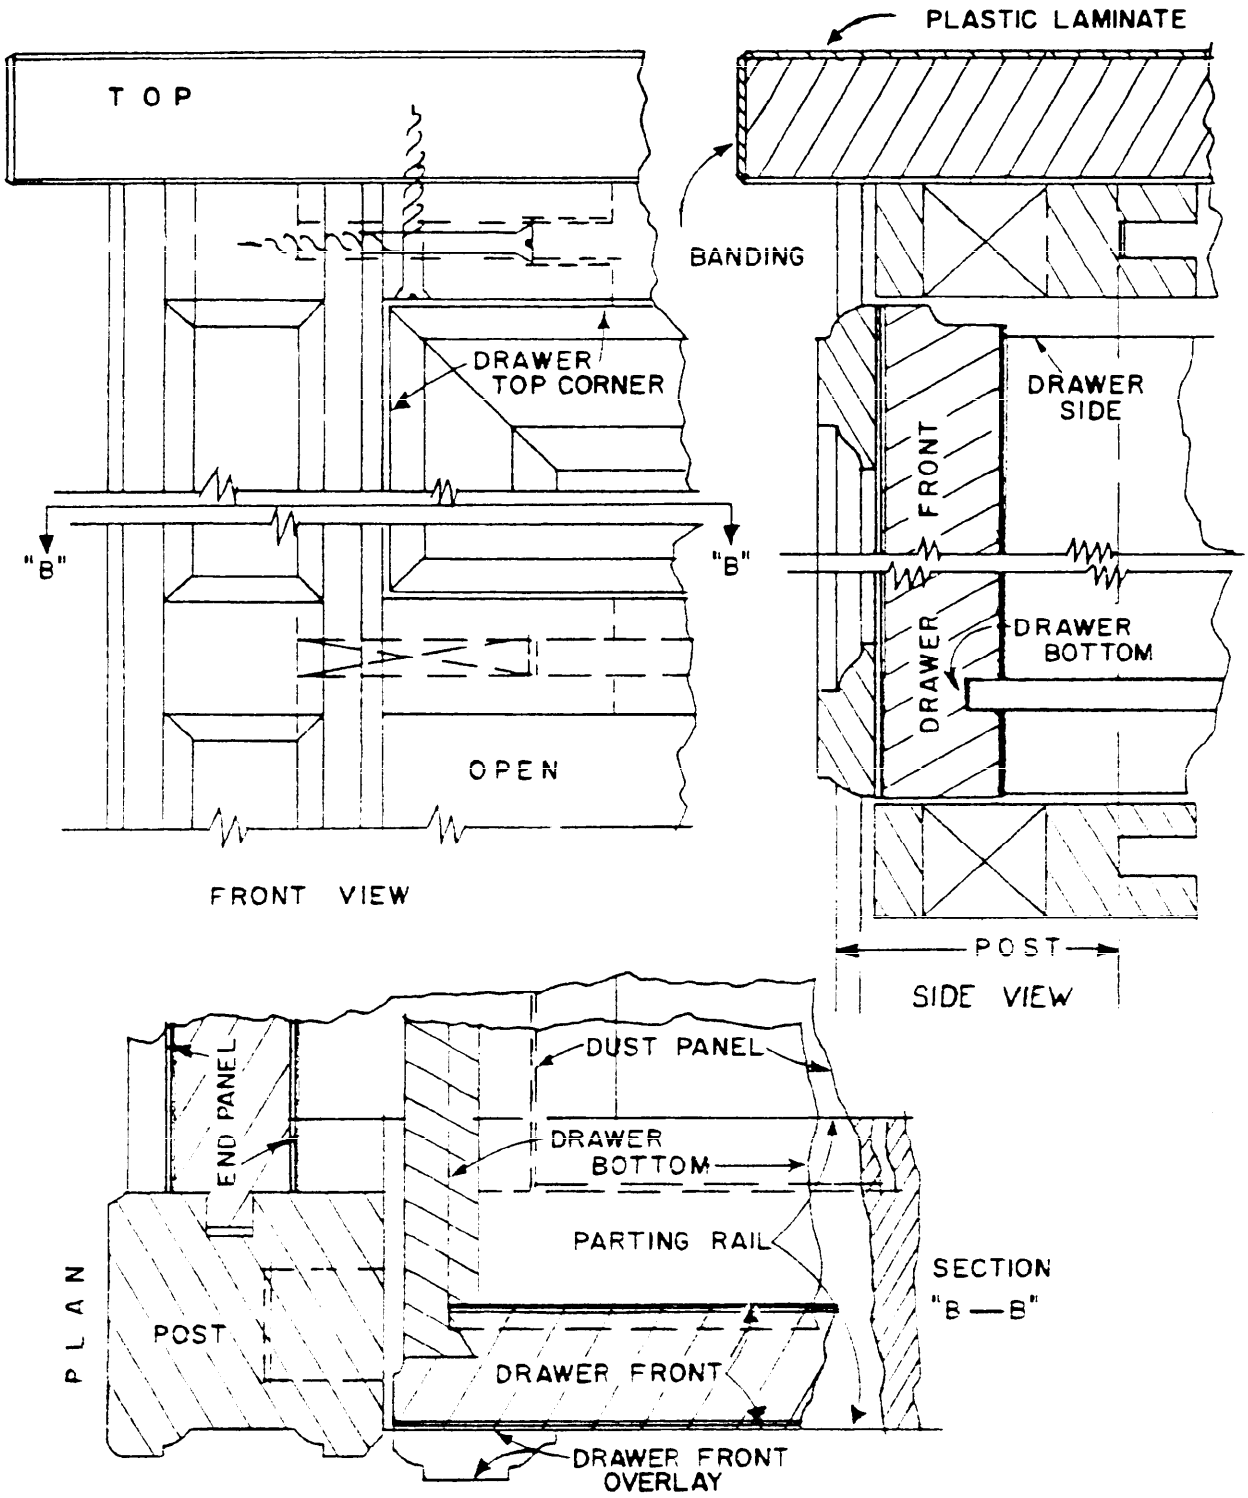

TYPICAL SECTIONS OF NIGHT STAND

Figure 27. NOT TO SCALE


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

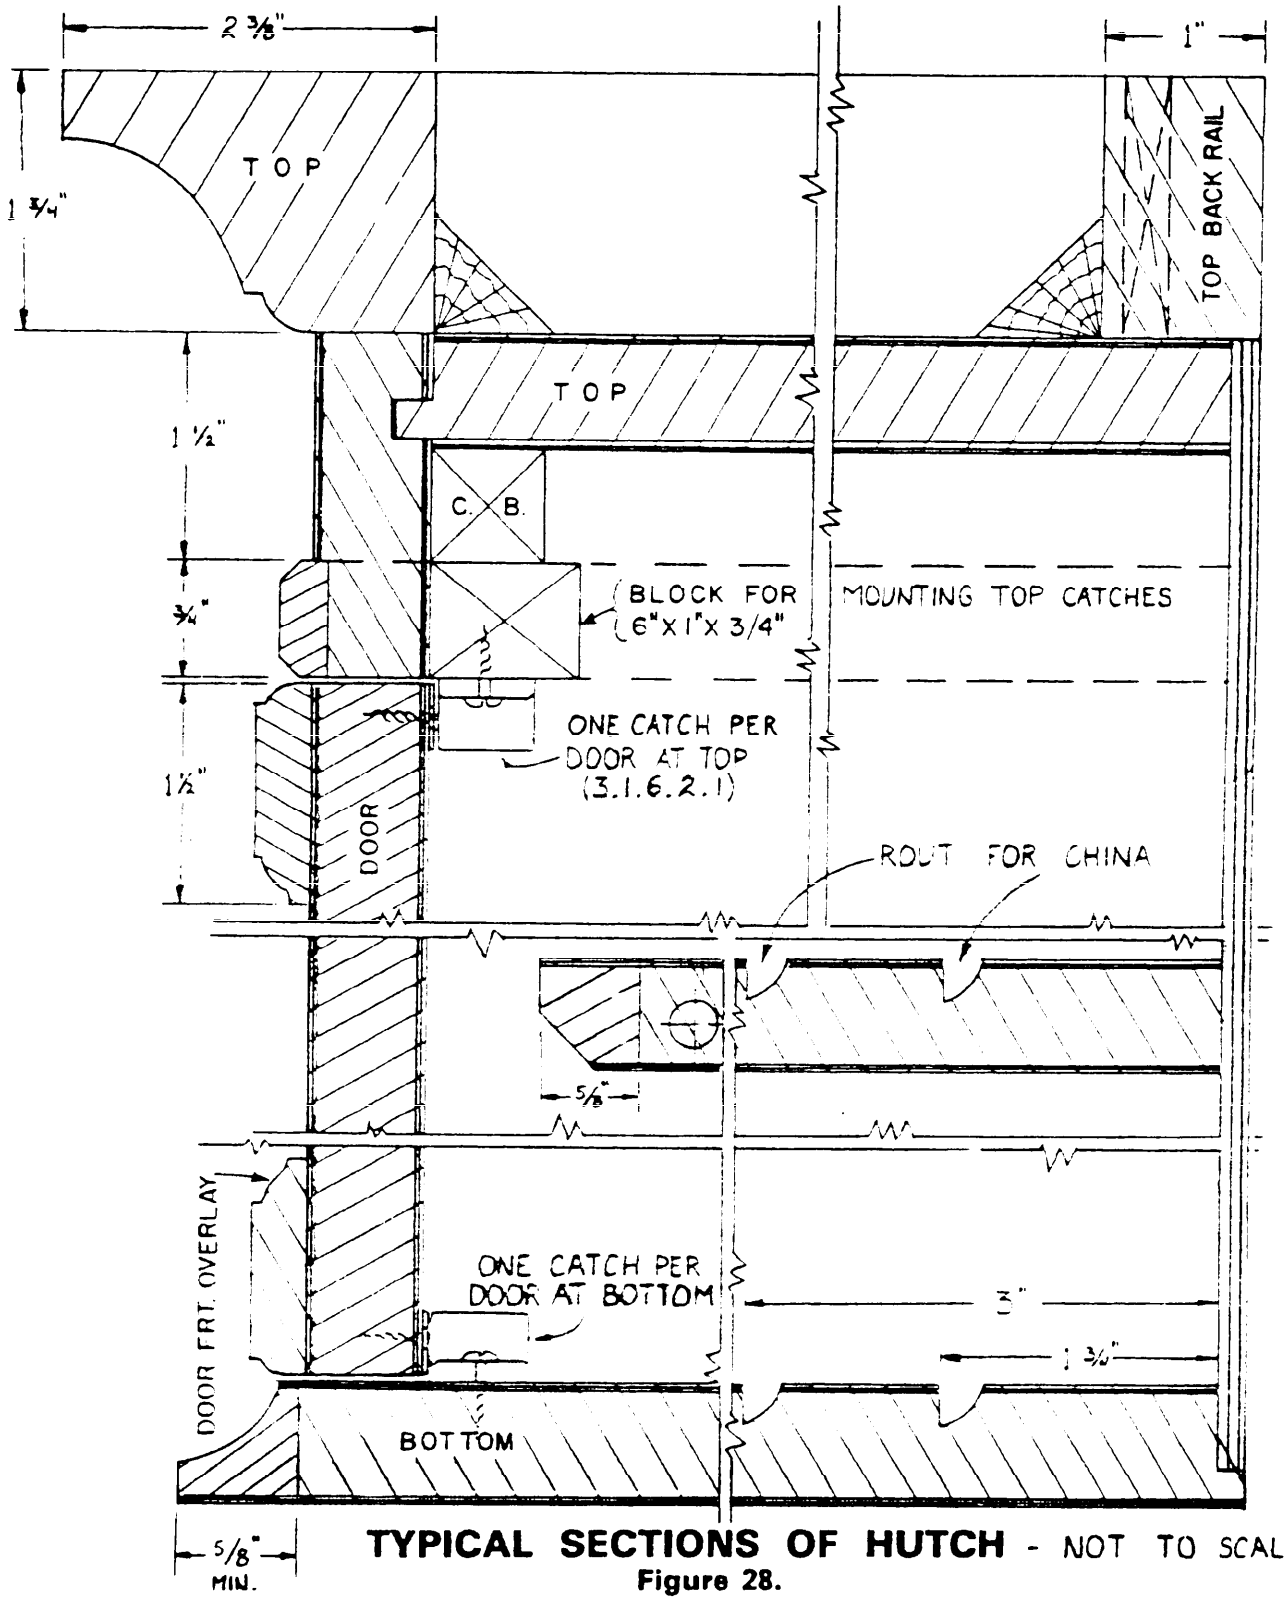

TYPICAL SECTIONS OF HUTCH - NOT TO SCALE

Figure 28.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

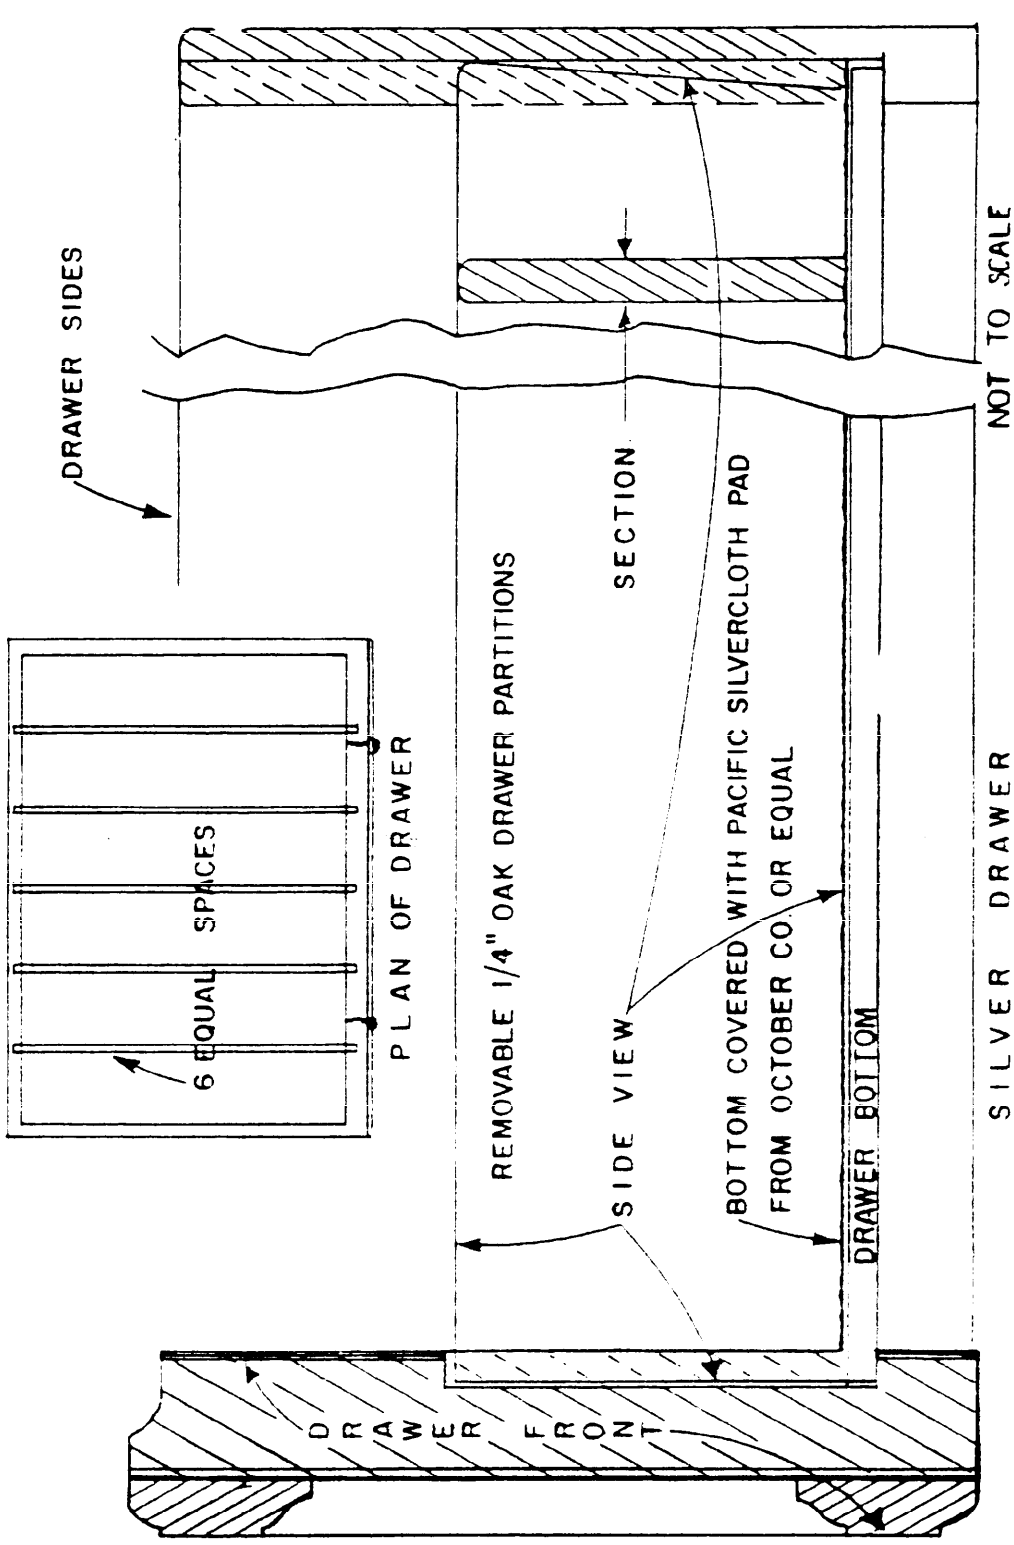

SECTION AND CONSTRUCTION DETAILS OF BUFFET TOP CENTER DRAWER-RIGHT HALF OF SERVER DRAWER SIMILAR

Figure 29.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

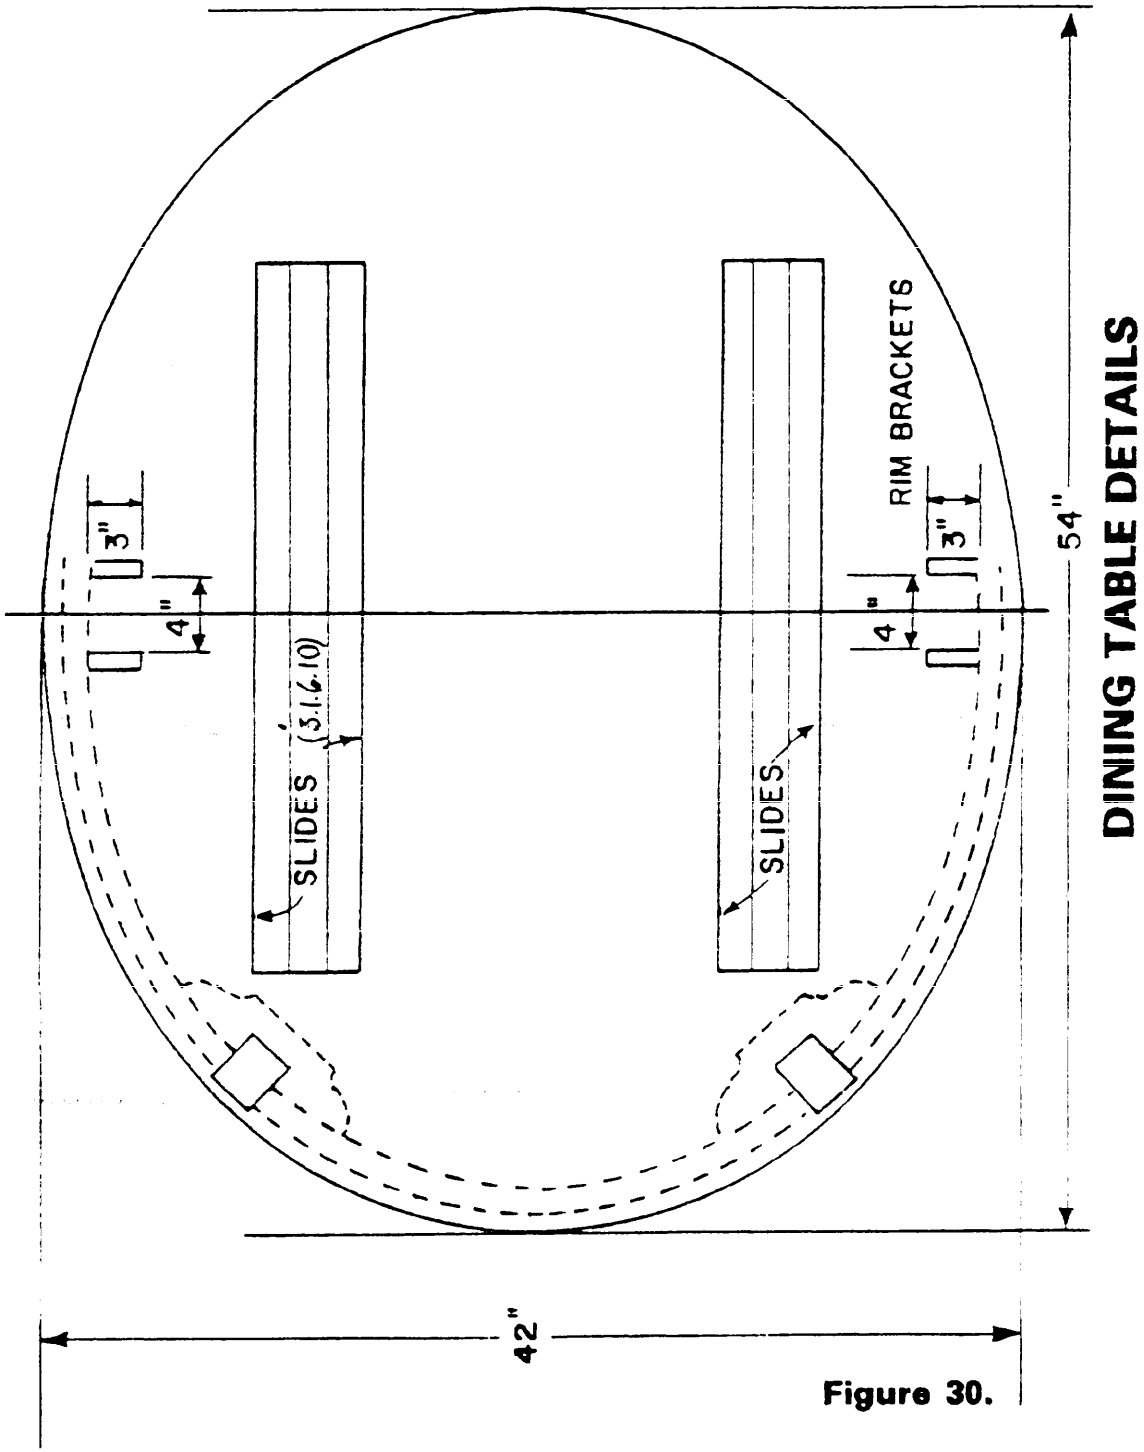


Figure 30.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.


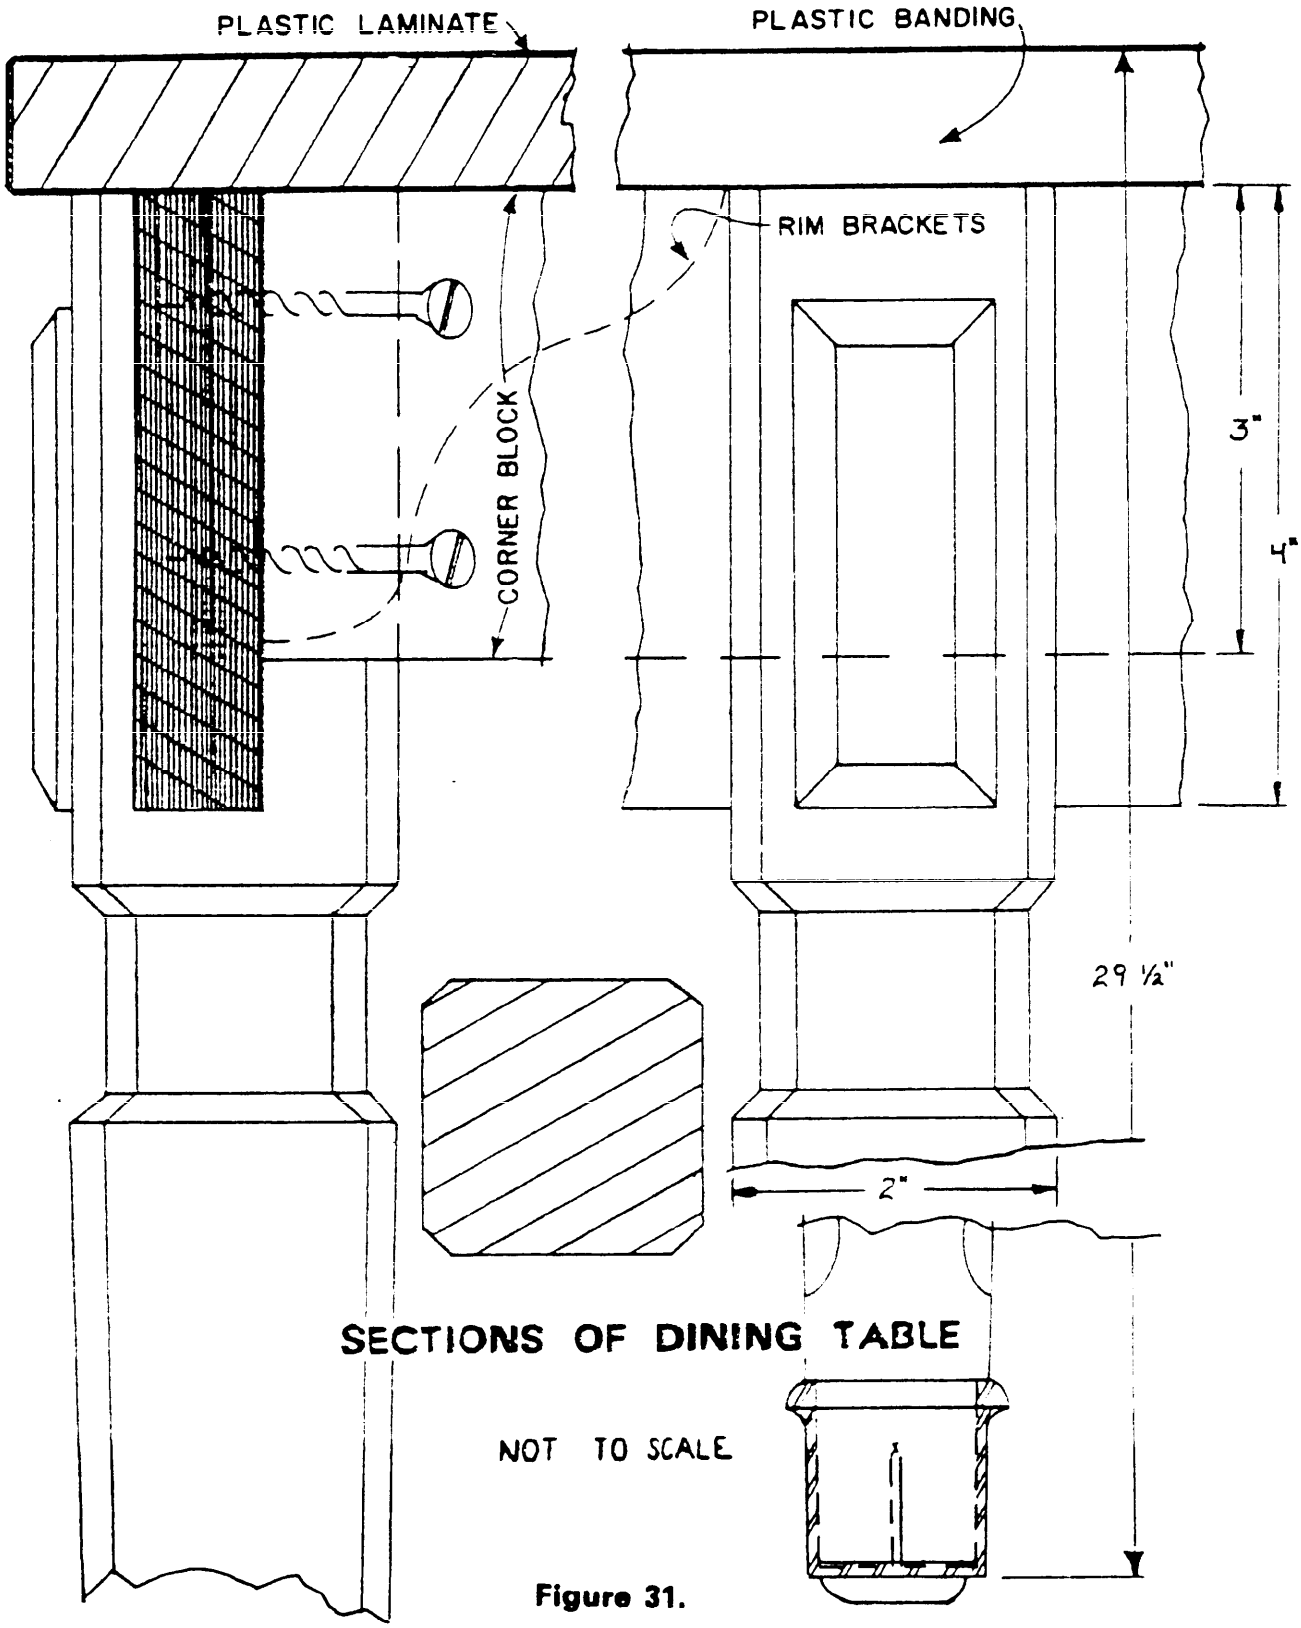


Figure 31.


321-884 0 - 80 - 4 : QL 4 Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the currentversion before use.

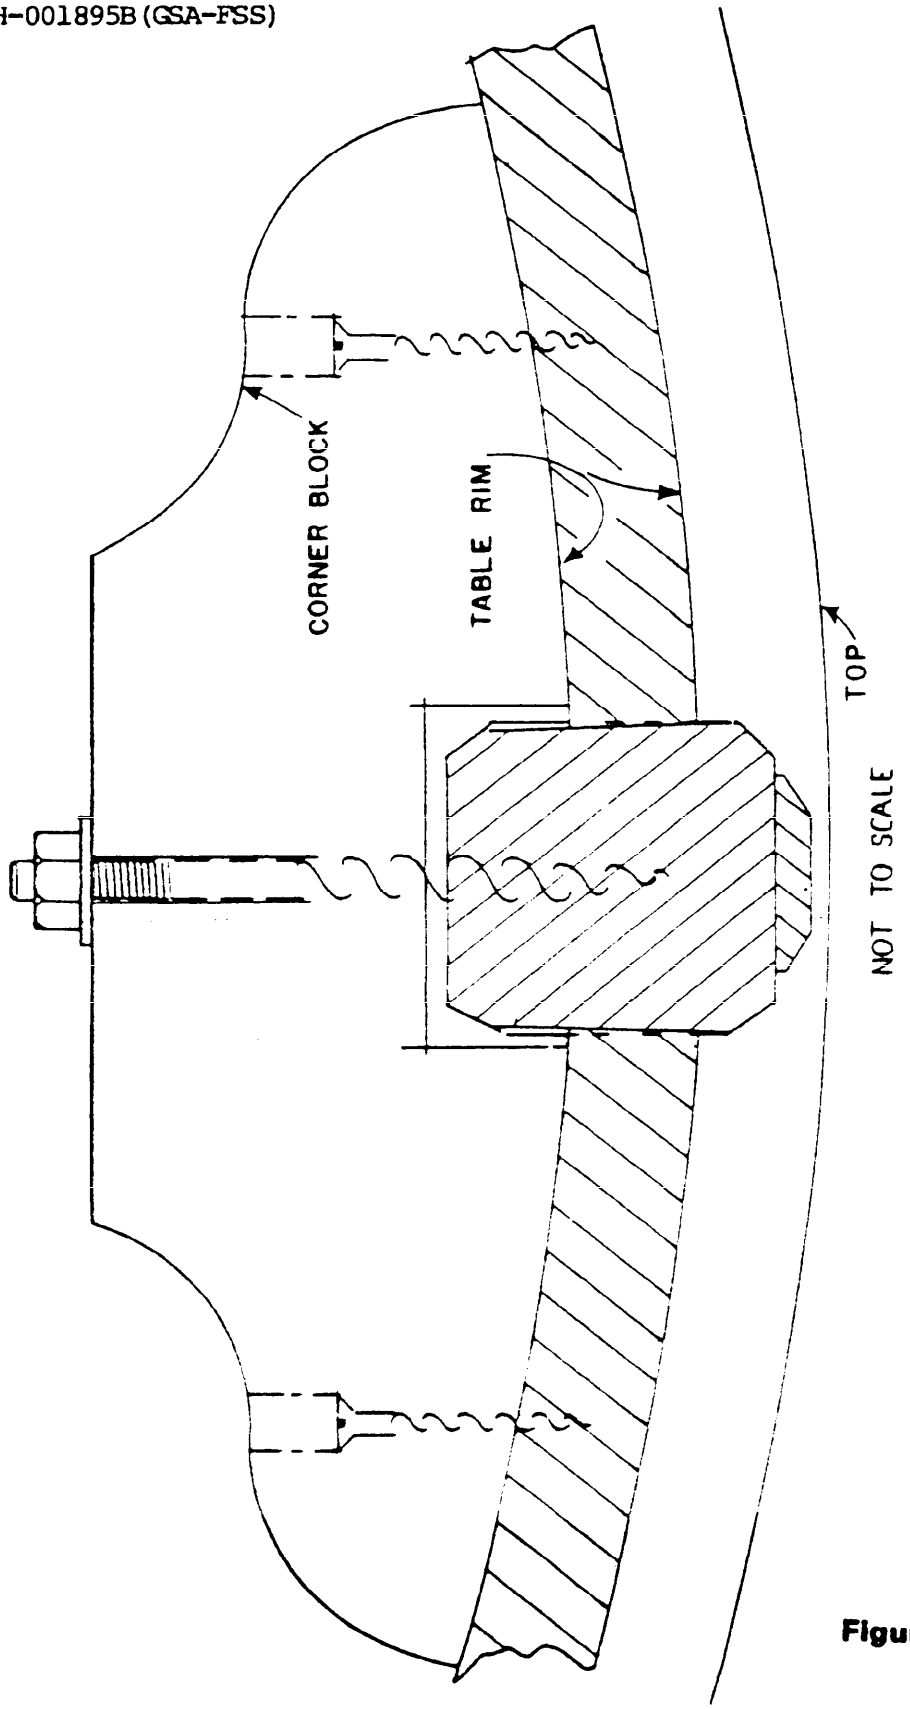

SECTION OF DINING TABLE LEG
COFFEE TABLE SAME EXCEPT FOR SIZE AND SHAPE OF OVAL

Figure 32.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

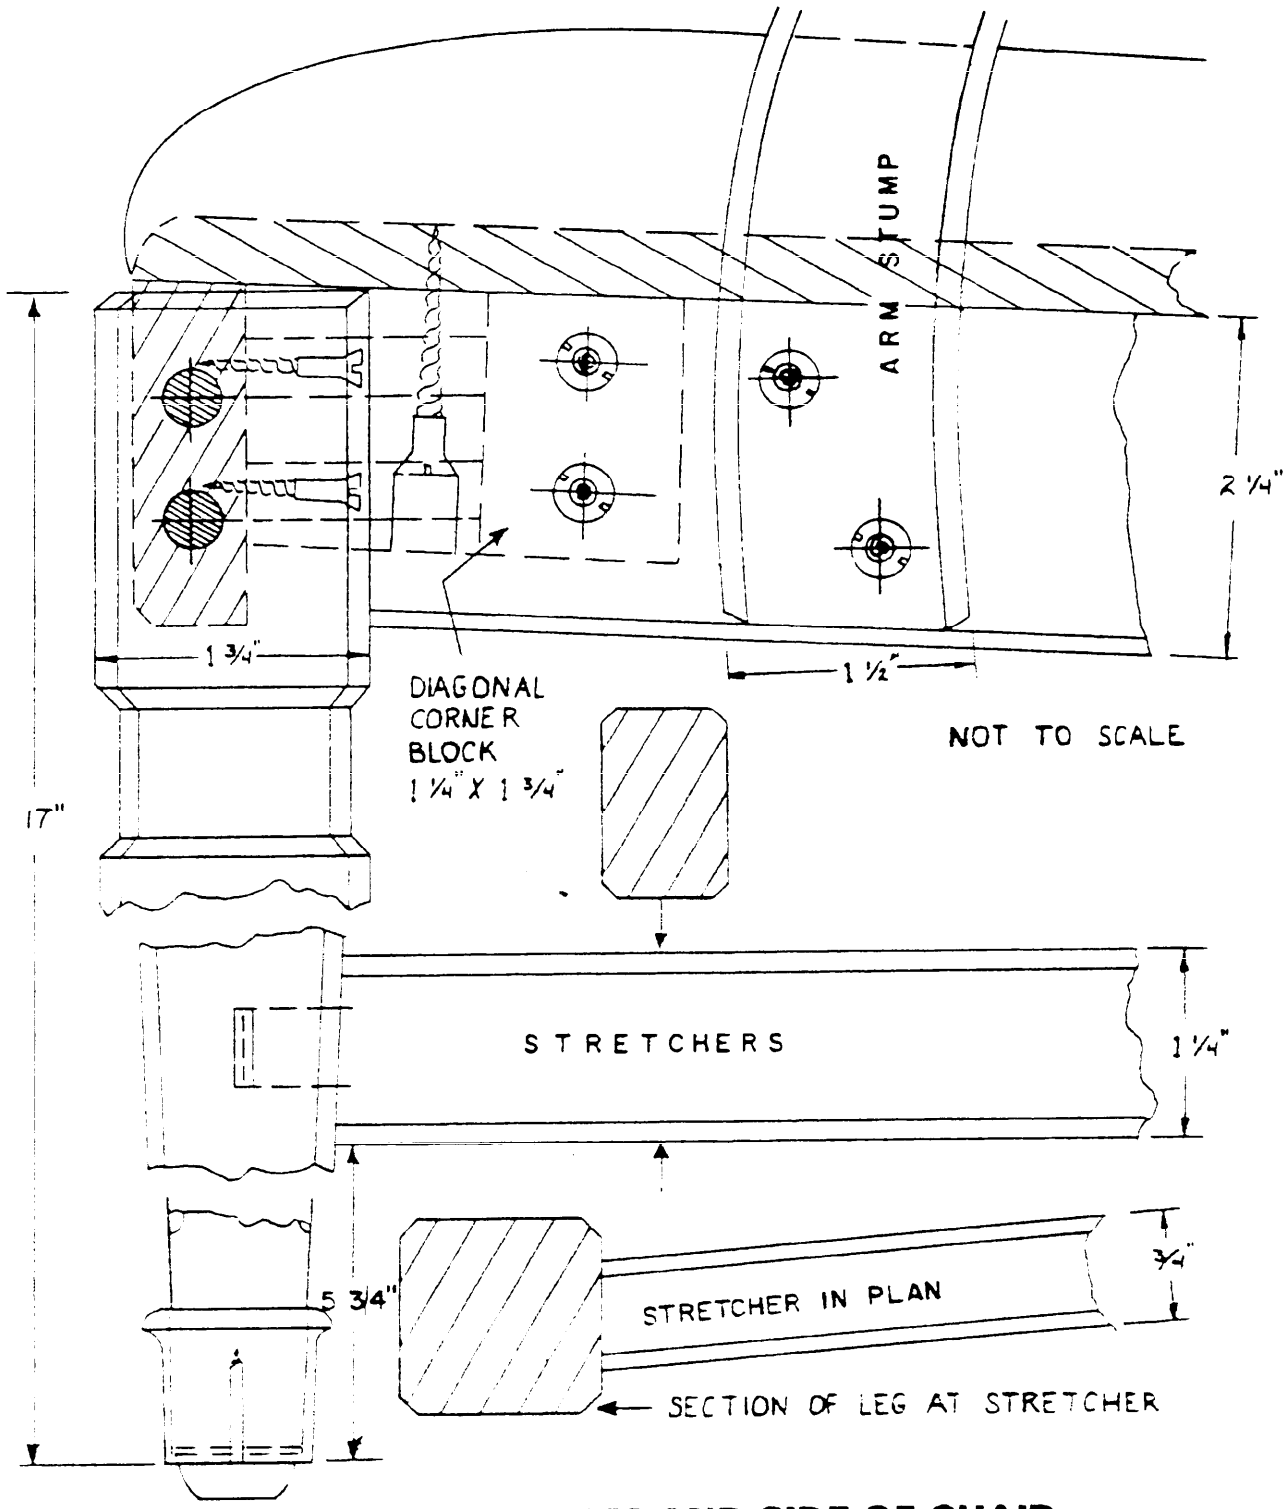

SECTIONS OF ARM AND SIDE OF CHAIR

Figure 33.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:41Z
Check the source to verify that this is the current version before use.

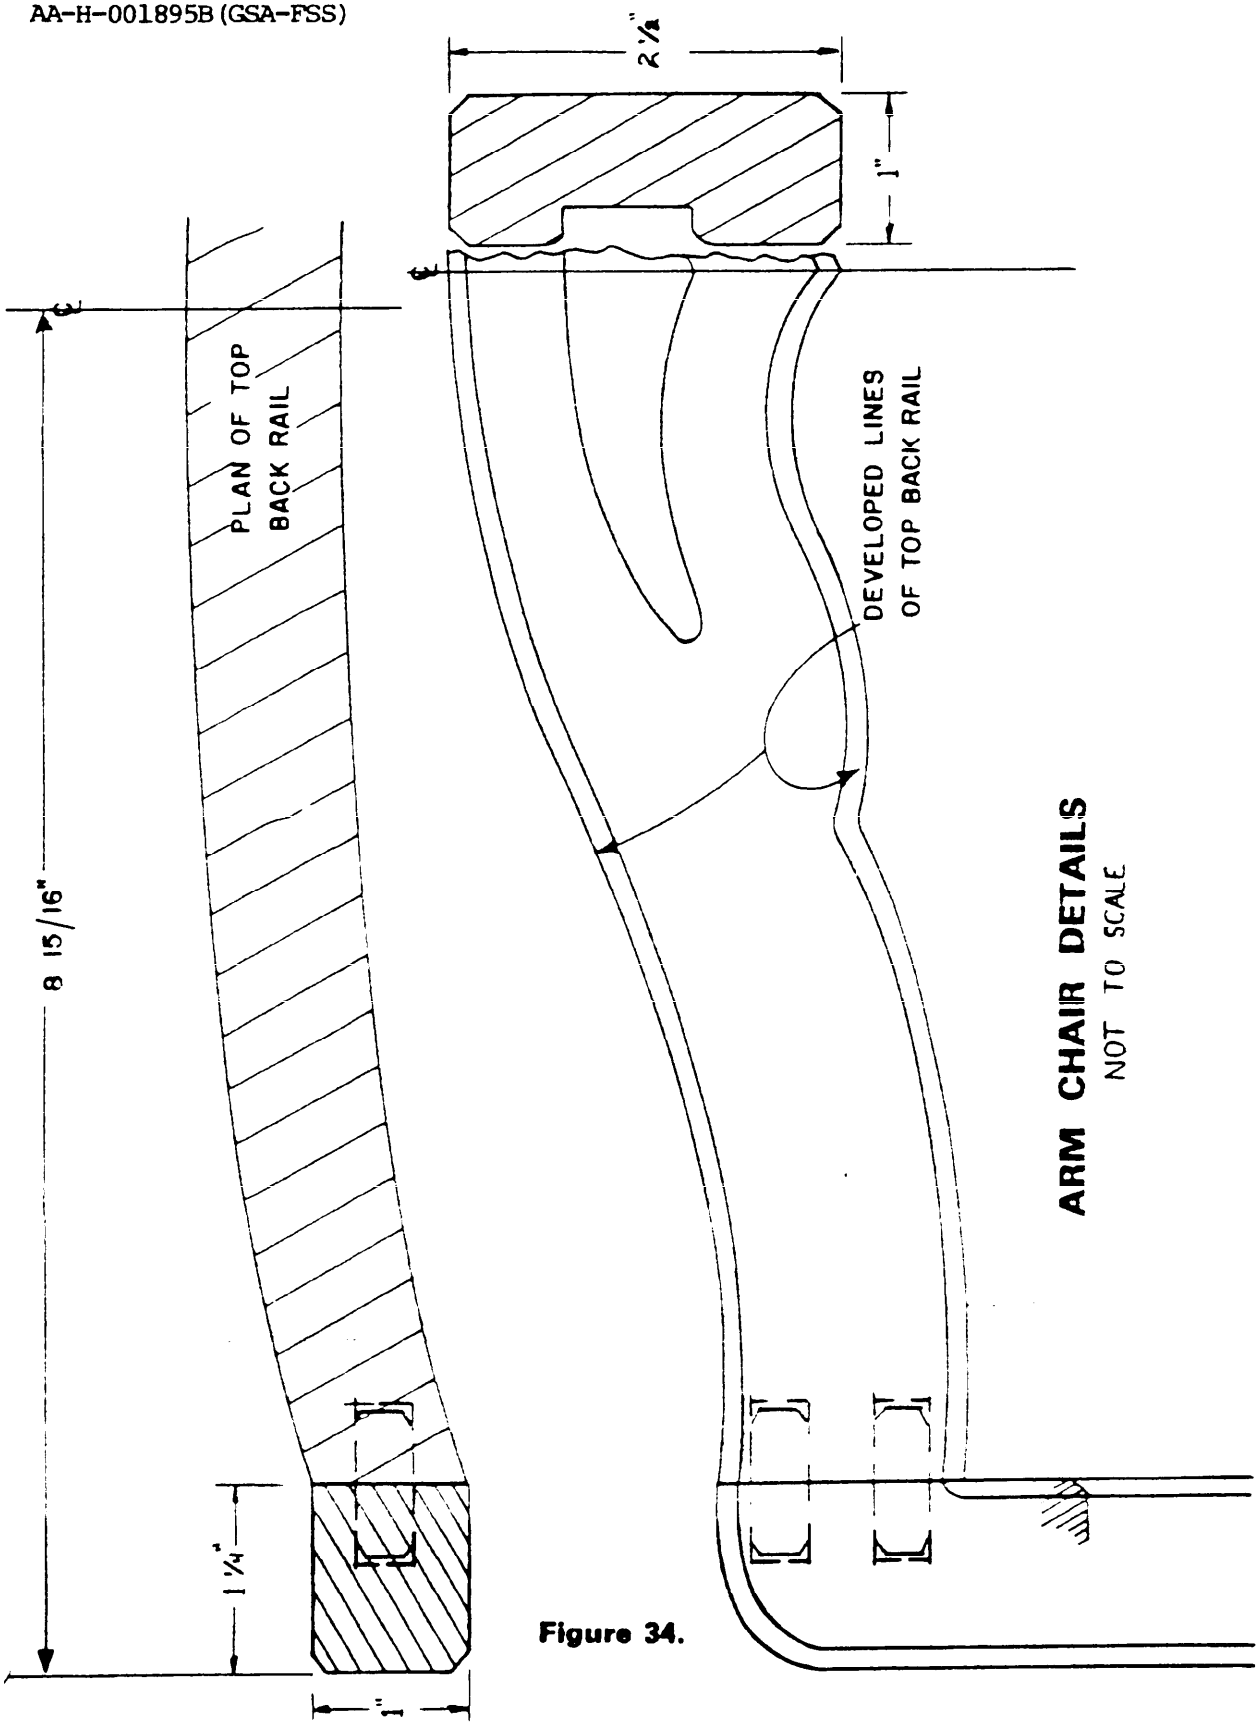


Figure 34.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.


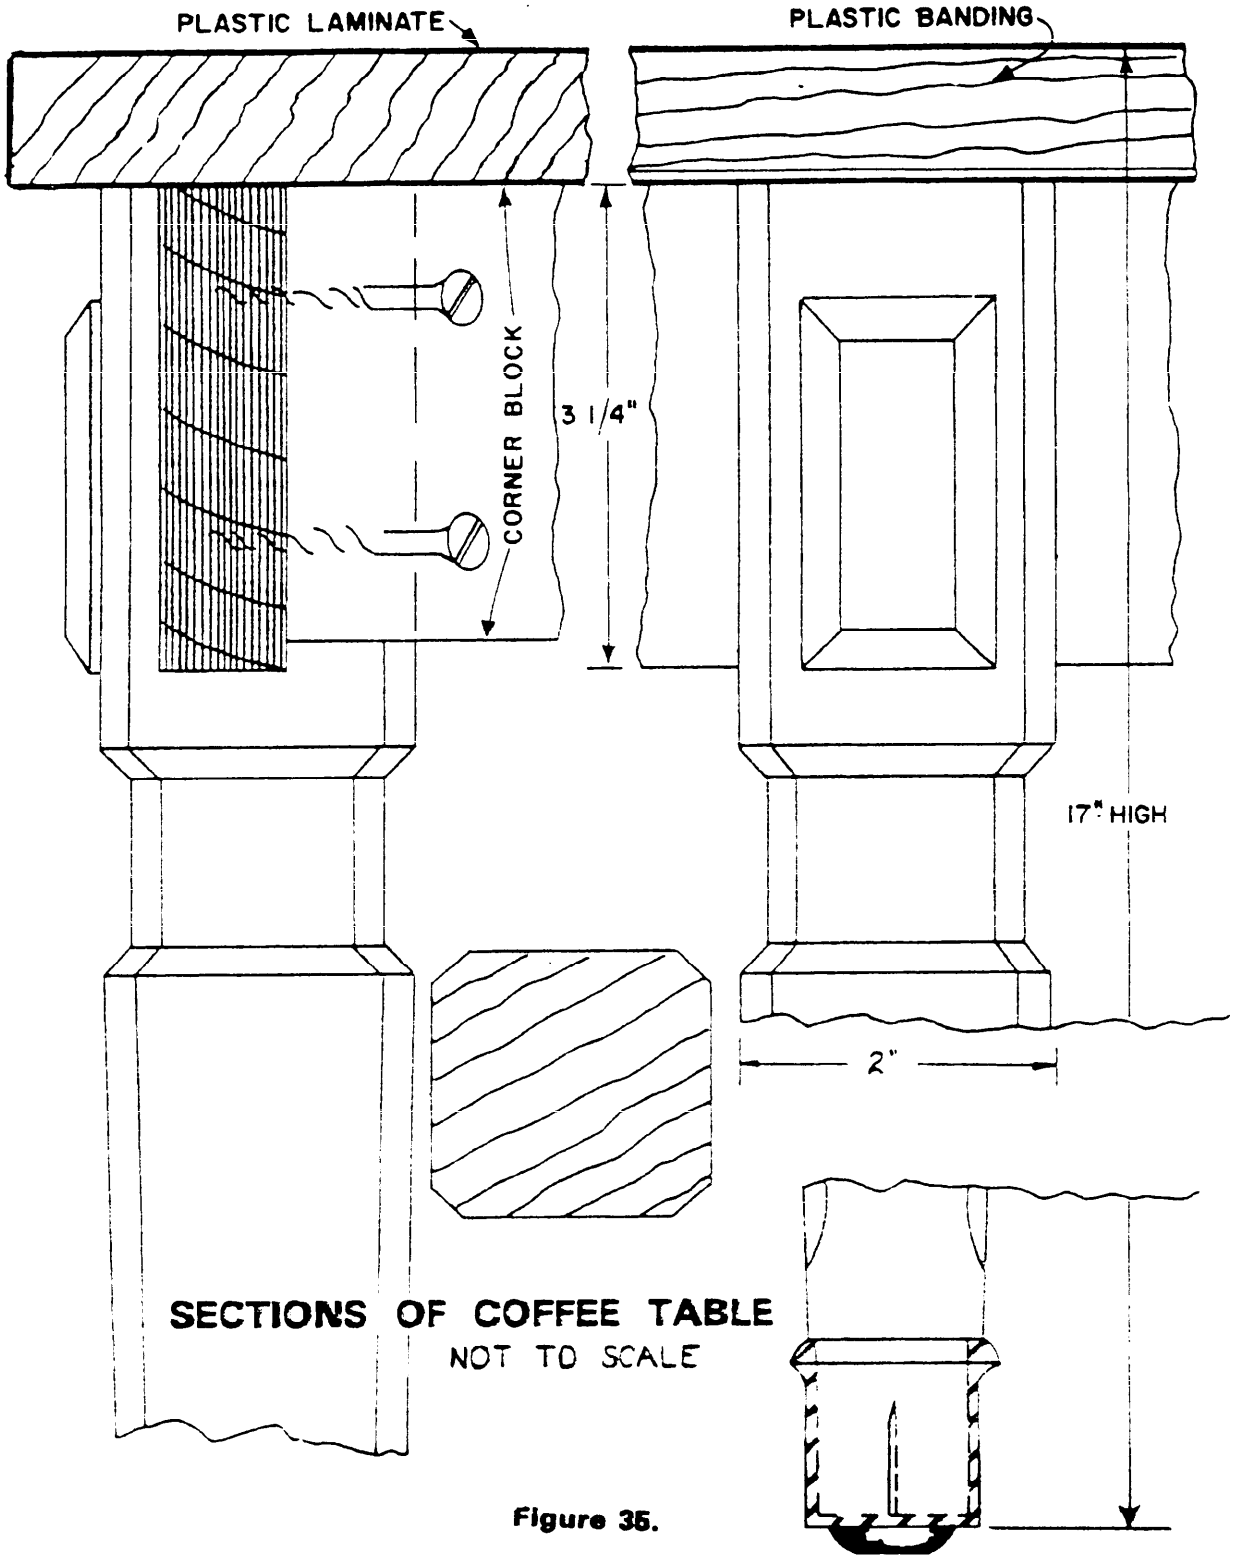


Figure 35.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

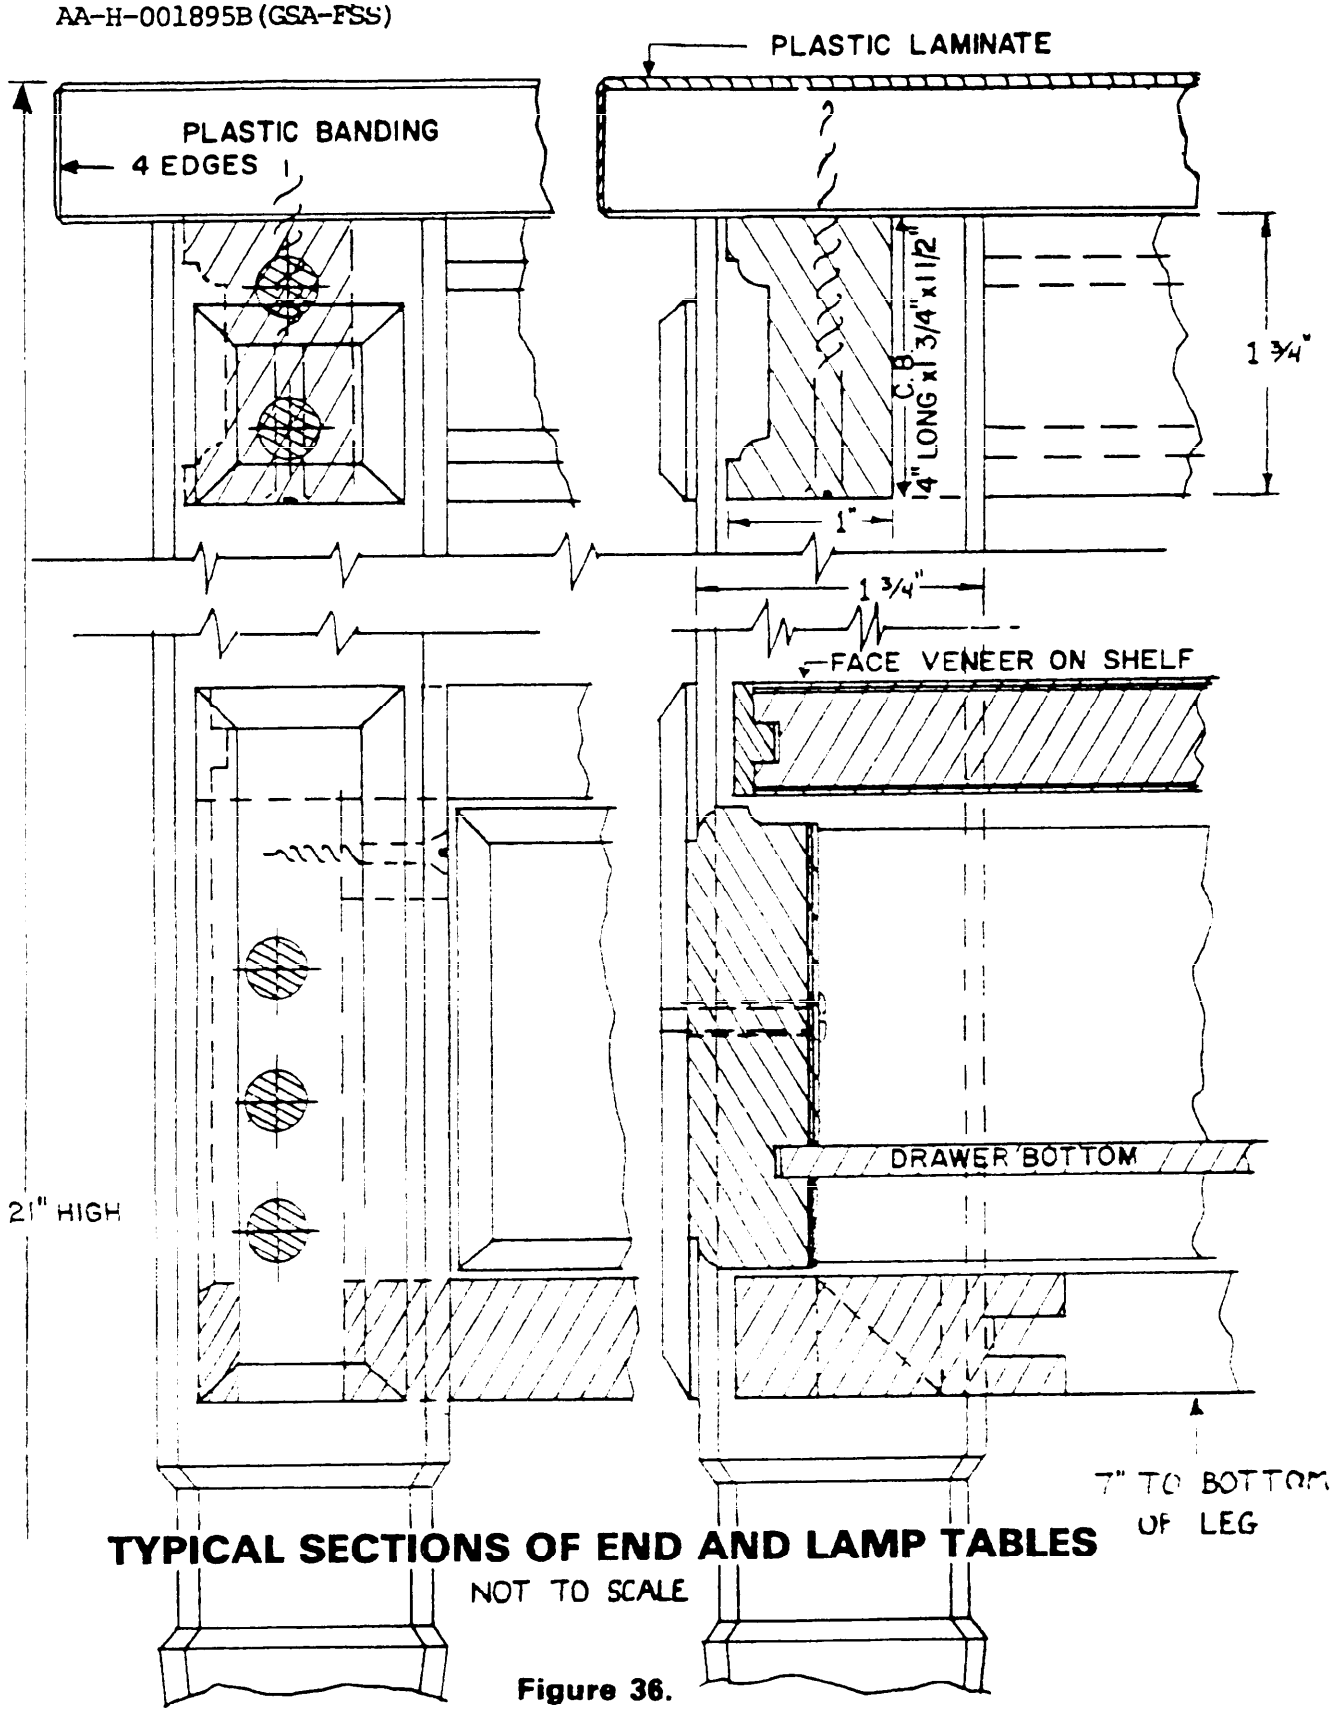

TYPICAL SECTIONS OF END AND LAMP TABLES

NOT TO SCALE

Figure 36.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

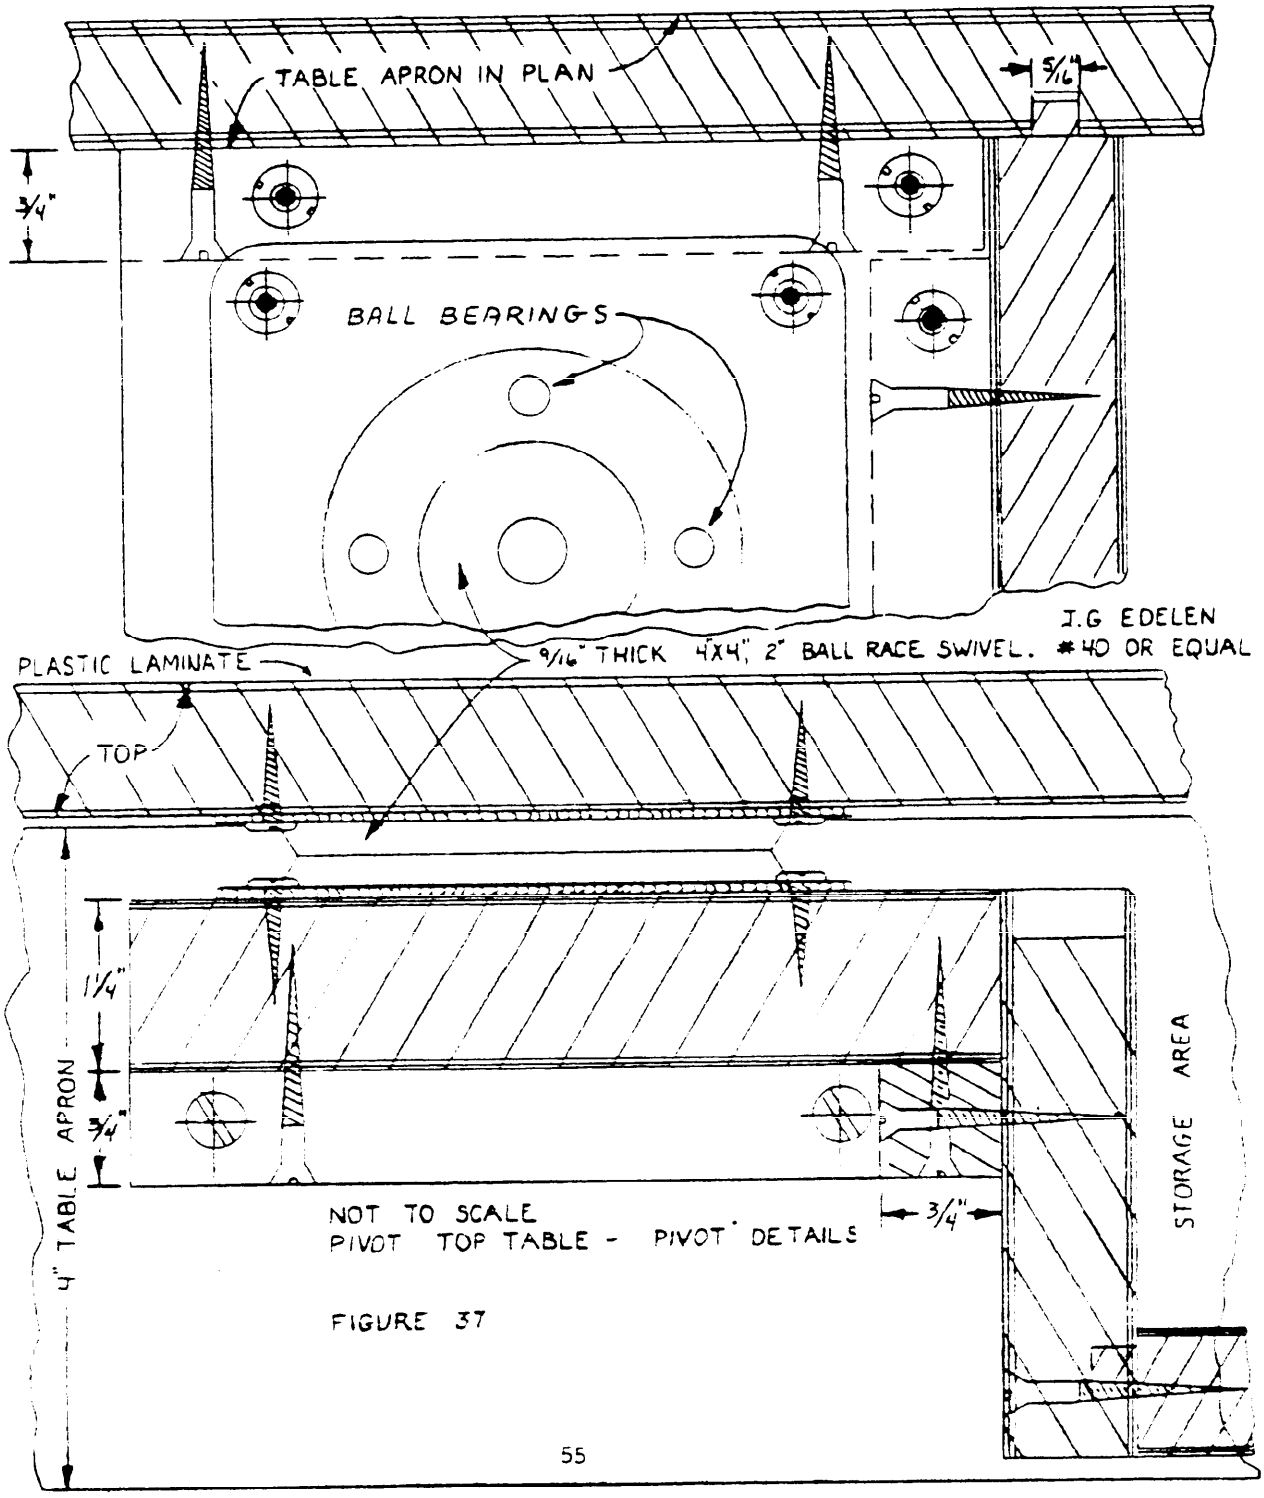


FIGURE 37

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.



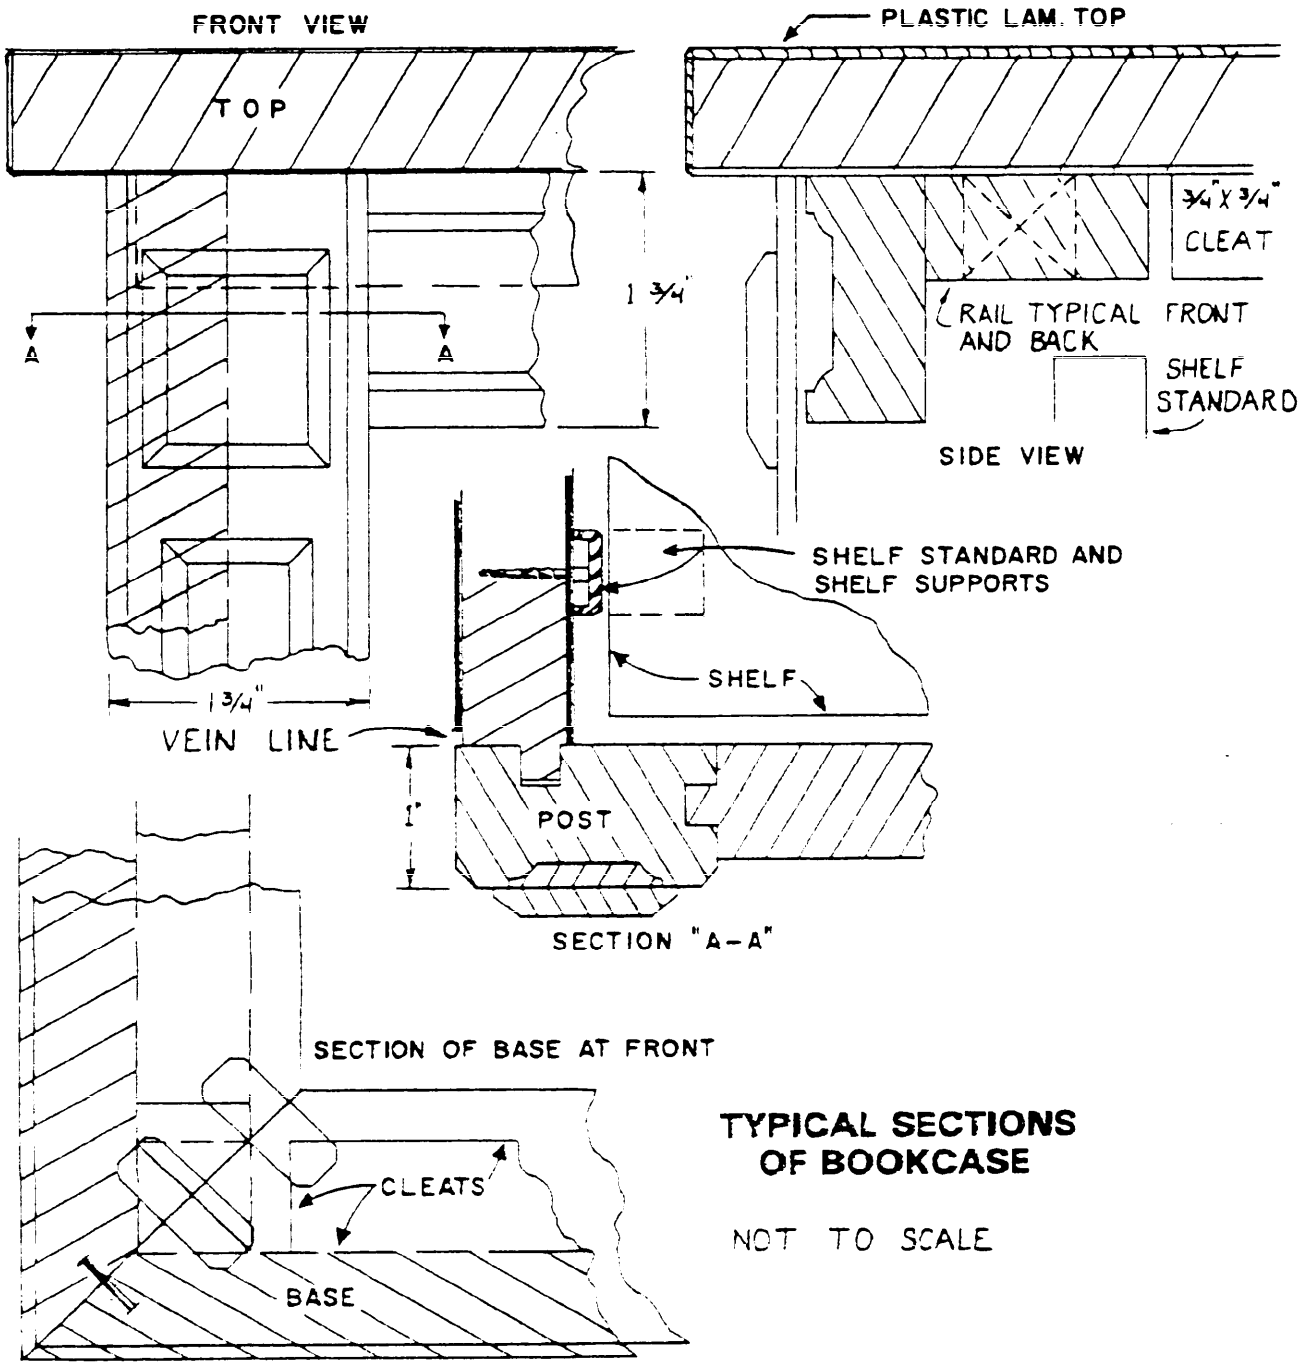


Figure 38.

Source: https://assist.dla.mil -- Downloaded: 2026l0-26T11:41Z
Check the source to verify that this is the currentversion before use.

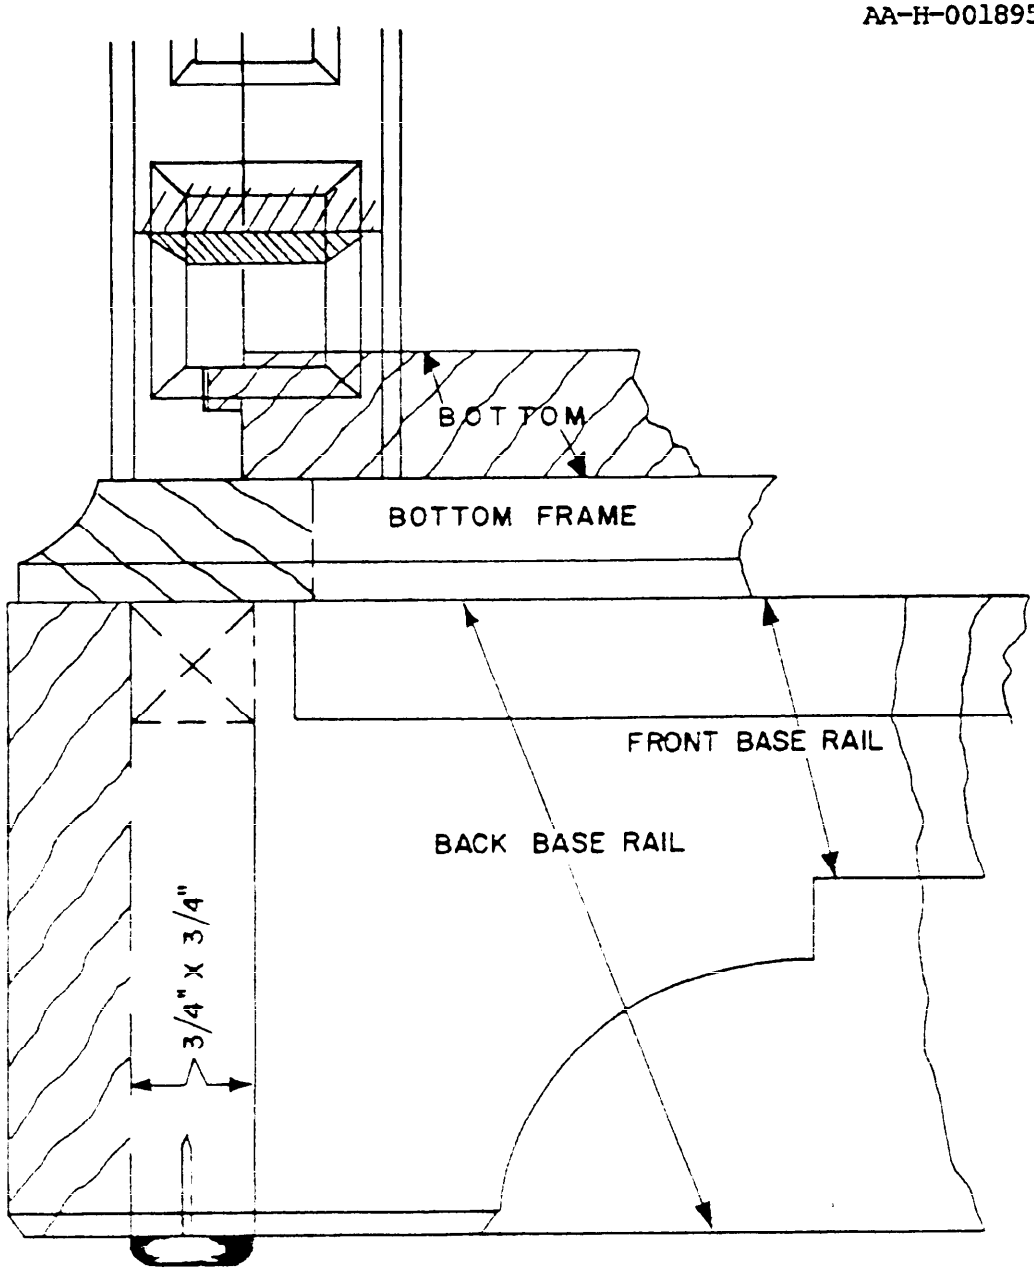

TYPICAL SECTIONS OF BOOKCASE

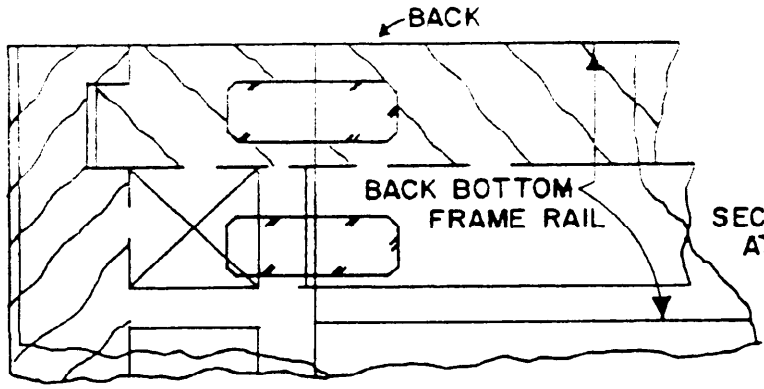

NOT TO SCALE

SECTION OF BASE AT BACK

Figure 39.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.


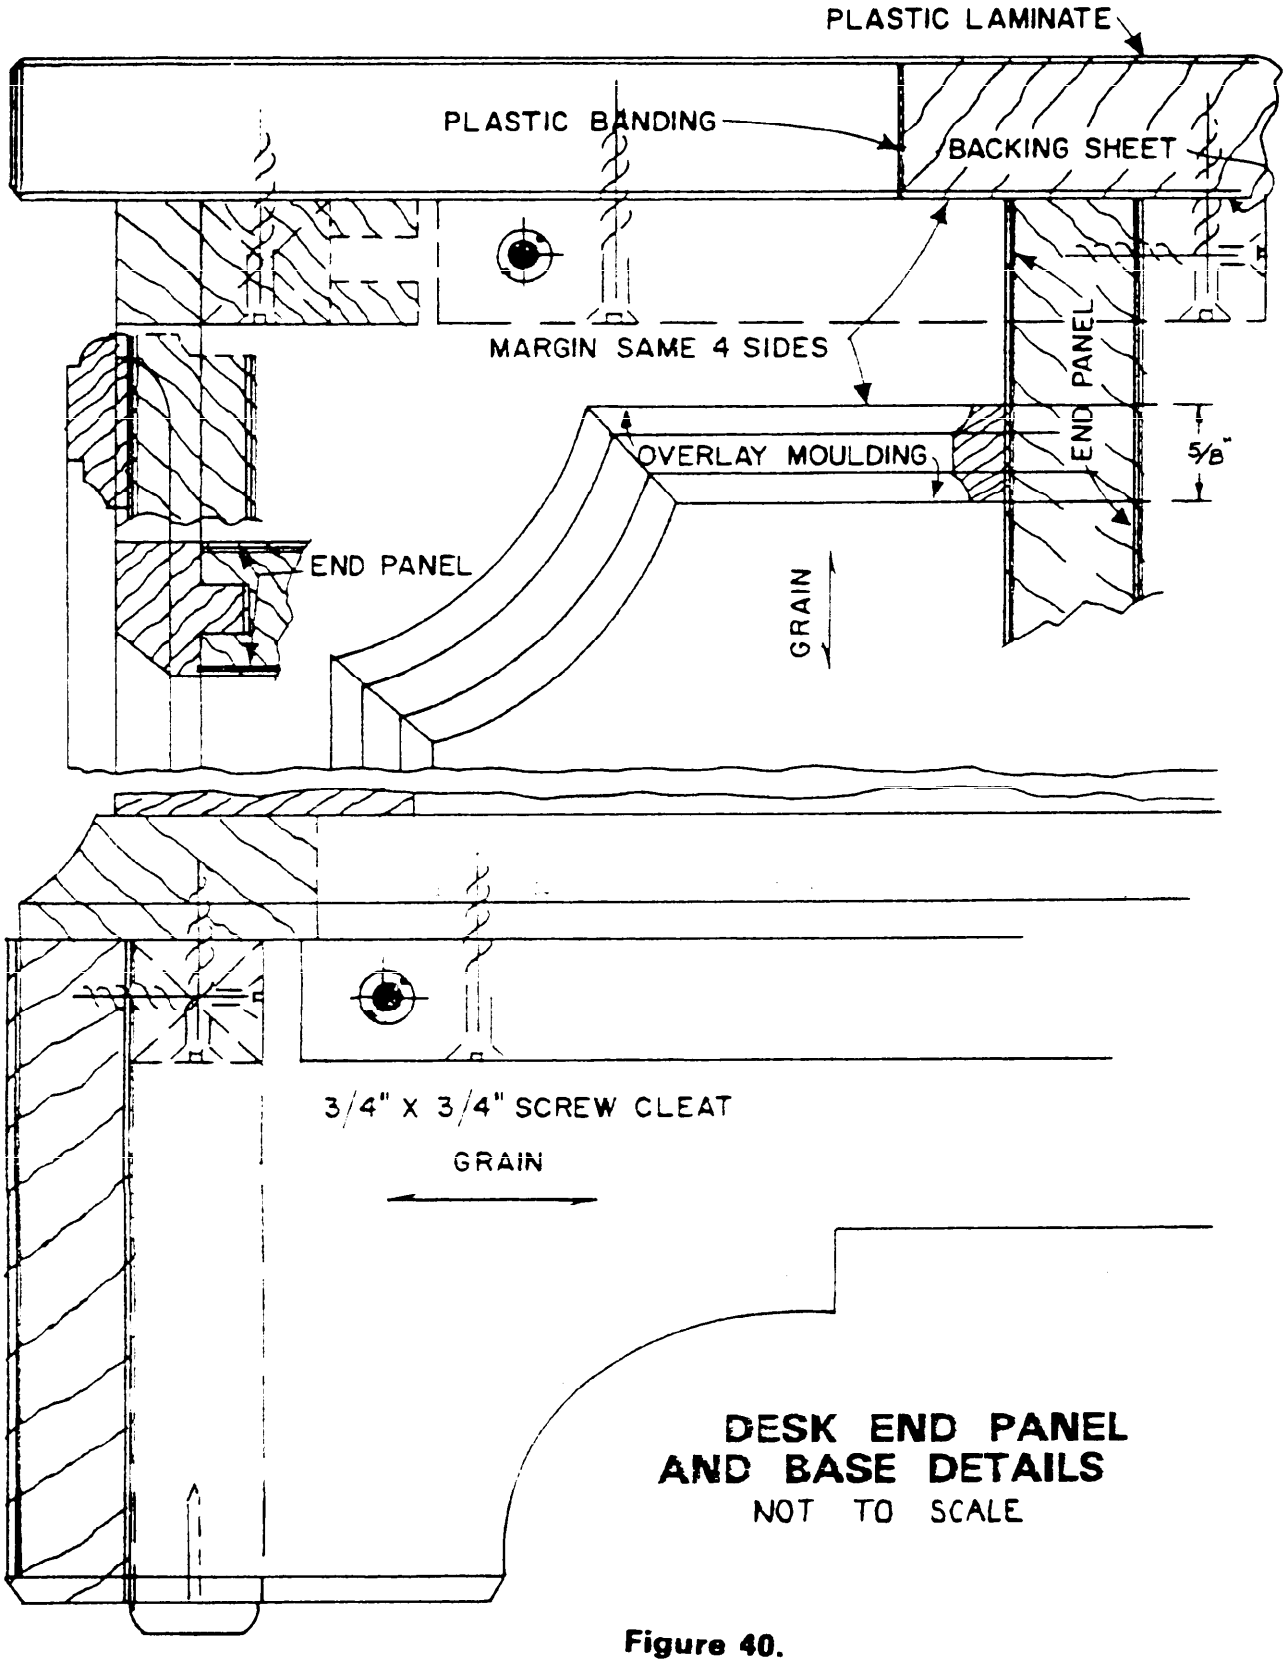


Figure 40.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.

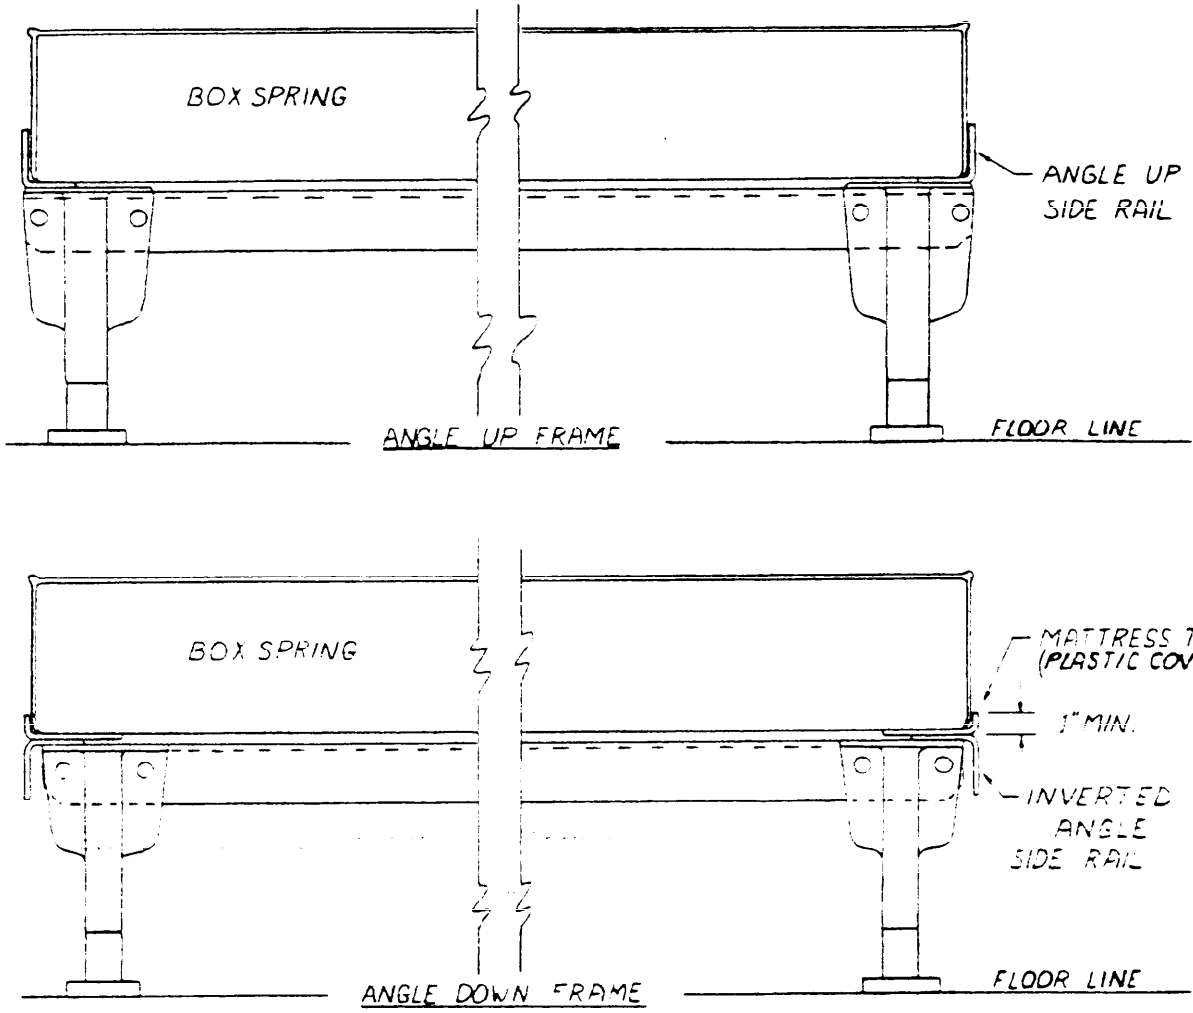

NOTES: (ON BOTH TYPES OF FRAME)

1. HEADBOARD MOUNTING PLATES, 13 GAGE (.0897") MIN.
2. SIDE RAILS 1½ X 1½, 12 GAGE MIN. STEEL, 70 INCHES LONG MIN.
3. EXPOSED ENDS OF SIDE RAILS, AT FOOT OF BED, SHALL BE PLASTIC COVERED.
4. KNOWN SOURCES OF SUPPLY ARE LISTED IN 6.4
5. GLIDE CONFIGURATION MAY VARY.

METAL BED FRAMES
FIGURE 41

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:41Z
Check the source to verify that this is the current version before use.