MIL-C-43808A(GL)
17 May 1983
SUPERSEDING
MIL-C-43808(GL)
19 September 1972

MILITARY SPECIFICATION

CLOTH, COATED, NYLON

This specification is approved for use by the Natick Research and Development Laboratories, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This document covers two types of coated nylon cloth, coated on only one side (see 6.1).

1.2 Classification. The coated cloth shall be of the following types as specified (see 6.2).

Type I - Chloroprene coated

Type II - Chlorosulphonated polyethylene coated

2. APPLICABLE DOCUMENTS

* 2.1 Government documents. Unless otherwise specified, the following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this document to the extent specified herein:

SPECIFICATION

FEDERAL

PPP-P-1136 - Packaging and Packing of Coated (Plastic; Rubber) and Laminated Fabrics

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: US Army Natick Research and Development Laboratories, Natick, MA 01760 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 8305

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

STANDARDS

FEDERAL

FED-STD-191 - Textile Test Methods
FED-STD-406 - Plastics; Methods of Testing
FED-STD-595 - Colors
FED-STD-601 - Rubber; Sampling and Testing

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-1487 - Glossary of Cloth Coating Imperfections

(Copies of documents required by manufacturers in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

* 2.2 Other publications. Unless otherwise specified, the following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this document to the extent specified herein.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 1424 - Tear Resistance of Woven Fabrics by Falling-Pendulum (Elmendorf) Apparatus

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Technical society and technical association documents are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

* 2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document shall take precedence.

3. REQUIREMENTS

* 3.1 Standard sample. The coated cloth shall match the standard sample for shade and shall be equal to or better than the standard sample with respect to all characteristics for which the standard sample is referenced (see 6.3).

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

3.2 Materials (see 6.5).

* 3.2.1 Base cloth. The base cloth shall be woven from bright high tenacity filament nylon and shall conform to the requirements of table I when tested as specified in 4.2.1.

*TABLE I. Physical requirements of base cloth

Characteristic	Requirement
Weight, ounces per square yard	2.3 ± 0.2
Weave	Plain
Color	Natural
Yarns per inch (minimum)	
Warp	38
Filling	38
Breaking strength, pounds (minimum)	
Warp	115
Filling	115

3.2.2 Coating compound (see 4.2.1).

3.2.2.1 Type I. The coating compound for type I shall be chloroprene rubber compounded and plasticized only with phthalate or phosphate ester plasticizers. The color of the coating compound shall be either natural or grey shade No. 36118 of FED-STD-595.

3.2.2.2 Type II. The coating compound shall be chlorosulphonated polyethylene compounded and plasticized only with phthalate or phosphate ester plasticizers and pigmented to match white color No. 37875 of FED-STD-595.

* 3.2.3 Dusting powder. The dusting powder shall be whiting, talc or other finely divided mineral material which does not support mildew growth (see 4.2.1).

3.3 Coated cloth.

3.3.1 Type I. The cloth shall be coated on one side only with the compound specified in 3.2.2.1, shall be fully vulcanized and shall conform to the requirements specified in table II when tested as specified in 4.2.3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

3.3.2 Type II. The cloth shall be coated on one side only with the compound specified in 3.2.2.2, shall be fully vulcanized and shall conform to the requirements specified in table II when tested as specified in 4.2.3.

*TABLE II. Physical requirements of coated cloth

Characteristic	Type I		Type II	
	Minimum	Maximum	Minimum	Maximum
Weight, ounces per square yard	6.6	7.3	3.05	3.55
Breaking strength, pounds:				
Initial:				
Warp	120	—	120	—
Filling	100	—	100	—
After oven aging:				
Warp	120	—	—	—
Filling	100	—	—	—
After accelerated weathering:				
Warp	120	—	96	—
Filling	100	—	80	—
Tearing strength, grams:				
Warp	2500	—	2300	—
Filling	2000	—	2000	—
Blocking, scale rating	—	(2)	—	(3)
Adhesion, pounds per 2-inch width	10.0	—	10.0	—
Stiffness, centimeters:				
At 70° ± 2°F	—	9	—	13.0
At minus 40° + 2°F	—	11	—	20.0
Resistance to low temperature	1/	—	—	—
Resistance to oven aging	2/	—	2/	—
Resistance to accelerated weathering	—	—	3/	—
Air retention	4/	—	—	—

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

*TABLE II. Physical requirements of coated cloth (cont'd)

Characteristic	Type I		Type II	
	Minimum	Maximum	Minimum	Maximum
Flame resistance:				
After flame, seconds				
Warp	--	3.0	--	--
Filling	--	3.0	--	--
Char length, inches				
Warp	--	4.5	--	--
Filling	--	4.5	--	--
Adherability	5/	--	--	--

1/ There shall be no evidence of cracking, flaking or separation of the coating on the specimen.

2/ The specimen shall not become stiff or brittle or soft or tacky when compared to unexposed specimens selected from the same sample unit.

3/ The coated cloth shall show no cracking or crazing when folded sharply on itself; and when inspected in the folded position, the specimen shall show no signs of blooming or chalking. In addition, after weathering the color of the coating shall not be changed.

4/ No signs of air leakage.

5/ Shall show no slippage.

3.4 Width. The minimum width of the coated cloth, without selvages, shall be as specified in the contract or purchase order (see 6.2). All selvages shall be trimmed from the coated cloth.

* 3.5 Length and put-up. The coated cloth shall be put up in rolls as specified in PPP-P-1136 in the lengths specified below for the applicable type. No individual roll shall contain more than three pieces and no individual piece shall be less than 6 yards in length. The ends of the pieces shall be overlapped and not joined by a seam.

Type	Linear yards	
	Minimum	Maximum
I	110	135
II	250	275

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

3.6 Color. The coated side of the cloth shall be natural or match the applicable color number of FED-STD-595 (see 3.2.2).

* 3.6.1 Matching. The color and shade of the finished coated side of the cloth shall match the standard sample (see 6.3) under artificial daylight having a color temperature of 7000 ± 500 kelvins and shall be a good approximation to the standard sample under incandescent lamplight at 2850 ± 100 kelvins. Specimens dusted with mineral powder shall be wiped with a wet cloth and allowed to dry before color matching.

* 3.7 Odor. The coated cloth shall be free from any objectionable odor. Characteristic odor of coating is not considered objectionable.

3.8 Workmanship. The finished coated cloth shall be clean, evenly coated, shall have no strike through of the coating to the back of the cloth and shall conform to the quality of product established by this document. The occurrence of defects shall not exceed the applicable acceptable quality levels.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the document where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

* 4.2 Quality conformance inspection. Unless otherwise specified, sampling for inspection shall be performed in accordance with MIL-STD-105.

* 4.2.1 Component and material inspection. In accordance with 4.1, components and materials shall be inspected in accordance with all the requirements of referenced documents unless otherwise excluded, amended, modified, or qualified in this document or applicable purchase documents. In addition, testing shall be performed for the characteristics specified in table III. All test reports shall contain the individual values used in expressing the final results. The sample unit for the base cloth shall be 1 yard full width. The lot size shall be expressed in units of 1 yard and the sample size shall be as specified below. The lot shall be unacceptable if one or more sample units fail to meet any requirement specified.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

Lot size (yards)	Sample size (number of sample units)
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

TABLE III. Component tests

Characteristic	Requirement reference	FED-STD-191 test method
Base cloth:		
Material identification	3.2.1	1/
Weight, oz./sq. yd.	3.2.1	5041
Weave	3.2.1	Visual
Color	3.2.1	Visual
Yarns per inch	3.2.1	5050
Breaking strength	3.2.1	5100
Coating compound	3.2.2	2/
Dusting powder	3.2.3	3/

1/ Unless otherwise specified, a certificate of compliance shall be submitted and will be acceptable for the stated requirement.

2/ A certificate of compliance shall be furnished with each shipment or lot specifying the following:

(a) Type I coating is compounded as specified in 3.2.2.1.
(b) Type II coating is compounded as specified in 3.2.2.2.

3/ A certificate of compliance shall be furnished with each shipment or lot specifying that the dusting powder is a mineral material that does not support mildew growth.

4.2.2 End item examination.

* 4.2.2.1 Yard-by-yard examination. The coated cloth shall be examined for the defects listed below. The required yardage of each roll in the sample shall be examined on the coated side only. The same yardage shall be given a through-light inspection for pinholes and thinly coated areas. The through-lighting inspection shall be performed in accordance with MIL-STD-1487. The defects found shall be counted regardless of their proximity to each other, except where two or more defects represent a single local condition of the cloth, in which case only the more serious defect shall be counted. A continuous defect shall be counted as one defect

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

for each warpwise yard or fraction thereof in which it occurs. The lot size shall be expressed in units of yards. The sample unit shall be 1 linear yard. The inspection level shall be II and the acceptable quality level (AQL), expressed in terms of defects per hundred units, shall be 4.0 for major defects and 10.0 for total (major and minor combined) defects. The number of rolls from which the sample is to be selected shall be in accordance with table IV. An approximately equal number of yards shall be examined in each roll sampled.

Defect	Classification Major	Minor
Any cut, hole, tear, scratch, or abrasion mark that results in baring the base cloth	X	
Any pinhole	X	
Any surface scratch or abrasion mark that does not result in baring the base cloth		X
Any uncoated area	X	
Any pit, blister, tunnel, or delamination of coating	X	
Any lump or heavily coated area		X
Any crease or wrinkle resulting in doubling or adhesion of surfaces that cannot be corrected by manual pressure	X	
Uneven coating, thin area where coating is missing or noticeably thinner	X	
Any light area or window (resulting from improper distribution of pigment)		X
Any foreign matter, which on removal leaves an uncoated or poorly coated area	X	
Any foreign matter resulting in unsightly appearance		X
Edges not straight and uniform		X
Edges heavily beaded, cannot be rolled in uniform layers		X
Cloth edges rolled, curled, folded, doubled, scalloped or wavy precluding a flat lay of the cloth	X	
Any spot, stain, or streak more than 1 inch in combined direction 1/	X	
Width less than minimum specified	X	
Any objectionable odor 2/		X
Color not as specified, off shade, uneven, mottled, or spotted		X
Any tackiness (coating will adhere and not unroll readily)	X	
Not clean		X

1/ Clearly visible at normal inspection distance (approximately 3 feet).

2/ Odors of chemicals commonly used in coating compounds shall not be regarded as objectionable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

TABLE IV. Sample size and acceptance criteria

Lot size (yards)	Sample size (rolls)	Maximum number of defects acceptable in sample 2/
Up to 1200 inclusive 1/	3	0
1201 up to and including 3200	5	0
3201 up to and including 10,000	8	0
10,001 up to and including 35,000	13	0
35,001 up to and including 150,000	20	1
150,001 and over	32	2

1/ If a lot contains fewer than three rolls, each roll in the lot shall be examined.

2/ Applicable to length examination only (see 4.2.2.2.1).

4.2.2.2 Length examination.

* 4.2.2.2.1 Examination for length in individual roll. Each roll selected for yard-by-yard examination shall be examined for the defects listed below. If the total number of defects in the sample rolls exceed the maximum number specified in table IV, the lot shall be rejected.

Any roll with a total length less than the minimum or more than the maximum specified
Any roll containing more than three pieces
Any piece in roll less than 6 yards in length
Ends of pieces in roll not overlapped, but joined by a seam
Any roll with a total length more than 2 yards less than that marked on ticket

4.2.2.2.2 Total yardage in sample. The rolls examined shall be those selected for examination of individual rolls as specified in 4.2.2.2.1. The lot shall be unacceptable if the total of the actual gross lengths of the rolls in the sample is less than the total of the gross lengths marked on the roll tickets.

* 4.2.3 End item testing. The coated cloth shall be tested for the characteristics listed in table V. The methods of testing specified in FED-STD-191, whenever applicable and as listed in table V, shall be followed. The physical values specified in section 3 apply to the average of determinations made on a sample unit for test purposes as specified in the applicable test method. The sample unit shall be 5 continuous yards full width of the coated cloth. The lot size shall be expressed in units of 1 linear yard and the sample size (number of sample units) shall be as specified below. The lot shall be unacceptable if any sample unit fails to meet any requirement specified. All test reports shall contain the individual values used in expressing the final results.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

Lot size (yards)	Sample size (number of sample units)
800 or less	2
801 to 22,000	3
22,001 and over	5

4.2.3.1 Standard test conditions. Results of physical tests obtained under testing conditions defined in FED-STD-191, FED-STD-406, or FED-STD-601 will be acceptable except in cases of dispute. In dispute cases, tests shall be conducted with both the specimen and test apparatus under standard conditions as defined in FED-STD-191.

*TABLE V. End item tests

Characteristic	Applicable to Types:	Requirement paragraph	Test method
Weight, oz./sq. yd.	I and II	3.3.1 and 3.3.2	5041
Breaking strength:			
Initial	I and II	3.3.1 and 3.3.2	5102
After oven aging	I	3.3.1	5850 1/ and 5102
After accelerated weathering	I and II	3.3.1 and 3.3.2	5804 2/ and 5102
Tearing strength	I and II	3.3.1 and 3.3.2	ASTM D 1424
Blocking	I and II	3.3.1 and 3.3.2	5872
Adhesion of coating	I and II	3.3.1 and 3.3.2	5970
Stiffness 3/:			
At 70°F	I and II	3.3.1 and 3.3.2	5204
At minus 40°F	I and II	3.3.1 and 3.3.2	5204
Resistance to low temperature	I	3.3.1	4.3.1
Resistance to oven aging	I and II	3.3.2	5850 1/
Resistance to accelerated weathering	II	3.3.2	5804 2/
Air retention	I	3.3.1	4.3.2
Flame resistance	I	3.3.1	5903
Adherability	I	3.3.1	4.3.3

1/ Expose for 96 hours at 158° ± 2°F.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

2/ Expose for 24 hours with the coated side exposed to the light source.

3/ The specimens and test equipment shall be conditioned at the specified temperature for a minimum of 4 hours before testing and tests shall be conducted in still air.

* 4.2.4 Preparation for delivery inspection. The inspection shall be in accordance with the quality assurance provisions of PPP-P-1136.

4.3 Methods of inspection.

4.3.1 Resistance to low temperature. After exposure for 4 hours at a temperature of -40° ± 2°F and while still at that temperature, the coated cloth shall be subjected to the test described in Method 5874 of FED-STD-191 except that the determination of hydrostatic resistance is not required under this test.

4.3.2 Air retention. Three specimens (13 inches in diameter) of the coated cloth shall be individually tested on the test jig as shown in figure 1. The specimen shall be placed, coated side down, on the holder and the plate collar tightly bolted thereon. Care should be taken to insure a leak-tight fit. Water shall be poured on top of the specimen, sufficient to keep the top of the specimen completely covered at all levels of pressure. The specimen shall be inflated to an air pressure of 10 psi for 5 minutes. The air bubbles on the cloth surface produced by air pressure closing the spaces between the cloth and coating shall be removed. Any sign of leakage as evidenced by continued production of air bubbles shall be considered a test failure.

4.3.3 Adherability of coated cloth.

4.3.3.1 Preparation of lap seam. Two rectangular swatches of coated cloth 8 inches by 10 inches each, shall be cut, with the shorter dimension parallel to the warp. The two swatches shall be joined by cementing to form a lap seam wherein the chloroprene coated side of one swatch shall be adhered to the uncoated side of the other swatch. The seam shall be made by overlapping the 8-inch sides a distance of 2 inches. The coated area to be cemented shall be thoroughly abraded using 80-grit carborundum cloth, then washed with a toluol-wetted, clean cotton cloth. The cleaned surfaces shall be allowed to dry for 10 to 15 minutes at room temperature. Two coats of two-part neoprene cement Bostick 1039/Boscodur 5 (16 to 1 ratio by volume) (see 6.4), shall be applied to each of the prepared surfaces. The first coat on each surface shall be allowed to dry for 15 minutes. Five minutes after the application of the second coat, assemble the two swatches and roll down the seam with a steel hand roller. The sample seam shall be allowed to cure at room temperature for seven days prior to testing.

4.3.3.2 Test specimens. One-inch wide strips shall be cut from the sample lap seam prepared as specified in 4.3.3.1. The strips shall be cut with their long dimension perpendicular to the seam.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

4.3.3.3 Apparatus. Apparatus shall consist of the following: Grip clamps for anchoring and for load-application of a type which shall preclude failure of the specimens at or in the grips and which shall hold the specimens uniformly across the 1-inch dimension.

* 4.3.3.4 Procedure. One end of the specimen shall be anchored in a clamp and a load of 40 pounds shall be applied at the other end for 4 hours at 65 percent ± 2 percent relative humidity at a temperature of 70°F ± 2°F. The anchoring and load-application clamps shall be applied to the specimen not closer than 2 inches from the lap seam and the load shall be applied uniformly and without twist. Gage marks should be made at the lap seam to assist in determining slippage. At the end of the test period, the tension shall be removed from the specimen, and the specimen examined. Any evidence of slippage in the cemented seam area shall be considered as a test failure.

5. PREPARATION FOR DELIVERY

5.1 Put-up and packaging. Put-up and packaging shall be level A or C as specified (see 6.2).

5.1.1 Level A and C. The coated cloth shall be put-up and packaged in accordance with the applicable requirements of PPP-P-1136.

5.2 Packing. Packing shall be level A, B or C as specified (see 6.2).

5.2.1 Levels A, B, and C. The coated cloth shall be packed in accordance with the applicable requirements of PPP-P-1136.

5.3 Marking. In addition to any special marking required by the contract or purchase order, shipments shall be marked in accordance with the requirements of PPP-P-1136.

6. NOTES

6.1 Intended use. The coated cloth covered by this document is intended for use in the manufacture of air supported shelter tents.

* 6.2 Ordering data. Acquisition documents should specify the following:

(a) Title, number and date of this document.
(b) Type of cloth required (see 1.2).
(c) Width of cloth required (see 3.4).
(d) Selection of the applicable levels of put-up, packaging and packing (see 5.1 and 5.2).

6.3 Standard sample. For access to standard samples, address the contracting activity (see 3.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

6.4 Adhesive source. Bostik 1039/Boscodur 5 (16 to 1 ratio by volume), may be obtained from USM Corporation, Chemicals Division, Middleton, MA 01949.

* 6.5 Recycled material. It is encouraged that recycled material be used when practical as long as it meets the requirements of the document (see 3.2).

* 6.6 Changes from previous issue. The margins of this document are marked with an asterisk to indicate where changes (additions, modifications, corrections, deletions) from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the previous issue.

Custodian:

Army - GL

Review activities:


Army - MD
DLA - CT

Preparing activity:

Army - GL

Project No. 8305-A370

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

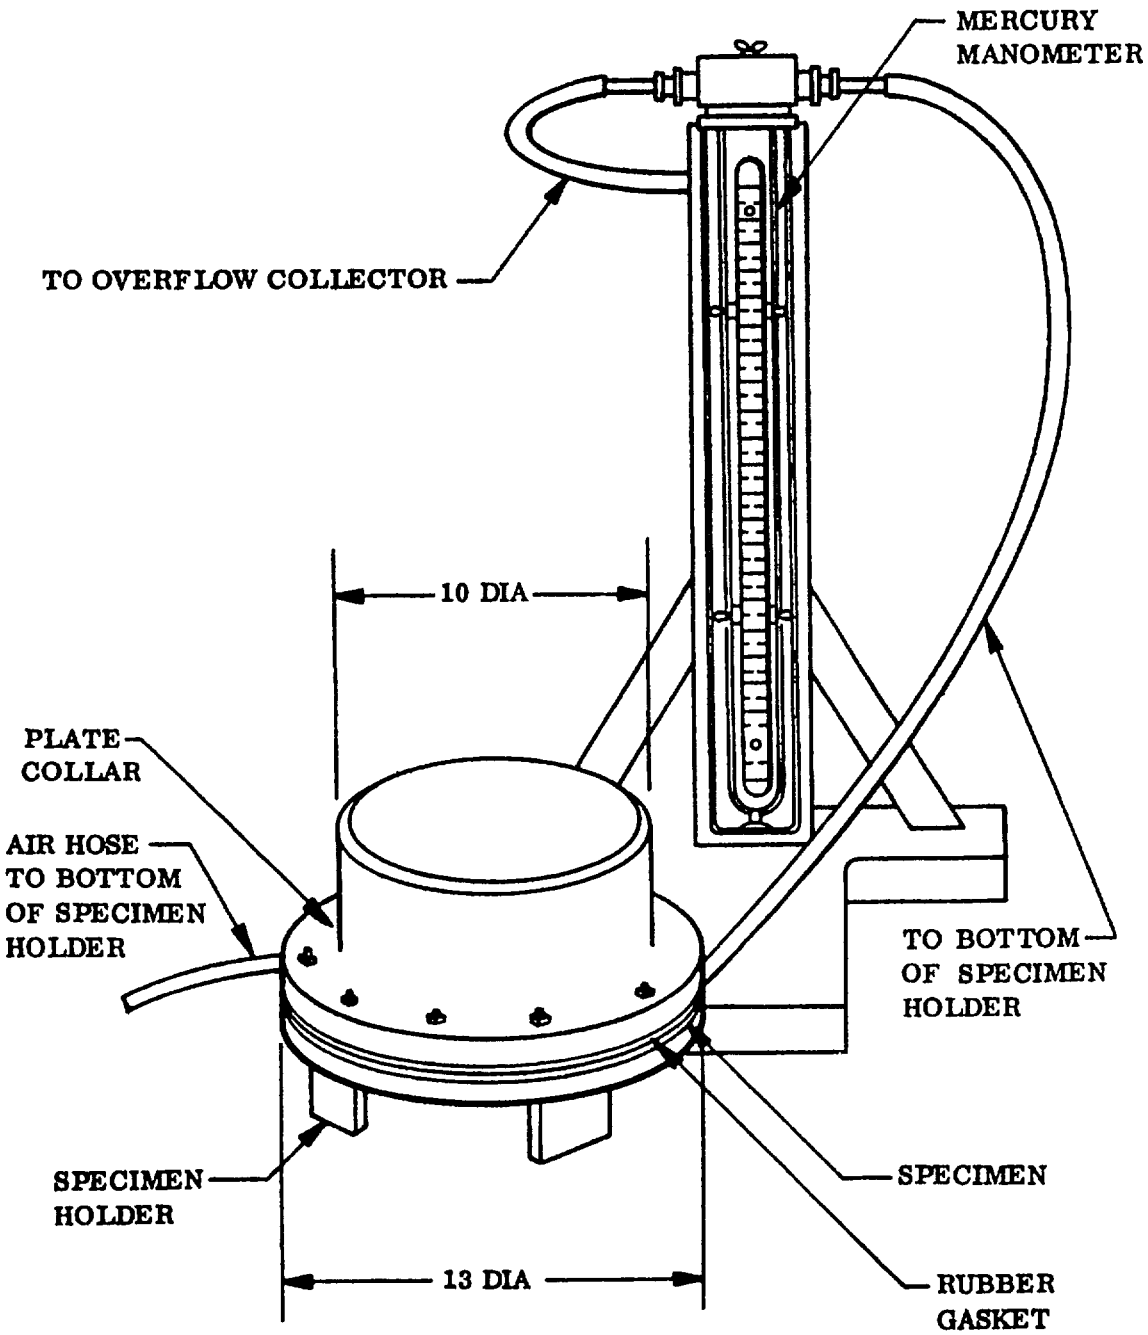

DIMENSIONS IN INCHES

FIGURE 1. AIR LEAKAGE TEST JIG

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY
US Army Natick Research and Development Laboratories
Natick, Massachusetts 01760

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300
DRDNA-ES

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Natick Research and Development Laboratories
ATTN: DRDNA-ES
Natick, MA 01760

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-C-43808A(GL)	Cloth, Coated, Nylon

3a. NAME OF SUBMITTING ORGANIZATION

b. ADDRESS *(Street, City, State, ZIP Code)*

4. TYPE OF ORGANIZATION *(Mark one)*

- ☐ VENDOR
- ☐ USER
- ☐ MANUFACTURER
- ☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

NATICK OP, 1 APR 83

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:24Z
Check the source to verify that this is the current version before use.