TT-P-54C
March 27, 1973
SUPERSEDING
Int. Fed. Spec. TT-P-0054B(GSA-FSS)
May 16, 1967 and
Fed. Spec. TT-P-54A
October 9, 1956

FEDERAL SPECIFICATION

PAINT, PHOSPHORESCENT, READY-MIXED (NON-RADIOACTIVE)

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. Phosphorescent paint covered by this specification is non-radioactive and is in ready-mixed form (see 3.2.1 for definition of phosphorescent paint).

1.2 Types. Ready-mixed phosphorescent paint shall be of the following types, as specified (see 6.2):

Type I - High-initial-brightness; short afterglow.
II - Low-initial-brightness; long afterglow.

2. APPLICABLE DOCUMENTS

2.1 The following documents, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Specifications:

TT-E-543 - Enamel-Undercoat, Interior, Tints and White.
TT-P-143 - Paint, Varnish, Lacquer and Related Materials; Packaging, Packing and Marking of.
TT-S-179 - Sealer Surface: Pigmented Oil, Plaster and Wallboard.
TT-V-109 - Varnish, Spar, Alkyd-Resin.
LLL-B-1188 - Building Board, Hard Pressed Vegetable Fiber(Laminated).
PPP-C-96 - Cans, Metal, 28 Gage and Lighter.

Federal Standard:

Fed. Test Method Std. No. 141/GEN - Paint, Varnish, Lacquer, and Related Materials; Methods of Inspection, Sampling, and Testing.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.

(Single copies of this specification and other Federal Specifications required by activities outside the Federal Government for bidding purposes are available without charge from Business Service Centers at the General Services Administration Regional Offices in Boston, New York, Washington, DC, Atlanta, Chicago, Kansas City, MO, Fort Worth, Denver, San Francisco, Los Angeles, and Seattle, WA.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

(Copies of Military Specifications and Standards required by contractors in connection with specification porcurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

FSC 8010

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:14Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 Materials. The manufacturer is given wide latitude in the selection of raw materials and process of manufacture, provided that the paint supplied meets all the requirements of this specification. Materials shall be of the best quality used in good commercial practice and entirely suitable for the purpose intended under normal condition of use. The paint shall be phosphorescent, ready-mixed, and the applied paint shall produce a smooth dried film completely hide the substrate. The solvents or solvent system used in the process shall comply with Air Pollution Regulations "Rule 66" 1/. A certificate of compliance to this effect is necessary.

3.2 Definitions.

3.2.1 Phosphorescent paint. Non-radioactive phosphorescent paint is defined as a paint which, after exposure to a source of radiant energy, either visible or invisible, will continue to emit energy in the visible spectral range for an appreciable period of time after excitation of the paint has ceased.

3.2.1.1 High-initial-brightness phosphorescent paint. High-initial-brightness phophorescent paint is defined as phosphorescent paint which has a comparatively high brightness for a relatively short period (approximately 30 minutes) after excitation has ceased. High initial brightness ordinarily is obtainable only in combination with a rapid rate of brightness decay, which results in reduction of the absolute brightness below useful levels within about an hour. Accordingly, this type is most suitable for applications requiring a high brightness for a short time; i.e., where it is necessary to observe the paint before the observer can become completely dark adapted, but not longer than one hour (see 6.1 and table I).

3.2.1.2 Low-initial-brightness phosphorescent paint. Low-initial-brightness phosphorescent paint is defined as phosphorescent paint which has a useful afterglow lasting several hours. It has a lower initial brightness and longer effective afterglow than high-initial-brightness paint and thus is suitable for most general applications (see 6.1 and table I).

TABLE I.

Type	Effective microlamberts at specified interval after end of activation					
	2 minutes	1 hour	2 hours	4 hours	6 hours	24 hours
I	10	0.25	--	--	--	--
II	--	0.8	0.4	0.18	0.12	0.03

3.2.2 Dark adaptation. Dark adaptation refers to the increase in degree of sensitivity of the eyes which occurs in darkness. An observer, in a place which is suddenly darkened, at first is unable to see anything. The human eye under such conditions gradually becomes more sensitive, so that sight may be restored after a period of dark adaptation. Complete dark adaptation of a daylight-adapted eye requires an extended period of time (one-half to three-fourths of an hour) which cannot be shortened (see 6.4).

3.2.3 Effective microlambert. The unit of brightness used in this specification is an "effective microlambert" which is defined in terms of the brightness of a white diffusing surface illuminated by an incandescent-filament source of color temperature 2360°K. (see 4.4.3.3.2).

3.3 Requirements.

3.3.1 Condition in container. The paint when tested as in 4.4.1 shall be free from grit, skins, lumps, abnormal thickening or livering and shall show no more pigment settling or caking than can be readily reincorporated to a homogeneous state.

3.3.2 Storage stability.

3.3.2.1 Partially full container. The paint shall show no skinning when tested as in 4.4.2.1. After aging as in 4.4.2.1, the paint shall show no livering, curdling, hard caking or gummy sediment. It shall mix readily to a smooth homogeneous state.

3.3.2.2 Full container. When tested as in 4.4.2.2 the paint shall show no skinning, livering, curdling, seeding, hard dry caking or gummy sediment. The paint shall mix readily to a smooth homogeneous state.

1/ Information of "Rule 66" may be obtained from the Air Pollution Control District, County of Los Angeles, Los Angeles, California 90013.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:14Z
Check the source to verify that this is the current version before use.

3.3.3 Brushing properties. The paint when tested as in 4.4.3 shall brush satisfactorily. The paint film shall be even and without streaks.

3.3.4 Drying time. The paint film applied in 4.4.4 shall set to touch in not less than one-half hour and not more than two hours and shall dry hard in not more than eight hours.

3.3.5 Appearance of dried film. The paint film applied in 4.4.5 shall be smooth and uniform both by reflected light and by its luminescence.

3.3.6 Phosphorescent color. Type I paint shall be green to yellow-green; type II shall be blue to blue-green when observed in dark room immediately after test paint has been activited or tested as in 4.4.6.

3.3.7 Flexibility. A film of the paint tested as in 4.4.7 shall withstand bending without cracking or flaking.

3.3.8 Phosphorescent brightness. When irradiated and measured as in 4.4.8 the photometric brightness shall be not less than the values in table I.

3.3.9 Resistance to radiant energy and moisture (type II). The paint film shall have the photometric brightness given in table I after exposure to radiant energy and moisture for 100 hours as described in 4.4.8. The exposed film (see 4.4.8) shall be uniform in appearance when examined by reflected light and by its own luminescence.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to the prescribed requirements.

4.2 Classification of inspection. Inspection shall be classified as follows:

(a) Production inspection of the paint.
(b) Inspection of preparation for delivery.

4.3 Production inspection.

4.3.1 Sampling and inspection. Sampling and inspection shall be in accordance with method 1031 of Fed. Test Method Std. No. 141.

4.4 Test procedures. The paint shall be tested in accordance with the applicable methods of Fed. Test Method Std. No. 141 as indicated in table II and as herein specified.

TABLE II. Index

Characteristics	Requirement Reference	Tests	
		Fed. Test Method Std. No. 141	Paragraph Reference
Condition in container	3.3.1	3011	4.4.1
Storage stability	3.3.2	3021, 3022	4.4.2.1
			4.4.2.2
Brushing properties	3.3.3	----	4.4.3
Drying time	3.3.4	----	4.4.4
Appearance dried film	3.3.5	----	4.4.5
Phosphorescent color	3.3.6	----	4.4.6
Flexibility	3.3.7	6221	4.4.7
Phosphorescent brightness	Table I	----	4.4.8

4.4.1 Condition in container. Determine package condition of the paint in accordance with method 3011 of Fed. Test Method Std. No. 141 and observe for compliance with 3.3.1.

4.4.2 Storage stability.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:14Z
Check the source to verify that this is the current version before use.

4.4.2.1 Partially full container. Determine skinning after 48 hours in accordance with method 3021 of Fed. Test Method Std. No. 141 except use a 3/4 filled 1/2 pint, multiple friction top can. Observe for compliance with 3.3.2.1.

4.4.2.2 Full container. In accordance with method 3022 of Fed. Test Method Std. No. 141, allow a standard quart can of paint to stand undisturbed for six months and then examine the contents. Evaluate pigment settling or caking as in 4.4.1 but agitate the can for 5 minutes on a paint shaker prior to re-examination for compliance with 3.3.2.2.

4.4.3 Brushing properties. Prime a 1-foot-square wall board panel conforming to LLL-B-1188 using a sealer surfacer conforming to TT-S-179. Let dry for 24 hours. Then apply a coat of white enamel undercoat conforming to TT-E-543 and allow to dry for 7 hours. When dry apply the phosphorescent paint evenly using 1-1/2 inch brush. While brushing observe for pull under brush. Allow the paint to dry for 24 hours then examine for compliance with 3.3.3.

4.4.4 Determine drying time of the paint when applied in 4.4.3 and observe for compliance with 3.3.4.

4.4.5 Appearance of dried film. Evaluate the paint film as prepared and tested as in 4.4.3 and observe for compliance with 3.3.5.

4.4.6 Phosphorescent color. Observe the phosphorescent color of the paint after it has been activated (see 4.4.8) for compliance with 3.3.6.

4.4.7 Flexibility. Determine flexibility in accordance with method 6221 of Fed. Test Method Std. No. 141. Apply a 2-inch wide film of paint with film applicator that will give a dry film thickness of 0.0009 to 0.0011 inch on a solvent cleaned tin panel prepared in accordance with method 2012 of Fed. Test Method Std. No. 141. Air-dry in a horizontal position for 18 hours then bake for 2 hours at 105° ± 2°C. Condition for 1/2 hour under referee conditions. Bend over 1/4-inch mandrel and examine for compliance with 3.3.7.

4.4.8 Phosphorescent brightness measurement.

4.4.8.1 Equipment.

4.4.8.1.1 Radiant energy and moisture.

Exposure apparatus shall be that meeting the requirements of either method 6151 or 6152 of Fed. Test Method Std. No. 141.

4.4.8.1.2 Excitation (activation) room and apparatus. The excitation of the test coating shall be made in a dark room, the sole illumination within which is a new 100-watt, general purpose, inside frosted, gas-filled, tungsten-filament lamp operated at its labeled voltage. The room shall be maintained at a temperature between 23° and 27°C. during the excitation and brightness measurement.

4.4.8.1.3 Photometer. A special photometer shall be employed, in which only mechanical means, that is, change of distance and diaphragms, are employed to control the brightness of the comparison field, so that no change in spectral composition is introduced. The exact details of a suitable "wide-angle" photometer are left to the choice of the maker. However, for the guidance of contractors who are interested in establishing control facilities, figure 1 is a drawing of the photometer now in use for this purpose by the National Bureau of Standards. Further details of this photometer are as follows (see also 6.5). The box in which the lamp runs on a track is about 4 inches square by 22 inches long. The brightness of the opal glass, S_1 depends upon the distance between it and the lamp, L (an automobile lamp of 32 c.p. nominal rating operated at about 3 amperes). pointer moves over a distance scale just above the rheostats and knob on the side of the photometer. The brightness of the screen S_2, depends upon the brightness of S_1. At the bottom of the tube on the left there is a swmi-circular mirror, which forms one-half of the photometric field, while a sample viewed directly forms the other half. A set of disphragms with holes having areas varying by factors of about 10 has been made and the distance can be varied enough to secure a factor of more than 15 to 1 in the square of the distance; accordingly, the instrument presents a wide range of brightness variation. In use the lamp, L, is operated at the current necessary to have the light emitted by screen, S_2, at a color temperature of 2360°K. A more detailed description is given in NBSJ, Research 34, 325 (April 1945), RP1646.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:14Z
Check the source to verify that this is the current version before use.

4.4.8.2 Preparation of test coating. Apply two brush coats of white enamel undercoat (TT-E-543) to a solvent cleaned tin panel (see method 2012 of Fed. Test Method Std. No. 141). Allow 24 hours drying time between coats. After the second coat has dried for 24 hours, apply, by brushing, spraying, or doctor blade, the phosphorescent paint to a wet film thickness of 0.009 ± 0.001 inch (equivalent to a spreading rate of 175 square feet per gallon). Allow the test coating to air dry in a horizontal position for 48 hours. For type II paint apply a clear transparent protective top-coat using material recommended by the manufacturer of the phosphorescent paint. Dry the top-coat in a horizontal position as specified by its manufacturer. In the absence of specific recommendations from the manufacturer of the phosphorescent paint, an alkyd-resin spar varnish conforming to TT-V-109 shall be used as the top-coat.

4.4.8.3 Procedure.

4.4.8.3.1 Expose the type II coating prepared as in 4.2.3.2 in one of the two machines described in 4.2.3.1.1 for 100 hours. Examine the exposed coating to determine if it meets the appearance requirements of 3.3.4.

4.4.8.3.2 Place the type II coating, after this exposure, or the type I coating, immediately after its preparation (see 4.4.3.2), in complete darkness for at least 24 hours. Now activate either the type I or type II coating, as the case may be, in the excitation room (see 4.4.3.1.2) for 100 footcandle-minutes at an illumination of 20 footcandles. Immediately after the activation of the test coating, measure its photometric brightness in "effective microlamberts" using the photometer (see 4.4.3.1.3). Take the measurements (see 3.2.3) at 2, 4, 8, 30, and 60 minutes for the type I coating and at 1, 2, 4, 6, and 24 hours for the type II coating after the end of the activation period. The measurements shall be made by an experienced observer, known to have no defects in color vision, while in a state approaching dark adaptation (see 3.2.2). Determine if these measurements meet the requirements of table I for the respective type of paint.

4.4.9 Inspection of preparation for delivery. The phosphorescent paint shall be examined for compliance with packaging, packing, and marking requirements of section 5 in accordance with TT-P-143. Any container in the sample having one or more defects or under required fill shall be rejected.

5. PREPARATION FOR DELIVERY

5.1 Packaging, packing, and marking. The paint shall be packaged, packed, and marked in accordance with TT-P-143. The level of packaging shall be A, B, or C, and the level of packing shall be A, B, or C as specified (see 6.2). The paint shall be furnished in 1/2-pint, 1-pint, or 1-quart multiple friction top cans as specified (see 6.2).

5.1.1 Direction for use. The manufacturer shall include directions for the preparation of surfaces and application.

5.2 Precautionary markings. In addition to the markings required by TT-P-143, all individual containers should have the following markings:

CAUTION: Adequate precaution should be taken when used for spraying. Avoid breathing of spray mist.

6. NOTES

6.1 Intended use. Purchasers should specify the type of paint required. Type I paint is suitable only for interior use, whereas the type II product may be used for either interior or exterior applications. In practice, the paints should be applied over a white lead-free primer or undercoater at a spreading rate of about 175 square feet per gallon. Enamel undercoat covered by TT-E-543 should be suitable for most interior and exterior uses. Alkyd-resin spar varnish covered by TT-V-109 is suggested as a suitable material for the clear protective top coat (see 4.4.3.2).

The phosphorescent paints contemplated under this specification are high-grade types designed for use as markers, indicators, etc., in non-operational military and other applications. Operational military uses are covered by MIL-L-3891, MIL-C-4996, and MIL-L-25142.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:14Z
Check the source to verify that this is the current version before use.

Phosphorescent paint in accordance with this specification also is intended for luminescent markings in interior accommodation, and working and machinery spaces of merchant vessels as required by subchapter O, title 46, Code of Federal Regulations, section 153.19. The markings applied should be sufficient in character to clearly show in darkness the positions of exit doors, ports, ladders, companionways; and the location of emergency lights, control valves, if necessary, and similar vital locations of accessories.

In selecting locations for the application of the paint it should be borne in mind that to be efficient, the paint must receive light during the daytime, or some artifical light. If one proposed location is approximately equal in value to another, the one in which the paint will receive the most reactivation by daylight or artificial illumination should be chosen. Every effort should be made to avoid placing it where it will be exposed to drip or excessive condensation, if suitable alternative locations are available.

Where some important markings are required in areas which ordinarily receive very little activating light, reactivation can be accomplished by the use of an ordinary flashlight or hand electric lantern. To accomplish this, hold the source of light a few inches from the paint surface and move slowly over the paint area. This should be repeated three or four times.

It is of interest to point out that the drak-adapted eye can detect a greenish or bluish glow more readily by peripheral vision than by direct central vision. Therefore, luminous markings will more readily be detected by observation out of the corners and sides of the eye.

6.2 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents.

(a) Title, number, and date of this specification.
(b) Selection of applicable level of packaging and packing required (See 5.1 and 5.2).
(c) Type required (see 1.2).
(d) Color of paint (see 3.3.8).

6.3 Standard Pack for civil agencies. The standard pack requirements in 5.3 are intended for use in procurements of Stores Stock replenishments. Procuring officers should use the standard pack requirements when it is known that the material will be shipped from a supplier to a domestic warehouse, supply depot or intermediate storage point for temporary storage, subsequent issue or shipment to eventual user.

6.4 Brightness. The following discussion of the consequences of the Purkinje effect 1/ in the measurement of brightness, which originally appeared in British Standard Specification BS/ARP-18, July 1940, is presented here in slightly modified form for the information and convenience of all parties concerned in the measurement of luminous paint:

6.4.1 All definitions of units of photometric brightness imply that comparisons between differently colored surfaces be made at values of brightness sufficiently high to insure that the observer's eye is in a state of light-adaptation. This is to insure that brightness values obey the additive law, by which a brightness of y units superimposed upon one of x units will provide a brightness of (x + y) units. If this law is not obeyed, the ordinary inverse square law and the rotating sector-disc ratio law may not be applied to the brightness values under consideration. If differently colored surfaces are viewed, obedience to the above-mentioned laws occurs only if and when the luminosity curve of the eye (see figure 2) is constant and independent of brightness throughout the range of brightness under consideration. Fortunately the eye in observing brightness greater than 1000 microlamberts does possess a constant luminosity curve, and so in these circumstances, when the eye is said to be light-adapted, the values of photometric brightness for differently colored surfaces not only obey the additive law, but also truly represent the apparent useful brightness.

6.4.2 Unfortunately the luminosity curve of the eye does not remain constant when the brightness of an extended surface is less than 1000 microlamberts; in fact, the eye becomes progressively relatively more sensitive to short-wave energy and less sensitive to long-wave energy as

1/ A detailed discussion of the Purkinje effect may be bound in British Standard BS/ARP-18 July 1940, and in the summary of American opinion on that specification prepared by Mr. L. A. Jones and reported to the American Standards Association under date of June 15, 1942.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:14Z
Check the source to verify that this is the current version before use.

the brightness observed is reduced from 1000 to 0.5 microlamberts, the rate of change being most pronounced between 200 and 1 microlamberts. This shift of the luminosity curve towards shorter wave lengths at low brightness is called the "Purkinje Effect". For brightness below 0.5 microlamberts, the eye has again reached a steady state, with a constant luminosity curve, and may be regarded as more or less dark adapted. In figure 2, curve A shows the luminosity curve for the light-adapted eye, and curve B that for the dark-adapted eye. As the brightness of the observed surface is diminished, the luminosity curve of the eye moves progressively from the curve A position towards the curve B position.

6.4.3 The values of brightness of phosphorescent materials fall mostly within the range in which this Purkinje change of luminosity is most pronounced. In order therefore to measure their brightness in ordinary self-consistent brightness-units that obey the additive law (such as microlamberts) which are based on curve A, it is essential that the photometric comparison should be made between surfaces that are not only color-matched but also matched with regard to their wave-length distribution of energy. This can often be done to a reasonable degree of accuracy with the aid of color filters, although the testing and selection of color filters may involve an undue expenditure of time. When this photometric procedure is followed, the method allows the brightness of a surface of any color and any brightness to be expressed in microlamberts.

6.4.4 It must be most emphatically pointed out, however, that because of the existence of the Purkinje effect, the relative values of the brightness of differently colored surfaces of low brightness expressed in microlamberts have little bearing on their relative effective brightness as directly judged by the eye; for example, suppose we compare a spectrally homogeneous orange-colored surface (wave length 615mμ), whose brightness is 1000 microlamberts, with a spectrally homogeneous blue-green surface (wave length 490mμ), also of 1000 microlamberts. (The homogeneity is introduced merely for simplicity in the argument and is of course quite unessential.) The average observer will say that these two surfaces appear equally bright. Their brightness might be presented on figure 2 by the lines AB and DE, respectively. Now let us introduce a rotating sector-disc whose transmission is 0.1 percent, between the eye of the observer and the two adjacent surfaces.

6.4.5 These facts make it plain that in order to express the relative practical usefulness of the effective brightness of luminescent materials of different colors, an entirely new type of unit is needed. Such a unit is formulated and defined in this specification. The new unit is called the "Effective Microlambert" in order to differentiate it from the commonly used units of photometric brightness such as the microlambert. The use of the new unit involves, of course, as the above example shows, the grave disadvantage of the abandonment of both the rotating sector-disc law and the inverse square law, except for the comparison source of 2360°K., but this is the price that the Purkinje effect exacts in order that the new unit should express the true subjective (effective) brightness of the luminescent surface.

6.4.6 A unit of brightness commonly used in photometric work is the microlambert, which is defined as one-millionth of brightness of a perfectly diffusing completely reflecting surface illuminated by a source or unit candlepower placed at a distance of one centimeter.

Since for brightness of the order of 1000 microlamberts or less the eye becomes progressively more sensitive to short-wave energy relative to the long, the objective evaluation of differently colored luminescent materials on the basis of their brightness in microlamberts, as above defined, does not usually give a true measure of their relative practical usefulness.

6.4.7 A photometric brightness of one effective microlambert can just be perceived by an observer practically immediately after he has been plunged from daylight into darkness, provided a sufficiently large area is viewed.

NOTE: The use of this unit (effective microlambert) is to be strictly confined to the statement of the final brightness as evaluated by the eye. This unit is not to be used as a basis of calculation for candlepower, flux or illumination, or applied to any other photometric calculation.

6.5 Manufacturers who wish to make measurements with pohotometric equipment on hand should make up a "standard sample" of their product. This sample may be made by placing a piece of their luminescent material between lantern-slide cover glass and sealing the edges with

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:14Z
Check the source to verify that this is the current version before use.

lantern-slide binding tape. Such samples can be calibrated by the National Bureau of Standards and should be rechecked at frequent intervals, at least three times a year. These samples will enable testing laboratories to employ color-matching filters on the comparison side of their photometer so that the routine testing may be done by observers who are comparatively inexperienced in low-brightness measurements with greater certainty that would be possible with a difference in color existing between the fields being compared.

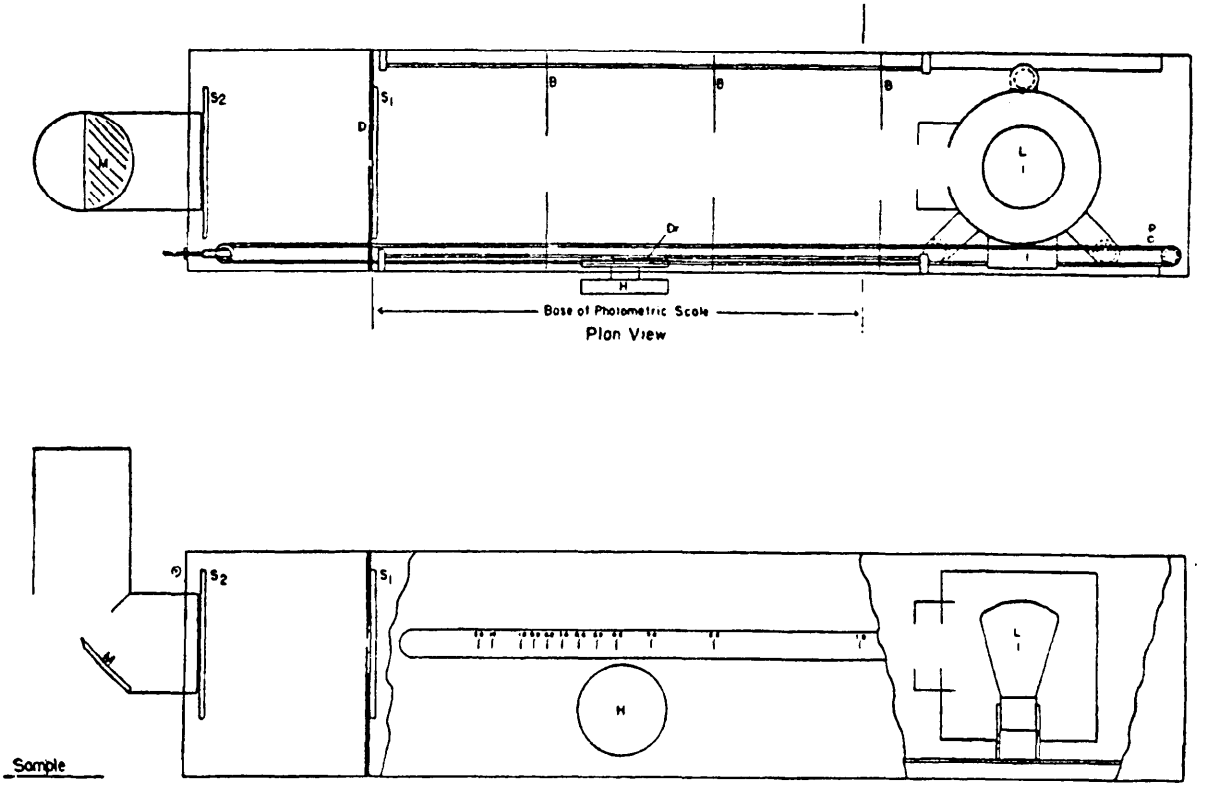


FIGURE 1.—Photometer

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:14Z
Check the source to verify that this is the current version before use.

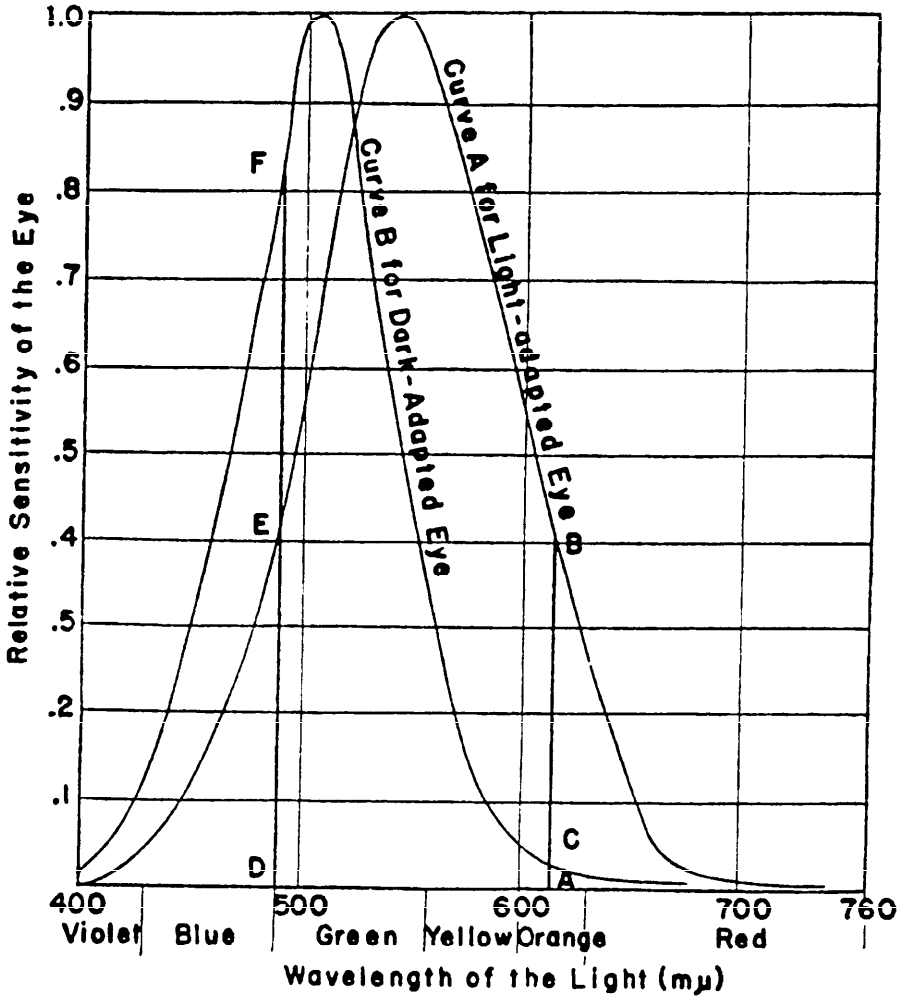


FIGURE 2.—Luminosity curves.

Military Coordinating Activity:

Navy - CG

CIVIL AGENCIES COORDINATING ACTIVITIES:
GSA - PSS, PBO
DOT - RDS, SMS
HUD - HHE
HEW - NIH
VA - DMS
COMMERCE - NBS
DC GOVT - DGS
INTERIOR - BOR
POSTAL - POS

Preparing activity:

GSA-FSS

Orders for this publication are to be placed with General Services Administration, acting as an agent for the Superintendent of Documents. See section 2 of this specification to obtain extra copies and other documents referenced herein. Price 15 cents each.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:14Z
Check the source to verify that this is the current version before use.