The documentation and process conversion measures necessary to comply with this revision shall be completed by 30 June 2003.

INCH-POUND

MIL-PRF-19500/590E
30 December 2002
SUPERSEDING
MIL-PRF-19500/590D
8 April 2002

PERFORMANCE SPECIFICATION

SEMICONDUCTOR DEVICE, DIODE, SILICON, ULTRAFAST RECOVERY, POWER RECTIFIER
1N6626 THROUGH 1N6631, 1N6626U THROUGH 1N6631U, 1N6626US THROUGH 1N6631US
JAN, JANTX, JANTXV, AND JANS

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for a silicon, ultrafast recovery semiconductor rectifier diodes. Four levels of product assurance are provided for each device type as specified in MIL-PRF-19500.

1.2 Physical dimensions. See figures 1 (similar to D0-41) and 2 (surface mount).

*1.3 Maximum ratings. Unless otherwise specified, T_A = +25°C.

*1.3.1 Ratings applicable to all part or identifying numbers (PIN). T_{STG} = T_J = -65°C to +175°C.

*1.3.2 Ratings applicable to individual types.

Col. 1	Col. 2	Col. 3	* Col. 4	Col. 5	Col. 6	Col. 7	* Col. 8	Col. 9	Col. 10
Types	V_{RWM}	$I_{F(AV)1}$ at T_{L} = +75°C L = .375 inch (9.52 mm) (1) (2) (3)	I_O $I_{F(AV)2}$ (1) (4) (5)	I_{FSM} at t_p = 8.3 ms	Barometric pressure	t_{rr1} (6)	$R_{\theta JL}$ at L = .375 (9.52 mm)	$R_{\theta JEC}$ at L = 0 (0.00 mm)	$Z_{\theta JX}$
	V dc	A	A dc	A(pk)	mm Hg	ns	°C/W	°C/W	°C/W
1N6626, U, US	200	4.0	2.0	75	8	30	22	10	1.5
1N6627, U, US	400	4.0	2.0	75	8	30	22	10	1.5
1N6628, U, US	600	4.0	2.0	75	8	30	22	10	1.5
1N6629, U, US	800	3.0	1.4	75	33	50	22	10	1.5
1N6630, U, US	900	3.0	1.4	75	33	50	22	10	1.5
1N6631, U, US	1,000	2.0	1.4	60	33	60	22	10	1.5

See notes on next page.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Defense Supply Center, Columbus, ATTN: DSCC-VAC, P.O. Box 3990, Columbus, OH 43216-5000, by using the Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 5961
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

* 1.3 Maximum ratings - Continued.

(1) Average current with a half sine wave including reverse voltage amplitude equal to the magnitude of full rated $V_{RWM.}$
(2) Derate linearly at 1.0 percent/°C for T_L > +75°C.
(3) These rated currents apply to U or US suffix types when the maximum temperature of the end caps (mounting surface) is +110 °C; derate at 1.5 percent/°C above T_{EC} > +110°C.
(4) Derate linearly at 0.67 percent/°C for T_A greater than + 25°C.
(5) This I_O rating is typical for PC boards where thermal resistance from mounting point to ambient is sufficiently controlled where $T_{J(max)}$in paragraph 1.3 is not exceeded.
(6) The reverse recovery time, method 4031 of MIL-STD-750 condition B, T_J = +125°C shall not exceed three times the +25°C limit.


1.4 Primary electrical characteristics. Unless otherwise noted, T_A = + 25°C.

Col. 11	Col. 12	Col. 13	Col. 14	Col. 15	Col. 16	Col. 17
Types	I_{R1} at T_J = +25°C	I_{R2} at T_J = +150°C	$I_{RM(REC)}$ at 2 A, 100A/µs	C_T at V_R = +10 V	V_{FM1} at I_F = (col. 3 of 1.3)	V_{FM2} at I_F = (col. 4 of 1.3)
	µA	µA	A pk	pF	V	V
1N6626, U, US	2.0	500	3.5	40	1.5	1.35
1N6627, U, US	2.0	500	3.5	40	1.5	1.35
1N6628, U, US	2.0	500	3.5	40	1.5	1.35
1N6629, U, US	2.0	500	4.2	40	1.7	1.40
1N6630, U, US	2.0	500	4.2	40	1.7	1.40
1N6631, U, US	4.0	600	5.0	40	1.95	1.60

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in sections 3 and 4 of this specification, whether or not they are listed.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

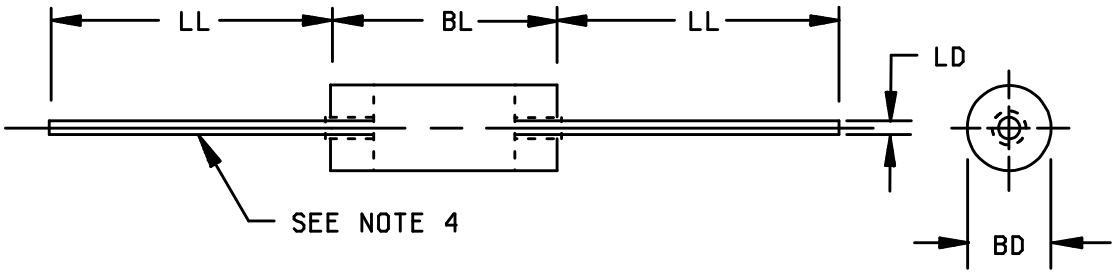


Ltr	Dimensions				
	Inches		Millimeters		
	Min	Max	Min	Max	Notes
BD	.115	.137	2.92	3.50	4
BL	.130	.300	3.30	7.62	3
LD	.037	.042	0.94	1.07	3
LL	.900	1.300	22.86	33.02	

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. Dimension BL shall include the sections of the lead over which the diameter is uncontrolled. This uncontrolled area is defined as the zone between the edge of the diode body and extending .050 inch (1.27 mm) onto the leads.
4. Dimension BD shall be measured at the largest diameter.
5. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 1. Physical dimensions (similar to D0-41).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

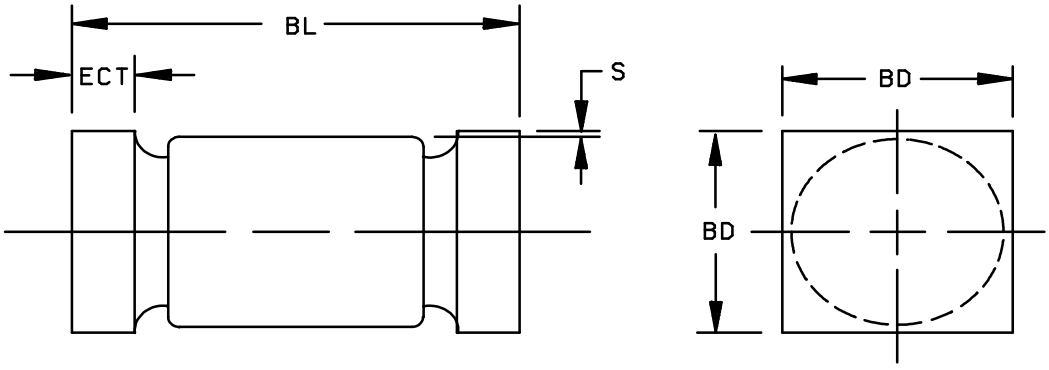

Dimensions				
Ltr	1N6626U, US through 1N6631U, US			
	Inches		Millimeters	
	Min	Max	Min	Max
BL	.200	.225	5.08	5.72
BD	.137	.148	3.48	3.76
ECT	.019	.028	0.48	0.71
S	.003		0.08	

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 2. Physical dimension of surface mount.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATION

DEPARTMENT OF DEFENSE

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

STANDARD

DEPARTMENT OF DEFENSE

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Unless otherwise indicated, copies of the above specifications, standards, and handbooks are available from the Document Automation and Production Services (DAPS), Building 4D (DPM-DODSSP), 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

* 3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturer's list (QML) before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500 and as follows:

$I_{RM(REC)}$ ..... Peak reverse recovery current.
T_{CVF} ..... Temperature coefficient of forward voltage.
V_{FRM} ..... Forward recovery voltage.
* EC ..... End cap.

3.4 Interface and physical dimensions. The interface and physical dimensions shall be as specified in MIL-PRF-19500 and on figures 1 (similar to D0-41) and 2 (surface mount) herein.

3.4.1 Diode construction. These devices shall be constructed utilizing non-cavity double plug construction with high temperature metallurgical bonding between both sides of the silicon die and terminal pins (see MIL-PRF-19500). Metallurgical bond shall be in accordance with the requirements of category I in MIL-PRF-19500. U and US version devices shall be structurally identical to the non-surface mount devices except for lead terminations. The US version shall be structurally identical to the U version.

* 3.4.2 Lead finish. Unless otherwise specified, lead or end cap finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750, and herein. When solder alloy is used for finish the maximum lead temperature is limited to 175°C maximum. Where a choice of finish is desired, it shall be specified in the acquisition document (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

3.5 Marking. Marking shall be in accordance with MIL-PRF-19500.

3.5.1 Marking for U and US devices. For U and US version devices only, all marking may be omitted from the device except for the cathode marking. All marking which is omitted from the body of the device shall appear on the label of the initial container.

3.6 Polarity. The polarity of all types shall be indicated with a contrasting color band to denote the cathode end. Alternatively, for U and US suffix devices, a minimum of three contrasting color dots spaced around the periphery on the cathode end of the device may be used.

3.7 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I herein.

3.8 Electrical test requirements. The electrical test requirements shall be the subgroups specified in table I, group A herein.

3.9 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified.herein.

4.2.1 Group E qualification. Group E qualification shall be performed herein for qualification or requalification only. In case qualification was awarded to a prior revision of the associated specification that did not request the performance of table II tests, the tests specified in table II herein shall be performed by the first inspection lot to this revision to maintain qualification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

4.3 Screening (JANS, JANTX, and JANTXV levels). Screening shall be in accordance with table IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table IV of MIL-PRF-19500)	Measurement	
	JANS Level	JANTXV and JANTX Level
1a	Required	Not required
1b	Required	Required (JANTXV only)
2	Optional	Optional
3a (1) 3c	Required Thermal impedance (see 4.3.2)	Required Thermal impedance (see 4.3.2)
4	Not applicable	Not applicable
5	Not applicable	Not applicable
6	Not applicable	Not applicable
7a	Not applicable	Not applicable
7b	Required	Required
8	Required	Not required
9	Required I_{R1} and V_{FM1}	Not required
10	Method 1038 of MIL-STD-750, condition A	Method 1038 of MIL-STD-750, condition A
11	I_{R1} and V_{FM1}, ΔI_{R1} = ±400 nA dc (±800 nA dc for 1N6631) or 100 percent of initial reading; whichever is greater. $\Delta V_{FM1} \leq \pm$ 0.05 V dc	I_{R1} and V_{FM1}
12	Required, see 4.3.1	Required, see 4.3.1
(2) 13	Subgroups 2 and 3 of table I herein: ΔI_{R1} = ±400 nA dc (±800 nA dc for 1N6631) or 100 percent of initial reading; whichever is greater. ΔV_{FM1} = ±0.05 V dc. Scope display evaluation, method 4023 of MIL-STD-750, see 4.5.4.	Subgroup 2 of table I herein: ΔI_{R1} = ±400 nA dc (±800 nA dc for 1N6631) or 100 percent of initial reading; whichever is greater. ΔV_{FM1} = ±0.05 V dc. Scope display evaluation, method 4023 of MIL-STD-750, see 4.5.4.
14a	Not applicable	Not applicable
14b	Optional	Optional
15	Required	Not required
16	Required	Not required
17	Not required	Not required

(1) Thermal impedance shall be performed any time after sealing provided temperature cycling is performed in accordance with MIL-PRF-19500, screen 3 prior to this thermal test.
(2) $Z_{\theta JX}$ is not required in screen 13, if already previously performed.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

* 4.3.1 Power burn-in conditions. Power burn-in conditions are as follows: These tests shall be conducted with a half-sine waveform as described in 4.5.5. With the written approval of the qualifying activity and the preparing activity, an alternate burn-in flow may be used (I_O or I_F). A study illustrating equivalence with ACOL testing will be required (see 4.5.3.1).

- Burn-in set up. Place a single device in your burn-in/life test rack. Adjust power (or current) until the part reaches T_J = 135°C minimum. This is the minimum power/current which must be applied to each device. Use method 3100 to measure T_J. Additional heat generated by self-heating is allowed but shall not cause any device to exceed the maximum temperature rating.

4.3.2 Thermal impedance $Z_{\theta JX}$ measurements for screening. The $Z_{\theta JX}$ measurements shall be performed in accordance with method 3101 of MIL-STD-750. The maximum screen limit shall be developed by the supplier using statistical methods and it shall not exceed table I, group A, subgroup 2.

4.3.2.1 Thermal impedance ($Z_{\theta JX}$ measurements) for initial qualification or requalification. The $Z_{\theta JX}$ measurements shall be performed in accordance with method 3101 of MIL-STD-750 (read and record date $Z_{\theta JX}$). $Z_{\theta JX}$ shall be supplied on one lot (500 pieces minimum and a thermal response curve shall be submitted.) Twenty-two of these samples shall be serialized and provided to the qualifying activity for correlation prior to shipment of parts. Measurements conditions shall be in accordance with 4.4.1.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500 and table I herein. The following test conditions shall be used for $Z_{\theta JX}$, group A inspection: $Z_{\theta JX}$ = 1.5°C/W.

a. I_H = 5 A minimum.

b. t_H = 10 ms.

c. I_M = 10 mA.

d. t_{MD} = 100 µs maximum.

* 4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in tables VIa (JANS) and VIb (JAN, JANTX and JANTXV) of MIL-PRF-19500 and 4.4.2.1 and 4.4.2.2 herein. Electrical measurements (end-points) shall be in accordance with table I, group A, subgroup 2. Delta measurements shall be in accordance with table III herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

* 4.4.2.1 Group B inspection, table VIa (JANS) of MIL-PRF-19500. For B5, if a failure occurs, resubmission shall be at the test conditions of the original sample.

	Subgroup	Method	Condition
*	B3	1056	Thermal shock, 0°C to +100°C, 10 cycles.
*	B3	1051	Temperature cycling, -55°C to +175°C, 20 cycles.
	B3	4066	I_{FSM} = rated I_{FSM} (see 1.3, col. 5); 10 surges of 8.3 ms each at 1 minute intervals, I_O = 0, V_{RWM} = 0.
	B4	1037	I_O = I_O rated minimum (see 1.3, col. 4); V_R = rated V_{RWM} (see 1.3, col. 2 and 4.5.3); 2,000 cycles.
	B5	1027	I_O = I_O rated minimum (see 1.3, col. 4); apply V_R = rated V_{RWM} (see 1.3, col. 2 and 4.5.3) adjust I_O to achieve T_J minimum; f = 50-60 Hz; n = 45, c = 0.
			Option 1: T_A = + 30°C max. ; T_J = 225°C minimum; t = 216 hours
		or	Option 2: T_A = + 30°C max. ; T_J = 200°C minimum; t = 1,000 hours
	B6	3101 or 4081	$R_{\theta JL}$ and $R_{\theta JEC}$ (maximum) (see 1.4 and 4.5.5).

* 4.4.2.2 Group B inspection, table VIb (JAN, JANTX and JANTXV of MIL-PRF-19500).

	Subgroup	Method	Condition
*	B2	1056	Thermal shock, 0°C to +100°C, 10 cycles.
*	B2	1051	Temperature cycling, -55°C to +175°C 20 cycles.
*	B3	1027	I_O = I_O (rated see 1.3, col. 4) minimum, adjust I_O to achieve the required T_J. Apply V_R = rated V_{RWM} (see 1.3, col. 2), f = 50-60 Hz (see 4.5.3.1).

* 4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VII of MIL-PRF-19500. Electrical measurements (end-points) shall be in accordance with table I, group A, subgroup 2. See table III for delta limits when applicable.

4.4.3.1 Group C inspection, table VII of MIL-PRF-19500.

	Subgroup	Method	Condition
	C2	2036	Tension: Test condition A; weight = 20 pounds; t = 30 seconds. Lead fatigue: Test condition E; weight 2 pounds. NOTE: Both tension and lead fatigue are not applicable for U or US devices.
*	C6	1027	I_O = I_O (rated see 1.3, col. 4) min. adjust I_O to achieve the required T_J. Apply V_R = rated V_{RWM} (see 1.3, col. 2), f = 50-60 Hz (see 4.5.3.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

* 4.4.4 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in appendix E, table IX of MIL-PRF-19500 and as specified herein. Electrical measurements (end-points) shall be in accordance with table I, group A, subgroup 2. See table III for delta limits when applicable.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

4.5.2 Inspection conditions. Unless otherwise specified, all inspections shall be conducted at T_A = room ambient as defined in the general requirements of MIL-STD-750 (see 4.5).

4.5.3 Burn-in and life tests. These tests shall be conducted with a half-sine waveform of the specified peak voltage impressed across the diode in the reverse direction followed by a half-sine waveform of the specified average rectified current. The forward conduction angle of the rectified current shall be neither greater than 180 degrees, nor less than 150 degrees.

* 4.5.3.1 Delta T_J rise. Adjusted Io such that the junction rise above ambient shall be delta TJ = 100°C min. for each diode and the junction temperature of each diode is maintained at TJ = 135°C min for burn-in and TJ = 150°C min for life testing. The delta TJ rise is intended to be achieved by device current and not by external or self-heating. (Tj – Ta) $\geq$ 100°C Deliberate heat sinking or forced air-cooling is prohibited unless otherwise approved by the qualifying activity. Ambient temperature shall be controlled to prevent TJ from exceeding rated TJ. The use of a current limiting or ballast resistor is permitted provided that each DUT still sees the full P_t (minimum) and that the minimum applied voltage, where applicable, is maintained through out the burn-in period.

* 4.5.4 Scope display evaluation. Scope display evaluation shall be stable in accordance with method 4023 of MIL-STD-750. Scope display may be performed on ATE (automatic test equipment) for screening only with the approval of the qualifying activity. Scope display in group A, subgroup 4 shall be performed on a scope. Reverse current (I_{BR}) over the knee shall be 500 μA peak.

4.5.5 Thermal resistance. Thermal resistance shall be measured in accordance with method 3101 of MIL-STD-750. The reference point shall be the lead temperature at .375 inch (9.52 mm) from the body of the device. L = 0 (endcap mount) for surface mounted devices.

a. I_H = 2.0 A dc minimum.

b. $t_{H\,=}$ thermal equilibrium.

c. I_M = 10 mA.

d. t_{MD} = 100 μs maximum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

4.5.6 Reverse recovery time.

4.5.6.1 Low current reverse recovery time. The low current reverse recovery time shall be 0.5 A forward current to 1.0 A reverse current. The reverse recovery time is defined as the time the rectifier begins to conduct in the reverse direction (crosses I = 0) until the reverse current decays to -0.25 A. The point of contact on the leads shall be no less than .375 inch (9.52 mm) from the diode body.

* 4.5.6.2 High current reverse recovery time. The high current reverse recovery time shall be measured in the circuit of figure 4 or equivalent. A pulse of forward current for the DUT is provided through S_1 and controlled by V_3, R_{L1} and the timing input pulse V_1. The duration of pulse, t_1, should be sufficient to fully establish the stored charge associated with the specified I_F; it is suggested to be between 10 and 30 microseconds. The reverse voltage (V_4) to the DUT is applied through S_2 at a rate determined by the rise time, t_2 and magnitude of the input pulse, V_2, which is applied slightly before the end of t_1. The negative supply, V_4, is to be specified. It should be sufficiently low to prevent the peak voltage, $V_{RM(REC)}$, from exceeding the rated reverse voltage, V_{RWM} , of the device under test. For most repeatable measurement, 30 V is recommended. The point of contact on the leads shall be no less than 0.375 inch (9.52 mm) from the body.

4.5.7 Thermal impedance. Thermal impedance $Z_{\theta JX}$ measurements shall be performed in accordance with method 3101 of MIL-STD-750. The maximum limit for $Z_{\theta JX}$ in screening (table IV of MIL-PRF-19500) shall be derived by each vendor by means of statistical process control techniques and applied in screening of all subsequent lots. This limit shall not exceed the group A, subgroup 2 limit. The following conditions shall apply:

a. I_H = 5 A minimum.

b. t_H = 10 ms.

c. I_M = 10 mA.

d. t_{MD} = 100 µs maximum.

* 4.5.8 Peak reverse power test. A 20 microsecond half-sine waveform of current shall be used and peak reverse power shall be determined by the product of peak reverse voltage and peak reverse current. A 20 microsecond square waveform may also be used with the approval of the qualifying activity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical examination	2071					
Subgroup 2						
Thermal impedance	3101	See 4.4.1	$Z_{\theta JX}$		1.5	°C/W
Forward voltage	4011	Duty cycle ≤ 2 percent (pulsed) (see 4.5.1) t_p = 8.3 ms (max).	V_{FM1}			
1N6626, U, US		I_{FM} = 4.0 A dc			1.5	V dc
1N6627, U, US		I_{FM} = 4.0 A dc			1.5	V dc
1N6628, U, US		I_{FM} = 4.0 A dc			1.5	V dc
1N6629, U, US		I_{FM} = 3.0 A dc			1.7	V dc
1N6630, U, US		I_{FM} = 3.0 A dc			1.7	V dc
1N6631, U, US		I_{FM} = 2.0 A dc			1.95	V dc
Forward voltage	4011	Duty cycle ≤ 2 percent (pulsed) (see 4.5.1) t_p = 8.3 ms (max).	V_{FM2}			
1N6626, U, US		I_{FM} = 2.0 A dc			1.35	V dc
1N6627, U, US		I_{FM} = 2.0 A dc			1.35	V dc
1N6628, U, US		I_{FM} = 2.0 A dc			1.35	V dc
1N6629, U, US		I_{FM} = 1.4 A dc			1.40	V dc
1N6630, U, US		I_{FM} = 1.4 A dc			1.40	V dc
1N6631, U, US		I_{FM} = 1.4 A dc			1.60	V dc
Reverse current leakage	4016	DC method; V_{RM} = rated V_{RM} (col. 2 of 1.3); pulsed (see 4.5.1)	I_{R1}		Col. 12 of 1.4	µA
Breakdown voltage	4022	I_R = 50 µA dc pulsed (see 4.5.1)	$V_{(BR1)}$	110 percent of col. 2 of 1.3		
Subgroup 3						
High temperature operation		T_A = +150°C				
Reverse current leakage	4016	V_{RM} = rated V_{RM} (col. 2 of 1.3) (pk); pulsed (see 4.5.1)	I_{R2}		Col. 13 of 1.4	µA dc

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection – Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 3 - Continued						
Low temperature operation:		T_A = -65°C				
Forward voltage	4011	I_{FM3} = 50 percent of $I_{F(AV1)}$ (pk) (col. 3 of 1.3); pulsed (see 4.5.1)	V_{FM3}		110 percent of col. 16 of 1.4	V
Breakdown voltage		I_R = 50 µA dc pulsed (see 4.5.1)	$V_{(BR2)}$	Col. 2 of 1.3		V
Subgroup 4						
Forward recovery voltage	4026	I_F =1 A; t_r = 12 ns	V_{FRM}			V
1N6626, U, US					8	
1N6627, U, US					8	
1N6628, U, US					8	
1N6629, U, US					12	
1N6630, U, US					12	
1N6631, U, US					20	
Capacitance	4001	V_R = 10 V dc, f = 0.1 to 1 MHz	C_T		40	pF
Low current reverse recovery time	4031	See 4.5.6.1 condition B, and figure 3 herein.	t_{rr1}			ns
1N6626, U, US					30	
1N6627, U, US					30	
1N6628, U, US					30	
1N6629, U, US					50	
1N6630, U, US					50	
1N6631, U, US					60	
High current reverse recovery time	4031	Condition D. See 4.5.6.2, I_F = 2A, di/dt = 100 A/µs, and figure 4 herein.	t_{rr2}			ns
1N6626, U, US					45	
1N6627, U, US					45	
1N6628, U, US					45	
1N6629, U, US					60	
1N6630, U, US					60	
1N6631, U, US					80	

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection – Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 4 - Continued						
Peak recovery current		See figure 4.	$I_{RM(REC)}$			A
1N6626, U, US					3.5	
1N6627, U, US					3.5	
1N6628, U, US					3.5	
1N6629, U, US					4.2	
1N6630, U, US					4.2	
1N6631, U, US					5.0	
Scope display	4023	Stable only (see 4.5.4), n = 116, c = 0				
Subgroup 5						
Not applicable						
Subgroup 6						
Forward surge	4066	I_{FSM} = rated I_{FSM} (1.3, col. 5) 10 surges of 8.3 ms each at 1 minute intervals. I_O = 0, V_{RWM} = 0, T_A = +25°C				
* Electrical measurement		See table I, group A, subgroup 2.				
Subgroup 7						
Not applicable						

1/ For sampling plan, see MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

* TABLE II. Group E inspection (all quality levels) for qualification only.

Inspection	MIL-STD-750		Sampling plan
	Method	Conditions	
Subgroup 1			45 devices c = 0
Thermal shock (glass strain)	1056	500 cycles, -65°C to +175°C.	
Temperature cycling	1051	500 cycles, -65°C to +175°C.	
Hermetic seal gross leak	1071		
Electrical measurement		See table I, group A, subgroup 2.	
Subgroup 2			22 devices c = 0
Blocking life	1048	T_A = +150°C; t = 1,000 hours +65, -0 hours; DC = 80 - 85 percent rated V_R	
Electrical measurement		See table I, group A, subgroup 2.	
Subgroup 3			
Not applicable			
Subgroup 4			22 devices c = 0
Thermal resistance, junction to lead	3101	Limits: 22°C/W, see 4.5.5	
Thermal resistance, junction to end caps	3101	Limits: 10°C/W, see 4.5.5	
Subgroup 5			22 devices c = 0
Barometric pressure (reduced) 1/	1001	1N6626 through 1N6628 at 8 mm Hg 1N6629 through 1N6631 at 33 mm Hg	
* Subgroup 6			22 devices c = 0
Forward surge	4066	Condition A, I_{FSM} = rated I_{FSM} (see 1.3, col. 5); 10 surges of 8.3 ms each at 1 minute intervals, I_O = 0, V_{RWM} = 0.	
Electrical measurement		See table I, group A, subgroup 2.	
* Subgroup 7 2/			
Peak reverse power		See 4.5.8 and figure 5 herein. Peak reverse power (P_{RM})= shall be characterized by the supplier and this data shall be available to the Government. Test shall be performed on each sublot.	
Electrical measurement		During the P_{RM} test, the voltage (V_{BR}) shall be monitored to verify it has not collapsed. Any collapse in V_{BR} during or after the P_{RM} test or rise in leakage current (I_R) after the test that exceeds I_{R1} in Group A shall be considered a failure to that level of applied P_{RM}. Progressively higher levels of P_{RM} shall be applied until failure occurs on all devices within the chosen sample size to characterize each sublot.	

1/ Also applies to U and US suffix versions.
* 2/ The sample size for this step stress requirement shall be determined by the supplier. A statistically significant sample size is required.


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

* TABLE III. Groups B, C, and E delta measurements. 1/ 2/ 3/

Step	Inspection	MIL-STD-750		Symbol	3/ Limits		Unit
		Method	Conditions		Min	Max	
1.	Forward voltage change	4011	I_{FM} = col. 4 of 1.3, pulsed (see 4.5.1)	ΔV_{FM1}	± 50 mV change from previous measured value		
2.	Reverse current change 1N6626 through 1N6631	4016	V_{RM} = col. 2 of 1.3	ΔI_{R1}		+2	µA

* 1/ The delta measurements for table VIa (JANS) of MIL-PRF-19500 are as follows: Subgroup 5, see table III herein, steps 1 and 2.
* 2/ The delta measurements for table IX of MIL-PRF-19500 are as follows: Subgroup 1, see table III herein, steps 1 and 2.
3/ See 1.4 herein.


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

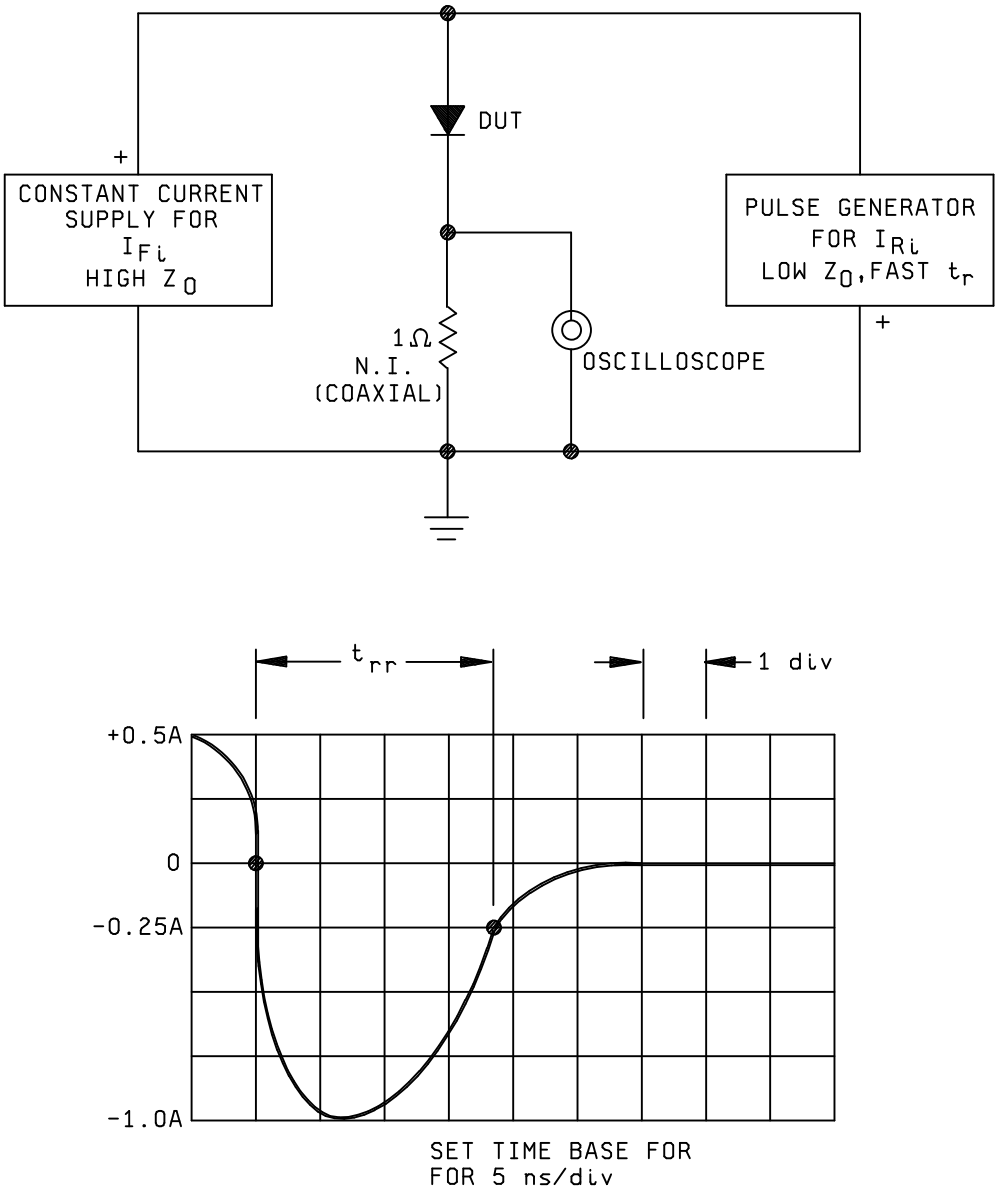

NOTES:
1. Oscilloscope: Rise time ≤ 3 ns; input impedance = 1 MΩ; 22 pF.
2. Pulse generator: Rise time ≤ 8 ns; source impedance = 10 Ω.

FIGURE 3. Reverse recovery time test circuit and characteristic waveform.


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

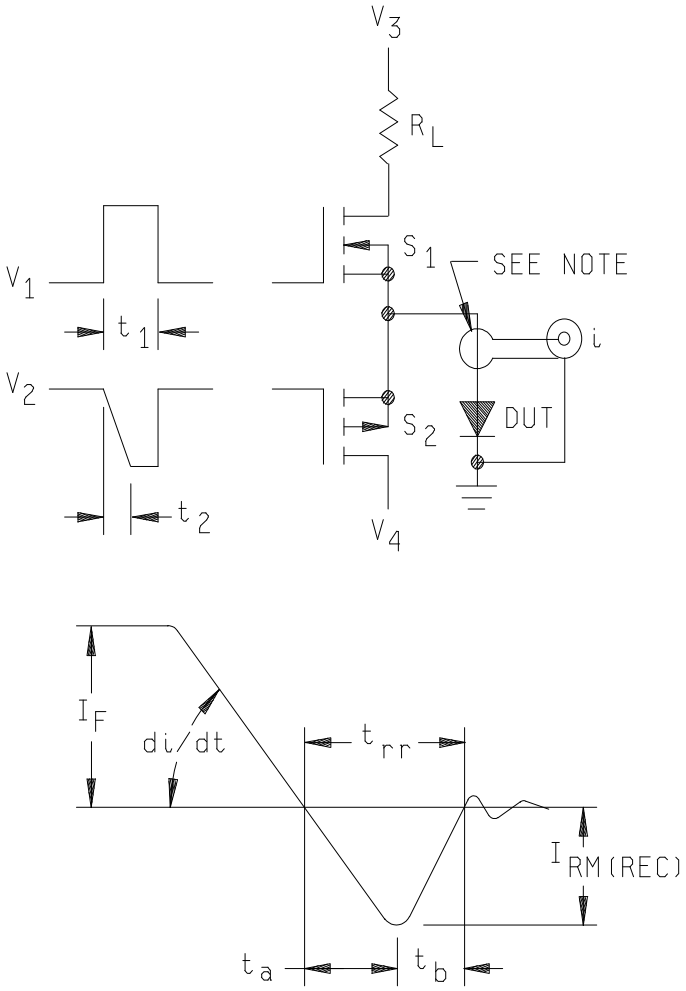


NOTE: Current sensing transformer; alternatively a low inductance resistor may be used, from the cathode to ground, for current vs time measurements.

FIGURE 4. High current reverse recovery test circuit and waveform.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

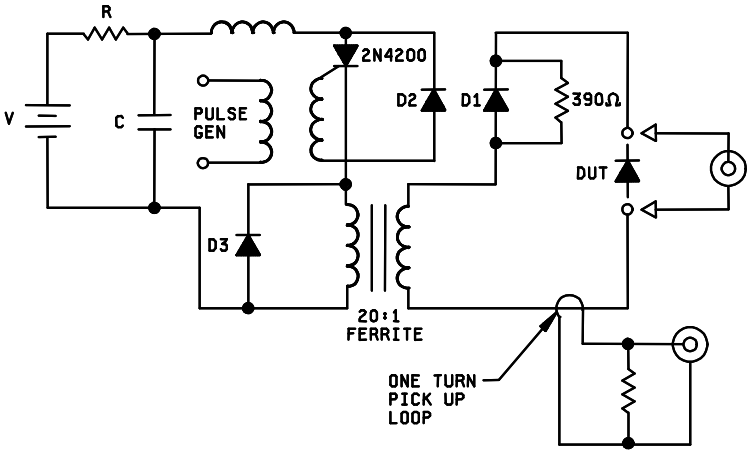

NOTES:
L = 13T H22 on 1 inch diameter form (air core).
C ~ 1 to 10 µfd to give 20 µs pulse width.
V - Adjustable to 200 volts for power desired in DUT.
D1 - 3 kV; 600 Ma (1N3647 or equivalent).
D2, D3 - 600 V; 3A (1N5552 or equivalent).
* Values not stated are determined at the time of test.

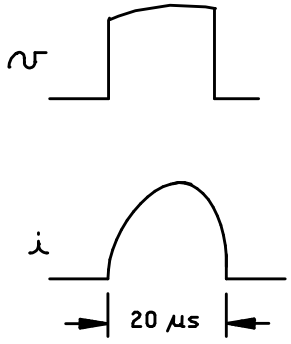

TYPICAL WAVEFORMS

FIGURE 5. Peak reverse power measurement circuit and waveform.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When actual packaging of materiel is to be performed by DoD personnel, these personnel need to contact the responsible packaging activity to ascertain requisite packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activity within the Military Department or Defense Agency, or within the Military Department's System Command. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The notes specified in MIL-PRF-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents must specify the following:

a. Title, number, and date of this specification.

b. Issue of DoDISS to be cited in the solicitation and if required, the specific issue of individual documents referenced (see 2.2.1).

c. The lead finish as specified (see 3.4.2).

d. Type designation and quality assurance level.

e. Packaging requirements (see 5.1).

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturer’s List QML No.19500 whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Defense Supply Center, Columbus, ATTN: DSCC-VQE, P.O. Box 3990, Columbus, OH 43216-5000.

6.4 Substitution of devices. The US version is substitutable for the U version and the U version is substitutable for the US version.

6.5 Changes from previous issue. The margins of this revision are marked with asterisks to indicate where changes from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Custodians:
Army - CR
Navy - EC
Air Force - 11
NASA - NA
DLA - CC

Review activities:
Army - AR, MI, SM
Navy - AS, MC
Air Force - 19

Preparing activity:
DLA - CC

(Project 5961-2658)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.

2. The submitter of this form must complete blocks 4, 5, 6, and 7.

3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-PRF-19500/590E	2. DOCUMENT DATE 30 December 2002

3. **DOCUMENT TITLE**
SEMICONDUCTOR DEVICE, DIODE, SILICON, ULTRAFAST RECOVERY, POWER RECTIFIER 1N6626 THROUGH 1N6631, 1N6626U THROUGH 1N6631U, 1N6626US THROUGH 1N6631US JAN, JANTX, JANTXV, AND JANS

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) COMMERCIAL DSN FAX EMAIL	7. DATE SUBMITTED

8. PREPARING ACTIVITY

a. Point of Contact Alan Barone	b. TELEPHONE Commercial: 614-692-0510 DSN: 850-0510 FAX: 614-692-6939 EMAIL: alan.barone@dscc.dla.mil
c. ADDRESS Defense Supply Center, Columbus ATTN: DSCC-VAC, P.O. Box 3990 Columbus, OH 43216-5000	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Standardization Program Office (DLSC-LM) 8725 John J. Kingman, Suite 2533, Fort Belvoir, VA 22060-6221 Telephone (703) 767-6888 DSN 427-6888

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:47Z
Check the source to verify that this is the current version before use.