
MS9918 (ASG)

FED. SUP CLASS 5306

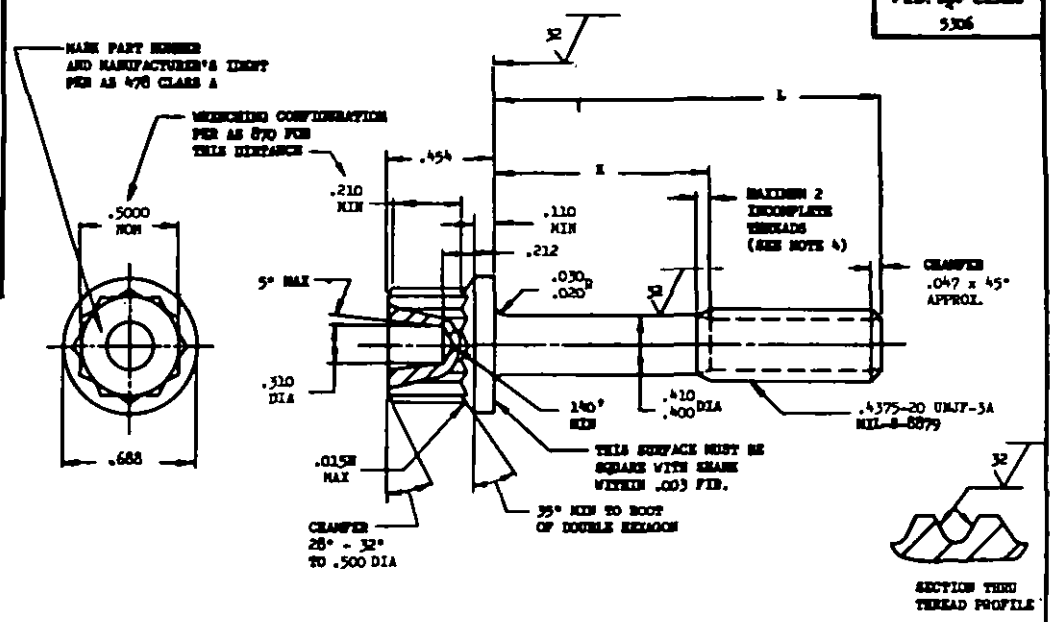

PART NO.	L	K	APPROX. WEIGHT LB/100
MS9918-04	.688	.105- .125	5.31
MS9918-05	.750	.105- .125	5.54
MS9918-06	.812	.105- .125	5.76
MS9918-07	.875	.105- .125	5.99
MS9918-08	.938	.105- .125	6.22
MS9918-09	1.000	.105- .125	6.45
MS9918-10	1.062	.105- .125	6.68
MS9918-11	1.125	.105- .125	6.90
MS9918-12	1.188	.105- .125	7.13
MS9918-13	1.250	.105- .125	7.36
MS9918-14	1.312	.128- .188	7.59
MS9918-15	1.375	.190- .250	7.82
MS9918-16	1.438	.252- .312	8.05
MS9918-17	1.500	.315- .375	8.27
MS9918-18	1.562	.378- .438	8.50
MS9918-19	1.625	.440- .500	8.73
MS9918-20	1.688	.502- .562	8.96
MS9118-21	1.750	.565- .625	9.19
MS9918-22	1.812	.628- .688	9.41
MS9918-23	1.875	.690- .750	9.64
MS9918-24	1.938	.752- .812	9.87
MS9918-25	2.000	.815- .875	10.10
MS9918-26	2.125	.940-1.000	10.56
MS9918-27	2.250	1.065-1.125	11.01
MS9918-28	2.375	1.190-1.250	11.47
MS9918-29	2.500	1.315-1.375	11.92
MS9918-30	2.625	1.440-1.500	12.38
MS9918-31	2.750	1.565-1.625	12.84
MS9918-32	2.875	1.690-1.750	13.29
MS9918-33	3.000	1.815-1.875	13.75
MS9918-34	3.125	1.940-2.000	14.20
MS9918-35	3.250	2.065-2.125	14.66
MS9918-36	3.375	2.190-2.250	15.12
MS9918-37	3.500	2.315-2.375	15.57
MS9918-38	3.625	2.440-2.500	16.03
MS9918-39	3.750	2.565-2.625	16.49
MS9918-40	3.875	2.690-2.750	16.94
MS9918-41	4.000	2.815-2.875	17.40
MS9918-42	4.125	2.940-3.000	17.86
MS9918-43	4.250	3.065-3.125	18.31
MS9918-44	4.375	3.190-3.250	18.77
MS9918-45	4.500	3.315-3.375	19.22
MS9918-46	4.625	3.440-3.500	19.68
MS9918-47	4.750	3.565-3.625	20.14
MS9918-48	4.875	3.690-3.750	20.59
MS9918-49	5.000	3.815-3.875	21.05
MS9918-50	5.125	3.940-4.000	21.50
MS9918-51	5.250	4.065-4.125	21.96
MS9918-52	5.375	4.190-4.250	22.42
MS9918-53	5.500	4.315-4.375	22.87
MS9918-54	5.625	4.440-4.500	23.33
MS9918-55	5.750	4.565-4.625	23.79
MS9918-56	5.875	4.690-4.750	24.24
MS9918-57	6.000	4.815-4.875	24.70

1. SHANK SHALL BE STRAIGHT WITHIN .0025 PER INCH OF BOLT LENGTH.
2. THE CONCENTRICITY OF THREAD PD IN RELATION TO THE SHANK SHALL BE WITHIN .006 FIR.
3. THE CONCENTRICITY OF THE SHANK IN RELATION TO THE WASHER FACE DIAMETER AND DOUBLE HEXAGON OD SHALL BE WITHIN .010 FIR.
4. INCOMPLETE THREADS NOT TO ENTER FILLET.
5. MATERIAL: STEEL AMS 6322.
6. HARDNESS: ROCKWELL C26-32.
7. FINISH: CADMIUM PLATE AMS 2400. DIMENSIONS SPECIFIED ARE AFTER PLATING.
8. MANUFACTURING SPECIFICATION: AMS 7452 EXCEPT HEAD SHALL BE UPSET.
9. HEAD TO SHANK FILLET SHALL BE COLD WORKED.
10. MAGNETIC PARTICLE INSPECTION PER AMS 2640 AFTER PLATING.
11. SURFACE TEXTURE: USAS B46.1-1962. UNLESS OTHERWISE SPECIFIED, SURFACES TO BE 125 MICROINCHES EXCEPT UPSET HEAD.
12. BREAK SHARP EDGES .003-.015 UNLESS OTHERWISE SPECIFIED.
13. DIMENSIONS IN INCHES. UNLESS OTHERWISE SPECIFIED, TOLERANCES: LINEAR DIMENSIONS ±.010, ANGULAR DIMENSIONS ±5°.
14. DO NOT USE UNASSIGNED PART NUMBERS.

AS & AMS ARE SOCIETY OF AUTOMOTIVE ENGINEERS, INC. PUBLICATIONS.
THIS STANDARD WAS DEVELOPED COOPERATIVELY WITH THE MILITARY SERVICES BY THE SAE AEROSPACE PART STANDARDS DIVISION.

APPROVED 15 Aug 69 REVISED

This military standard is approved by the Department of the Air Force and the Bureau of Naval Weapons and is mandatory for use by those activities. All other military activities are required to employ this standard where suitable.

Review activities: USAF - 82, 85

P.A. USAF - 11 Other Cust Navy - AS	TITLE BOLT, MACHINE - DOUBLE HEXAGON EXTENDED WASHER HEAD, PD SHANK, STEEL AMS 6322, CADMIUM PLATED, .4375-20 UNJF-3A	MILITARY STANDARD MS9918 (ASG)
PROCUREMENT SPECIFICATION None	SUPERSEDES	SHEET 1 OF 1

DD FORM 672-1 (Modified overprint (ASG)) PREVIOUS EDITIONS OF THIS FORM ARE OBSOLETE.
ASG use only

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T13:27Z
Check the source to verify that this is the current version before use.

☆U.S. GOVERNMENT PRINTING OFFICE: 1969-393-065/S1743