HH-I-00536a(GSA-FSS)
April 1, 1963
Interim Revision of
Fed. Spec. HH-I-536
January 23, 1952

INTERIM FEDERAL SPECIFICATION

INSULATION, ELECTRICAL, MICA, NATURAL MUSCOVITE

This Interim Federal Specification was developed by General Services Administration, Federal Supply Service, Washington 25, D.C., based upon current available technical information. It is recommended that Federal agencies use it in procurement and forward recommendations for changes to the preparing activity at the address shown above. The General Services Administration has authorized Federal agencies to use this Interim Federal Specification as a valid exception to Federal Specification HH-I-536, dated January 23, 1952.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers natural muscovite block mica in the full- or partially-trimmed sheet form for use as electrical insulation.

1.2 Classification

1.2.1 Types, classes, visual qualities, and grade sizes. Natural muscovite mica furnished under this specification shall be of one type (block) and the following classes, visual qualities, and grade sizes, as specified (see 6.2).

Classes:
Class 1 - Full-trimmed sheet
Class 2 - Partially-trimmed sheet

Visual quality:
V-1 - Clear
V-2 - Clear and slightly stained
V-3 - Fair stained
V-4 - Good stained
V-5 - Stained A quality
V-6 - Stained B quality
V-7 - Heavy stained
V-7A- Densely stained
V-8 - Black dotted
V-9 - Black spotted
V-10- Black stained
V-10A- Densely black and red stained

FSC 5970

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:55Z
Check the source to verify that this is the current version before use.

Grade sizes:

OOEE	Special
OEE	Special
EE	Special
E	Special
A-1	(Special)
No.1	
No.2	
No.3	
No.4	
No.5	
No.5½	
No.6	

1.2.2 Color. The basic color of the mica shall be as specified in the invitation for bids (see 6.2).

NOTE: For definition of the various technical terms, visual qualities, grade sizes, etc., used throughout this specification, reference should be made to A.S.A. Standard C59.27.

2. APPLICABLE SPECIFICATIONS, STANDARDS, AND OTHER PUBLICATIONS

2.1 Specifications and standards. The following specifications and standards, of the issues in effect on date of invitation for bids, form a part of this specification.

Federal Specifications:

UU-P-271	-	Paper, Wrapping, Waterproofed Draft.
PPP-B-585	-	Boxes, Wood, Wirebound.
PPP-B-601	-	Boxes, Wood, Cleated-Plywood.
PPP-B-621	-	Boxes, Wood, Nailed and Lock-Corner.
PPP-B-636	-	Box, Fiberboard.
PPP-T-76	-	Tape, Pressure-Sensitive Adhesive Paper, Water Resistant (for Carton Sealing).

Federal Standards:

Fed.Std. No. 102 - Preservation, Packaging, and Packing Levels
Fed.Std. No. 123 - Marking for Domestic Shipment (Civilian agencies).

(FOR INSTRUCTIONS ON OBTAINING COPIES OF FEDERAL SPECIFICATIONS AND STANDARDS, SEE LAST PAGE).

Military Specifications:

MIL-B-138 - Boxes, Wood, Fiberboard-Lined for Overseas Shipment (for weight of contents not to exceed 500 pounds).

MIL-A-140 - Adhesive, Water-Resistant, Waterproof Barrier-Material

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:55Z
Check the source to verify that this is the current version before use.

Military Standards:
MIL-STD-129 - Marking for Shipment and Storage.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following publications form a part of this specification. Unless otherwise indicated, the issue in effect on date of invitation for bids shall apply.

American Standards Association, Inc.
C59.27 - Natural Muscovite Mica Based on Visual Quality, Specification for

C68.1 - Measurement of Test Voltage in Dielectric Tests.

(Copies may be obtained from the American Standards Association, Inc., 10 East 40th Street, New York 16, N.Y.)

3. REQUIREMENTS

3.1 Composition. The mica electrical insulation shall be muscovite mica not calcined or treated in any manner which will affect its suitability for the purposes intended. It shall consist entirely of selected sheets or blocks of the naturally occurring minerals. (See 4.5.7).

3.2 Visual quality classification. The mica electrical insulation shall conform to visual quality classification specified in A.S.A. C59.27.

3.3 Thickness. The thickness shall be not less than 0.007 inch. (See 4.5.3).

3.4 Size grading. (See 1.2.1 and 4.5.2).

3.4.1 The natural mica shall be graded for size according to the area of the maximum rectangle which can be cut from the specimen and the minimum dimension of one side as indicated in table I. The mica in the maximum rectangle shall meet the requirements for visual quality specified.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:55Z
Check the source to verify that this is the current version before use.

Table I - Size grading

Grade Size	Minimum area of maximum rectangle	Average area of grade (see 4.5.2)	Minimum dimension of one side
	Square inches	Square inches	Inches
OOEESpecial	100	--	4.0
OEESpecial	80	90	4.0
EESpecial	60	70	4.0
ESpecial	48	54	4.0
A-1(Special)	36	42	4.0
1------	24	30	3.0
2---	15	19.5	2.0
3---	10	12.5	2.0
4---	6	8	1.5
5---	3	4.5	1.0
5½--	2¼	2.5	7/8
6---	1	1.5	3/4

3.5 Cleavability. The natural mica shall have laminae of uniform thickness throughout and at least 90 percent of the sections resulting from the test for cleavability specified in 4.5.4 shall have a size grading equal to that of the original piece insofar as maximum usable area is concerned.

3.6 Dielectric strength. When five tests are conducted per sheet as specified in 4.5.5, the average dielectric strength short-time per sheet shall be not less than 1,000 volts per mil. When one test is conducted per sheet the dielectric strength short-time per sheet shall be not less than 850 volts per mil.

3.7 Conducting inclusions. There shall be no acute sparking when the natural mica sheet is tested as specified in 4.5.6.

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 Supplier responsibilities for inspection. The supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own or any other inspection facilities and services acceptable to the Government. Inspection records of the examination and tests shall be kept complete and available to the Government as specified in the contract or order (see 6.2). The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:55Z
Check the source to verify that this is the current version before use.

4.2 Sampling.

4.2.1 Lot. For purposes of sampling, a lot shall consist of all mica of the same visual quality and grade size, (see 1.2.1) offered for delivery at one time. The unit of sampling shall be a case when the mica is packed loose in 100-pound cases and shall be a 5-pound carton when it is packed in cartons.

4.2.2 Sampling for lot acceptance inspection. The sample units for lot acceptance inspection shall be taken at random in accordance with table II. For each case sample unit a total of 50 ounces shall be extracted from at least four different parts of the case. For each carton sample unit, a total of 10 ounces shall be taken from at least four different parts of the carton. The mica so taken shall be used for the lot acceptance inspection specified in 4.3.

Table II. Sampling plan for lot acceptance inspection

Visual quality of mica	Grade Size	When packed loose in cases percent of cases selected	When packed in 5-lb. cartons percent of cartons selected 1/
V-1	1 and larger	100	25
V-2	2,3,4	50	12.5
	5,5½,6	30	7.5
V-3	1 and larger	100	25
	2,3,4	30	7.5
	5,5½,6	20	5
V-4	1 and larger	100	25
	2,3,4	30	7.5
	5,5½,6	10	2.5
V-5 through	1 and larger	50	25
	2.3,4	20	5
V-10A	5,5½,6	5	1

1/ Not less than five cartons shall be taken unless the lot contains less than five cartons when all cartons shall be inspected.

4.2.2.1 When purchase contract or order provides for visual inspection only, inspection for lot acceptance shall be limited to visual quality (4.5.1), size grading (4.5.2), and thickness (4.5.3).

4.2.3 Sampling for lot acceptance test. The number of sample sheets (taken from each 10-ounce portion of the sample units inspected in accordance with 4.2.2 and 4.3) required for lot acceptance tests shall be as specified in table III.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

Table III - Sampling plan for lot acceptance inspection tests

Test	Number of sample sheets per 10-ounce portion of sample unit
Cleavability	3
Dielectric strength	3
Conducting inclusions	3
Special tests of mica for capacitors and similar applications, when required (see 4.5.7 and 6.2.1)	3

4.3 Lot acceptance inspection.

4.3.1 The samples taken in accordance with 4.2.2 shall be inspected under the supervision of the Government inspector, as follows:

Visual quality---------- (See) 4.4.1
Size grading---------- (See) 4.4.2
Thickness---------- (See) 4.4.3

4.3.2 The defective sheets of mica shall be separated from the rest and weighed. The following tolerances shall be allowed:

Percent
5 - for under 0.007 inch thick
10 - for next lower quality
10 - for next smaller size
15 - maximum for all causes

4.3.3 Rejection. Acceptance or rejection of the entire lot shall be determined as indicated in 4.3.2.

4.4 Lot acceptance tests.

4.4.1 The sample sheets taken in accordance with 4.2.3 shall be tested under the supervision of the Government inspector, as follows:

Cleavability---------- (See) 4.5.4
Dielectric strength---------- (See) 4.5.5
Conducting inclusions---------- (See) 4.5.6
Special tests of mica for capacitors and similar applications (when required) (See) 4.5.7 and 6.2.1.

4.4.2 Rejection. If any of the sample sheets taken in accordance with 4.2.3 fails any of the tests specified in 4.4.1, the entire lot shall be rejected.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

4.5 Inspection and tests/

4.5.1 Visual quality. The natural mica shall be examined visually for hardness, color, degree of flatness, stains and foreign inclusions, waves, cracks, buckles, air inclusions and similar defects.

4.5.2 Size grading. Before grading for size, all edges of natural mica shall be fully trimmed. All cracks, holes, reeves or cross grains shall be trimmed out. In eliminating such defects the trimming shall follow the natural contour of the mica. There shall be not more than two V or figure cuts on any one piece of mica, and no such V cuts shall be longer than one-fourth the width of the piece of mica measured at the point of cut. The mica shall be graded for size according to the area of the maximum rectangle which can be cut from the specimen and the minimum dimension of one side. At least 30 percent by weight of the mica for each grade shall have a maximum rectangle with an area equal to or greater than the average area between the minimum for the specified grade and the next higher grade. (See dotted lines on figure 1.) The mica in the maximum rectangle shall meet the requirements for visual quality specified in A.S.A. C59.27. A standard chart, as illustrated in figure 1, shall be used for grading the mica according to size. In grading the mica for size, all dimensions apply to the smaller surface measured from the foot of the bevel trimmed edge. The specimen to be graded shall be laid upon the chart so that it covers point O and has its maximum and minimum dimensions extending along and covering lines OA and OB, respectively. The specimen shall be shifted until the usable area completely covers the largest rectangle determined by a diagonal extending from point O to or beyond a point on any of the curves. The number of the curve at the greatest distance from O cut by the diagonal of the rectangle designates the grade of the specimen. (See 3.4).

4.5.3 Thickness. The thickness shall be determined by a machinist's micrometer with rachet. Because of the abrasive nature of mica the micrometer shall be checked periodically for accuracy. The anvil and spindle shall be cleaned as frequently as necessary to prevent the accumulation of mica dust on the surfaces so as to preserve the accuracy of the measurements. To clean, the micrometer shall be closed lightly on a clean sheet of bond paper and the paper moved between the surfaces. Care must be exercised in moving from one measurement location to another to maintain the surfaces of the anvil and spindle parallel to the surfaces of the specimen at all times so as to avoid scratching the mica and accumulating dust under the micrometer surfaces causing false readings. When size permits, at least five readings shall be taken to determine the average thickness in mils.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

4.5.4 Cleavability. The cleavability or splitting quality shall be tested by splitting the samples to a uniform thickness of not more than 0.0015 inch and determining the size grade of the films, resulting from the splitting, by the method specified in 4.5.2.

4.5.5 Dielectric strength.

4.5.5.1 Test equipment. A suitable high-voltage transformer shall be connected to an alternating-current supply having as nearly a true sine wave as possible. The capacity of the source of supply of energy shall be not less than 2 kilovolt-amperes for voltages of 50,000 volts or less, and not less than 5 kilovolt-amperes for voltages above 50,000 volts. The frequency shall not exceed 100 cycles per second.

4.5.5.2 Voltage control. The regulation shall be so controlled that the voltage from the secondary of the testing transformer can be raised gradually, in no case more than 500 volts per step, if step control is used. Any method of regulating the voltage will be satisfactory, provided the crest factor (ratio of maximum to mean effective) of the test voltage does not differ by more than plus or minus 5 percent from that of a sinusoidal wave over the upper half of the range of voltage.

4.5.5.3 Voltage measurements. The voltage may be measured by an approved method which gives root-mean-square values, preferably by means of a voltmeter connected to a special voltmeter coil in the high-voltage winding of the testing transformer, or to a separate step-down instrument potential transformer. A voltmeter on the low-voltage side of the transformer will be satisfactory if the known ratio of transformation does not change by more than 2 percent under the test condition. A properly calibrated electrostatic voltmeter connected across the high voltage supply will also be satisfactory. A sphere spark gap may be used in accordance with A.S.A. C68.1 to check the readings at very high-voltages.

4.5.5.4 Surge protection. Some protection is desirable in the high-voltage circuit of testing transformers where the voltage is 25,000 volts or over, to prevent dangerous surges and limit the current at flash-over or when the test specimen is punctured. It is however, desirable to have as much energy available as possible when puncture occurs. If impedance in the form of choke coils is used in series with the high-voltage terminals, it should be not greater than that which will limit the current through the specimen to double the normal rated current of the testing transformer.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:55Z
Check the source to verify that this is the current version before use.

4.5.5.5 Spark gap. When a sphere spark gap is used, a noninductive resistance approximately 1 ohm per volt may be inserted in series with 1 terminal of the spark gap, to damp high-frequency oscillations at the time of break-down, and to limit the current flow. This resistance shall be as near the gap as possible. If the test is made with one side grounded, this resistance shall be on the ungrounded side of the circuit and, if neither side is grounded, one-half of the resistance shall be inserted on each side of the spark gap. Water tube resistors are preferable to carbon for this purpose as the resistance of the carbon resistors may be materially decreased by the passage of current.

4.5.5.6 Test electrodes. The test electrodes shall be made of brass or copper, with flat polished contact surfaces. They shall be cylinders 1 inch in length and 2 inches in diameter, with the contact edges rounded to a radius of 1/8 inch, except that in the case of mica too small for the 2-inch diameter electrodes, the electrodes may be 1/4 inch in diameter with edges rounded to a radius of 1/32 inch. The electrodes shall be self-aligning and shall be placed exactly opposite one another, with the specimen in a horizontal plane between them.

4.5.5.7 Type and application of the electrodes and sample size shall be such as to avoid flash-over. The tests shall be made under oil.

4.5.5.8 Rate of rise of voltage. Starting at zero the testing voltage shall be increased uniformly to break-down at a rate of 500 volts per second.

4.5.5.9 Number of tests. When possible, five tests shall be conducted per sheet and the average dielectric strength shall be reported in volts per mil of thickness. If five tests are not possible per sheet, one test shall be conducted per sheet.

4.5.6 Conducting inclusions.

4.5.6.1 Apparatus. The apparatus shall consist of the following:

4.5.6.1.1 Spark coil. A spark coil of the vibrator type capable of giving a spark from 3/8 to 1 inch in length between needle points.

4.5.6.1.2 Current source. Six volts direct current.

4.5.6.1.3 Electrodes. One electrode consisting of a sharp-pointed 0.1285-inch (No. 8 B&S gage) bare copper wire, about 4 inches in length, mounted on the end of a hard rubber rod about 1 inch in diameter and 1 foot in length. The electrode shall be connected to the high-tension side of the spark coil. The other electrode shall be a sheet of metal of suitable size on which the mica under test can be laid. This electrode shall be connected to the grounded terminal of the spark coil.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:55Z
Check the source to verify that this is the current version before use.

4.5.6.2 Procedure.

4.5.6.2.1 With both electrodes connected to the spark coil, the spark coil vibrator shall be adjusted to give as smooth and steady a tone as possible. The pointed electrode shall be brought within 3/8 to 1 inch of the plate electrode, depending upon the capacity of the coil used. A continuous spark discharge should take place under these circumstances.

4.5.6.2.2 The test specimen shall be laid on the grounded electrode and the pointed electrode brought to within 1/4 inch of the specimen. Under these circumstances a small amount of typical bluish brush discharge will be noted at the point. The test specimen shall be carefully explored for scintillations or acute sparking with the pointed electrode over its entire face and edges. This test shall be made in subdued light in a lighted room.

4.5.6.3 Conducting stains and spots. Electrical conductivity adjacent to or located in visible spotted and stained areas of sheet or block mica is revealed when visible sparking, scintillation or glowing occurs either inside or on the surface of the test specimen in the vicinity of the test probe and not by actual puncture of the mica by the high potential current. If actual puncture of the test specimen does take place, this indicates that the dielectric strength of the mica has been exceeded or indicates the presence of mechanical faults, such as pin holes, tears, or cracks which extend completely through the mica.

4.5.7 Identify test for muscovite mica. When it is required that an identity test for muscovite mica be made, the tests for optical angle and weight loss on heating as described in A.S.A. C59.27 are recommended. (See 6.2).

5. PREPARATION FOR DELIVERY

(For civil. agency procurement, the definitions and applications of the various levels of packaging and packing shall be as specified in Fed. Std. No. 102).

5.1 Packaging.

5.1.1 Level A and B. Sheets of insulation of like description shall be packaged together in quantities of 5 pounds in snug-fitting fiberboard boxes conforming to PPP-B-636, compliance symbol W6s or W6c. Suitable cushioning shall be provided to prevent movement within the boxes. The boxes shall be closed and sealed in compliance with the appendix to the box specification, and in addition, all joints and seams, including those occurring in the manufacture of the boxes, shall be covered with minimum 3-inch-wide gummed tape conforming to PPP-T-76, extended over all corners and edges at least 3 inches.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

5.1.2 Level C. Block mica shall be packaged in accordance with standard commercial practice which will afford the degree of protection required for shipment and use of the product for its intended purpose within the continental limits of the United States of America.

5.2 Packing.

5.2.1 Level A. and B. Insulation, packaged as specified in 5.1.1, shall be packed in cleated plywood boxes, nailed wood boxes, wire-bound wood boxes, fiberboard boxes, or fiberboard-lined wood boxes conforming to the requirements of PPP-B-601, PPP-B-621, PPP-B-585, PPP-B-636, and MIL-B-138, respectively. The gross weight of wood boxes shall not exceed approximately 200 pounds; of fiberboard boxes, approximately 70 pounds.

5.2.1.1 Contents shall be enclosed within a sealed waterproof bag, or its equivalent, made from material conforming to the requirements of UU-P-271 for caseliner material. Seams and closures shall be sealed with adhesive conforming to the requirements of MIL-A-140.

5.2.2 Level C. The subject commodity shall be packaged and packed in substantial containers of the type, size, and kind commonly used for the purpose, so constructed as to insure acceptance and safe delivery by common or other carriers, at the lowest rate, to point of delivery called for in the contract or purchase order.

5.3 Marking.

5.3.1 Civil agencies. In addition to any special marking required in the contract or order, shipping containers shall be marked in accordance with Fed.Std. No. 123.

5.3.2 Military agencies. In addition to any special marking required in the contract or order, shipping containers shall be marked in accordance with MIL-STD-129.

6. NOTES

6.1 Intended use. Mica of visual qualities V-1 through V-4 is intended for use in high-quality capacitors and similar electronic applications requiring both high dielectric strength and low dielectric loss. All other qualities of mica are intended for applications where less stringent electrical characteristics are required. Natural mica of higher quality than V-5 should not be issued for routine stock purposes. The following tabulation is provided as a guide in the selection of the proper visual quality:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

Visual Quality	Characteristic Designation	Use
V-1 V-2	Superfine	Highest quality microwave, television, bolometer,etc., applications.
V-3 V-4	Capacitor quality	Capacitors for radio receivers, transmitters; general electronic purposes.
V-5 V-6	Radio tube quality	High quality tube spacers;lowest quality small capacitors.
V-7	Clear electric	Highest quality low voltage applications.
V-8 V-9	Spotted electric	Applicances, 110/220-volt and transformer layer insulation.
V-10	Stained electric	Motors, appliances, and resistors.

6.2 Ordering data. Purchasers should exercise any desired options offered herein and procurement documents should specify the following:

(a) Title, symbol, and date of this specification.
(b) Class, visual quality, and grade size of mica (1.2.1).
(c) Color of mica (1.2.2).
(d) Administrative provisions for inspection records (4.1).
(e) Identity test, if required (4.5.7).
(f) Level of packaging and packing required (5.1 and 5.2)
(g) Special marking, if required (5.3).

6.2.1 Special tests of mica for capacitors and similar applications (see 6.1). In the case of natural mica to be employed for use in high-quality capacitors and similar electronic applications it may be desirable to require tests for Q value (reciprocal of power factor). In such cases the property limit and test method should be specified in the contract or order (see 6.2). The property limit and indirect or rapid, direct-reading test methods described in American Standards Association, Inc., Standard C59.26 Specification for Natural Block Mica and Mica Films Suitable for Use in Fixed Mica-Dielectric Capacitors) are suggested for this purpose.

6.3 Federal specifications do not include all types, classes, grades, sizes, etc., of the commodities indicated by the titles of the specifications or which are commercially available, but are intended to cover the types, etc., which are suitable for Federal Government requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

6.4 Transportation description. Transportation descriptions and minimum weights applicable to this commodity are:

Rail:

Sheets, mica
Carload minimum weight 30,000 pounds.

Motors:

Sheets, Mica
Truckload minimum weight 30,000 pounds, subject to Rule 115, National Motor Freight Classification.

Notice. (See last page).

GSA-WASH DC 63-13645

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

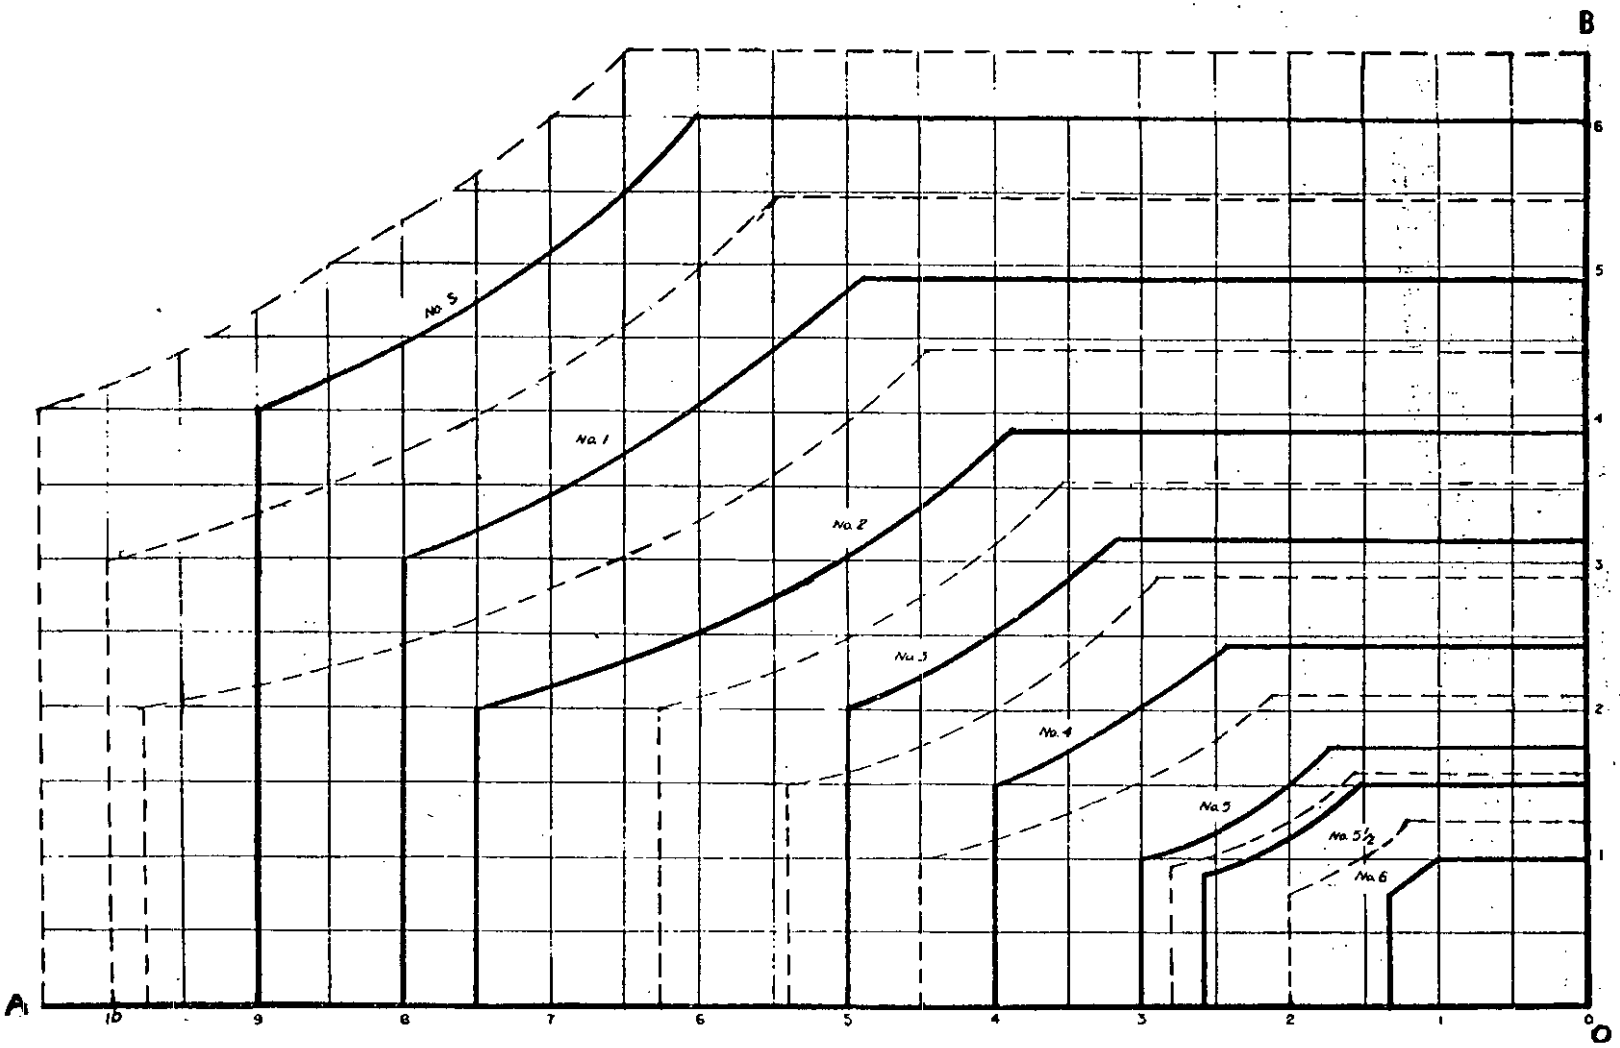


FIGURE 1.

STANDARD TEMPLATE FOR GRADING MICA, SIZES "S" AND SMALLER
NOT TO SCALE

Note 1. This template may be readily extended for larger sizes listed in table I.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

ADDENDUM

INSTRUCTIONS ON OBTAINING COPIES OF FEDERAL SPECIFICATIONS AND STANDARDS

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications, Standards and Handbooks and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington 25, D. C.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, and Auburn, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications, Standards and Handbooks from established distribution points in their agencies.)

NOTICE

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:55Z
Check the source to verify that this is the current version before use.

GSA WASH DC 62-12099