MIL-F-0051095F(EA)
8 August 1983
SUPERSEDING
MIL-F-0051095E(EA)
20 August 1976
USED IN LIEU OF
MIL-F-51095B
30 September 1964

MILITARY SPECIFICATION

# FILTER MATERIAL, GAS-AEROSOL, C18R1

This limited coordination military specification has been prepared by the US Army Armament, Munitions and Chemical Command based upon currently available technical information, but it has not been approved for promulgation as a coordinated revision of Military Specification MIL-F-51095B. It is subject to modification. However, pending its promulgation as a coordinated military specification, it may be used in acquisition.

## 1. SCOPE

1.1 Scope. This specification covers two types of gas-aerosol filter material.

2.1 Classification. The filter material shall be of the following types as specified (see 6.2):

Type II - Low weight.
Type III - High weight.

## 2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. Unless otherwise specified, the following specifications, standards, and handbooks of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation form a part of this specification to the extent specified herein.

: Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed: to: Commander, US Army Armament Research and Development Command, ATTN: DRDAR-TSC-S, Aberdeen Proving Ground, MD 21010 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 4240

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

SPECIFICATIONS

FEDERAL

PPP-B-636 - Boxes, Shipping, Fiberboard.

MILITARY

MIL-P-116 - Preservation-Packaging, Methods of.
MIL-B-131 - Barrier Materials, Watervaporproof, Flexible, Heat-Sealable.
MIL-C-51096 - Core Material, C18.
MIL-B-51097 - Backing Material, C18.
MIL-F-51425 - Filter Element Set, Chemical-Biological Mask, C13A2.

STANDARDS

FEDERAL

Fed. Std. No. 123 - Marking for Shipment (Civil Agencies).

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.
MIL-STD-414 - Sampling Procedures and Tables for Inspection by Variables for Percent Defective.

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this specification to the extent specified herein.

DRAWINGS

US ARMY ARMAMENT, MUNITIONS AND CHEMICAL COMMAND

CHEMICAL RESEARCH AND DEVELOPMENT CENTER

DL136-41-600-1 - All Purpose Apparatus, Gas Life Testing, Q95.
DLB136-42-102-30 - Penetrometer, Filter Testing, DOP, Q127.

(Copies of specifications, standards, handbooks, drawings, and publications required by manufacturers in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. The issues of the documents which are indicated as DoD adopted shall be the issue listed in the current DoDISS and the supplement thereto, if applicable.

ASTM STANDARDS

D-645 - Thickness of Paper and Paperboard.
D-828 - Tensile Breaking Strength of Paper and Paperboard.

(Application for copies of the above publications should be addressed to ASTM, 1916 Race Street, Philadelphia, PA 19103.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

3. REQUIREMENTS

3.1 Manufacture. The filter material shall be a uniform laminated sheet (see 6.2) consisting of several layers of core material conforming to MIL-C-51096, between single outside layers of backing material conforming to MIL-B-51097.

3.1.1 Basis weight. Prior to lamination, the basis weight of the combined core layers, using the basis weight designated on the outside wrap of the core material roll, shall be as follows:

Type II - 1.05 kilograms per square meter (minimum)
Type III - 2.05 to 2.25 kilograms per square meter

3.2 Physical and chemical requirements. The filter material shall conform to table I when tested as specified therein.

3.3 Delamination. Each disk taken as specified in 4.4.4.1 shall be an integral unit when died out from the test strip (see table II) and tested as specified in 4.4.4.4.7.

3.4 Preproduction sample. Prior to the start of regular production and following any change in regular production methods, materials, or equipment, a preproduction sample of filter material shall be produced in accordance with this specification for examination and tests (see 4.3).

3.5 Workmanship. The filter material shall be free from foreign matter, wrinkles, burn holes, scorching, charring, tears, cracks, holes, thin spots, blisters, or misalignments when examined in accordance with 4.4.3.



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

TABLE I. Physical and chemical requirements

| Property | Requirement | | | | Test paragraph |
|---|---|---|---|---|---|
| | Type II | | Type III | | |
| | min | max | min | max | |
| Airflow resistance, mm water | - | 35 | - | 50 | 4.4.4.2 |
| DOP smoke penetration, % | - | 0.1 | - | 0.10 | 4.4.4.2 |
| Accelerated gas sorption, min | | | | | 4.4.4.3 |
| Cyanogen chloride (CK) | 16 | - | 12.5 | - | |
| Chloropicrin (PS) | 20 | - | 12.5*** | - | |
| Thickness, inches | 0.17 | 0.19 | 0.30 | 0.33 | 4.4.4.4.1 |
| Tensile strength, lbs/inch | | | | | 4.4.4.4.2 |
| Cross machine direction | 7.0 | - | 12 | - | |
| Moisture content, % | - | 2.0 | - | 2.0** | 4.4.4.4.3 |
| Flexibility, inches | - | 0.10 | - | - | 4.4.4.4.4 |
| *Diffusivity, cm/sec | .050 | - | - | - | 4.4.4.4.5 |
| Flexure at -40° ± 5°F | No cracks or breaks | | | | 4.4.4.4.6 |

*Not applicable to filter material for the CD V-805 civilian mask.
**A maximum moisture content of 5.0% is permitted for filter material fabricated into filter elements within six months of date of manufacture of core material.
***Not applicable to filter material for the M13A2 Filter Element Set.



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

TABLE II. Tests

| Property | Test strips | Test specimens (see 4.4.4.1) | Retest | Defective specimen | Action | Test and retest combined: Failures | Test and retest combined: Action | Test paragraph |
|---|---|---|---|---|---|---|---|---|
| Preproduction sample | | | | 5 | Accept | | | |
| Airflow resistance | 150 | 150 | 0 | 6 | Reject | --- | --- | 4.4.4.2 |
| DOP smoke penetration | 150 | 150 | 0 | 5 | Accept | --- | --- | 4.4.4.2 |
| | | | | 6 | Reject | | | |
| **Accelerated gas sorption | --- | CK 34<br>PS 34 | 0 | --- | * | --- | --- | 4.4.4.3 |
| ***Physical properties | 20 | 10<br>each property | 10<br>each property | 0-2<br>3-5<br>6 | Accept<br>Retest<br>Reject | <br>3-5<br>6 | <br>Accept<br>Reject | 4.4.4.4 |
| Delamination | 150 | 150 | 0 | 5 | Accept | --- | --- | 4.4.4.4.7 |
| | | | | 6 | Reject | | | |
| Regular production | | | | | | | | |
| Airflow resistance | AQL 1.5 percent defective MIL-STD-105 | | | | | | | 4.4.4.2 |
| DOP smoke penetration | AQL 1.5 percent defective MIL-STD-105 | | | | | | | 4.4.4.2 |
| **Accelerated gas sorption | | | | | | | | |
| CK | * | 1 per strip | --- | | * | See 4.4.5 | | 4.4.4.3 |
| PS | | 1 per strip | | | | | | |
| ***Physical properties | 20 | 10<br>each property | 10<br>each property | 0-2<br>3-5<br>6 | Accept<br>Retest<br>Reject | <br>3-5<br>6 | <br>Accept<br>Reject | 4.4.4.4 |
| Delamination | AQL 1.5 percent defective MIL-STD-105 | | | | | | | 4.4.4.4.7 |

*Use MIL-STD-414 with Inspection Level II; Sampling Plan for Single Specification Limit-Form 1, with Variability Unknown-Standard Deviation Method; and an AQL of 1.50 percent; Unit of Product-One Sheet; for preproduction sample use K factor of 1.76. In no case shall the sample size be less than the size indicated for code letter H in MIL-STD-414.

**Test specimens shall be taken at random from those specimens which have passed 4.4.4.2.

***For tests 4.4.4.4.4, 4.4.4.4.5, and 4.4.4.4.6 test specimens shall be obtained from sample sheets (see 4.3.2.2 and 4.4.2.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

## 4. QUALITY ASSURANCE PROVISIONS

### 4.1 Responsibility for inspection.

4.1.1 Contractor's responsibility. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.2 Government's responsibility. The Government will be responsible for the examination and tests in 4.3.2. Samples shall be forwarded to the laboratory designated by the contracting officer (see 6.2 and 6.5).

4.1.3 Objective evidence. The contractor shall provide objective evidence acceptable to the contracting officer that the requirements of 3.1 and section 5 for which specific inspection has not been provided in this specification have been satisfied.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

(a) Preproduction inspection (4.3)
(b) Quality conformance inspection (see 4.4)

### 4.3 Preproduction inspection.

4.3.1 Sample. A preproduction sample of sufficient filter material shall be manufactured using the same methods, materials, and equipment as will be used during regular production, to produce 196 sheets (see 6.2) and 196 test strips. The test strips shall be no less than 10 inches long and shall be taken at the shears from the continuous run and not less than 3 feet apart.

4.3.2 Inspection procedure.

4.3.2.1 For nondestructive examination. Fifty sheets shall be taken at random and examined for defects listed in 4.4.3.3(a). The acceptance number is zero.

4.3.2.2 For destructive tests. Test strips for 4.4.4.2, 4.4.4.3, 4.4.4.4.1, 4.4.4.4.2, 4.4.4.4.3, and 4.4.4.4.7 shall be taken ar random for testing as specified in table II. Specimens for testing in accordance with 4.4.4.4.4, 4.4.4.4.5, and 4.4.4.4.6 shall be taken from ten sample sheets taken at random from those which have passed the examination specified in 4.3.2.1 and then tested in accordance with table II.



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

4.3.3 Tests. Tests shall be conducted as specified in 4.4.4.

4.3.4 Acceptance/rejection criteria. The preproduction sample shall meet the examinations and tests specified by 4.3.2 to be acceptable. The contractor shall obtain written approval from the contracting officer before proceeding with regular production.

4.4 Quality conformance inspection.

4.4.1 Lotting. A lot shall consist of the filter material produced during one work shift not exceeding 12 hours, by one manufacturer, under essentially the same manufacturing conditions. No more than two lots of core material, produced by one manufacturer, shall be used in one lot of filter material.

4.4.2 Sampling.

4.4.2.1 For examination and nondestructive test. Sampling shall be conducted in accordance with MIL-STD-105.

4.4.2.2 For destructive tests. Test strips (minimum 10-inch length taken at the shears from the continuous run and no less than 3 feet apart) for 4.4.4.2, 4.4.4.3, 4.4.4.4.1, 4.4.4.4.2, 4.4.4.4.3, and 4.4.4.4.7 shall be taken at random for testing as specified in table II. Specimens for testing in accordance with 4.4.4.4.4, 4.4.4.4.5, and 4.4.4.4.6 shall be taken from ten sample sheets taken at random from those sheets which have passed the examination specified in 4.4.3.1.

4.4.3 Inspection procedure.

4.4.3.1 For examination and nondestructive tests. Sample sheets of filter material shall be examined in accordance with the classification of defects and with MIL-STD-105.

4.4.3.2 For destructive tests. Test strips and specimens from sample sheets (see 4.4.2.2) shall be tested in accordance with table II.

4.4.3.3 Classification of defects.

(a) Filter material, gas-aerosol.

| Categories | Defects |
|---|---|
| Critical: | None defined |
| Major: | AQL 0.65 percent defective |
| 101 | Damage (tears, cracks, holes, blisters, or thin spots) |
| 102 | Foreign matter |
| 103 | Burn holes, charring, or scorching |
| 104 | Wrinkles |



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

Minor: AQL 2.5 percent defective

| | |
|---|---|
| 201 | Sheet size |
| 202 | Charcoal on top or bottom surfaces |
| 203 | Misalignment of core material exceeding 1/4 inch |

4.4.4 Tests.

4.4.4.1 Preparation of test specimens. One 5-1/4 inch diameter disk shall be taken from each test strip (4.4.2.2) for airflow resistance and DOP tests. Disks and specimens for physical tests shall be taken at random locations from test strips but not within one inch of the edge. Specimens for testing moisture content shal be taken immediately prior to heat-sealing finished packs (see 5.1) and these specimens shall be sealed immediately in packages in the same manner as the finished packs.

4.4.4.2 Airflow resistance and DOP smoke penetration. Airflow resistance and DOP smoke penetration of the specimens shall be determined at a flow-rate of 32 liters per minute using the Q127 DOP Filter Testing Penetrometer (DLB136-42-102-30).

4.4.4.3 Accelerated gas sorption. The accelerated gas sorption of each specimen shall be determined using the Q95 Gas Life Testing All Purpose Apparatus (DLB136-41-600-1) with the test conditions of table III. The accelerated gas sorption of each specimen shall be corrected for variations in concentration and reported to the nearest 0.1 minute.

4.4.4.4 Physical properties.

4.4.4.4.1 Thickness. Three thickness readings shall be taken on each test disk (see 4.4.4.1) in accordance with method C of ASTM D645 except that conditioning of specimens shall be omitted. The thickness of a specimen shall be the averge of 3 readings.

4.4.4.4.2 Tensile strength. Tensile strength of the test specimens shall be determined in accordance with ASTM D828, except that conditioning of specimens shall be omitted.

4.4.4.4.3 Moisture content. Each test specimen (5-1/4 inch diameter disk) shall be weighed to the nearest 0.01 gram (wet weight). Place the specimens in a forced air drying oven at 105° to 110°C and a maximum of 20 percent relative humidity until constant dry weight, within 0.01 gram, is reached. Calculate the percent moisture as follows:

$$\text{Percent moisture content} = \frac{100\ (\text{wet weight} - \text{dry weight})}{\text{Wet weight}}$$

4.4.4.4.4 Flexibility. One specimen, 1 by 6 inches shall be died at random locations from each of 10 of the sample sheets. Five shall be died in the machine direction and five in the cross machine direction.



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

TABLE III. Test conditions

| Filter material | Test gas | Concentrations* | Flow rate | Relative humidity for equilibrating and testing |
|---|---|---|---|---|
| Type II | CK | 1 mg/l | 12.5 l/min, intermittent flow | 80-80% |
| | PS | 4 mg/l | 12.5 l/min, intermittent flow | 50-50% |
| Type III | CK | 4 mg/l | 12.5 l/min, intermittent flow | 80-80% |
| | PS | 50 mg/l | 8 l/min, continuous flow | 0-50% |

*The indicated test gas concentration shall be maintained within ± 5%. Equilibrating and test temperatures will be recorded and maintained at 80° ± 10°F.

4.4.4.4.4.1 Apparatus. Flexibility shall be determined by means of an Aminco "Modulimeter."

4.4.4.4.4.2 Procedure. Level the test apparatus, adjust its anvils to a span of 4 inches and determine the deflection, in thousandths of an inch, imparted to each test specimen by a 0.10 pound load applied midway between the anvils by a presser foot 1.375 inches long, and 0.25 inches diameter.

4.4.4.4.5 Carbon dioxide diffusivity. One specimen, 13-1/2 by 13-1/2 inches, shall be cut at random locations from each of 10 selected sheets.

4.4.4.4.5.1 Apparatus. Use a diffusion chamber conforming to figure 1 and a Holdane-Guthrie gas analysis apparatus. An alternate method may be used provided it is shown to be equivalent to the Holdane-Guthrie Analysis Apparatus.

4.4.4.4.5.2 Procedure. Perform the test as follows:

(a) Connect the gas analysis apparatus to the capillary tube of the diffusion chamber.

(b) Seal the specimen, without distortion, to the bottom of the chamber; then block off the outside area of the specimen, using an impervious barrier material placed against the outer surface and held by suitable means.

(c) Pass into the chamber sufficient carbon dioxide, at a temperature of 75° ± 3°F, to yield a concentration greater than 10 percent. Do not rotate the box in any manner during this period.



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

INSIDE DIMENSIONS- 12 BY 12 BY 12 INCHES
MATERIAL 3/4 INCH PLYWOOD, PAINTED

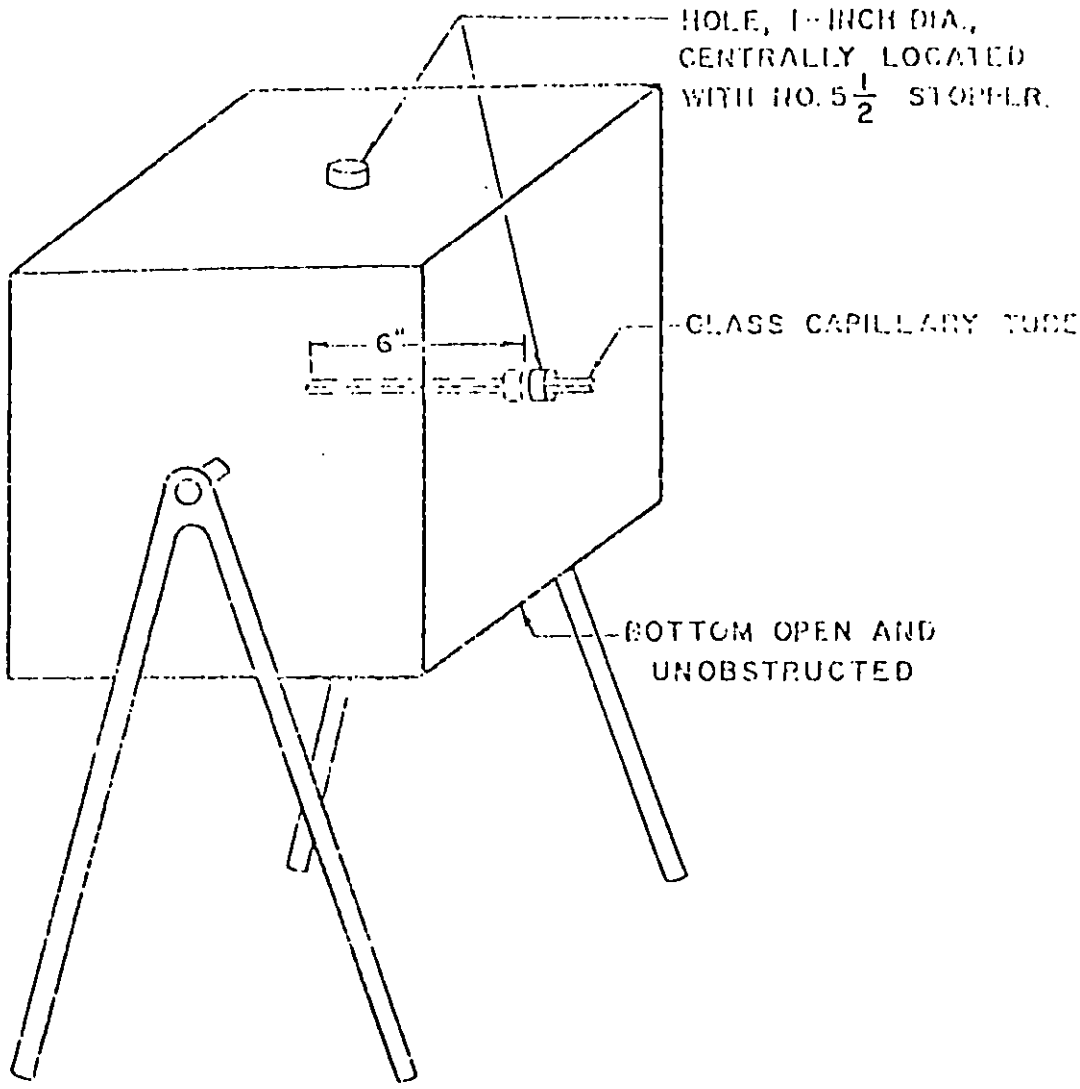



Figure 1- DIFFUSION CHAMBER



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

(d) After an interval of 5 minutes, remove the outside barrier and measure the carbon dioxide concentration in the chamber. At no time during the test should air be permitted to flow across the surface of the test specimen.

(e) Continue to measure the carbon dioxide concentration in the chamber, at intervals of 3 minutes, until it is below 2 percent.

(f) Plot concentration versus time on semi-log paper and construct the best straight line of the plotted values covering the range between 2 and 8 percent carbon dioxide.

(g) Calculate the diffusivity as follows:

$$\text{Diffusivity} = \frac{1.386\ V}{AT}$$

where: V = Volume of chamber (cu. cm.)
A = Area of exposed specimens (sq. cm.)
T = Elapsed time (seconds) required for the carbon dioxide concentration to drop from 8 to 2 percent according to the straight line graph.

4.4.4.4.6 Flexure. One specimen, 5 by 5 inches, shall be died at random locations from each of 10 of the sample sheets. Five shall be flexed in the machine direction and five in the cross machine direction.

4.4.4.4.6.1 Procedure. The specimens shall be equilibrated at -40 ± 5°F and each specimen shall be flexed once through 180 degrees (folded) at -40° ± 5°F.

4.4.4.4.7 Delamination. The test specimen (5-1/4 inch diameter disk) shall be lifted from a flat surface so that the lower backing layer is not held by the fingers. The test shall be repeated on the inverted disk. The test specimen shall be considered an integral unit if neither the top nor bottom backing layer separates completely from the core material.

5. PACKAGING

5.1 Packing, level B. A uniform quantity of filter material sheets of a single type shall be packed, not to exceed a gross weight of 40 pounds, in a W5c, style FTC, fiberboard box, conforming to PPP-B-636. The entire quantity of filter material that is to be packed within one box shall be inclosed within a heat-sealed water-vaporproof barrier bag fabricated from material conforming to MIL-B-131. Closure and test requirements for these barrier bags shall be the same as specified for method 1A-14 of MIL-P-116. The box shall be closed in accordance with the closure and reinforcing requirements for weather-resistant boxes in the appendix to PPP-B-636.



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

5.2 Interplant shipment (see 6.3). The filter material shall be packed to provide adequate protection from physical damage from the supply source to the first receiving activity for immediate use or further processing. Shipping containers shall be in compliance with the rules and regulations applicable to the mode of transportation.

5.3 Marking. In addition to any special marking required by the contract or order, the barrier bag and shipping containers (5.1) shall be marked in accordance with MIL-STD-129. Mark on each shipping container, "STORE IN A COOL, DRY LOCATION." Interplant shipment containers shall be marked in accordance with Fed. Std. No. 123 and shall include the contractor's name, address and contract number.

6. NOTES

6.1 Intended use. Type II filter material is intended for use in the CD V-805 Civilian Protective Mask; M2 Infant Protector; and the M18 Headwound Protective Mask. Type III filter material is intended for use in the M17, M17A1 and M17A2 Masks.

6.2 Ordering data. Acquisition documents should specify the following:

(a) Title, number, and date of this specification.
(b) Type and intended use of filter material.
(c) Sheet size of material.
(d) The laboratory to which samples are to be sent.
(e) Level of packing (see section 5).
(f) Preproduction:

(1) Time allowed for contractor submission of samples for Government test and evaluation after award of contract.
(2) Name and address of test facility and shipping instructions when testing is performed by the Government.
(3) Time required for the Government to notify the contractor whether or not sample is acceptable.

6.3 Interplant shipments. Packaging for interplant shipment is for supplies and materials that do not directly enter the military supply system. Typical interplant shipments are shipments from a vendor to a contractor or from a contractor to a military arsenal.

6.4 Manufacturing tests. The Government will fabricate filter elements from the preproduction sample of type III filter material in accordance with MIL-F-51425. These elements will be tested for "Plastisol edgeseal," "DOP smoke penetration," "Airflow resistance," and "Gas life" requirements of MIL-F-51425.



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

6.5 Non-military procurements. For non-military procurement, the procuring agency shall be responsible for preproduction sample inspection.

6.6 Significant places. For the purpose of determining conformance with this specification, an observed or a calculated value shall be rounded off "to the nearest unit" in the last right-hand place of figures used in expressing the limiting value, in accordance with the rounding-off method of the Recommended Practices for Designating Significant Places in Specified Limiting Values (ASTM Designation: E29).

Custodians:

Army - EA

Preparing activity:

Army - EA

Project No. 4240-A794



Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

**BUSINESS REPLY CARD**

FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
Armament Research and Development Center
US Army Armament, Munitions and Chemical Command
ATTN: DRSMC-TSC-S(A)
Aberdeen Proving Ground, MD 21010

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T20:50Z
Check the source to verify that this is the current version before use.

# STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

*(See Instructions – Reverse Side)*

| 1. DOCUMENT NUMBER | 2. DOCUMENT TITLE |
|---|---|
| MIL-F-0051095F(EA) | FILTER MATERIAL, GAS-AEROSOL, C18R1 |

| 3a. NAME OF SUBMITTING ORGANIZATION | 4. TYPE OF ORGANIZATION *(Mark one)* |
|---|---|
| | ☐ VENDOR |
| b. ADDRESS *(Street, City, State, ZIP Code)* | ☐ USER |
| | ☐ MANUFACTURER |
| | ☐ OTHER *(Specify)*: |

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation.

6. REMARKS

| 7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional | b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional |
|---|---|
| c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional | 8. DATE OF SUBMISSION *(YYMMDD)* |

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T20:50Z
Check the source to verify that this is the current version before use.