INCH POUND
MIL-DTL-15011K
w/AMENDMENT 2
29 April 2025
SUPERSEDING
MIL-DTL-15011K
w/AMENDMENT 1
31 March 2017

DETAIL SPECIFICATION

PALLETS, MATERIAL HANDLING, WOOD POST CONSTRUCTION, 4-WAY ENTRY

Reactivated after 09Apr13 and may be used for new or existing design acquisitions.

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE.

1.1. Scope. This specification covers the design, materials, fabrication requirements, and examinations of 4-way entry, wood post construction pallets.

1.2. Classification. The pallets covered by this specification are classified into the following types and classes as specified (see 6.3).

Type I	- Assembled
Type II	- Unassembled
Class 1	- Seasoned lumber (specified moisture content see 3.2.1.4)
Class 2	- Unseasoned lumber (unspecified moisture content see 3.2.1.4)
Style 1	- General storage, Size - 40” L X 48” W
Style 1A	- General storage, Size - 35” L X 45-1/2” W
Style 1B	- General storage, Size - 42” L X 53” W

Comments, suggestions, or questions on this document should be addressed to: U.S. Army DEVCOM Armaments Center, ATTN: FCDD-ACE-QSA , Picatinny Arsenal, New Jersey 07806-5000 or emailed to usarmy.pica.devcom-ac.list.ardec-stdzn-branch@army.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A FSC 3990

Distribution Statement A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS.

2.1. General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2. Government documents.

2.2.1. Specifications, standards, and handbooks. The following specifications, standards, and handbooks of the exact revision listed below form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract (see 6.3).

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-DTL-117	– Bags, Heat-Sealable
MIL-PRF-61002	– Labels, Pressure-Sensitive Adhesive, for Bar Coding

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-129	– Military Marking for Shipment and Storage
MIL-STD-1916	– DOD Preferred Methods for Acceptance of Products

(Copies of these documents are available online at: https://quicksearch.dla.mil.)

2.2.2. Other Government documents, drawings and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEFENSE AMMUNITION CENTER DRAWINGS

ACV00831	– Heat Treatment of Wooden Pallets, Skids, Filler Assemblies, and Dunnage Assemblies

(Copies of the above drawings are available online at: https://defenseammunitioncenter.army.mil/index.html or https://defenseammunitioncenter.army.mil/usatces/capdraw/drawings/miscitems.html or by email at usarmy.pica.devcom-ac.list.drawing-request-help-desk@army.mil.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

U.S. ARMY COMBAT CAPABILITIES DEVELOPMENT COMMAND – ARMAMENT CENTER (DEVCOM AC) DRAWINGS

13060578	– Preservative, Wood
13064136	– Wood Packing Material, Preservative Treated

(Copies of the above drawings are available by email at: usarmy.pica.devcom-ac.list.drawing-request-help-desk@army.mil.)

DEPARTMENT OF DEFENSE MANUAL

DoDM 4040.65	– Issue, Use, and Disposal of Wood Packaging Material (WPM)

(Copies of the above documents are available online at: https://www.esd.whs.mil/directives/issuances/dodm/.)

2.3. Non-government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

ASTM INTERNATIONAL

ASTM F1667/F1667M	– Standard Specification for Driven Fasteners: Nails, Spikes, and Staples
ASTM D3953	– Standard Specification for Strapping, Flat Steel and Seals
ASTM D4442	– Standard Test Methods for Direct Moisture Content Measurement of Wood and Wood-Based Materials
ASTM D6199	– Standard Practice for Quality of Wood Members of Containers and Pallets

(ASTM publications may be ordered online at https://www.astm.org.)

INTERNATIONAL PLANT PROTECTION CONVENTION
International Standards for Phytosanitary Measures (ISPM) 15:

ISPM 15	– Regulation of Wood Packaging Material in International Trade

(Copies of ISPM-15 are available online from https://www.ippc.int/en/core-activities/standards-setting/ispms/.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

2.4. Order of precedence. Unless otherwise specified herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS.

3.1. First article. When specified (see 6.3), a sample shall be subjected to first article inspection in accordance with 4.2.

3.2. Materials. The materials shall be as specified herein.

3.2.1. Wood. Unless otherwise specified, Style 1, Style 1A, or Style 1B pallets shall be constructed of any of the species of wood or combination thereof from Group IV of ASTM D6199 and from Group III only Red Maple (*Acer rubrum*).

3.2.1.1. Wood quality. Wood shall be free of decay which can be detected visually or by abnormal brashness (see 6.4) when picked with a sharp instrument. Lumber shall be free from insects, beetles, powder post beetle deterioration, and any other infestation at time of delivery that may result in subsequent pallet destruction. All hardwood and softwood component parts shall be absolutely free from bark. The quality of the wood selected for pallet construction shall also be free of defects set forth in 3.2.1.3.

3.2.1.2. Heat treatment. Unless otherwise specified, (see 6.3) pallets shall be fabricated from wood heat treated in accordance with Defense Ammunition Center Drawing ACV00831 which address the requirements of the International Standards for Phytosanitary Measures (ISPM 15).

3.2.1.3. Wood defects. The following defects shall apply to lumber as cut to size and assembled in the pallet.

3.2.1.3.1. Splits. Splits (see 6.4) caused by the expansion of season checks, shakes, and the driving of fasteners during assembly shall be no longer than the width of the boards at time of manufacture; however, these splits will propagate over time. At Lot acceptance of the pallets, the boards shall have splits that are no longer than what is detailed in TABLE 1. If there are multiple splits in one board, then the longest split shall be compared with TABLE 1. Regardless of the cause of splitting, the split shall be straddled with additional fasteners when the split is more than 3 inches in length. Open splits with visible fastener shanks or legs shall be limited as follows. No more than one open split with a visible fastener shank or leg per connection shall be permitted and not more than one-third of the components per pallet shall contain open splits with visible fastener shanks or legs at the completion of manufacture.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

TABLE I. Allowable length of splits at time of lot acceptance.

Pallet component	Component numbers from Figure 5, 6, or 7			Maximum allowable split length
	Style 1	Style1A	Style1B	
Outer top deckboards	1	1	1	W
Inner top deckboards	2,4	2,4	2,4	1/4 L
Outer stringer boards	7	7	7	W
Center stringer board	3	3	3	1/4 L
Outer bottom deckboards	8	8	8	W
Center bottom deckboard(s)	9	9	9	1/4 L
Outer posts	6	6	6	1/2 L, or 1/2 H, or 1/2 W
Center posts	5	5	5	1/2 L, or 1/2 H, or 1/2 W
Notes: L = Length of board, H = Height of board, W = Width of board				

3.2.1.3.2. Shakes. Shakes (see 6.4) shall be considered as splits (see 3.2.1.3.1) when the shake goes through the entire thickness of the board. Shakes running the full thickness of a component and longer than 3 inches shall be straddled with additional fasteners in the top and bottom deckboards.

3.2.1.3.3. Season checks. Season checks (see 6.4) which extend through the board shall be considered as splits (see 3.2.1.3.1). Season checks running the full thickness of a component and longer than 3 inches shall be straddled with additional fasteners in the top and bottom deckboards.

3.2.1.3.4. Knots and holes. Sound knots, loose knots, knot holes, and knot clusters shall be measured and restricted. The maximum allowable width of these knots shall be no more than 1/3 the width of the board in which contains them. The location of the knots shall be as close to the center of the board as possible. Deckboards and stringers shall not have knots, loose knots, knot holes, or knot clusters along their edges. Knots which occur in fastening areas shall not be used. For knot clusters, the sum of the width of the knots within a length equal to the width of the board in which they occur shall not exceed 1/3 the width of the board in which contains them.

3.2.1.3.5. Wane. Exposed wane (see 6.4) shall not be permitted on the outer edges of the outer deckboards, stringer boards, or posts. Wane is permissible on the surface or edge of the other components, but in no case shall fasteners be driven into or through this defect. The maximum allowable portion of the actual deckboard or stringer board with exposed wane shall not exceed one-quarter the width by two-thirds the thickness for the full length of the board. The maximum allowable portion of the actual deck board or stringer board with exposed wane shall not exceed one-quarter the width for the full length of the board.

a. 1 x 4: Min 3 inches clear wood for the width of the board
b. 1 x 6: Min 4.5 inches clear wood for the width of the board
c. 1 x 8: Min 6 inches clear wood for the width of the board.
(See actual dimensions in figures 5, 6, and 7)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

3.2.1.3.6. Warp. The bow in a member shall not exceed 1⁄16 inch per foot of length. The cup in a member shall not exceed 1⁄4 inch in an 8 inch width, or 1⁄8 inch in a 4 inch width, or a like proportion in other widths. The twist in a member shall not exceed 1⁄4 inch per foot of length in an 8 inch width, 1⁄8 inch per foot of length in 4 inch width, or a like proportion in other widths.

3.2.1.4. Moisture content. Unless otherwise specified, (see 6.3) the seasoned lumber used to construct Class 1 pallets at the time of manufacture and prior to the application of preservative treatment shall not be greater than 19 percent nor less than 12 percent of its oven dry weight as evidenced by the test specified in 4.4.1. For Class 2 pallets, the average moisture content for wood components is unrestricted.

3.2.2. Preservative treatment. Unless otherwise specified (see 6.3), the constructed pallet, or the finished wood parts thereof, shall be treated with preservative 13060578, Type I or III, in accordance with 13064136.

3.2.3. Fasteners. The type, style, length, diameter and quantity per joint are dependent upon the location and width and of the boards to be fastened. Fasteners shall be made of hardened steel with a minimum Rockwell hardness of HRC 35. The fasteners shall be mechanically deformed (drive screw) type conforming to ASTM F1667/F1667M, Type I, Style 16 – Pallet Nails (see 6.14). The fasteners shall be helically threaded with a minimum of 4 flutes. The fastener point may be diamond or chisel provided the width does not exceed the wire diameter. Length and size of fasteners shall be as specified in TABLE II.

TABLE II. Fastener schedule.

Style of pallet	Size: *Length x Shank Diameter* Figure 9 (REF)	ASTM F1667/F1667M identification
1, 1A, 1B	3-1/4” x 0.135”	NLPLD-10
1, 1A, 1B	2-1/4” x 0.120”	NLPLD-04
1, 1A, 1B	1-5/8” x 0.120” [1]	NLPLD-02
Notes: [1] Alternative nails: 1-1/2” x 0.120”, NLPLD-01, shall be used when 3/4” thick boards are utilized in construction.		

3.3. Construction. The construction of pallets shall be as specified herein.

3.3.1. Design and construction. The design and construction of pallets shall be as specified herein and in accordance with Figure 5, Figure 6, or Figure 7 as applicable.

3.3.2. Component details.

3.3.2.1. Deckboards. Deckboards shall be sized to a uniform thickness. Pre-drilling of deckboards of assembled pallets is at the option of the supplier. When specified in the contract or order, the top

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

deckboards shall have strap slots and shall extend the length of the board. See Figure 5, Figure 6, or Figure 7 for strap slot locations and applicable sizes and tolerances.

3.3.2.2. Stringer boards. Stringer boards shall be sized to a uniform thickness. See Figure 5, Figure 6, or Figure 7 for applicable sizes and tolerances.

3.3.2.3. Posts. Posts shall be cut square with sides and shall be sized to a uniform thickness. See Figure 5, Figure 6, or Figure 7 for applicable sizes and tolerances.

3.3.3. Assembly.

3.3.3.1. Component placement. All inner deckboards shall be parallel to the edges. All posts shall have the grain of the wood parallel to the length of the stringer boards and shall be positioned as shown on the applicable drawing. For construction details, see Figure 9 which illustrates the specific order of component placement and fasteners used for specific joints.

3.3.3.2. Assembly tolerances. Unless otherwise specified herein, tolerances for the assembled pallet shall be as specified in Figure 5, Figure 6, or Figure 7. Tolerances for the locations of fasteners shall be as specified in 3.3.3.3.

3.3.3.3. Fastener locations. Pallets shall be assembled with fasteners specified in 3.2.3. Fasteners shall be positioned not less than 3/4 inch from the ends or sides of deckboards, stringer boards, or posts. The remaining fasteners shall be uniformly spaced between them. Fasteners shall be driven in a staggered pattern. Staples shall be driven in two rows. Splits caused by fastening shall be supported by additional fasteners as specified in 3.2.1.3.1. All fasteners bent in driving shall be removed or broken off below the surface and replaced. The heads of fasteners shall be driven such that the head is flush to the surface of the board, or driven no more than 1/16 inch below the surface of the board.

3.4. Identification. Unless otherwise specified, (see 6.3) the pallets shall be marked by stamping, stenciling, branding, or roller coating with a material such that the markings are clearly visible, durable, contrasting, and legible. Markings that are not easily read shall be obliterated with a natural wood colored paint such as tan and the markings reapplied.

3.4.1. Manufacturer’s mark. The pallet shall have the manufacturer’s initials, month, and year of manufacture marked on at least one side of the center post for identification and reference for lot acceptance. The markings shall be 3/4 inch minimum in height (see Figure 5, Figure 6, or Figure 7).

3.4.2. Preservative treatment mark. Pallets shall be marked with preservative identification in accordance with 13064136. The marking shall be on the outside of the center post on both ends (see Figure 5, Figure 6, or Figure 7).

3.4.3. ISPM 15 certification mark. The pallet shall be marked to show the conformance to the IPPC standard. The applicable ISPM 15 compliance marking shall be marked in accordance with the contract requirements or the locations specified in Defense Ammunition Center Drawing ACV00831.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

3.5. Workmanship. Assembled pallets shall be free of dirt, grease, or oils. Assembled pallets shall be free of large splinters, exposed fastener points, or sharp edges that may cause injury when manually handled. The assembled pallet's fastener heads shall not be above flush as this will affect items being strapped to the decks of the pallet (see 3.3.3.3). In addition, unassembled pallets shall be free of defects which may affect field assembly.

3.6. Transportability. The following requirements are for the Type II unassembled pallets. The Type II unassembled pallets shall be packed in accordance with Figure 8. The fasteners to be supplied with the pallet components shall be separated by type and placed into individual bags that conform to a MIL-DTL-117, Type I, Class E, Style 1, 2 or 3 bag. The individual bags shall be marked in accordance with MIL-STD-129 using pressure-sensitive, water resistant labels in accordance with MIL- PRF-61002 such that they identify the type of fastener. The strapping utilized to tie down the components shall be ASTM D3953, Flat strapping, Type 1, Heavy Duty, Finish B (Grade 2), size 1-1/4" x 0.035", or 0.031", or 0.029".

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

4. VERIFICATION.

TABLE III. Requirement/verification cross-reference matrix.

Method of verification N/A – Not Applicable 1 – Analysis 3 – Examination 2 – Demonstration 4 – Test		Classes of verification A – First Article B – Acceptance							
Section 3 Requirement		Verification Methods					Verification Class		Section 4 Verification
		N/A	1	2	3	4	A	B	
3.1	First Article				X	X	X		4.2 / / 4.2.1
3.2	Materials	X							-
3.2.1	Wood				X		X	X	TABLE IV
3.2.1.1	Wood quality				X		X	X	TABLE IV
3.2.1.2	Heat treatment				X		X	X	TABLE IV
3.2.1.3	Wood defects	X							-
3.2.1.3.1	Splits				X		X	X	TABLE IV
3.2.1.3.2	Shakes				X		X	X	TABLE IV
3.2.1.3.3	Season checks				X		X	X	TABLE IV
3.2.1.3.4	Knots and holes				X		X	X	TABLE IV
3.2.1.3.5	Wane				X		X	X	TABLE IV
3.2.1.3.6	Warp				X		X	X	TABLE IV
3.2.1.4	Moisture content				X	X	X	X	TABLE IV / 4.4.1
3.2.2	Preservative treatment			X	X	X	X	X	4.4.2
3.2.3	Style 1, 1A, 1B pallet fasteners				X		X	X	TABLE IV
3.3	Construction	X							-
3.3.1	Design and construction				X		X	X	TABLE IV
3.3.2	Component details	X							-
3.3.2.1	Deck boards				X		X	X	TABLE IV
3.3.2.2	Stringer boards				X		X	X	TABLE IV
3.3.2.3	Posts				X		X	X	TABLE IV
3.3.3	Assembly	X							-
3.3.3.1	Component placement				X		X	X	TABLE IV
3.3.3.2	Assembly tolerances				X		X	X	TABLE IV
3.3.3.3	Fastener locations				X		X	X	TABLE IV
3.4	Identification				X		X	X	TABLE IV
3.4.1	Manufacturers marking				X		X	X	TABLE IV
3.4.2	Preservative marking				X		X	X	TABLE IV
3.4.3	ISPM-15 marking				X		X	X	TABLE IV
3.5	Workmanship				X		X	X	TABLE IV
3.6	Transportability				X		X	X	TABLE IV

4.1. Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.2)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

b. Conformance inspection (see 4.3)

4.1.1. Verification conditions. Unless otherwise specified, all verifications shall be performed in accordance with the test methods and conditions specified in section 4.4.

4.1.2. Classification of characteristics. For examinations and tests cited herein or when required by contract; critical, major, and minor characteristics are defined in MIL-STD-1916.

4.2. First article inspections. When specified, (see 6.3) a first article inspection shall be preformed when a first article sample is required (see 3.1). The first article sample shall consist of three consecutively produced pallets of one grade, type and style (see Figure 5, Figure 6, or Figure 7 as applicable) which has been produced using the same production processes, procedures and equipment as will be used in fulfilling the contract. These sample pallets shall be manufactured within 30 days of inspection. All materials shall be obtained from the same sources of supply as will be used in regular production.

4.2.1. First article rejection. If any item of the sample fails to comply with any of the applicable requirements, the first article sample shall be rejected.

4.3. Conformance inspection. The sample pallets shall be subjected to conformance verification in accordance with TABLE IV. Sampling plans and procedures for Major and Minor defects shall be in accordance with MIL-STD-1916 except that continuous sampling plans may be used if approved by the procuring activity.

4.3.1. Lot formation. Lot formation shall be in accordance with the formation and identification of lots or batches in MIL-STD-1916.

4.3.2. Examination. Sampling plans and procedures for Major and Minor defects shall be in accordance with MIL-STD-1916 except that continuous sampling plans may be used if approved by the procuring activity. The attribute sampling plan required for the examination for defects in TABLE IV shall be in accordance with MIL-STD-1916, using Verification Level IV for major characteristics and Level II for minor characteristics unless otherwise noted.

4.3.3. Conformance rejection. If any sample fails to comply with the conformance inspection requirements, the lot shall be rejected.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

TABLE IV. Inspection by classification of characteristics

Classification	Examination or Test	Conformance Criteria	Requirement Paragraph	Inspection Method
Critical	None defined			
Major				
101	Wood species not Group IV from ASTM D6199 or Red Maple (*Acer rubrum*)	100%	3.2.1	Material Certificate of Conformance (COC)
102	Wood not free of decay	100%	3.2.1.1	Visual
103	Wood not free from bark	100%	3.2.1.1	Visual
104	Wood heat treatment lacking presence	100%	3.2.1.2	Visual
105	Deleted			
106	Fasteners not the correct size, diameter, or incorrect hardness value	VL-IV	3.2.3	COC
107	Overall opening for materials handling equipment not compliant	VL-IV	3.3.1	Gauge
108	Strap slots (if specified) missing in top deckboards	VL-IV	3.3.2.1	Visual
109	Preservative marking missing	VL-IV	3.4.2	Visual

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

TABLE IV. Inspection by classification of characteristics - Continued

Classification	Examination or Test	Conformance Criteria	Requirement Paragraph	Inspection Method
Major (cont)				
110	ISPM-15 marking missing	VL-IV	3.4.3	Visual
111	ISPM-15 marking not clearly visible, durable, contrasting or legible	VL-IV	3.4	Visual
112	Type II pallet components loose in bundled unitized load	VL-IV	3.6	Visual
113	Overall length and width of pallet within tolerance	VL-IV		Gauge
Minor				
201	Split in component not longer than specified	VL-II	3.2.1.3.1	Gauge
202	Knots, loose knots, knot holes, and knot clusters not within specified limits	VL-II	3.2.1.3.4	Gauge
203	Knots, loose knots, knot holes, and knot clusters located along edge of deckboards or stringers	VL-II	3.2.1.3.4	Visual
204	Wane along outer edges of outer deckboards, stringers, or posts not within specified limits	VL-II	3.2.1.3.5	Visual

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

TABLE IV. Inspection by classification of characteristics - Continued

Classification	Examination or Test	Conformance Criteria	Requirement Paragraph	Inspection Method
Minor (cont)				
205	Warp in excess of specified limits	VL-II	3.2.1.3.6	Gauge
207	Deleted			
208	Top and bottom deckboard thicknesses not compliant	VL-II	3.3.2.1	Gauge
209	Stringer boards thickness not compliant	VL-II	3.3.2.2	Gauge
210	Posts not cut square	VL-II	3.3.2.3	Gauge
212	Spacing of the top deckboards not within specified limits	VL-II	3.3.3.1	Gauge
213	Fasteners driven into boards less than specified limit from the edges of the boards	VL-II	3.3.3.3	Gauge
214	Fasteners driven into boards less than specified limit from the ends of the boards	VL-II	3.3.3.3	Gauge
215	Fastener heads above flush	VL-II	3.3.3.3	Gauge

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

TABLE IV. Inspection by classification of characteristics - Continued

Classification	Examination or Test	Conformance Criteria	Requirement Paragraph	Inspection Method
Minor (cont)				
216	Splits longer than specified limit not straddled by additional fasteners	VL-II	3.3.3.3	Gauge, Visual
218	Manufacturers marking missing	VL-II	3.4.1	Visual
219	Manufacturers marking not clearly visible, durable, contrasting or legible	VL-II	3.4	Visual
220	Preservative marking not clearly visible, durable, contrasting or legible	VL-II	3.4	Visual
221	Assembled pallet not free of dirt, grease, or oils	VL-II	3.5	Visual
222	Assembled pallet not free of large splinters, exposed fastener points, or sharp edges	VL-II	3.5	Visual
223	Strapping material for bundling Type II pallets not as specified	VL-II	3.6	COC
224	Deckboard width assembly not meeting dimensional tolerances	VL-II	Figure 5, 6, or 7	4.4.3
225	Overall pallet assembly out of square	VL-II	Figure 5, 6 or 7	4.4.7

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

4.4. Methods of inspection. (See 6.6).

4.4.1. Moisture content prior to construction. One sample each of lumber blanks used for the top and bottom deckboards, stringer boards, and posts shall be tested to represent the material used in pallet construction. The moisture content shall be tested with an electric type moisture meter (see 6.15) or by one of the oven drying methods of ASTM D4442. If a moisture meter is used, the meter shall be capable of reading moisture contents as high as 30 percent with a minimum accuracy of plus or minus one percent of true moisture content. Three readings shall be taken from each blank, and if any one of the three measurements of moisture content fails to meet the requirements of 3.2.1.4, the lot shall be rejected.

4.4.2. Preservative treatment. Verify that the constructed pallet, or the wood parts thereof, comply with 13064136 requirements and inspections.

4.4.3. Deleted.

4.4.4. Deleted.

4.4.5. Deleted.

4.4.6. Deckboard width. Measurements for overall width of deckboards shall be performed by measuring across the fastener area with an ordinary tape measure. There is a potential of misrepresentation of the deckboard width if the measurements are taken at mid-span. The wood members tend to shrink due to wood cell moisture loss after construction which could cause boards to be nonconforming.

4.4.7. Pallet squareness. Measurements for overall pallet squareness shall be performed by measuring the diagonals from one corner to another with an ordinary tape measure.

5. PACKAGING.

5.1. Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order. When packaging of materiel is to be performed by DOD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. Notes.

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1. Deleted.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

6.2. Intended use. Items covered by this specification are intended for use in the palletization of military items and it has no commercial application.


6.3. Procurement requirements. Acquisition documents should specify the following:

a. Title, number and date of this specification and all reference documentation cited in this specification (see 2.2.1). The referenced documents will be those current at the time of solicitation or contract.
b. Requirements for submission of first article sample (see 4.2).
c. Type, class, style, and size of pallet (see 1.2).
d. When moisture content is specified (see 3.2.1.4).
e. When heat treatment is required (see 3.2.1.2).
f. When preservative treatment is required (see 3.2.2).
g. When pallets are to be marked (see 3.4).
h. Requirements for acceptance inspection equipment designs (see 6.5).

6.4. Wood defect definitions.

brash – decay characteristic, which is the breaking of the grain without splintering.


season checks – separations of the wood that normally occur across or through the annual rings, usually as a result of seasoning (see Figure 1).

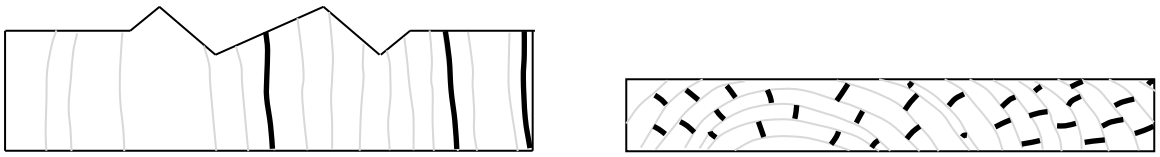

Top of board End of board

Figure 1. Depiction of season checks

shake – separation or a weakness of fiber bond, between or through the annual rings, that is presumed to extend lengthwise without limit (see Figure 2).

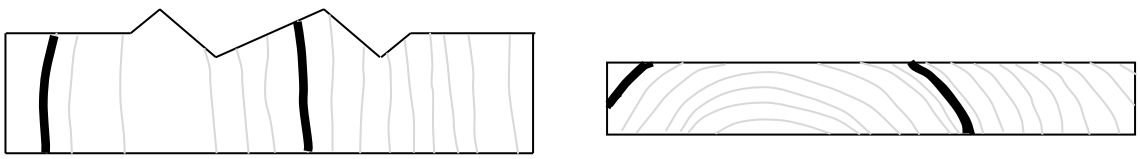

Top of board End of board

Figure 2. Depiction of shakes

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

split – separation of the wood through the piece to the opposite surface or to an adjoining surface caused by tearing apart of the wood cells (see Figure 3).

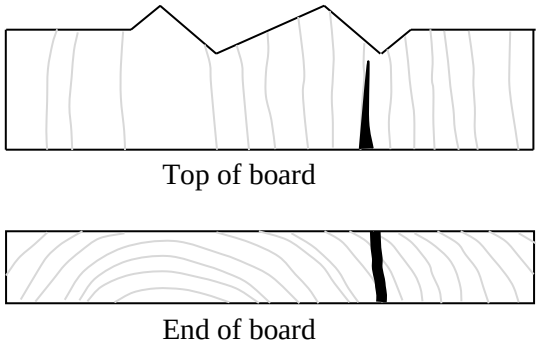


Figure 3. Depiction of splits

wane – bark or lack of wood on the edge or corner of a piece of lumber, regardless of cause; however, manufactured eased edges will not be considered as wane. (see Figure 4).

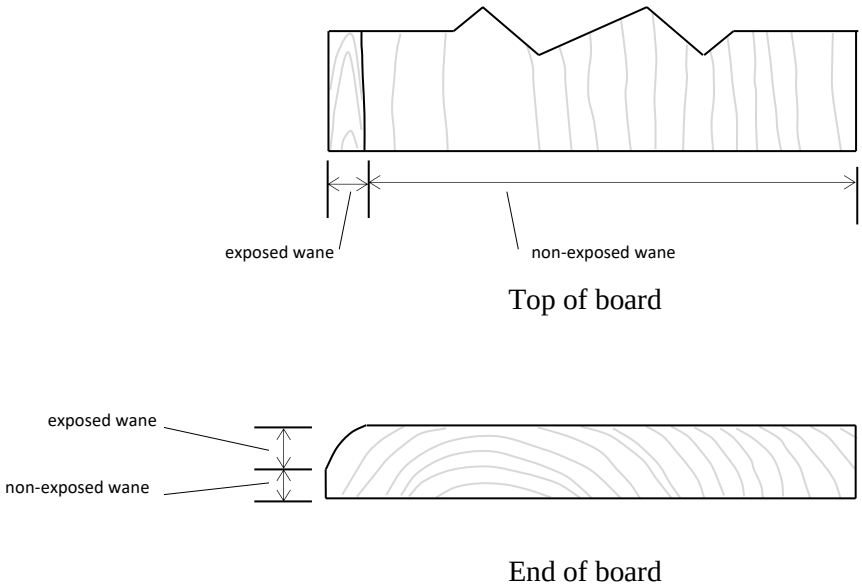


Figure 4. Depiction of wane

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

6.5. Submission of contractor inspection designs for approval. Contractor should submit copies of designs as required to: Commander, U.S. Army DEVCOM AC, ATTN: FCDD-ACE-QMD, Picatinny Arsenal, New Jersey 07806-5000.

6.6. Equivalent test method. Prior approval of the contracting officer is required for use of equivalent test methods. A description of the proposed method should be submitted through the Contracting Officer to: Commander, U.S. Army DEVCOM AC, ATTN: FCDD-ACE-QMD, Picatinny Arsenal, New Jersey 07806-5000. This description should include but not be limited to the accuracy and precision of the method, test data demonstrating the accuracy and precision and drawings of any special equipment required.

6.7. Deleted.

6.8. Deleted.

6.9. Deleted.

6.10. Deleted.

6.11. Deleted.

6.12. Deleted.

6.13. Deleted.

6.14. Fasteners. The ASTM F1667/F1667M, Type I, Style 16 – Pallet Nails may be obtained from Maze Nails, 100 Church St., Peru, IL 61354 08865 or equivalent facility.

6.15. Moisture meter. Electric-type moisture meters may be either the resistance type or radio frequency power loss type except that only the resistance type may be used on rough sawn will be acceptable, except for discoloration that would interfere with marking on the outside of the container or the pallet.

6.16. The Styles 1, 1A, and 1B pallets comply with STANAG 2828 to include exceptions for the U.S.to weight and size, as applicable.

6.17. Overview of changes. This amendment incorporates R22K3008 which updated the fastener style as specified in accordance with ASTM F1667/F1667M Standard Specification for Driven Fasteners Nails, Spikes, and Staples, (2021a). This amendment also incorporates R24K2004 which added Red Maple (*Acer rubrum*) to the list of allowable wood species in paragraphs 3.2.1 and TABLE IV, Major 101.

6.18. Subject term (key word) listing

Deckboard
Stringer board

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

Post
Fastener
Preservative
Copper-8-quinolinolate
Zinc Naphthenate
Copper Naphthenate
Moisture content
Red Maple (*Acer rubrum)*

6.19. Amendment notations. The margins of this specification are marked with vertical lines to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

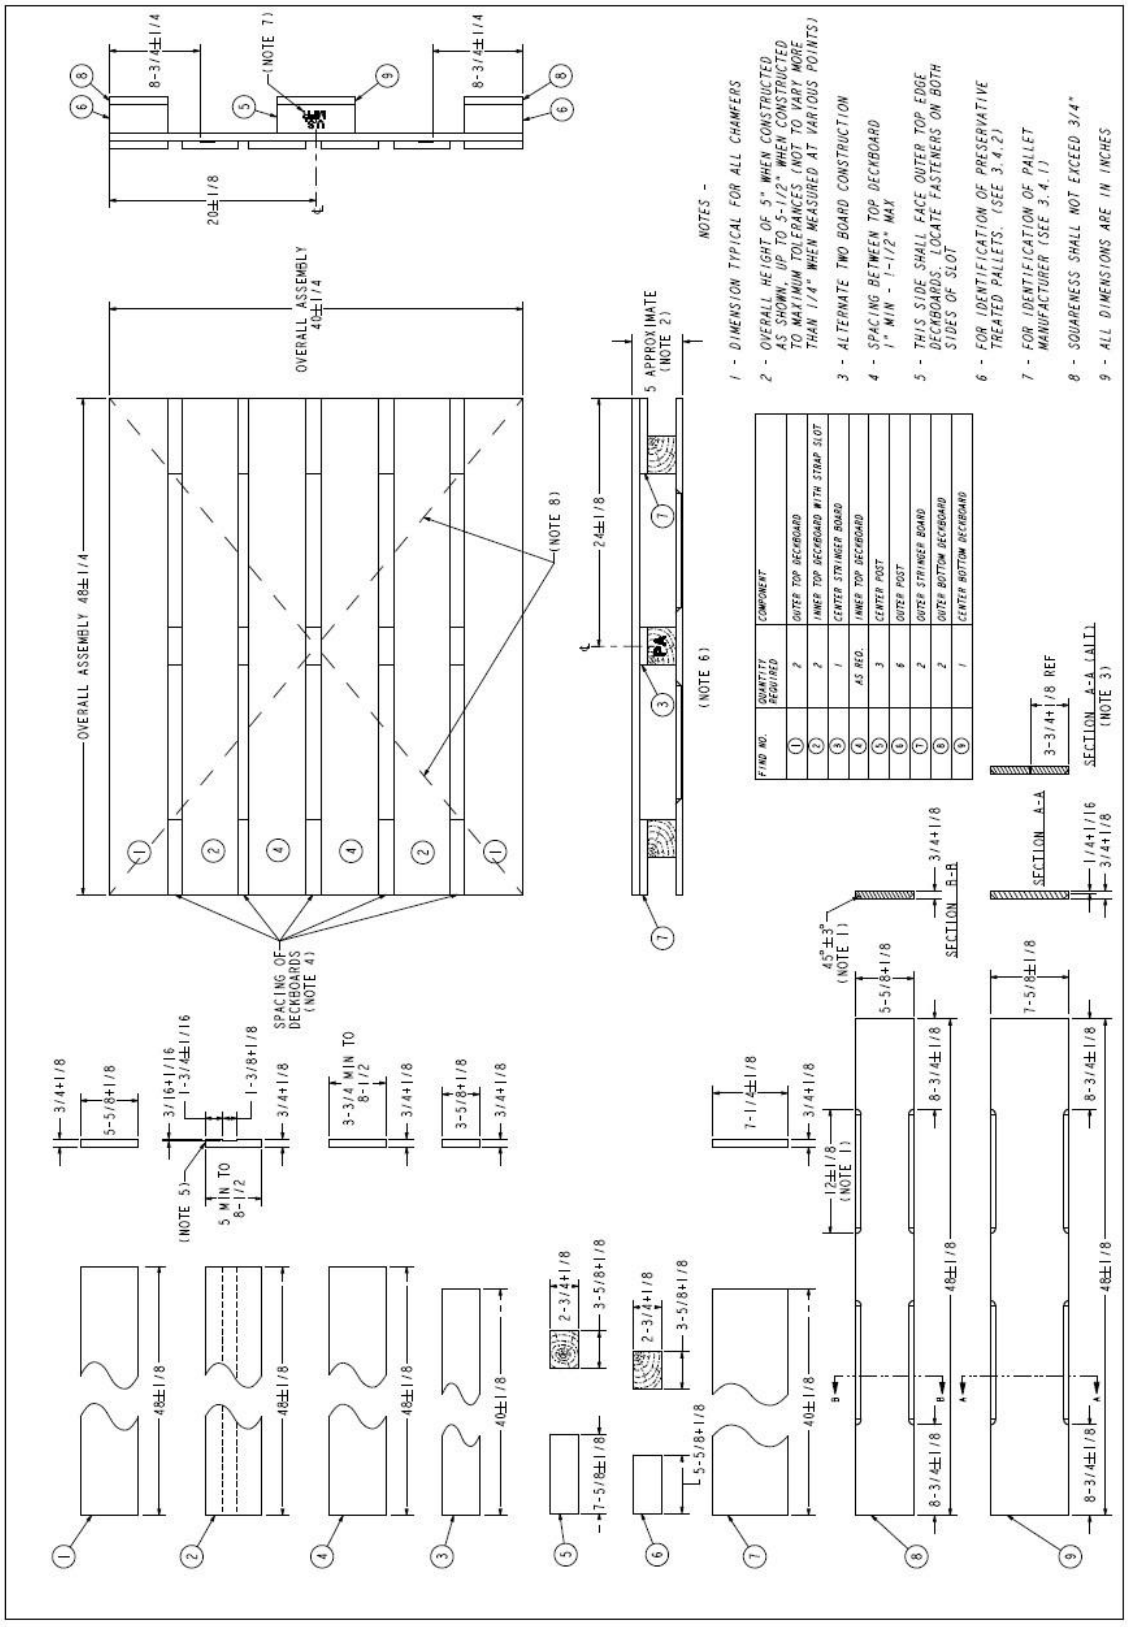


Figure 5. Style 1, 40” x 48” Pallet Assembly

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

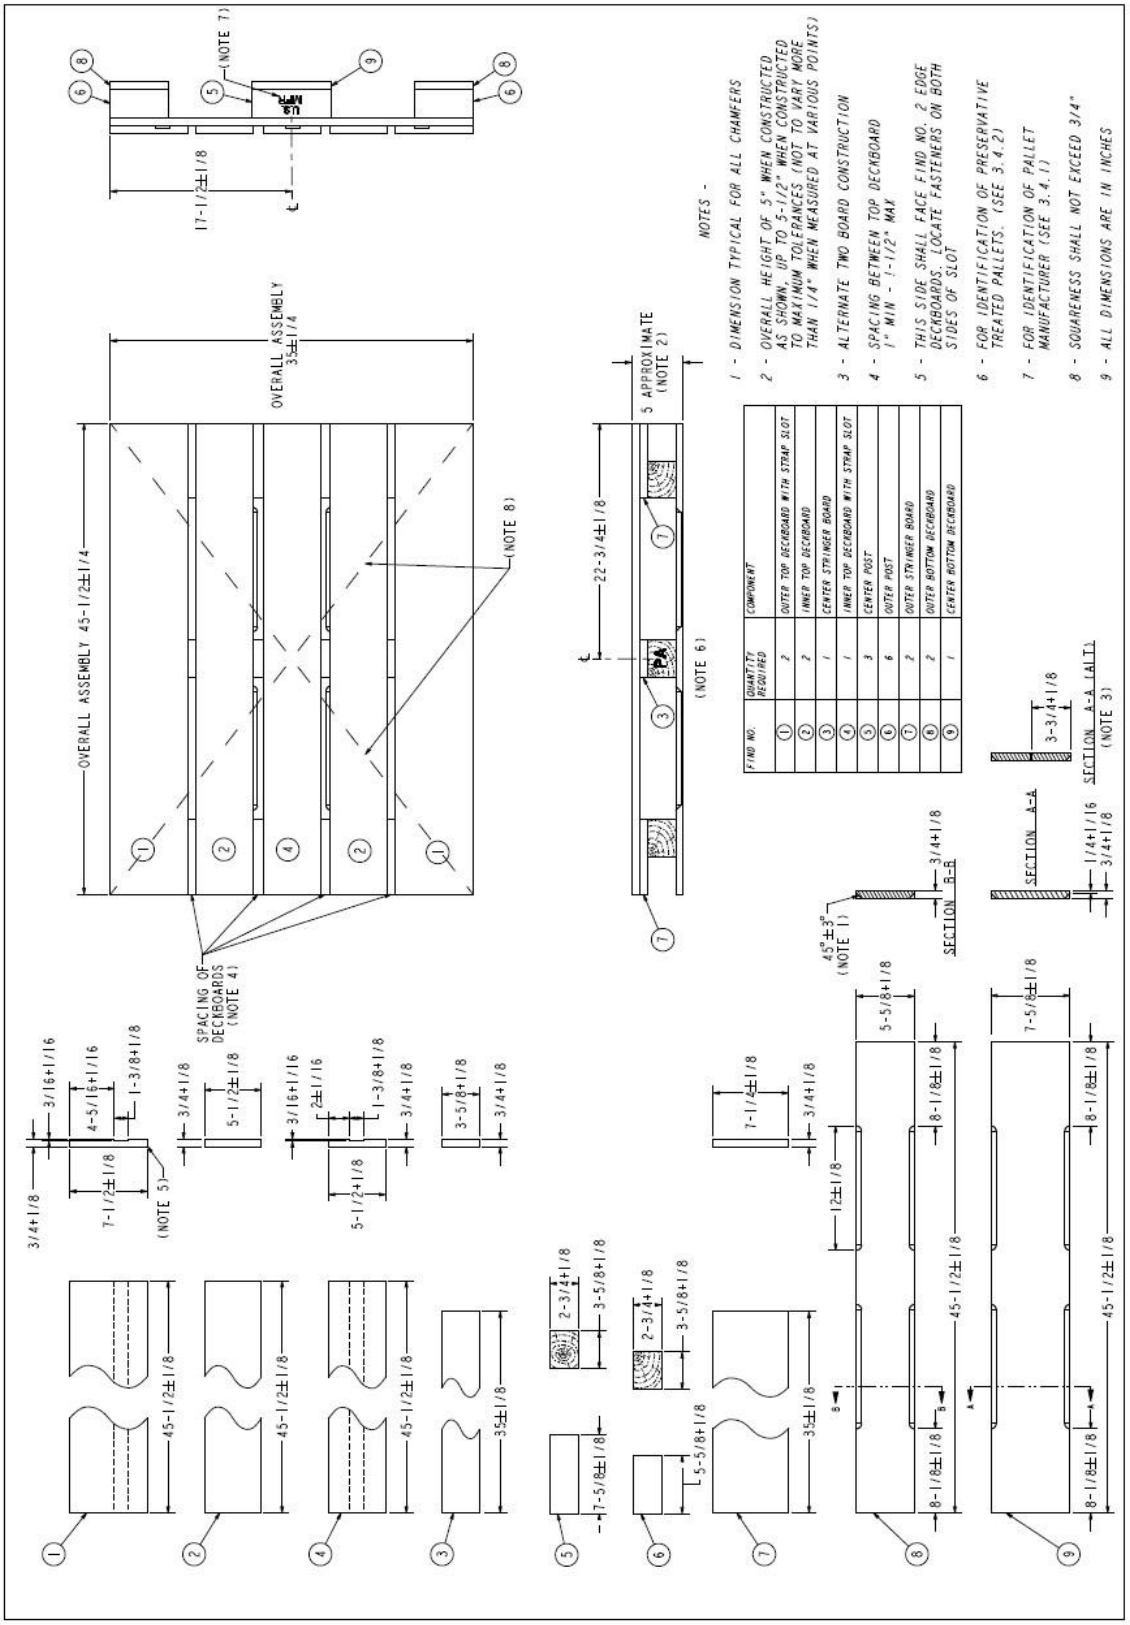


Figure 6. Style 1A, 35” x 45-1/2” Pallet Assembly

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

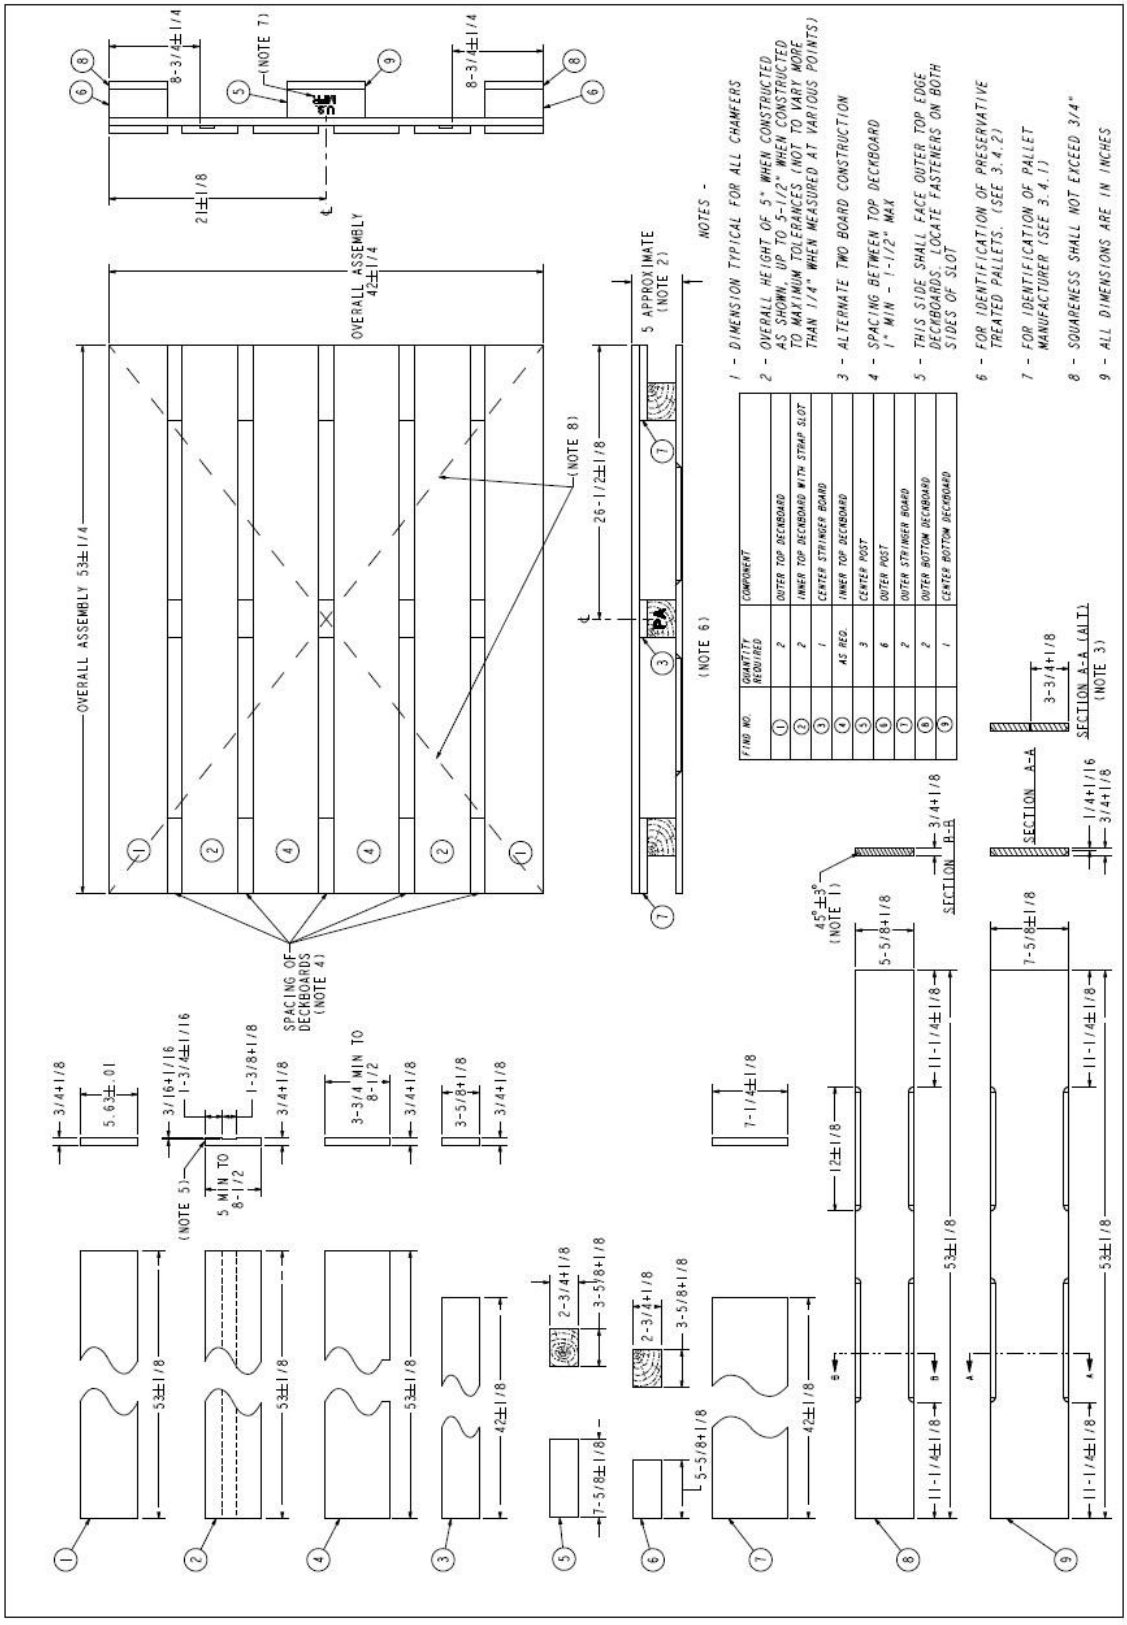


Figure 7. Style 1B, 42" x 53" Pallet Assembly

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

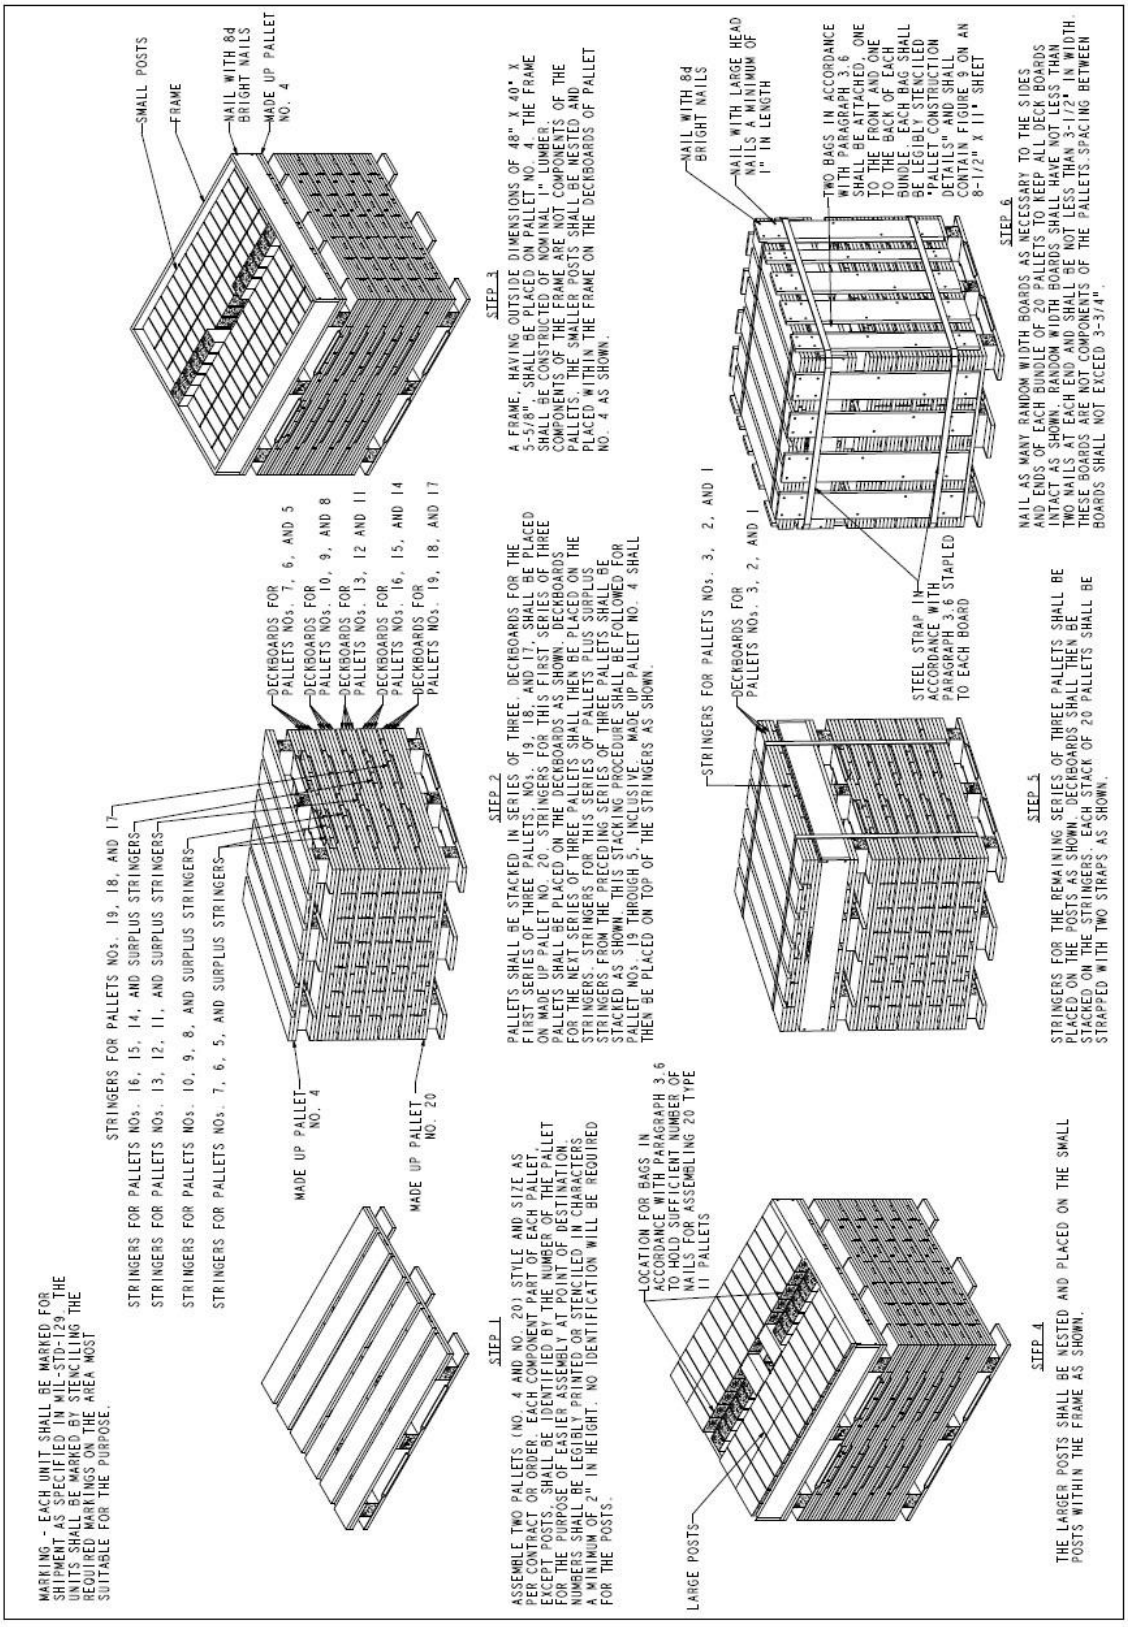


Figure 8. Type II Pallet, Method of unitizing 20 pallets for domestic and overseas shipments

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

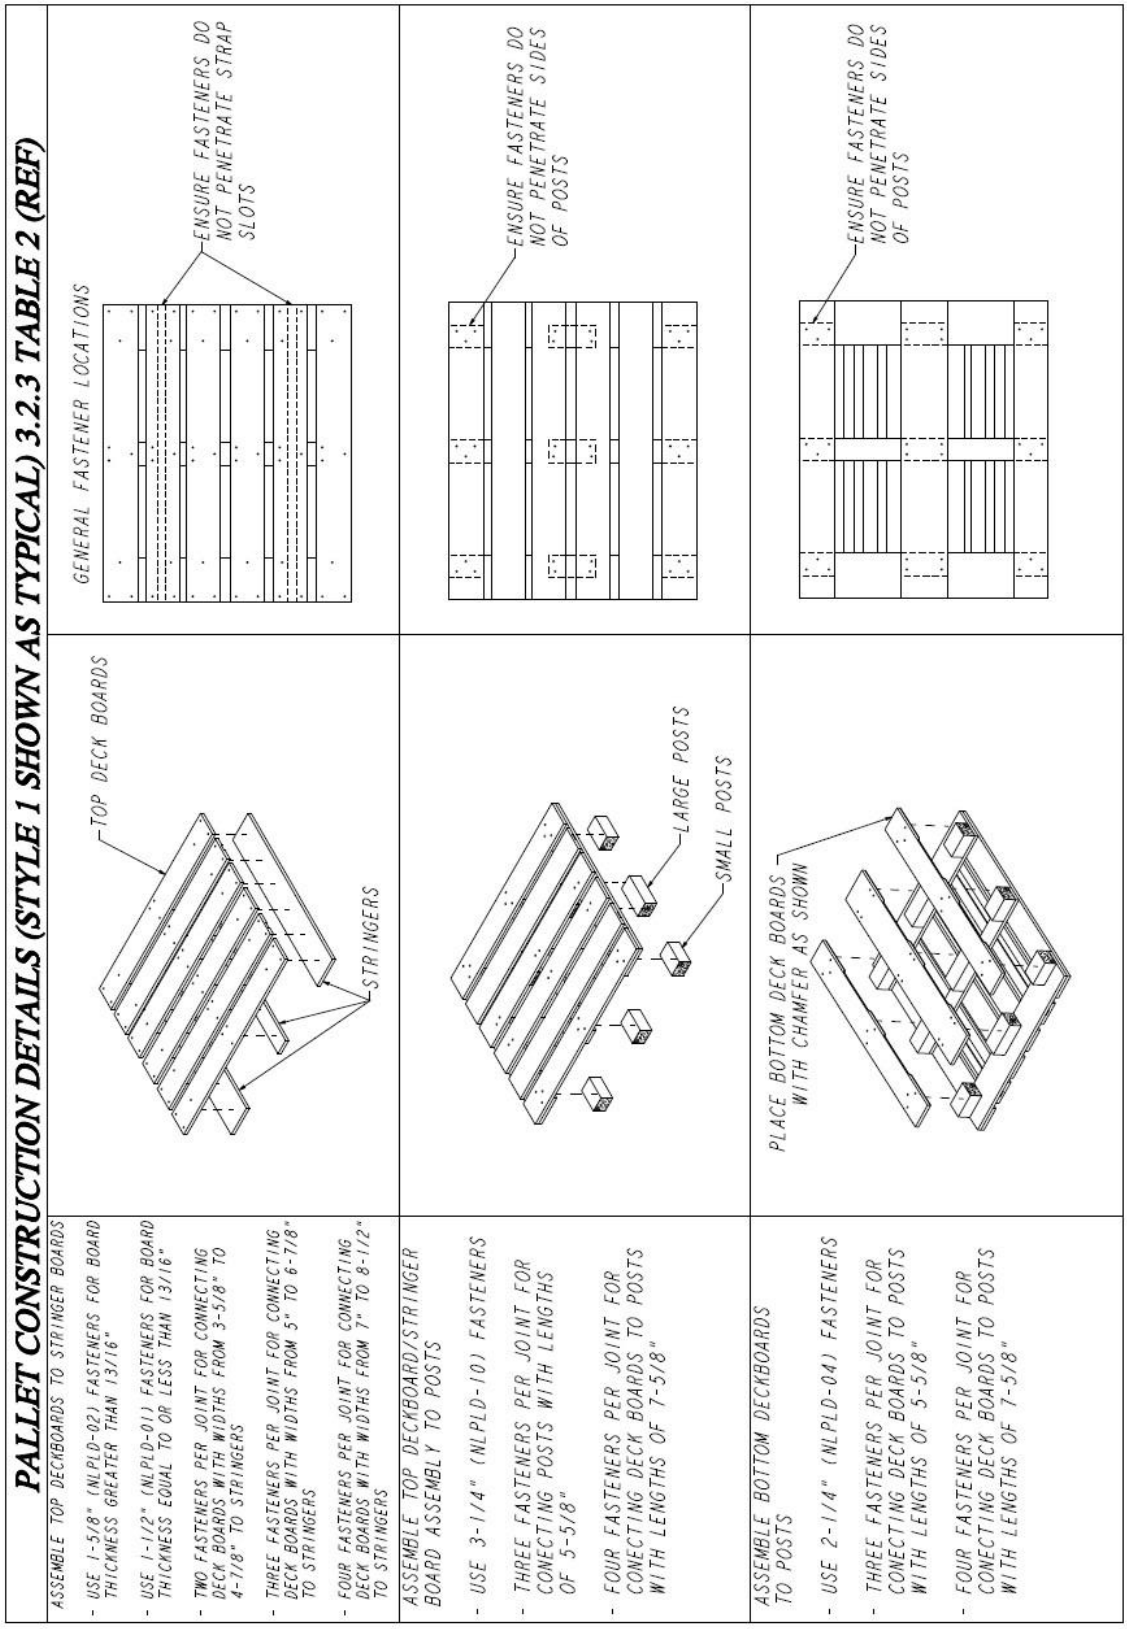


Figure 9. Pallet construction details

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.

CONCLUDING MATERIAL

CUSTODIANS:

Army - AR
Navy – OS
Air Force - 184

Review Activities:
Army – EA, SM
Navy – MC, SA
Air Force – 69

Preparing Activity:

Army – AR

(Project 3990-2025-003)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T05:21Z
Check the source to verify that this is the current version before use.