MIL-D-87030B(SH)
11 December 1986
SUPERSEDING
MIL-D-87030A(SH)
21 June 1978
(See 6.9)

MILITARY SPECIFICATION

DIVERS DRESS SUIT (MK-12)

This specification is approved for use within the Naval Sea Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for the MK-12 diver's dress suit.

1.2 Classification. The suit shall be of one type in the following sizes as specified (see 6.2.1).

1 (Small)
2 (Medium)
3 (Large)
4 (X-Large)
5 (XX-Large)

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. The following specifications and standards form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DoDISS) and supplement thereto, cited in the solicitation.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Naval Sea Systems Command, SEA 5523, Department of the Navy, Washington, DC 20362-5101 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 4220
DISTRIBUTION STATEMENT A Approved for public release; distribution unlimited

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

SPECIFICATIONS

FEDERAL

DDD-L-20 - Label: for Clothing, Equipage, and Tentage (General Use).
PPP-B-601 - Boxes, Wood, Cleated-Plywood.
PPP-B-636 - Boxes, Shipping, Fiberboard.

STANDARDS

FEDERAL

FED-STD-191 - Textile Test Methods.
FED-STD-751 - Stitches, Seams, and Stitchings.

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.

(Copies of specifications and standards required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting activity.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted shall be those listed in the issue of the DoDISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed *in* the DoDISS shall be the issue of the nongovernment documents which is current on the date of the solicitation,

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 395 - Standard Test Method for Rubber Property - Compression Set. (DoD adopted)
D 412 - Standard Test Method for Rubber Properties in Tension. (DoD adopted)
D 1056 - Standard Specification for Flexible Cellular Materials - Sponge or Expanded Rubber. (DoD adopted)
D 3951 - Standard Practice for Commercial Packaging. (DoD adopted)

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Nongovernment standards and other publications are normally available from the organizations which prepare or which distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein (except for associated detail specifications, specification sheets or MS standards), the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 First article. When specified in the contract or purchase order, a sample shall be subjected to first article inspection (see 4.3 and 6.3).

3.2 Materials.

3.2.1 Chloroprene foam. The chloroprene foam for the suit shall be pigmented black. Gas expanded chlorinated cellular rubber, having a closed cell structure shall conform to classification RE-41-EI of ASTM D 1056 and other requirements specified herein when tested as specified in 4.6.1. The chloroprene foam shall have a minimum density of 10 and a maximum density of 20 pounds per cubic foot (lb/ft^3). The foam thicknesses used for the suit shall be 1/4 ± 1/16 inch thick with no skin on both sides; 1/4 ± 1/16 inch thick with skin on one side only; 1/8 ± 1/16 inch with no skin on both sides. The foam material shall conform to table I when tested as specified in 4.6.1.

TABLE I. Foam .

Characteristic	Requirement
Compression set under constant deflection	25 percent ❑aximum
Compression deflection	2.0 lb/in^2 minimum 7.0 lb/in^2 maximum
Water absorption	6.0 percent maximum
Accelerated aging shrinkage	5.0 percent ❑aximum in each direction
Tensile stress	135 lb/in^2 maximum (500 percent elongation)

3.2.2 Knitted stretch cloth. The stretch cloth shall be circular knit from 100 percent continuous filament nylon yarn and conform to the physical requirements of table II when tested as specified in 4.6.1.

TABLE II. Knitted stretch cloth.

Knitted stitch	Yarn per inch (minimum) wales courses	Weight, ounce per sq yd	Elongation percent wales courses	color
Jersey	36 by 38	2.4 ± 0.2	150 min 225 min 225 max 400 max	Black (outside) Blue (inside)

3.2.2.1 Colorfastness. The knitted cloth shall show fastness to laundering, crocking and perspiration equal to or better than the standard sample. When no standard sample is available the finished material shall show a minimum of good fastness to laundering, perspiration and a Munsell Value for dry and wet crocking not lower than 8.5. Testing shall be as specified in 4.6.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

3.2.3 Lamination. The stretch cloth shall be laminated to the different foam thicknesses as follows:

(a) 1/4 inch thick foam, which has two cut surfaces, stretch cloth laminated to both sides.
(b) 1/4 inch thick foam, which has one cut surface and one skin surface, stretch cloth laminated to cut surface side.
(c) 1/8 inch thick foam, which has two cut surfaces, stretch cloth laminated to one cut surface. The cloth shall be laminated to the chloroprene foam by an adhesive or other process which conforms to the physical requirements of the laminated foam material. The adhesive used shall be non-toxic, non-irritant and free from objectionable odor. The fabric backed (laminated) side shall be smooth and free of wrinkles or puckers and show no sign of blocking, tackiness or adhesive strike-through when tested as specified in 4.6.1.

3.2.3.1 Laminated foam. The finished laminated foam material shall conform to table III when tested as specified in 4.6.1.

TABLE III. Laminated foam.

Characteristic	Requirement
Laundering resistance	No delamination
Adhesion, original	8.0 pounds minimum per 2 inches
Adhesion, after laundering	8.0 pounds minimum per 2 inches
Adhesion, after aging	8.0 pounds minimum per 2 inches
Blocking	NO blocking

3.2.4 Adhesive cement. The cement used to seal the seams and reinforcement pieces shall be chloroprene compound.

3.2.5 Cemented seams. The abutted and cemented seams (without reinforcement pieces) shall have an initial and after aging minimum breaking strength of 35 pounds per 2 inches when tested as specified in 4.6.1.

3.2.6 Reinforced seams. The abutted and cemented seams reinforced with 1/8 inch foam shall have an initial and after aging minimum adhesion of 5.0 pounds per inch when tested as specified in 4.6.1.

3.2.7 Fused seams. The abutted and cemented seams reinforced with seal tape shall have an initial and after aging minimum adhesion of 10.0 pounds per inch when tested as specified in 4.6.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

3.2.8 Slide fastener. The slide fastener to be used for the back zipper closure shall be a water and gas proof zipper conforming to either the Dynat style size II (sol) zipper with neoprene coated tape or the Talon style 17310 EB size 84 type I 0.025 black or an equal item (see 6.4). The zipper shall be 33 inches long for all sizes. It shall be supplied with a wire stirrup pull. The thong shall be constructed of either nylon or cotton webbing, black in color and have a minimum length of 5 inches (see 6.5).

3.2.9 Seal tape. The material for the seal tape shall be a fusible nylon knit, 1 inch in width consisting of knitted stretch cloth as specified in 3.2.2 and a polyamide resin system that, when heat sealed, achieves a minimum adhesion strength as specified in 3.2.7.

3.2.10 Size numbers. The material for the sleeve size numbers shall conform to 3.2.1 and shall be l/8-inch thick having yellow nylon on face side and black nylon on back side.

3.2.11 Butyl rubber. The material used for the neck gasket shall be a butyl rubber compound having a thickness of 0.060 ± 0.005 inch and a durometer harness number of 65 ± 5 when tested as specified in 4.6. Both surfaces of the butyl rubber shall have fabric imprinted surfaces to provide good gripping characteristics.

3.2.12 Label. Each suit shall have a combination, identification, size and instruction label conforming to type I, class 14 of DDD-L-20. The inscription shall be as follows:

"DIVER'S DRESS SUIT (MK12)
SIZE: 2 (MEDIUM) (EXAMPLE)
STOCK NO: 4220-00-000-0000 (EXAMPLE)
CONTRACT NO: DLA 100-00-0-0000 (EXAMPLE)
NAME OF SUPPLIER:"

"INSTRUCTIONS

1. Wash with fresh water and a mild soap solution after each use.
2. Allow to dry before storage.
3. Hang suit, full length, on hanger. The hanger shall be placed in shoulder area with hook portion of hanger protruding through neck ring.
4. Store in cool area away from hot objects.
5. Do not allow contact with chemicals that may harm neoprene foam rubber."

3.2. 12.1 Label position. The label shall be positioned as specified in 3.6.16 and secured to the suit with a suitable adhesive.

3.2.13 Recovered materials. Unless otherwise specified herein, all equipment, material, and articles incorporated in the products covered by this specification shall be new and may be fabricated using materials produced from recovered materials to the maximum extent practicable without jeopardizing the intended *use. The* term "recovered materials" means materials which have been collected or recovered from solid waste and reprocessed to become a source of raw materials, as opposed to virgin raw materials. None of the above shall be interpreted to mean that the use of used or rebuilt products is allowed . under this specification unless otherwise specifically specified.

Source: https://assist.dla.mil -- Downloaded: 2026l0-23T11:36Z
Check the source to verify that this is the currentversion before use.

3.3 Leakage. Each suit shall be tested for leaks in accordance with 4.8.1. One leak per suit is allowed and shall be repaired only once in accordance with 4.8.2. If the suspect area shows further leakage after repair, the suit shall be rejected. Any suit containing more than one leak shall be rejected.

3.4 Fabricate. The dress suit shall have a zipper closure across the back shoulder area, attached boots and neck gasket ring. The seams shall be cemented and reinforced on the inside with seal tape (see figure 1).

3.5 Patterns. Standard patterns will be furnished by the Government. The standard patterns shall not be altered in any way and shall be used for cutting the contractor's working patterns. The working patterns shall be identical to the standard patterns.

3.5.1 Pattern parts. The component parts of the dress suit shall be cut from the material specified and in accordance with the following pattern parts required for the manufacturing process as specified in table IV.

TABLE IV. Pattern parts,

Material	Nomenclature of pattern parts	Cut parts
Laminated foam, both sides, 1/4 inch thick	Back piece	1
	Front chest piece	1
	Side body piece	2
	Leg and groin piece	2
	Back yoke piece	1
	Sleeve	2
	Boot right	1
	Boot left	1
Laminated foam, one side, 1/8 inch thick	Neck piece	2
	Back zipper (top ply)	1
	Back zipper (bottom ply)	1
Laminated foam, one side, 1/4 inch thick	Gauntlet sleeve	2
Laminated foam, one side, 1/8 inch thick	Back reinforcement piece	1
	Front reinforcement piece	1
	Reinforcement strip	1
	Neck gasket ring	1
	Size numbers	
Butyl rubber Laminated foam, both sides, 1/8 inch thick	1	2
	2	2
	3	2
	4	2
	5	2
Template	Zipper panel marker	

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

3.6 Manufacturing requirements. The suits shall be manufactured in accordance with the operation requirements specified in 3.6.1 through 3.6.23. The contractor is not required to follow the exact sequence of operations provided that the finished suits are identical to that produced by the following sequence of operations.

3.6.1 Cutting. The component parts of the dry suit shall be cut in accordance with the patterns furnished specifying size and shape for proper assembly of all component parts.

3.6.2 Replacement of defective components. During the spreading, cutting and manufacturing process, components having material defects or damages that are classified as defects in 4.5.2 shall be removed from production and replaced with nondefective and properly matched components.

3.6.3 Procedure for seam cementing. Procedure for seam cementing shall be as follows:

(a) Check surface of the seams ensuring they are clean, dry and free from grease and oil.
(b) Each surface shall be given two coats of cement (pre-cementing) allowing 10 minutes drying time between coats. The surfaces shall be rechecked ensuring the pre-cementing procedure has completely covered the cellular structure of the foam.
(c) The third and final coat of cement shall completely cover the first two coats. Allow this coat to become tacky and press the cemented edges together firmly. Turn to inside and press the back side of the seam together. After pressing the seam inside and outside, the seam shall be pinched together inside and outside. Upon completion of the suit all seams inside and outside shall be touched up with cement.

3.6.4 Procedure for reinforcement piece cementing. Procedure for reinforcement piece cementing shall be as follows:

(a) Check surfaces ensuring they are clean, dry and free from grease and oil.
(b) The nylon surfaces of the suit shall be given three pre-coats of cement . The reinforcement pieces shall be given one pre-coat of cement applied onto the open-cell foam side of the reinforcement piece. Allow 10 minutes drying time between coats.
(c) After the pre-cementing coats have dried, apply a final coat to each surface. When tacky, surfaces shall be joined by rolling with a heavy metal roller (see figure 2).
(d) After allowing sufficient time for the bond between the two surfaces to set, the edges of the reinforcement pieces shall be rolled down. To achieve this, pre-cement the edges of the reinforcement pieces and the nylon of the suit where there will be contact. When dry, cement the surfaces and roll the edges of the reinforcement pieces over onto the surfaces of the suit with a heavy metal roller (see figure 2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

3.6.5 General procedure. The procedure specified in 3.6.3 shall be strictly followed in performing operations 3.6.6 through 3.6,19. The procedure specified in 3.6.4 shall be strictly followed in performing 3.6.22. Allow 24 hours of drying time for cemented seams before applying the seal tape to the individual seams (see 3.6.21).

3.6.6 Procedure for boot making. Procedure for boot q aking shall be as follows:

(a) Apply cement to the cut dart of each boot.
(b) Abut and press firmly together.
(c) Apply cement to the joining seams of each boot.
(d) Abut and press firmly together the matching guides of the boot, joining seams from heel to top of boot.

3.6.7 Procedure for making neck pieces and insert neck gasket. Procedure for making neck pieces and insert neck gasket shall be as follows:

(a) Apply cement to the neck seam of the outer neck piece.
(b) Abut and press the neck joint firmly together.
(c) Apply cement to the inner surface (open pore) of the inside neck piece and matching surface of the neck gasket.
(d) Mount neck gasket onto the neck piece, allowing a 3/4 ± 1/8 inch overlap.
(e) Stitch neck gasket onto the neck piece using a single straight stitch conforming to type 301 of FED-STD-751. The stitch line shall be 1/4 inch in from the inside edge of the neck gasket using thread type Anefil, 100 percent nylon, bonded BT/138 black; 7 ± 1 stitch per inch.
(f) Apply cement to the inner neck piece seam.
(g) Abut and press the neck joint firmly together.
(h) Apply cement to the inner neck piece (open pore side) and on the matching surface of the outer neck piece and gasket.
(i) Press neck piece onto neck piece gasket assembly and roll with a heavy roller (see figure 2).
(j) The bottom of the two neck pieces shall be fused with one another.

3.6.8 Procedure for joining front chest piece to back yoke. Procedure for joining front chest piece to back yoke shall be as follows:

(a) Apply cement to the front chest piece and back yoke joining seams .
(b) Abut and press the front chest pieces and the back yoke joining seams firmly together, according to guides.

3.6.9 Procedure for attaching gauntlet sleeves to sleeves for finished appearance. Procedure for attaching gauntlet sleeves to sleeves for finished appearance shall be as follows: The gauntlet sleeves shall finish with the skin surface on the outside.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

(a) Apply cement to the gauntlet sleeves and sleeves at their points of joining with one another.
(b) Abut and press the gauntlet sleeves and sleeves firmly together.

3.6.10 Procedure for making zipper assembly for finished appearance. Procedure for making zipper assembly for finished appearance shall be as follows: The finished zipper assembly shall be smooth and flat with no puckers or twists which would restrict operation of the zipper. The outer edges of the assembly shall finish even and flush with each other. The zipper shall be in a closed position before and during assembly.

(a) Apply cement to the split side of the back zipper bottom ply and the bottom side of the zipper tape.
(b) Press the zipper to the back zipper bottom ply firmly together using a heavy metal roller (see figure 2).
(c) Apply cement to the back zipper top ply and top side of zipper tape.
(d) After allowing sufficient time for the partially assembled zipper to dry, press the back zipper top ply and the partially assembled zipper assembly firmly together with a heavy metal roller (see figure 2). Be careful to ensure that cement is not applied to the scoops of the slide fastener.
(e) Allow sufficient time for the completed zipper assembly to dry, place zipper panel marker over zipper assembly and trim according to template. Add marks to zipper assembly in accordance with the template.

3.6.11 Procedure for joining side body pieces to front chest pieces . Procedure for joining side body pieces to front chest pieces shall be as follows:

(a) Apply cement to the side body and front chest joining seam.
(b) Abut and press the side body and front chest joining seams firmly together according to guides.

3.6.12 Procedure for joining assembled sleeves to front chest pieces and yoke. Procedure for joining assembled sleeves to front chest pieces and yoke shall be as follows:

(a) Apply cement to the sleeve and front chest yoke joining seams.
(b) Abut and press the joining seams firmly together according to guides.

3.6.13 Procedure for joining zipper assembly to back yoke for finished appearance. Procedure for joining zipper assembly to back yoke for finished appearance shall be as follows: Zipper assembly shall be positioned onto the suit so that the direction of pull to close the zipper is right to left. The joining seam of the zipper assembly and back yoke shall finish even and flush with each other.

(a) Apply cement to the zipper assembly and back yoke joining seam.
(b) Align the two assemblies according to guides. Abut and press the zipper assembly and back yoke joining seam firmly together.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

3.6.14 Procedure for joining leg and groin pieces to side body. Procedure for joining leg and groin pieces to side body shall be as follows:

(a) Apply cement to the leg and groin pieces and side body joining seams.
(b) Apply cement to the side bodies at the knee seams.
(c) Abut and press the joining seams firmly together according to guides .

3,6.15 Procedure for closing crotch, seat and front seams. Procedure for closing crotch, seat and front seams shall be as follows:

(a) Apply cement to the crotch, seat and front seams.
(b) Abut and press the crotch, seat and front seams firmly together according to guides.

3.6.16 Procedure for joining back piece to side body and attaching label. Procedure for joining back piece to side body and attaching label shall be as follows:

(a) Apply suitable adhesive to back side of label and secure to inside of back piece. Label shall be centered (1/4 inch off center tolerance) and approximately 1-1/2 to 2 inches from the top edge of back piece.
(b) Apply cement to the back and side body joining seams.
(c) Abut and press the back and side body joining seams firmly together according to guides.

3.6.17 Procedure for joining zipper assembly to back, side body and sleeve pieces and closing assembled sleeve seams. Procedure for joining zipper assembly to back, side body and sleeve pieces and closing assembled sleeve seams shall be as follows:

(a) Apply cement to zipper assembly, back, side body and sleeve pieces . Apply cement to assembled sleeve seams.
(b) Abut and press the joining seams firmly together according to guides .
(c) The joining of the above seams shall start in the center of the zipper panel; work one side of the suit then the other.

3.6.18 Procedure for joining boots to suit for finished appearance. Procedure for joining boots to suit for finished appearance shall be as follows: The joining seams of the boots to the suit shall finish even and flush with each other. The boots shall finish on the proper leg, that is right on right; left on left.

(a) Apply cement to the bottom of each leg and the top edges of each assembled boot.
(b) Abut and press the boots and leg joining seams firmly together, according to guides.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

3.6.19 Procedure for joining assembled neck pieces to suit. Procedure for joining assembled neck pieces to suit shall be as follows:

(a) Apply cement to the bottom edge of the assembled neck piece and neck opening.
(b) Abut and press firmly together, according to guides, so that a smooth bond and fit is achieved between the two assemblies. The seams of the assembly shall be even and flush.

3.6.20 Checking of cemented seams.

(a) Cemented seams shall be checked inside and outside for proper cementing.
(b) Touch up with cement all seams inside and outside.

3.6.21 Procedure for attaching reinforcement pieces. Procedure for attaching reinforcement pieces shall be as follows:

(a) Apply cement to the front reinforcement, back reinforcement, reinforcement strip and suit.
(b) Secure reinforcement to inside of suit.
(c) The positioning of the reinforcement pieces shall be as follows:

(1) Front reinforcement piece. Position on inside with the "Y" shaped end down facing the crotch seam. The reinforcement piece shall begin by overlapping the "V" of the front pieces, continuing down the front seam onto the side body and leg, until reaching the groin joining seams.
(2) Back reinforcement piece. Position on inside with the "T" shaped end down facing the seat seam. The reinforcement piece shall begin by overlapping the "V" of the back piece, continuing down onto the side body and leg until reaching the groin joining seams.
(3) Reinforcement strip. Position on inside between and abutting the front and back reinforcement pieces along the crotch and seat seam.

3.6.22 Procedure for attaching fusible seal tape for finish appearance. Procedure for attaching fusible seal tape for finish appearance shall be as follows: Seams, except that portion covered by reinforcement pieces on the inside of the suit, shall be covered by seal tape. The seal tape shall finish smooth without wrinkles or ridges. The tape shall be centered over the seam. Ends of seal tape shall overlap each other approximately 1/2 inch.

(a) Apply seal tape to all seams on inside of suit.

3.6.23 Procedure for attaching size numbers. Procedure for attaching size numbers shall be as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

(a) Size numbers shall be positioned on fronts of sleeves as follows:

(1) Center of number shall be placed in line with back yoke and front joining seam.
(2) Top of number shall be approximately 1/4 inch from sleeve and front chest joining seam.
(3) Edge of number shall be approximately 1 inch from zipper panel seam.

3.7 Sizes and measurements. The finished measurements of the suit shall be as shown in table V. Measurements and tolerances in table V are expressed in inches unless otherwise specified herein.

TABLE V. Finished measurements.

	Sizes					Tolerance
	1	2	3	4	5	
Chest	38-1/2	39-1/2	42-1/2	43	48-1/2	+ 3/4 - 1/2
Waist	31	33	35	39	40	+ 3/4 - 1/2
Hip	35	37	39	42	45	+ 3/4 - 1/2
Trunk length	32-1/4	34	33-1/2	37-1/2	35	+ 3/4 - 1/2
Overall length top of boot seam	49-1/4	50-1/2	53-3/8	56	60-3/8	+ 3/4 - 1/2
Thigh	21-1/2	23	23-1/2	25	27	+ 3/4 - 1/2
Sleeve length	16	17	17-1/2	18-1/2	19	± 1/4
Sleeve seam	6	6-1/2	7-1/4	8-1/2	8-3/4	± 1/4
Inseam to top of boot	21-1/4	22	22-3/4	23	25-1/4	+ 3/4 - 1/2
Boot height	13-1/2	14-1/4	14-1/2	14	15	± 1/4
Boot length	11	11-3/4	12-1/4	12-7/8	13-1/2	± 1/4

NOTES : The following measurements shall be taken with the suit laid face side up flat and smooth:

(a) Chest. Double the measurement taken 4-1/2 to 5 inches down from bottom of center neck seam, across chest from folded edge to folded edge.
(b) Waist. Double the measurement taken at "V" of front chest piece from folded edge to folded edge.
(c) Hip. Double the measurement taken at junction of side body pieces and leg and groin pieces from folded edge to folded edge.
(d) Trunk length. Measurement shall be taken from fold at crotch to fold at shoulder.
(e) Overall length to top of boot seam. Measurement shall be taken from top of boot to fold at shoulder.
(f) Thigh. Measurement shall be taken 1/2 inch below fold at crotch to outer fold of leg.
(g) Sleeve length. Measurement shall be taken from bottom of cuff to sleeve and front chest piece joining seam.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

(h) Inseam to top of boot. Measurement shall be taken from inseam at fold of crotch to top of boot.
(i) Boot height. Measurement shall be taken with boot laid flat on its side, down center of boot from top of boot to bottom of boot.
(j) Boot length. Measurement shall be taken with boot laid flat on its side, from back seam to tip of boot along its center.

The back sleeve measurement shall be taken with the suit laid face down flat and smooth from the top of the cuff to the zipper panel seam.

3.8 Workmanship. The finished suit shall conform to the quality of product established by this specification and the occurrence of defects shall not exceed the applicable acceptable quality level (AQL) (see 4.5.1).

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4,1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

(a) First article inspection (see 4.3).
(b) Quality conformance inspection (see 4.4).

4.3 First article inspection shall consist of the examinations of 4.5 and the tests specified in 4.6. When specified in the contract or order, a test report shall be prepared (see 6.2.2).

4.4 Quality conformance inspection. Quality conformance inspection shall consist of the examination and tests specified in 4.5 and 4.6.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

4.4.1 Sampling for quality conformance inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise specified herein. For purpose of sampling, an inspection lot for quality conformance inspection shall consist of all material of the same type offered for delivery at one time. Lot and sample size shall be as specified in table VI.

TABLE VI. Sample size.

Lot size	Sample size
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

4.4.2 Rejection criteria. The lot shall be unacceptable if one or more units fail to meet any requirement specified. The basis for lot size for laminated and unlaminated chloroprene foam shall be one sheet, and 1 yard full width for the knitted stretch fabric. The sample unit for testing shall be as follows:

Unlaminated foam - 1 square yard.
Laminated foam - 1 square yard.
Knitted stretch fabric - 1 yard full width.

4.5 Examination.

4.5.1 Inspection levels and acceptable quality levels. The inspection levels and acceptable quality levels (AQL's), expressed in defects per 100 units, for visual and dimensional examination in accordance with MIL-STD-105, shall be as follows:

	AQL	Inspection levels
For examination in 4.5.2		
Major	2.5	II
Total (major and minor combined)	6.5	II
For examination in 4.7		
One class	4.0	S-3

4.5.2 Visual examination. Visual examination shall be as specified in table VII.

TABLE VII, Visual defects.

Defect	Classification	
	Major I	Minor
MATERIAL DEFECTS AND WORKMANSHIP DAMAGES		
Any hole.	x	
Deep crease or fold line.	x	
Cut or tear.	x	

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

TABLE VII. Visual defects. - Continued

Defect	Classification	
	Major	Minor
BASIC MATERIAL		
Any evidence of delamination.	X	
Area of excess cement, for example, solid runs or ridges.		X
Chloroprene foam or cement tacky.	X	
Any brittle area which cracks when bent.	X	
Any imbedded foreign material which, when removed, results in damage to basic material.	X	
Any imbedded foreign material which, when removed, does not damage basic material.		X
Any blister or pin hole.	X	
Any objectionable odor.		X
Color not as specified.		X
CLEANNESS		
One or more spots or stains of a permanent nature.		X
Unsightly cement mass (other than on fastener chain).		X
COMPONENT AND ASSEMBLY		
Any component part omitted or any required operation omitted or improperly performed (unless otherwise specified herein).	X	
CUTTING		
Any component part not cut in accordance with marks indicated on pattern or not in accordance with specification requirements.	X	
SEAL TAPE		
Not specified type.	X	
Not positioned on inside cemented seams as specified.	X	
Incomplete taping of cemented seams.	X	
Seal tape insecure, not performing intended purpose.	X	
Edges of seal tape curled.		X
Ends of seal tape overlapped less than 1/2 inch.		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

TABLE VII. Visual defects. - Continued

Defect	Classification	
	Major	Minor
CEMENTED SEAMS		
Any open seam.	X	
Twisted or puckered seam.	X	
Seam not properly joined.	X	
Uneven seam, for example, one edge higher by 1/8 inch or more for a distance of 1 inch or more.	X	
SLIDE FASTENER 1/		
Not specified type or size.	X	
Slide fastener less than or more than 33 inches in length.	X	
Wire stirrup pulls not provided with thongs.		X
Thongs not made of nylon tape or cotton webbing.		X
Thongs less than 5 inches in length.		X
Thongs not color black as specified.		X
BACK ZIPPER CLOSURE		
Slide fastener omitted or misplaced.	X	
When closed, twisted, puckered or bulging.	X	
The direction of pull to close slide fastener is not in the specified direction of right to left.		X
Cement on chain of slide fastener restricting use of slide fastener.	X	
Excessive cement on chain of slide fastener not restricting use of slide fastener.		X
REINFORCEMENT PIECES		
Reinforcement pieces omitted, not positioned as specified.	X	
Reinforcement pieces insecurely centered.		X
BOOT		
Boots reversed, for example, right on left and left on right.	X	
CUFFS		
Cuffs attached to suit with skin side on inside.	X	

1/ Slide fasteners shall be checked for proper function by opening and closing slide fastener at least three times.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

4.5.3 Dimensional examination. The suit shall be examined for defects in dimensions in accordance with the following:

(a) Any measurement deviating from nominal dimensions and tolerances specified shall be scored as a measurement defect.
(b) Sleeve lengths unequal in length by 1/2 inch or more shall be scored as size measurement defect.

4.6 Tests.

4.6.1 Testing of components. The components listed in table VIII shall be tested for the characteristics shown therein.

TABLE VIII. Testing of components.

Components	Characteristic	Determinations	Requirement paragraph	Test method
Chloroprene foam	Material identification	-	3.2.1	
	Color	1	3.2.1	Visual
	Thickness	5	3.2.1	ASTM D 1056
	Compression set under constant deflection	5	3.2.1	4.6.1.1
	Compression deflection	5	3.2.1	ASTM D 1056
	Shrinkage after accelerated aging	3	3.2.1	4.6.1.2
	Water absorption	3	3.2.1	ASTM D 1056
	Density	5	3.2.1	4.6.1.3
	Tensile stress	5	3.2.1	4.6.1.5
Knitted nylon stretch cloth	Material identification	-	3.2.2	
	Weight	5	3.2.2	FED-STD-191, method 5040
	Wales and courses	5	3.2.2	FED-STD-191, method 5070
	Elongation	5	3.2.2	4.6.1.4
	Color	-	3.2.2	Visual
	Colorfastness Laundering	1	3.2.2.1	FED-STD-191, method 5614
	Crocking	1	3.2.2.1	FED-STD-191, method 5651
	Perspiration	1	3.2.2.1	FED-STD-191, method 5680

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

TABLE VIII. Testing of components. - Continued

Components	Characteristic	Determinations	Requirement paragraph	Test method
Laminated foam	Adhesive strike through	-	3.2.3	Visual
	Wrinkled or puckered	-	3.2.3	Visual
	Laundering resistance	5	3.2.3.1	FED-STD-191, method 5556
	Adhesion:			
	Initial 1/	5	3.2.3.1	FED-STD-191, method 5950
	After three launderings 1/ 2/	5	3.2.3.1	FED-STD-191, method 5556 and 5950
	After aging 2/	5	3.2.3.1	4.6.1.2 and FED-STD-191, method 5950
	Blocking 3/	3	3.2.3.1	FED-STD-191, method 5872
Adhesive cement	Material identification	-	3.2.4	
Cemented seam	Breaking strength:			
	Initial 4/ 5/	5	3.2.5	FED-STD-191, method 5100
	After aging 4/ 5/ 6/	5	3.2.5	FED-STD-191, method 5100
Reinforced seam	Adhesive strength:			
	Initial 5/	3	3.2.6	FED-STD-191, method 5950
	After aging 5/ 6/	3	3.2.6	FED-STD-191, method 5950
Fused seam	Adhesive strength:			
	Initial 5/	5	3.2.7	4.6.1.6
	After aging 5/ 6/	5	3.2.7	4.6.1.6

See footnotes at top of next page.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

1/ Three cotton laundering cycles shall be performed on 8 by 6 inch specimens using 1/4 inch double laminated foam.
2/ The distance between the clamps shall be 2 inches at the start of the test. Slitting the specimen between the nylon knit and foam to help separate the fabric from the foam sufficiently to fit the clamps is permissible. The adhesion shall be tested in the fabric's length (wales) direction and on one side only of the 1/4 inch foam laminated on both sides.
3/ Specimens 4 by 4 inches shall be placed together fabric side to fabric side.
4/ Cemented seams shall be centered equidistant from the clamps, Breaks shall be made with the seam at right angles to load direction. The clamps shall be 1 inch apart at the start of the test and the face of each jaw shall be not less than 1 by 2 inches. The cemented seam test specimen shall be rectangular, 2 inches wide by not less than 4 inches long.
5/ The test shall be performed on specially prepared cemented seams, reinforced seams and fused seams, similar to those made on the end item. When preparing specimens of the reinforced and fused seams for testing, a minimum of 1 inch tab shall be left free to facilitate testing for adhesion strength.
6/ The specimen shall be suspended vertically in the air-oven at 158 ± 2 *degrees* Fahrenheit (°F) for 7 days. At the conclusion of the aging interval the specimens shall be cooled at room temperature on a flat surface and allowed to rest 4 hours before determination of adhesion.

4.6.1.1 Compression set under constant deflection. The circular die used to prepare standard test specimens shall have an inside diameter measurement of 1.129 ± 0.001 inches. Test specimens shall have a 1 square inch surface area with the top and bottom surfaces parallel to each other. Thickness of test specimens shall be 1/2 inch. If a 1/2 inch thick specimen is not readily available, then two 1/4 inch thick specimens may be plied to obtain the required 1/2 inch thickness. The apparatus and procedure shall be the same as that described in method B of ASTM D 395. The test specimens shall be compressed to 50 percent of their measured original thicknesses. The test shall be run at room temperature for 22 hours. The load shall be released at the end of the test period and the thickness measured after 24 hours at room temperature. Thickness shall be measured as specified in ASTM D 1056. Chromium-plated metal plates are not required for the apparatus. Any stiff plates that are clean and smooth may be used.

Calculate the percentage compression set as follows:

$$\text{Compression set, percent} = \left[\frac{(t_o - t_1)}{(t_o - t_s)}\right] X\ 100$$

Where:

t_o = Original thickness.
t_1 = Thickness of specimen after specified recovery period.
t_s = Thickness of spacer bar used.

4.6.1.2 Shrinkage after accelerated aging. Three specimens each with a minimum dimension of 8 by 8 inches shall be measured to the nearest 1/32 inch in both length and width by means of a steel rule. The specimens shall be suspended vertically in the air oven at 158 ± 2°F for 7 days. At the conclusion

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

of the aging interval, the specimens shall be cooled at room temperature on a flat surface and allowed to rest not less than 4 hours before determination of shrinkage. The average shrinkage in each direction shall be calculated as follows and reported to the nearest 0.1 percent:

$$\text{Percent shrinkage} = \frac{O - A}{0} \times 100$$

Where O = Original length or width (inches).

A = Length or width after aging (inches).

4.6.1.3 Density. Five specimens each 2 inches square shall be weighed separately to the nearest 0.001 gram on an analytical balance. The thickness of each specimen shall be determined in accordance with ASTM D 1056 and the following formula shall be used to determine density:

$$D = \frac{0.95 \times W}{T}$$

Where D = Density in lb/ft^3.
w = Sum of the weights of the five specimens (grams).
T = Sum of the thicknesses of the five specimens (inches).

4.6.1.4 Elongation. An incline plane type of machine (for example I-P-4 or similar type) with a suitable autographic recording device shall be used. Specimens of the fabric shall be cut 4 by 6 inches with the long direction parallel to the direction to be tested. The specimen shall be evenly aligned without tension or slack in the 1- by 3-inch clamps set 2 inches apart. The machine shall run through two complete cycles, proceeding to its maximum depression so as to exert a 5-pound tension. Five specimens, each containing different wales and courses shall be tested, using individual recorded elongation graphs. The average stretch of five specimens for each direction shall be measured at the peak of the last recorded cycles, in a line perpendicular to the horizontal zero axis and reported to the nearest percent.

4.6.1.5 Tensile stress. The test specimen shall be dumbbell shape and cut using die “C” as specified in ASTM D 412. Specimens shall be cut in the length direction of the sample. The tensile stress test shall be made on a power-driven machine equipped with suitable jaws to firmly hold the specimen in place while they are separating at 20 ± 2 inches per minute, The machine shall be equipped with a recording device so that the applied force is accurately measured during the extension of the specimen, The test specimen shall be conditioned for 4 hours in a conditioned atmosphere of 65 percent relative humidity and 70°F. Dumbbell specimens shall be marked with a marker having a marking edge 1/16 inch in thickness. The sample shall be under no tension at the time it is marked. Marks shall be placed equidistant from its center and perpendicular to its longitudinal axis. The center of the marks shall be 1.0 ± 0.003 inch apart. Set the grip separation at 2.5 inches minimum. Place the dumbbell tabs in the grips of the testing machine, using care to adjust them symmetrically in order that the tension will be distributed uniformly over the cross

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

section. Start the machine and note continuously the distance between the two bench marks, determining the elongation. Record the stress at 500 percent elongation. Calculate the stress by dividing the load at 500 percent elongation by the original cross-sectional area of specimen.

$$\text{Stress lb/in}^2 = \frac{\text{Loads (pounds) at 500 percent elongation}}{\text{Width (inches) x thickness (inches)}}$$

No single value shall be more than the maximum requirement as specified in table I.

4.6.1.6 Adhesion of fused tape. The specimens shall be prepared with fused tape seams similar to those on the end item, at least 6 inches in length. One end of the tape shall be left free so as to leave a tab about 1 inch in length. The test apparatus shall have an autographic recording mechanism that shall be the same as that specified in test method 5100 of FED-STD-191. The upper and lower jaws shall be a minimum of 1 by 3 inches with the long dimension perpendicular to the application of load. The gauge length between jaws shall be of such lengths so as to allow a minimum of 1 inch peel of the fused tape from the surface of the foam. The tester shall be operated at a uniform pulling speed of 12 ± 0.5 inches per minute. The panel and ratchet mechanism on the tester shall be disengaged to permit reading of variable force when the tester is placed in operation. Secure the separated foam material of the specimen in the upper clamp and the prepared tab of the fusible tape in the lower jaw of the tester in such a way that the longitudinal axis of the specimen forms a right angle with the closed clamping surface. Determine the adhesion of each specimen to the nearest 0.5 pounds as the average of the five highest and the five lowest peak loads of resistance per 1 inch of specimen width recorded for a minimum 1 inch of separation. If the nylon knit tape tears prior to 1 inch of separation then the force registered to produce the tear shall be considered the adhesion of the fused tape. Any one individual specimen result that is less than 10 pounds shall constitute failure of test sample. The specimens shall be prepared at least 12 hours prior to testing.

4.7 Examination of the end item. Examination of the end item shall be in accordance with 4.5.2 and 4.5.3. The applicable inspection levels and AQL's shall be as specified in 4.5.1. The sample unit shall be one finished suit. The lot size shall be expressed in units of suits.

4.8 Testing of end item. The method of testing shall be as specified in 4.8.1. The leak test shall be performed by the contractor under the surveillance of the Government quality assurance representative. A leak test shall be performed on every suit produced.

4.8.1 Leak test procedure. The arm plugs and neck adapter blanking plate will be loaned to the contractor by the contracting activity for performing the leak test. Upon completion of the contract or testing the arm plugs and neck adapter blanking plate shall be returned to the contracting activity. The leak test procedure shall be as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

(a) Insert arm plugs in each sleeve and secure with hook and pile fastener tape straps.
(b) Install neck adapter blanking plate.
(c) Attach a low pressure air supply hose to blanking plate.
(d) Inflate suit to 2 lb/in^2 (do not use more than 2 lb/in^2).
(e) Place suit into a tank containing room temperature water. Examine for leaks paying. particular attention to the seams. Any steady stream of air bubbles indicates leakage.
(f) Mark any leak area for repair.
(g) Disconnect air supply.
(h) Remove blanking plate and sleeve plugs.
(i) Allow suit to dry.
(j) Repair leak (see 4.8.2).
(k) Once the leak has been repaired, the suits shall be retested in accordance with 4.8.1.

The tank shall be large enough to accept the suit fully extended. An open bar or similar type of arrangement shall be attached to the tank. The bar shall, when lowered, hold the suit in place. The suit shall be checked for leaks by immersing sections of the suit under water. Both sides of the suit shall be checked in this manner.

4.8.2 Procedure for repairing a seam leak. Procedure for repairing seam leaks shall be as follows:

(a) Slice open the seam with a razor blade, almost to the inner seal tape. The slice shall be about 3/4 inch on either side of the leak. Do not cut through the inner seal tape. If cut > retape.
(b) Open the seam far enough to allow for a proper regluing (see 3.6.3).
(c) Reglue and press the seam firmly together with the fingers, pinch seam, and touch up seam.

Repaired seams shall be accomplished neatly with no excess mass of cement in seam area.

4.9 Packaging inspection. An examination shall be made to determine that the preservation, packing and marking complies with the section 5 requirements. Defects shall be scored in accordance with table IX. The sample unit shall be one shipping container fully prepared for delivery with the exception that it need not be closed. Examination for the closure defects listed in table IX shall be made on shipping containers fully prepared for delivery. The lot size shall be the number of containers in the end item inspection lot. The inspection level shall be S-2 in accordance with MIL-STD-105 and the AQL shall be 2.5 defects per hundred units.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

TABLE IX. Packaging defects.

Examine	Defects
Marking (interior) and exterior)	Omitted; incorrect; illegible; of improper size, location, sequence or method of application.
Materials	Any component missing, damaged, or not as specified.
Workmanship	Inadequate application of components, such as polyethylene bags with heat-sealed seams that are crooked, noncontinuous, open or not parallel. Tie down tapes not properly secured. Closure of shipping container not as specified. Bulged or distorted containers.
Content	Number of suits per shipping container is more or less than required.

4.9.1 Inspection of interior and exterior containers. When interior and exterior containers are required to be in accordance with PPP-B-636 or PPP-B-601, examination for defects in the assembly and closure (for fiberboard containers) shall be in accordance with the appendix of the applicable container specification.

5. PACKAGING

(The packaging requirements specified herein apply only for direct Government acquisition. For the extent of applicability of the packaging requirements of referenced documents listed in section 2, see 6.7.)

5.1 Preservation. Preservation shall be level A or commercial as specified (see 6.2.1).

5.1.1 Level A.

5.1.1.1 Polyethylene bag. Each divers dress suit, with sleeves in natural position over body front, shall be placed full length within a flat style clear polyethylene film bag having a minimum thickness of 0.004 inch plus or minus 20 percent tolerance. The bag shall be formed with heat sealed seams that are straight, continuous, and parallel to each other and the formed edges of the bag. The final closure of the bag shall be heat sealed with the seal made as close as possible to the open end. The bag shall measure 76 inches in length by 32 inches in width (plus 1 inch minus 0 tolerance) (see figure 4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

5.1.1.2 Unit package. One divers dress suit, bagged as specified in 5.1.1.1, shall be placed front down, full length within a fiberboard container conforming to style FTC (all flaps on length dimension), grade W5C of PPP-B-636 (see figure 4). Inside dimensions of the fiberboard container shall be approximately 70 inches in length, 28 inches in width and 5 inches in depth. Approximate dimensions are furnished as a guide only. The box body shall be provided with three 1 inch cotton or nylon tie-down tapes for securing the divers dress suit at just below the armpit (approximately 14 inches from box end), over the waist and just above the ankles. The tie-down tapes shall be secured to the box body by any one of the methods specified on figure 3. Each divers dress suit shall then be tied in place to prevent movement while in transit, but not tied tight as to cause permanent creasing of the suit material at point of contact. The fiberboard box shall be closed with pressure sensitive tape as specified in the appendix of PPP-B-636.

5.1.2 Commercial. Divers dress suits shall be preserved in accordance with ASTM D 3951.

5.2 Packing. Packing shall be level A, B or commercial, as specified (see 6.2.1).

5.2.1 Level A. Three divers dress suits, of one size only, preserved as specified in 5.1, shall be packaged flat in a reusable plywood-cleated shipping container conforming to overseas type, style A of PPP-B-601, except that the container top shall be closed with wood screws, spaced as specified (see figure 5). Inside dimensions of each container shall be approximately 71 inches in length, 29 inches in width and 16-1/2 inches in depth. Approximate dimensions are furnished as a guide only. Toward the end of the contract, or when there are less than the required amount per shipping container of the same size, mixed sizes may be packed within the same container.

5.2.2 Level B. Three divers dress suits, of one size only, preserved as specified in 5.1, shall be packed flat in a reusable plywood-cleated shipping container conforming to domestic type, style A of PPP-B-601, except that the container top shall be closed with wood screws, spaced as specified (see figure 5). Inside dimensions of each container shall be approximately 71 inches in length, 29 inches in width and 16-1/2 inches in depth. Approximate dimensions are furnished as a guide only. When there are less than the required amount per shipping container of the same size, mixed sizes may be packed within the same container.

5.2.3 Commercial. Divers dress suits, of one size only, preserved as specified in 5.1, shall be packed in accordance with ASTM D 3951.

5.3 Marking. In addition to any special marking required (see 6.2.1), interior packages and shipping containers shall be marked in accordance with MIL-STD-129. Marking for commercial shipment shall be in accordance with ASTM D 3951.

5.3.1 Special marking. Each interior package and shipping container shall be marked on the top, in block letters, not less than 1-1/2 inches in height, with the legends as shown on figures 4 and 5, respectively. In addition, two sides of each shipping container shall be marked with the same size letters and symbol as the legend shown on figure 5.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

5.3.2 Labels, mixed sizes. Each shipping container, packed with mixed sizes , shall have securely attached to the end and side, directly under the printing or stenciling, a white paper label 5 by 4 inches with the words "MIXED SIZES" plainly printed or stamped thereon, and under these words shall be legibly printed or stamped the correct quantities and sizes contained therein.

6. NOTES

6.1 Intended use. The suits are intended to be worn with the coveralls, mitten and helmet of a MK-12 diving system, which is designed to keep personnel dry in a diving situation.

6.2 Ordering data.

6.2.1 Acquisition requirements. Acquisition documents should specify the following:

(a) Title, number, and date of this specification.
(b) Sizes required (see 1.2).
(c) When first article is required (see 3.1).
(d) Selection of applicable levels of preservation and packing (see 5.1 and 5.2).
(e) Special marking as required (see 5.3).

6.2.2 Data requirements. When this specification is used in an acquisition and data are required to be delivered, the data requirements identified below shall be developed as specified by an approved Data Item Description (DD Form 1664) and delivered in accordance with the approved Contract Data Requirements List (CDRL), incorporated into the contract. When the provisions of DoD FAR Supplement, Part 27, Sub-Part 27.410-6 (DD Form 1423) are invoked and the DD Form 1423 is not used, the data specified below shall be delivered by the contractor in accordance with the contract or purchase order requirements. Deliverable data required by this specification are cited in the following paragraph.

Paragraph no.	Data requirement title	Applicable DID no.	Option
4.3	First article inspection report	DI-T-4902	----

(Data item descriptions related to this specification, and identified in section 6 will be approved and listed as such in DoD 5010.12-L., AMSDL. Copies of data item descriptions required by the contractors in connection with specific acquisition functions should be obtained from the Naval Publications and Forms Center or as directed by the contracting officer.)

6.2.2.1 The data requirements of 6.2.2 and any task in sections 3, 4; or 5 of this specification required to be performed to meet a data requirement may be waived by the contracting/acquisition activity upon certification by the offeror that identical data were submitted by the offeror and accepted by the

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

Government under a previous contract for identical item acquired to this specification. This does not apply to specific data which may be required for each contract regardless of whether an identical item has been supplied previously (for example, test reports).

6.3 First article. When a first article inspection is required, the item should be a first article sample. The first article should consist of one unit. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examinations, approval of first article test results and disposition of first articles. Invitations for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection to those bidders offering a product which has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending contract.

6.4 Equal item. Prior to the use of an "or equal" item the contractor should submit the item with supporting data to the contracting activity for subsequent approval or disapproval by the responsible military agency.

6.5 Slide fastener. The slide fastener may be obtained from Dynat, GMBH, Hildersheim, West Germany.

6.6 Adhesive cement. The following chloroprene adhesives have been found acceptable: Bostik 1177, Bostik Division, Middleton, MA 01949 and Anchorweld 0836, and 0206 (for zipper and neck gasket assembly), Roberts Consolidated Industries, City of Industry, CA 91749.

6.7 Sub-contracted material and parts. The packaging requirements of referenced documents listed in section 2 do not apply when material and parts are acquired by the contractor for incorporation into the equipment and lose their separate identity when the equipment is shipped.


6.8 Subject term (key word) listing.

Cement
Cemented seams
Divers
Dress suit
Foam
Laminated foam
Reinforcement pieces
Seams

6.9 Changes from previous issue. Asterisks are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Preparing activity:
Navy - SH
(Project 4220-N304)


Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

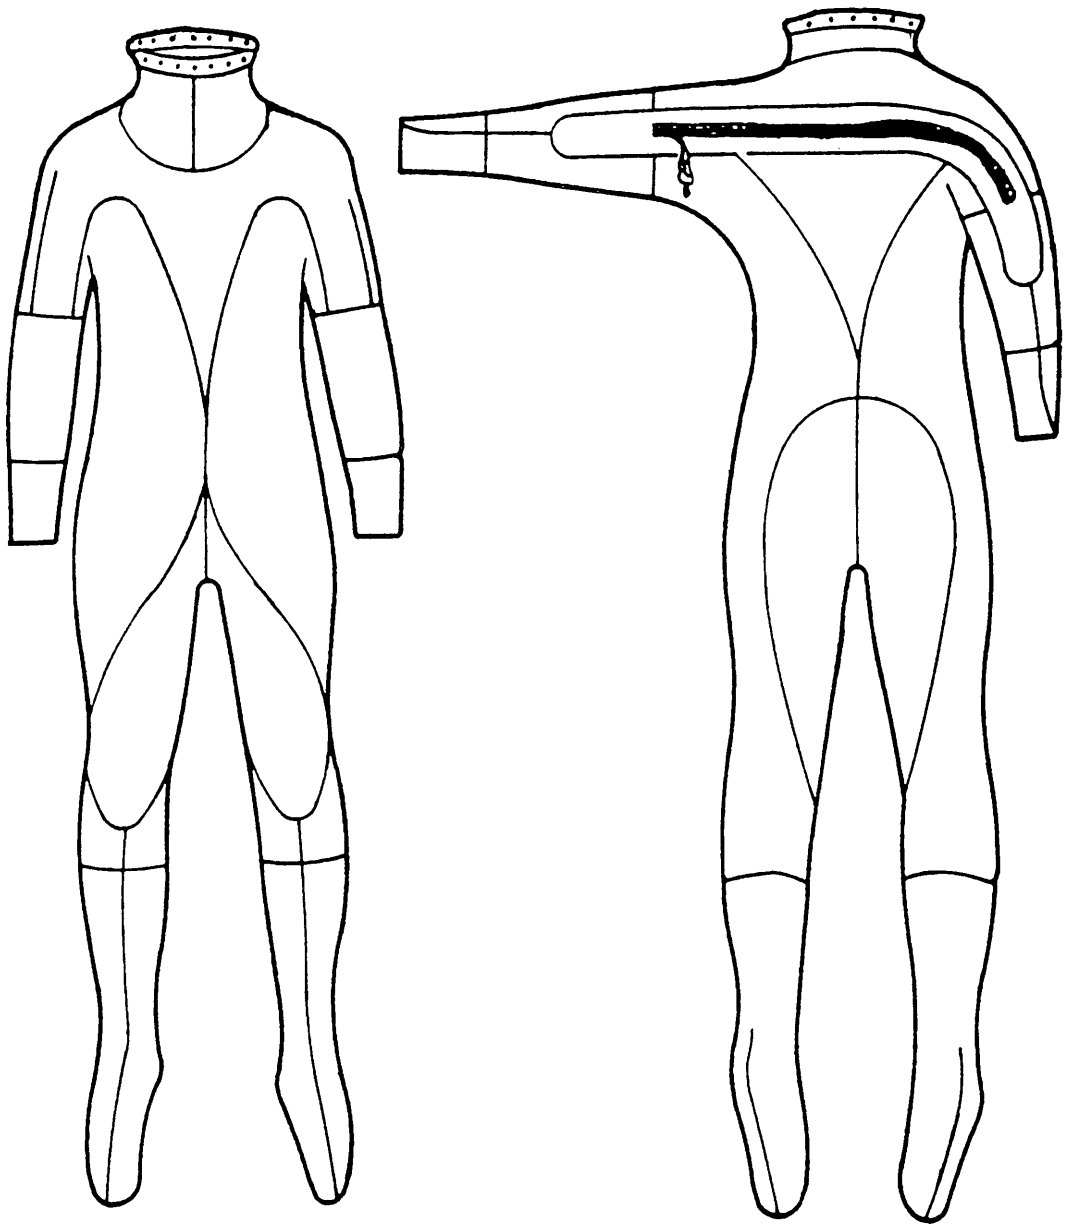


SH 13203135

FIGURE 1. Divers dress suit (MK-12).

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

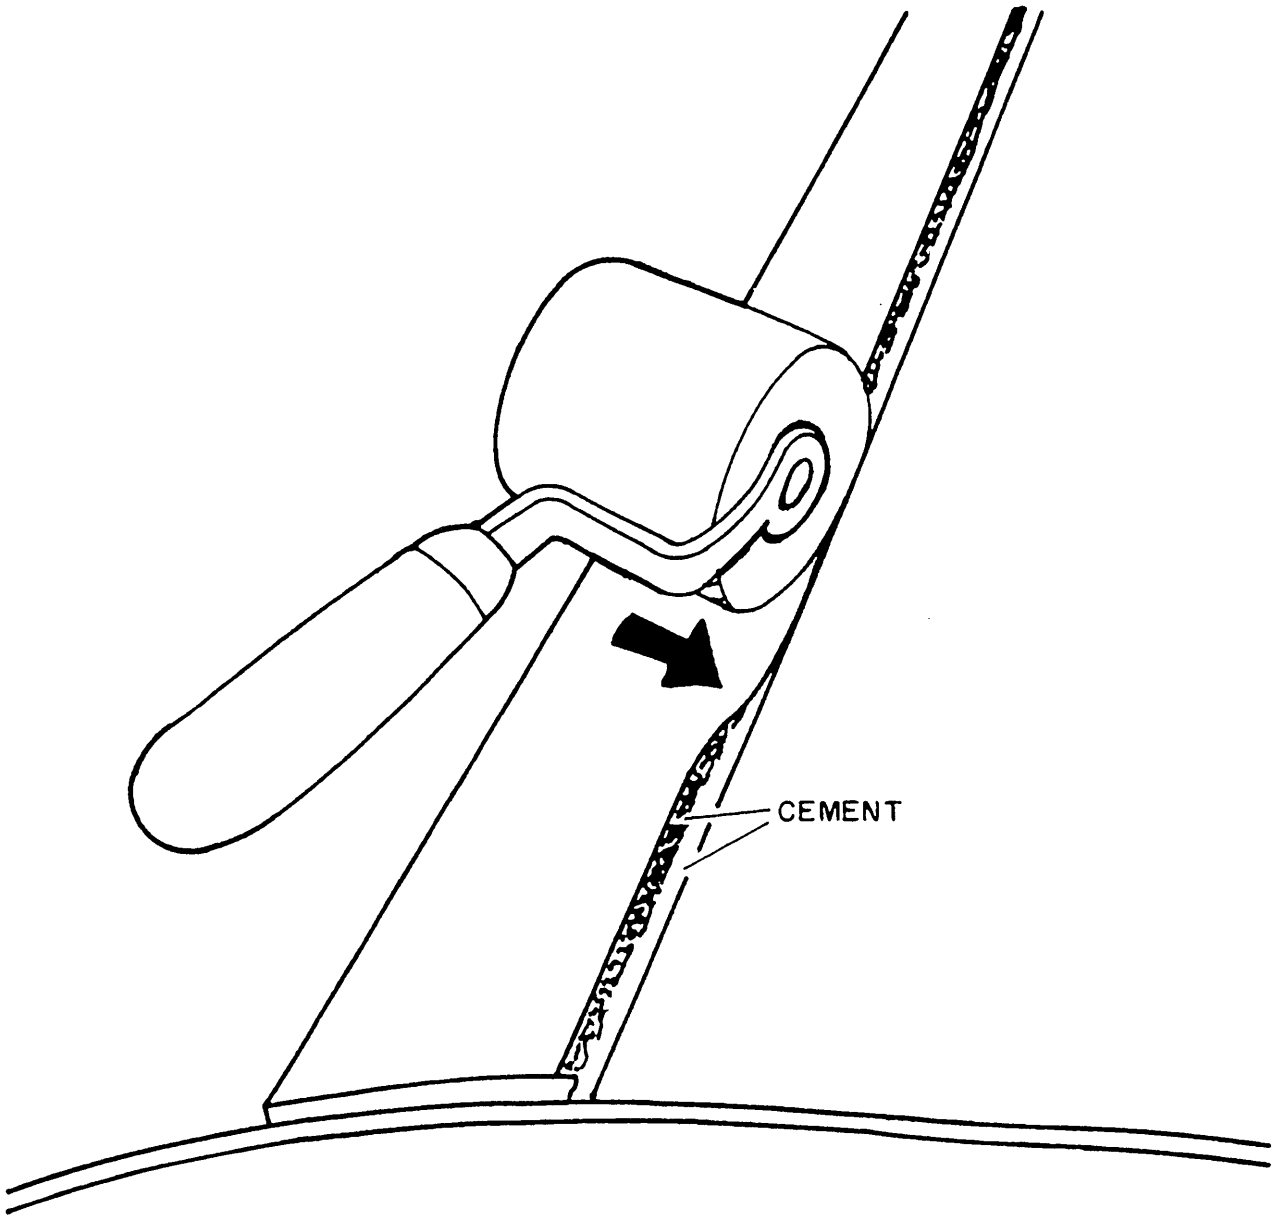


Side view from end

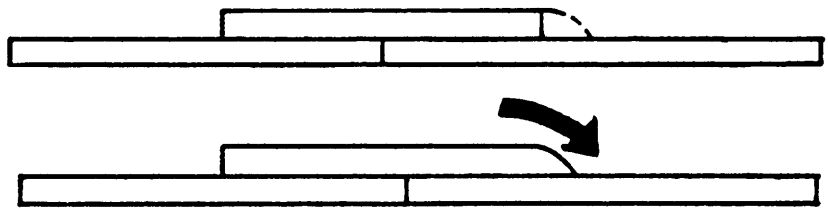

SH 13203136

FIGURE 2. Application reinforcement pieces.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

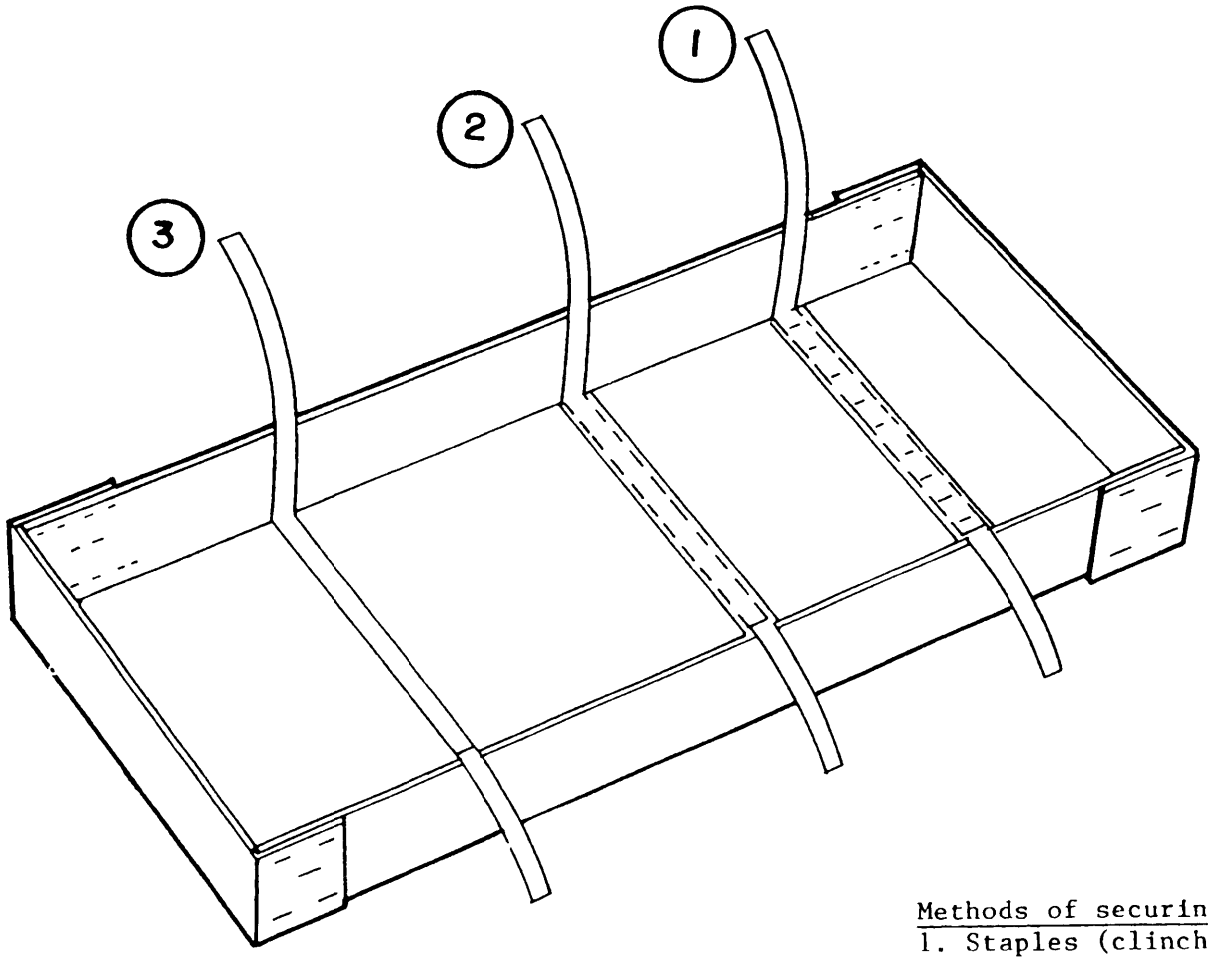

Box body with
tie-down tapes


Methods of securing tapes

1. Staples (clinched) covered with gummed or pressure sensitive tape.
2. Reinforced gummed or pressure sensitive tape.
3. Water resistant adhesive (on underside of tape only).

SH 13203137

FIGURE 3. Box body with tie-down tapes.

Source: https://assist.dla.mil -- Downloaded: 2026-02-23T11:36Z
Check the source to verify that this is the current version before use.

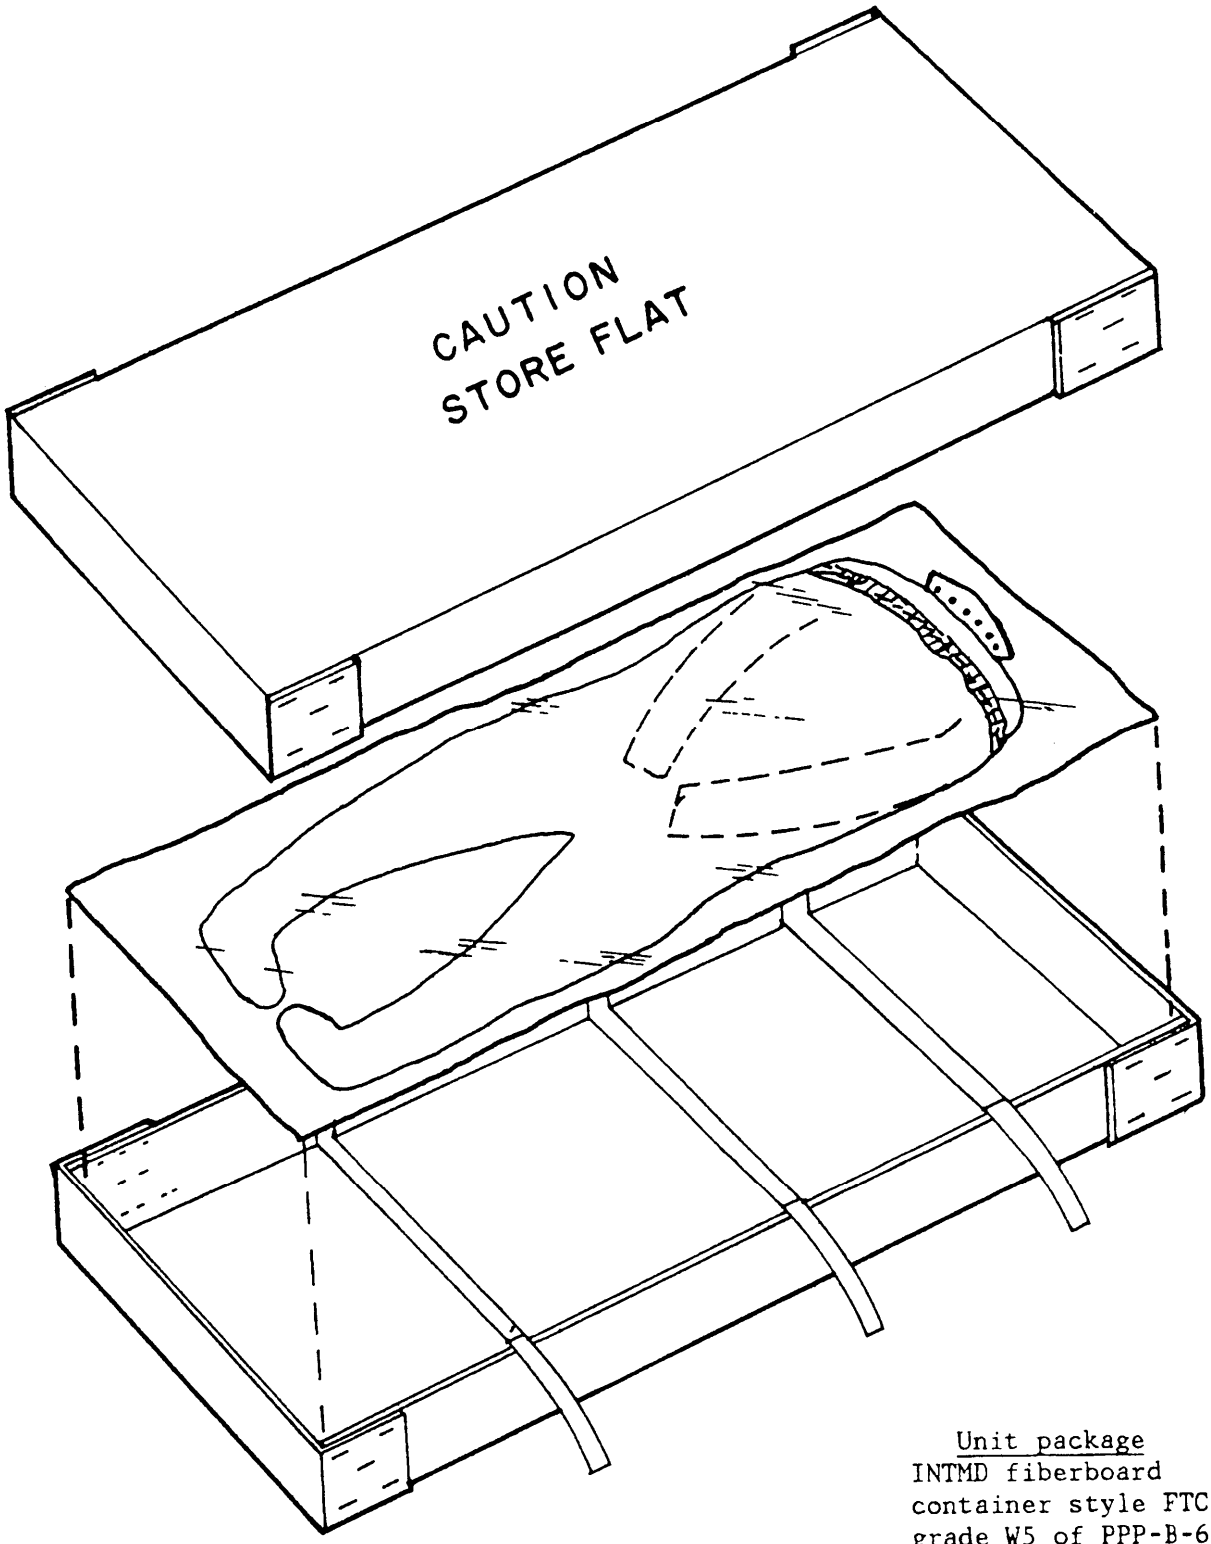


Unit package
INTMD fiberboard
container style FTC,
grade W5 of PPP-B-636,
ID 70" x 28" x 5"

SH 13203138

FIGURE 4. INTMD fiberboard container style FTC.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

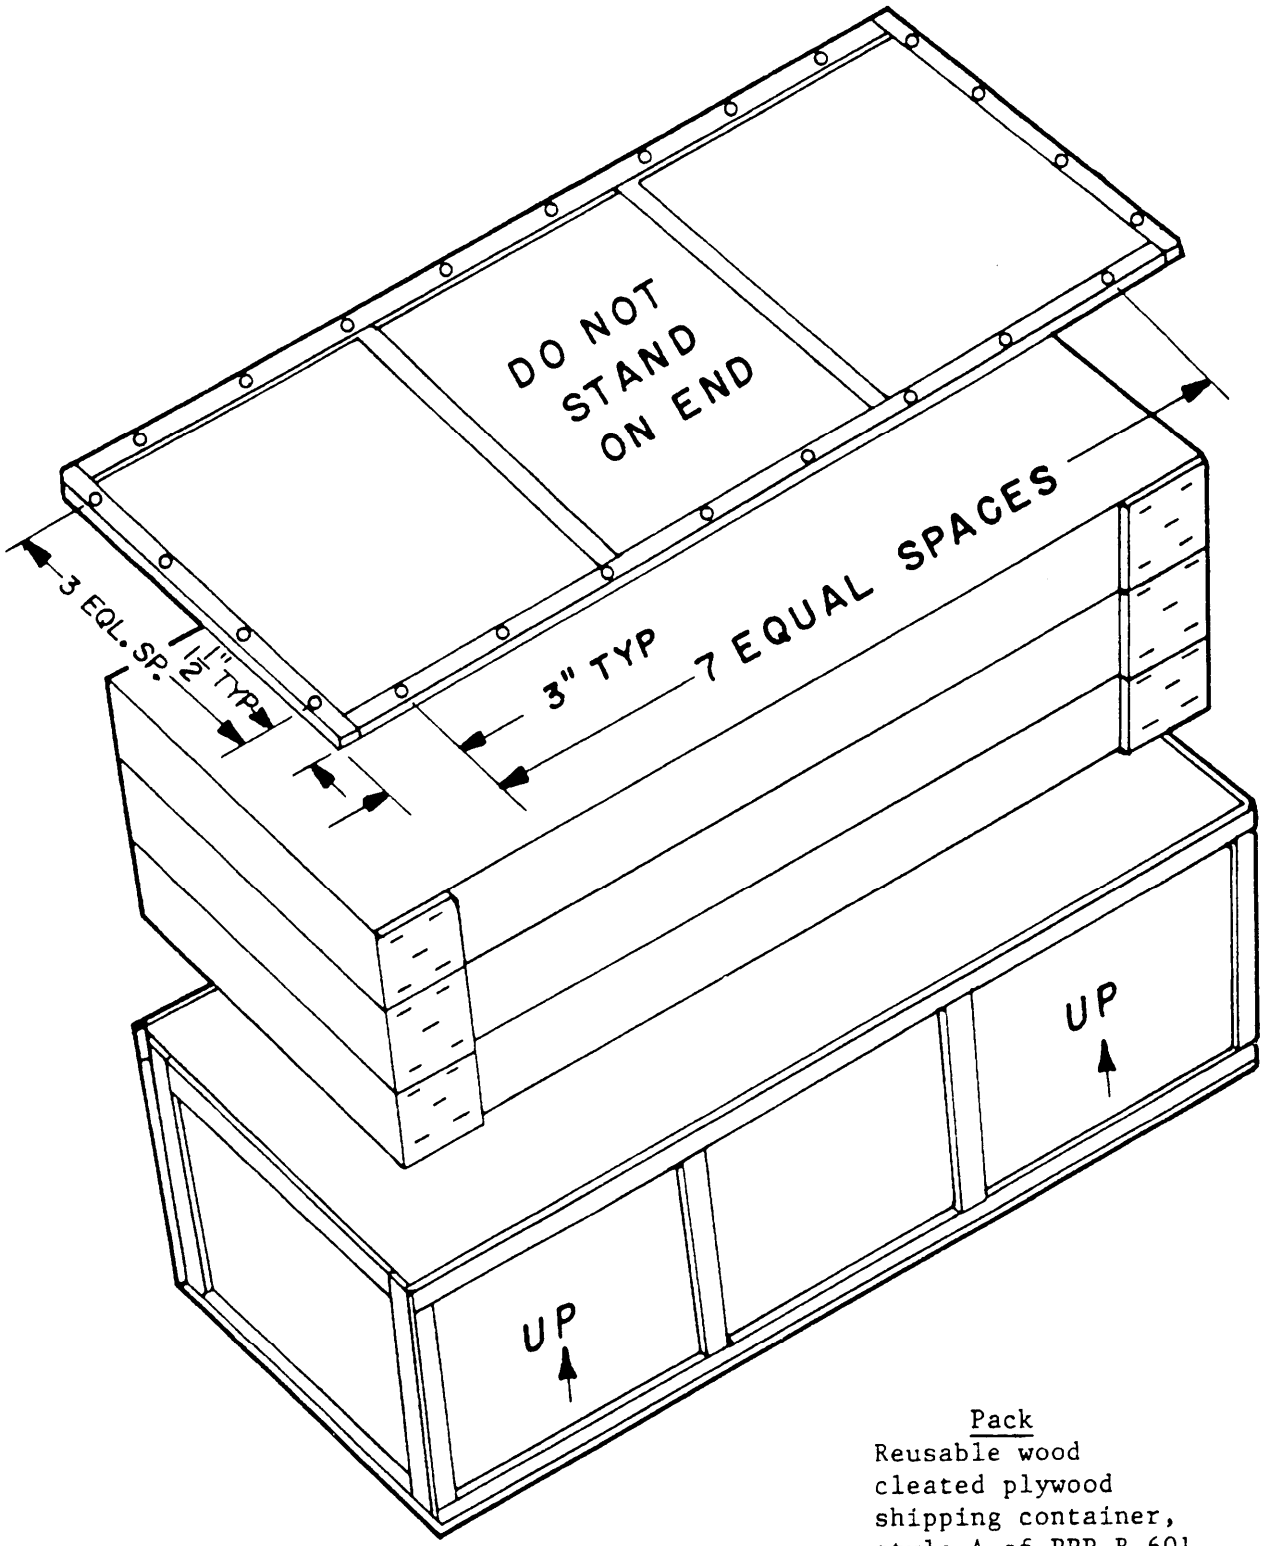

Pack
Reusable wood
cleated plywood
shipping container,
style A of PPP-B-601,
ID 71" x 29" x 16-1/2"

SH 13203139

FIGURE 5. Reusable wood-cleated plywood shipping container.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:36Z
Check the source to verify that this is the current version before use.

FRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in nitting comments and suggestions for improvements. All users of military standardization documents are invited to provide estions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and ed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the lems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an owledgement will be mailed to you within 30 days to let you know that your comments were received and are being idered.

E: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of ification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization aive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

ARTMENT OF THE NAVY

DER
SEA SYSTEMS COMMAND (SEA 55Z3)
MENT OF THE NAVY
GTON, DC 20362

CIAL BUSINESS
LTY FOR PRIVATE USE $300

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

COMMANDER
NAVAL SEA SYSTEMS COMMAND (SEA 55Z3)
DEPARTMENT OF THE NAVY
WASHINGTON, DC 20362

Source: https://assist.dla.mil -- Downloaded: 202610-23T11:36Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-D-87030B	DIVERS DRESS SUIT (MK-12)

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
	☐ USER
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ MANUFACTURER
	☐ OTHER *(Specify)*:

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426

PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 202610-23T11:36Z
Check the source to verify that this is the current version before use.