INCH - POUND

MIL-DTL-22759/92 A
23 February 1998
SUPERSEDING
MIL-W-22759/92
9 September 1994

MILITARY SPECIFICATION SHEET

# WIRE, ELECTRICAL, POLYTETRAFLUOROETHYLENE/POLYIMIDE INSULATED, LIGHT WEIGHT, NICKEL COATED, COPPER CONDUCTOR. 260°C, 600 VOLTS.

This specification sheet has been approved by all departments and agencies within the Department of Defense; however it is not intended for use in Naval aircraft or Naval Air Systems applications.

The requirements for acquiring the product described herein shall consist of this specification sheet and the issue of the following specification listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation: MIL-W-22759

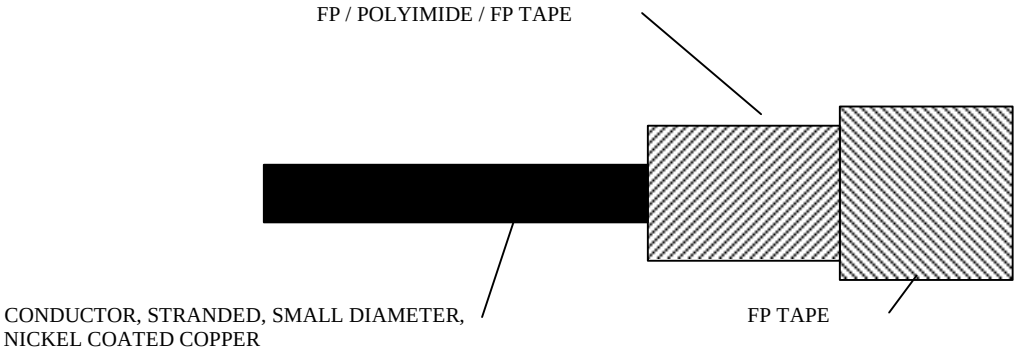


FP -Fluorocarbon Polymer, modified Polytetrafluoroethylene (PTFE)

FIGURE 1. General configuration.

AMSC N/A FSC 6145
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:54Z
Check the source to verify that this is the current version before use.

Table I. Construction details.

| Part No. [1/] | Wire Size | Conductor | | | Finished Wire | | | |
|---|---|---|---|---|---|---|---|---|
| | | Stranding (number of strands x AWG gauge of strands) | Diameter (in.) | | Resistance at 20° C (68°F) (ohms/ 1000 ft max.) | Diameter (in.) | | Weight (lb./1000 Ft) (Max.) |
| | | | MIN. | MAX. | | Min. | Max. | |
| M22759/92-26-* | 26 | 19 x 38 | 0.0175 | 0.0204 | 42.2 | 0.030 | 0.034 | 1.43 |
| M22759/92-24-* | 24 | 19 x 36 | 0.0225 | 0.0244 | 25.9 | 0.034 | 0.038 | 1.93 |
| M22759/92-22-* | 22 | 19 x 34 | 0.0285 | 0.0314 | 16.0 | 0.040 | 0.043 | 2.85 |
| M22759/92-20-* | 20 | 19 x 32 | 0.0365 | 0.0394 | 9.77 | 0.048 | 0.051 | 4.38 |
| M22759/92-18-* | 18 | 19 x 30 | 0.0455 | 0.0494 | 6.10 | 0.056 | 0.060 | 6.60 |
| M22759/92-16-* | 16 | 19 x 29 | 0.0515 | 0.0554 | 4.76 | 0.063 | 0.067 | 8.30 |
| M22759/92-14-* | 14 | 19 x 27 | 0.0645 | 0.0694 | 3.00 | 0.076 | 0.080 | 12.6 |
| M22759/92-12-* | 12 | 37 x 28 | 0.0835 | 0.0894 | 1.98 | 0.096 | 0.100 | 19.6 |
| M22759/92-10-* | 10 | 37 x 26 | 0.106 | 0.112 | 1.24 | 0.119 | 0.123 | 30.6 |

[1/] Part Number: The asterisks in the part number column of Table I shall be replaced by color code designators in accordance with MIL-STD-681. Examples: M22759/92-20-93 is a 20 AWG white with orange stripe.

Table II. Wire Insulation materials. [1/]

| Tape Code | Thickness (Nom) | Material |
|---|---|---|
| 1 | 0.0012 | 0.00045 (FP)/ 0.00065 (Polyimide) / 0.0001 (FP) |
| 2 | 0.0020 | FP (Unsintered) |
| 3 | 0.0025 | FP (Unsintered) |

[1/] Physical properties of FP unsintered tapes shall be in accordance with MIL-W-22759 requirements.

TABLE III. Physical properties of FP/Polyimide/FP Tapes.

| | |
|---|---|
| Tensile Strength | 20,000 lb/in sq. (average minimum) |
| Tensile Modulus | 400,000 lb/in sq. (average minimum) |
| Elongation | 40 percent (average minimum) |
| Dielectric Strength | 4,000 volts/mil (average minimum) |
| 0.00045 FP Layer | Distinguishable color (next to conductor) |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:54Z
Check the source to verify that this is the current version before use.

TABLE IV. Tape overlap requirements. [1/]

| Wire Size | Wrap 1 | | | Wrap 2 | | | Nominal Wall Thickness (mils) |
|---|---|---|---|---|---|---|---|
| | Tape Code | Percent Overlap | | Tape Code | Percent Overlap | | |
| | | Min | Max | | Min | Max | |
| 26 | 1 | 50.5 | 54.0 | 2 | 50.5 | 54.0 | 5.8 |
| 24 | 1 | 50.5 | 54.0 | 2 | 50.5 | 54.0 | 5.8 |
| 22 | 1 | 50.5 | 54.0 | 2 | 50.5 | 54.0 | 5.8 |
| 20 | 1 | 50.5 | 54.0 | 2 | 50.5 | 54.0 | 5.8 |
| 18 | 1 | 50.5 | 54.0 | 2 | 50.5 | 54.0 | 5.8 |
| 16 | 1 | 50.5 | 54.0 | 2 | 50.5 | 54.0 | 5.8 |
| 14 | 1 | 50.5 | 54.0 | 2 | 50.5 | 54.0 | 5.8 |
| 12 | 1 | 50.5 | 54.0 | 3 | 50.5 | 54.0 | 6.7 |
| 10 | 1 | 50.5 | 54.0 | 3 | 50.5 | 54.0 | 6.7 |

[1/] Wrap 1 is innermost tape which is in contact with the conductor with the 0.00045 inch FP side of the tape against the conductor.

TABLE V. Fluid table.

| Test Fluid | Test temperature (°C (°F)) | Immersion time (hrs.) |
|---|---|---|
| A. MIL-A-8243 Anti - icing and Deicing Defrosting Fluid, undiluted | 48 - 50 (118 - 122) | 20 |
| B. MIL-A-8243 Anti - icing and Deicing Defrosting Fluid, diluted 60/40 (fluid/water) ratio | 48 - 50 (118 - 122) | 20 |
| C. MIL-C-43616, Cleaning Compound, Aircraft Surface, Type I | 48 - 50 (118 - 122) | 20 |
| D. ASTM D1153, Methyl Isobutyl Ketone (For use in Organic Coatings) | 20 - 25 (68 - 77) | 168 |
| E. SAE AS 1241, Fire Resistant Hydraulic Fluid for Aircraft | 48 - 50 (118 - 122) | 20 |
| F. MIL-L-7808, Lubricating Oil, Aircraft Turbine Engine, Synthetic Base | 118 - 121 (244 - 250) | 30 |
| G. MIL-C-87937, Cleaning Compound, Aerospace Equipment, Type II or Type IV, undiluted | 63 - 68 (145 - 154) | 20 |
| H. MIL-C-87937, Cleaning Compound, Aerospace Equipment, Type II or Type IV, diluted 25/75 (fluid/water) ratio | 63 - 68 (145 - 154) | 20 |
| I. TT-S-735, Standard Test Fluids: Hydrocarbon, Type I | 20 - 25 (68 - 77) | 168 |
| J. TT-S-735, Standard Test Fluids: Hydrocarbon, Type II | 20 - 25 (68 - 77) | 168 |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:54Z
Check the source to verify that this is the current version before use.

TABLE V. Fluid table. - Continued.

| | | |
|---|---|---|
| K. TT-S-35, Standard Test Fluids: Hydrocarbon, Type IV | 20 - 25 (68 - 77) | 168 |
| L. Dielectric - coolant Fluid Synthetic Silicate Ester Base, Monsanto Coolanol 25 or approved equivalent. | 20 - 25 (68 - 77) | 168 |
| M. MIL-G-3056, Gasoline, Automotive , Combat | 20 - 25 (68 - 77) | 168 |

RATINGS:

Temperature rating: 260° C (500°F) maximum continuous conductor temperature.
Voltage rating: 600 volts (rms.) at sea level

ADDITIONAL REQUIREMENTS:

Wet arc propagation resistance (Test required for initial qualification only): Test in accordance with MIL-STD-2223 Method 3006. Measure the damage of the bundle along the axis. The wire is acceptable if the following criteria are met:

1. A minimum of 64 wires pass the dielectric test.
2. Three wires or less fail the dielectric test in any one bundle.
3. Actual damage to the wire is not more than 3 inches in any test bundle.

Dry arc propagation resistance (Test required for initial qualification only): Test in accordance with MIL-STD-2223 Method 3007. Measure the damage of the bundle along the axis. The wire is acceptable if the following criteria are met:

1. A minimum of 64 wires pass the dielectric test.
2. Three wires or less fail the dielectric test in any one bundle.
3. Actual damage to the wire is not more than 3 inches in any test bundle.

Blocking: 260°C ± 2°C (500°F ± 3.6°F)

Color: In accordance with MIL-STD-104, class 1; except as noted below. White preferred. Conformity of color to the limits of MIL-STD-104 shall not be required after oven exposure.

Munsell color limits for UV laser markable wire

| Color | Hue | | Value | | Chroma | |
|---|---|---|---|---|---|---|
| | From | To | From | To | From | To |
| Black | 2.5RN | 2.5RN | 7 | 8.5 | N/A | N/A |
| Blue | 5PB | 7.5B | 7 | 8 | 4 | 6 |
| Green | 2.5G | 7.5G | 7 | 9 | 2 | 6 |
| Red | 10RP | 5R | 7 | 8 | 4 | 6 |
| Yellow | 5Y | 10Y | 8 | 9 | 4 | 6 |
| Brown | 2.5YR | 7.5R | 7 | 9 | 2 | 4 |
| Orange | 10R | 2.5YR | 6 | 7 | 8 | 10 |
| Violet | 2.5P | 7.5R | 7 | 8 | 4 | 8 |
| Gray | Same as Black | | Same as Black | | Same as Black | |

Color striping or banding durability: 125 cycles (250 strokes), 250 grams weight



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:54Z
Check the source to verify that this is the current version before use.

Conductor strand adhesion: Not required

Continuous lengths: Schedule B

Dynamic cut- through (Test required for initial qualification only: Test in accordance with ASTM D 3032, Section 22. Blade shall be the standard cutting blade except the cutting edge radius shall be 0.005 ± 0.001 inch. Minimum average dynamic cut - through (lbs.) shall be as follows:

| Wire Size | 23±5°C | 150±5°C | 200±5°C | 260±5°C |
|---|---|---|---|---|
| 26 | 10 lbs. | 8 lbs. | 6 lbs. | 4 lbs. |
| 20 | 25 lbs. | 20 lbs. | 15 lbs. | 10 lbs. |
| 16 | 20 lbs. | 15 lbs. | 15 lbs. | 10 lbs. |

Flammability: Test in accordance with MIL-STD-2223, Method 1006, Procedure A:
Requirements:
Duration of after - flame 3 seconds (max)
Flame travel 3.0 inches (max)
No flaming of tissue

Forced Hydrolysis: (Test required for initial qualification only) 2000 hours at 70°C. Test 5 samples of AWG size 20 only in accordance with SAE AS4373 method 602. All 5 samples must pass the dielectric test as listed in method 602.

High frequency spark test: (When used in lieu of Impulse dielectric test) Test in accordance with MIL-STD-2223 Method 3008, 5.7 kilovolts (rms.) Test 100 percent of the wire.

Humidity resistance: After humidity exposure wire shall meet the requirements for initial insulation resistance.

Identification of product: Not required for size 26. Color code designator not required.

Identification durability: 125 cycles (250 strokes), 250 grams weight.

Immersion (Test required for initial qualification only): Test in accordance with MIL-STD-2223 Method 1001 including the additional fluids listed in Table V of this specification. Use mandrels and weights listed in Table VI for Bend testing. Dielectric test, 2500 volts (rms), 60 Hz. For turbine fuel immersion test of MIL-STD-2223, either JP 4 or MIL-T-83133 type JP-8 (NATO Type F-34) may be used.

Impulse dielectric test: 8.0 kilovolts (peak). Test 100 percent of the wire

Insulation resistance: 5000 megohms for 1000 feet (min.)

Insulation State of Sinter: (Test required for qualification ) Evaluate FP layers with a Differential Scanning Calorimeter per ASTM D 4591.

| | Energy to Melt (Joules/gram) |
|---|---|
| First Heat | Less than 25 J/g |

Life cycle: 500 hours at 290°C ± 2°C (554°F ± 3.6°F). Dielectric test, 2500 volts (rms), 60 Hz. Use mandrels coated with polytetrafluoroethylene such that the diameter of the mandrels, after coating, still conform to the required test mandrels diameters of table VI. After oven exposure, layers shall not separate and or tapes shall not lift along the insulation or at the ends.

Low temperature (cold bend): Use mandrels and weights specified in Table VI. Chamber temperature , -65°C ± 2°C (-85°F ± 3.6 F). Dielectric test, 2500 volts (rms), 60 Hz.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:54Z
Check the source to verify that this is the current version before use.

Shrinkage: 0.091 inch (max.) at 290°C ± 2°C (554°F ± 3.6°F).

Smoke Quantity: 260°C ± 5°C (500°F ± 9°F); no visible smoke.

Solderability: Not required. This slash sheet is primarily intended for crimp terminations. For solderability applications use the silver coated copper version of this specification.

Strippability: (Group II quality conformance test). Test size 26 - 14 wire only in accordance with ASTM D 3032 section 27. The length of the insulation slugs shall be 0.25 inches. The strip force shall be as follows. There shall be no evidence of insulation left on the conductor when viewed with the naked eye.

| Wire Size | Min. Force | Max. Force |
|---|---|---|
| 26-20 | 0.25 lbs. | 6.0 lbs. |
| 18-14 | 0.5 lbs. | 7.0 lbs. |

Tape Overlap: In accordance with MIL-STD-2223, method 6005.

Tensile Modulus: Test composite film in accordance with ASTM D 822, Method A

Thermal index: 260°C (500°F) minimum for 10,000 hours (Test required for initial qualification only). Test size 20 only in accordance with ASTM D 3032, Section 14.

Thermal shock resistance: Oven temperature, 260°C ± 2°C (500°F ± 3.6°F), Maximum change in measurement , 0.091 inches. No cracking.

UV Laser Marking: (Test required for initial qualification only) FP materials shall be formulated in such a manner to achieve a 62 % minimum contrast level when marked by an Ultraviolet (UV) laser source operating at a delivered power not to exceed 1.5 Joules/$cm^2$. The contrast level is defined as

$$CL = \frac{\text{(Reflectance of the background insulation - Reflectance of the laser mark)}}{\text{Reflectance of the background insulation}} \times 100$$

Wrap (mandrel wrap): No cracking, no dielectric breakdown. Use mandrels specified in Table VI. Dielectric test, 2500 volts (rms), 60 Hz.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:54Z
Check the source to verify that this is the current version before use.

TABLE VI. Test mandrel and test load requirements.

| Wire Size (AWG) | Test Mandrel Diameter [1/] (inches) | | | Test Load [1/] (lbs) | |
|---|---|---|---|---|---|
| | Cold Bend | Life Cycle/ Bend Test | Wrap | Cold Bend | Life Cycle/ Bend Test |
| 26 | 1.00 | 0.375 | 0.125 | 3.00 | 0.50 |
| 24 | 1.00 | 0.500 | 0.125 | 3.00 | 0.75 |
| 22 | 1.00 | 0.500 | 0.125 | 4.00 | 1.00 |
| 20 | 1.00 | 0.500 | 0.125 | 4.00 | 1.50 |
| 18 | 1.50 | 0.750 | 0.250 | 5.00 | 2.00 |
| 16 | 1.50 | 1.00 | 0.250 | 5.00 | 2.00 |
| 14 | 2.00 | 1.00 | 0.375 | 5.00 | 3.00 |
| 12 | 2.00 | 1.50 | 0.375 | 5.00 | 3.00 |
| 10 | 3.00 | 2.00 | 0.375 | 6.00 | 3.00 |

[1/] Tolerance shall be ± 3 percent of the given values.

Qualification of wire:

For qualification, a source is required to submit data on quality conformance tests and any finished wire tests as required by the qualification authorization letter. All other testing will be performed by the qualifying activity at the source's expense.

Due to the extended time period over which the thermal index test is performed, a source may become qualified under this specification sheet while this test is still in progress.

Custodian:
Army - CR
Navy - AS
Air Force - 85
NASA - NA

Preparing Activity
Navy - AS

Project (6145-2142-13)

Review Activities:
Army - AV, MI
Air Force - 11, 19, 70, 99
DLA - CC



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:54Z
Check the source to verify that this is the current version before use.