INCH-POUND

MIL-C-10387J
10 April 1992
SUPERSEDING
MIL-C-10387H
3 March 1982
and in part (see 6.6)
AWWA C606

MILITARY SPECIFICATION

COUPLINGS, CLAMP, PIPE; WITH BOLTS AND SYNTHETIC-RUBBER GASKETS FOR GROOVED-END PIPE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers clamp-type couplings, with for grooved-end pipe, used with fuel.

1.2 Classification. Couplings (including gaskets) and gaskets for use with petroleum fuel (see 6.2), will be of the following classes and sizes (see 6.2 and 6.4).

Coupling or gasket

A -	Aluminum (including gasket)
B -	Malleable iron, ductile iron, or steel (including gasket)
C -	Gasket only.

Nominal size (inches)

3/4	4
1	5
1-1/4	6
1-1/2	8
2	10
2-1/2	12
3	14
3-1/2	

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: USA Belvoir Research, Development, and Engineering Center, ATTN: STRBE-TSE, Fort Belvoir, VA, 22060-5606 by using the Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 4730

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:59Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. The following specifications and standards form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDERAL

QQ-A-367	-	Aluminum Alloy Forgings.
PPP-B-601	-	Boxes, Wood, Cleated-Plywood.
PPP-B-636	-	Boxes, Shipping, Fiberboard.

MILITARY

MIL-T-704	-	Treatment and Painting of Materiel.

STANDARDS

FEDERAL

FED-STD-595	-	Colors Used in Government Procurement.
FED-STD-601	-	Rubber: Sampling and Testing.

MILITARY

MIL-STD-105	-	Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	-	Marking for Shipment and Storage.
MIL-STD-130	-	Identification Marking of US Military Property.
MIL-STD-889	-	Dissimilar Metals.
MIL-STD-1190	-	Minimum Guidelines for Level C Preservation, Packing and Marking.

(Unless otherwise indicated, copies of federal and military specifications and standards are available from the Standardization Documents Order Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.2 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2).

AMERICAN SOCIETY OF MECHANICAL ENGINEERS (ASME)

B 18.10	-	Track Bolts and Nuts.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:59Z
Check the source to verify that this is the current version before use.

(Application for copies should be addressed to the American Society of Mechanical Engineers, United Engineering Center, 345 East 47th Street, New York, NY 10017.)

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

A 27	-	Steel Castings, Carbon, for General Applications.
A 47	-	Ferritic Malleable Iron Castings.
A 108	-	Steel Bars, Carbon, Cold Finished, Standard Quality.
A 536	-	Ductile Iron Castings.
A 193	-	Steel, Stainless and Alloy Steel Bolting Materials for High-Temperature Service.
A 194	-	Nut for Bolts, Carbon and Alloy-Steel for High Pressure and High-Temperature Service.
B 26	-	Aluminum Alloy Sand Castings.
B 108	-	Aluminum-Alloy Permanent Mold Castings.
B 633	-	Electrodeposited Coatings of Zinc on Iron and Steel.
D 395	-	Rubber Property - Compression Set.
D 412	-	Rubber Properties in Tension.
D 471	-	Rubber Property - Effect of Liquids.
D 573	-	Rubber Deterioration in an Air Oven.
D 1053	-	Rubber Property - Stiffening at Low Temperatures: Flexible Polymers and Coated Fabrics.
D 1229	-	Rubber Property - Compression Set at Low Temperatures.
D 2240	-	Rubber Property - Durometer Hardness.
D 3953	-	Strapping, Flat Steel and Seals.
D 4675	-	Selection and Use of Flat Strapping Materials.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Description. The coupling for joining two pieces of pipe or pipe fittings shall consist of a two-piece semicircular housing, a synthetic rubber gasket of pressure responsive design, and nuts and bolts, or other type of fasteners to secure the two halves together.

3.2 First article. When specified (see 6.2), a sample shall be subjected to first article inspection (see 6.3) in accordance with 4.3 and 4.5.

3.3 Material. Material shall be as specified herein. Materials not specified shall be selected by the contractor and shall be subject to all provisions of this specification.

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:59Z
Check the source to verify that this is the currentversion before use.

3.3.1 Class A - Aluminum housing. Aluminum permanent mold castings shall conform to ASTM B 108, alloy 356.0 (UNS A03560) in T6 temper. Aluminum sand castings shall conform to ASTM B 26, alloy 356.0 (UNS A03560) in T6 temper. Aluminum forgings shall be in accordance with QQ-A-367, alloy number 6151 in T6 temper.

3.3.2 Class B - Malleable iron, ductile iron, and steel housing. Malleable iron castings shall conform to ASTM A 47, grade 35018 or grade 32510. Ductile (nodular) iron castings shall conform to ASTM A 536, grade 65-45-12. Steel castings shall conform to ASTM A 27, grade 65-35.

3.3.3 Material deterioration prevention and control. The couplings shall be fabricated from compatible materials, inherently corrosion resistant or treated to provide protection against the various forms of corrosion and deterioration that may be encountered in any of the applicable operating and storage environments to which the couplings may be exposed.

3.3.3.1 Dissimilar metals. Dissimilar metals shall not be used in intimate contact with each other unless protected against galvanic corrosion. Dissimilar metals and methods of protection are defined and detailed in MIL-STD-889.

3.3.3.2 Identification of materials and finishes. The contractor shall identify the specific material, material finish or treatment for use with component and subcomponent, and shall make information available upon request to the contracting officer or designated representative.

3.3.3.3 Recovered materials. For the purpose of this requirement, recovered materials are those materials which have been collected from solid waste and reprocessed to become a source of raw materials, as distinguished from virgin raw materials. The components, pieces and parts incorporated in the coupling may be newly fabricated from recovered materials to the maximum extent practicable, provided the couplings produced meets all other requirements of this specification. Used, rebuilt or remanufactured components, pieces and parts shall not be incorporated in the couplings.

3.4 Coupling housing. Coupling housings shall be bolted over grooved-end pipe sections. The coupling shall provide an all-around grip on the grooved-end pipe with positive flexible locking action. The amount of flexibility shall be in accordance with table I. The coupling housing shall be designed such that it does not pinch the gasket. Bolts for joining the coupling halves shall be zinc-plated steel, (see 3.6.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:59Z
Check the source to verify that this is the current version before use.

TABLE I. Coupling flexibility.

Nominal Pipe Size Inches	Flexibility (Deflection from center line) (°) degrees	Nominal Pipe Size Inches	Flexibility (Deflection from center line) (°) degrees
3/4	6 ° -45' ±0 ° -15'	4	3 ° -10' ±0 ° -15'
1	5 ° -30' ±0 ° -15'	5	2 ° -10' ±0 ° -15'
1-1/4	4 ° -20' ±0 ° -15'	6	2 ° -10' ±0 ° -15'
1-1/2	3 ° -45' ±0 ° -15'	8	1 ° -40' ±0 ° -15'
2	3 ° ±0 ° -15'	10	1 ° -20' ±0 ° -15'
2-1/2	2 ° -30' ±0 ° -15'	12	1 ° -10' ±0 ° -15'
3	2 ° ±0 ° -15'	14	1 ° ±0 ° -15'
3-1/2	2 ° -30' ±0 ° -15'		

3.5 Gasket. The gasket shall be made from epichlorohydrin and shall be compatible for use with fuels such as diesel fuels and jet fuels. Gaskets shall perform satisfactorily at all temperatures ranging from -25 °F to + 150 °F. The gasket shall be made from injection-molded or compression-molded synthetic rubber. Gasket size will be identified with the nominal pipe size. Physical properties of the gasket shall meet or exceed the requirements shown in table II. All gaskets shall be no more than 12 months old on date of acceptance by the Government.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:59Z
Check the source to verify that this is the current version before use.

TABLE II. Physical requirements of the gasket.

Description of Properties	Requirements	ASTM and FED-STD-601 Test Methods
Original Properties		
Tensile Strength PSI (minimum)	1,500	D 412
Ultimate Elongation (% minimum)	300	D 412
Hardness, Shore A Durometer, points	60 ±10	D 2240
After Oven Aging for 22 Hours at 158 °F		
Tensile Retained (% minimum)	80	D 573
Elongation Retained (% minimum)	80	D 573
Hardness Change, Shore A, Points (maximum)	±10	D 2240
Compression Set (% maximum)	45	D 395 Using Method B
After immersion in ASTM Reference Fuel B for 94 hours at 73.4 °F (23 °C)		
Tensile Retained (% minimum)	45	6111 1/
Volume Change (% maximum)	25	D 471 2/
Elongation Retained (% minimum)	50	D 471
After immersion in ASTM Reference Fuel A for 94 hours at 73.4 °F (23 °C)		
Volume increase (% maximum)	15	D 471 3/
Low temperature properties after extraction in ASTM reference Fuel B for 94 hours at 73.4 °F (23 °C), dried and cold conditioning at -25 °F (-31.7 °C) for seven days.		
Compression Set (% maximum)	55	D 1229 3/ 4/
Torsional Stiffness Ratio (maximum)	10	D 1053 3/
After immersion in distilled water (med. # 10) for 14 days at +160 °F		
Tensile Retained (% minimum)	65	6111 1/
Volume Change (% maximum)	15	D 471 2/

1/ Tensile strength calculations shall be based on swollen cross-sectional area of the specimen (4.8.1 of method 6111).

2/ Test specimen shall be 2.125 inches by 0.875 inch and not over 0.0625-inch thick.

3/ Test specimen shall be cut from strips that have been prepared as follows:
(a) Buff to required thickness.
(b) Immerse in Reference fuel B of ASTM D 471 at +73.4 °F (23 °C) ±3.6 °F (±2 °C) for 94 hours (±2 hours).
(c) Blot and dry while exposed on all sides to circulating air at room temperature for 24 hours.
(d) Dry in air-circulating oven at +130 °F for 72 hours.
(e) Cool to room temperature for not less than 4 hours.

4/ Test specimens shall be compressed 40 percent regardless of hardness.

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:59Z
Check the source to verify that this is the current version before use.

3.6 Fasteners.

3.6.1 Bolts and nuts. The bolts shall conform to either ASME B 18.10 or ASTM A 193, grade B7. Nuts shall conform to ASTM A 194 grade 2H, heavy hex zinc type. Both bolts and nuts shall be zinc plated in accordance with ASTM B 633, type II, classification Fe-Zn-13.

3.6.2 Retaining pins. If retaining pins are used in lieu of bolts and nuts, pins shall be manufactured of ASTM A 108, grade 1045 carbon steel, heat treated to Rockwell C30 to C35. Pins shall have enough chamfer for ease of installations. The pins shall be zinc plated in accordance with ASTM B 633, type II, classification Fe-Zn-13. Retaining pins shall be captively (preferably with tape) retained to the coupling.

3.7 Pressure ratings. Couplings (of the nominal pipe size) shall have the working pressure ratings and be tested to hydrostatic pressures as shown in table III for a period of not less than 5 minutes without evidence of leakage or permanent deformation.

TABLE III. Pressure ratings.

Nominal pipe size (inches) Outside Diameter - O.D.	DUCTILE IRON COUPLING		ALUMINUM COUPLING	
	Working pressure rating (psi)	Hydrostatic test pressure (psig)	Working Pressure (psi)	Hydrostatic test pressure (psi)
3/4 (1.050)	1000	2000	---	---
1 (1.315)	1000	2000	500	800
1-1/4 (1.660)	1000	2000	---	---
1-1/2 (1.900)	1000	2000	500	800
2 (2.375)	1000	2000	500	800
2-1/2 (2.875)	1000	2000	500	800
3 (3.500)	1000	2000	500	800
3-1/2 (4.000)	1000	1500	---	---
4 (4.500)	1000	1500	500	800
5 (5.563)	1000	1500	500	750
6 (6.625)	1000	1500	400	600
8 (8.625)	800	1200	300	500
10 (10.750)	800	1200	---	---
12 (12.750)	600	1000	---	---
14 (14.000)	300	800	---	---

3.8 Performance requirements. The coupling including gasket shall be operable at all temperature from -25 to +160 °F, under working pressure from 20 inches of mercury vacuum to 1000 psig (or rated working pressure of 8-inch, 10-inch, 12-inch size coupling) without any leakage or permanent deformation.

3.9 Treatment and painting. Unless otherwise specified (see 6.2), all exterior surfaces of couplings shall be cleaned, treated and painted in accordance

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:59Z
Check the source to verify that this is the current version before use.

with MIL-T-704, type A. Topcoat color shall be in accordance with FED-STD-595, color no. 33446.

3.10 Identification marking. Each coupling shall be identified in accordance with MIL-STD-130. In addition, the gaskets shall be marked with the year of manufacture.

3.11 Workmanship. The couplings shall be free of burrs, cracks, and imperfections.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.1.2 Component and material inspection. The contractor is responsible for ensuring that components and materials are manufactured, examined, and tested in accordance with referenced specifications and standards, as applicable.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3).
b. Quality conformance inspection (see 4.4).
c. Inspection of packaging (see 4.6).

4.3 First article inspection.

4.3.1 Examination. When required (see 6.2), the first article couplings shall be examined as specified in 4.5.1. Presence of one or more defects shall be cause for rejection.

4.3.2 Tests. When required (see 6.2), the first article couplings shall be tested as specified in 4.5.2. Failure of any test shall be cause for rejection.

4.4 Quality conformance inspection.

Source: https://assist.dla.mil -- Downloaded: 202640-17T13:59Z
Check the source to verify that this is the current version before use.

4.4.1 Lot. For the purpose of inspection, a lot shall consist of all the couplings of the same material and manufacturing classification offered for delivery at one time.

4.4.2 Sampling. Sampling for examination and tests shall be in accordance with MIL-STD-105, special inspection level S-2. Sample size shall be determined by using MIL-STD-105, tables I and IIa. A lot shall be accepted when 0 defects are found and rejected when 1 or more defects are found.

4.4.2.1 Sample preparation. Whenever a complete gasket could not be used for testing, samples shall be prepared from sheets and blocks. The rubber shall be taken from a batch used in the manufacture of the lot represented, and the sheets and blocks shall be cured identically to the procedure (i.e., method, temperature, and time) used in the curing of the gaskets represented.

4.4.3 Examination. Samples selected in accordance with 4.4.2 shall be examined as specified in 4.5.1. Presence of one or more defects shall be cause for rejection.

4.4.4 Tests. Samples selected in accordance with 4.4.2 shall be tested as specified in 4.5.2. Failure to meet any test requirements shall be cause for rejection.

4.5. Inspection procedure.

4.5.1 Examination. The couplings shall be examined as specified herein for the following defects:

Major

101. Materials not as specified (see 3.3.1 and 3.3.2).
102. Materials not resistant to corrosion and deterioration, or treated to be resistant to corrosion and deterioration of the applicable storage and operating environments (see 3.3.3).
103. Dissimilar metals as defined in MIL-STD-889 are not effectively insulated from each other (see 3.3.3.1).
104. Contractor does not have documentation available for identification of materials, material finishes, or treatment (see 3.3.3.2).
105. Used, rebuilt or remanufactured components, pieces, or parts incorporated in the couplings (see 3.3.3.3).
106. Coupling housing not as specified (see 3.4).
107. Gasket not as specified (see 3.5).
108. Fasteners not as specified (see 3.6).
109. Treatment and painting not as specified (see 3.9).
110. Identification marking missing, or incomplete (see 3.10).
111. Workmanship not as specified (see 3.11).

4.5.2 Tests. Quality conformance tests shall be performed in accordance with 4.5.2.1 and 4.5.2.2.

4.5.2.1 Coupling. The coupling with gasket shall be installed on a pipe joint in accordance with 3.4 and subjected to an applicable hydrostatic test pressure in accordance with table V for a period of not less than 15 minutes, after which time the pressure shall be reduced to the vacuum specified herein and held for not less

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:59Z
Check the source to verify that this is the current version before use.

than 5 minutes and then increased to the test pressure and held there for not less than 5 minutes. Evidence of leakage under pressure or under vacuum shall constitute failure of this test. On successful completion of the hydrostatic pressure/vacuum test, the coupling shall be disassembled and inspected. Any evidence of permanent deformation or damage to any part, such as cracking, splitting, or rupturing, shall constitute failure of the test.

4.5.2.2 Gasket. The gasket shall be tested in accordance with applicable ASTM and FED-STD-601 test methods as specified in table IV. Nonconformance to the applicable requirements of 3.5 shall constitute failure of this test.

4.6 Inspection of packaging.

4.6.1 Quality conformance inspection of pack.

4.6.1.1 Unit of product. For the purpose of inspection, a completed pack prepared for shipment shall be considered a unit of product.

4.6.1.2 Sampling. Sampling for examination shall be in accordance with MIL-STD-105. Sample size shall be determined by using MIL-STD-105, table I and table IIa. A lot shall be accepted when 0 defects are found and rejected when 1 or more defects are found.

4.6.1.3 Examination. Samples selected in accordance with 4.6.1.2 shall be examined for the following major defects. One or more defects shall be cause for rejection.

112.	Containers not as specified (see 5.1.1 and 5.2.1).
113.	Couplings not assembled as specified (see 5.1.1).
114.	Couplings size 4 inches or less not preserved together as specified (see 5.1.1).
115.	Couplings size 6 inches or greater not individually preserved as specified (see 5.1.1).
116.	Packing not as specified (see 5.2).
117.	Strapping not as specified for level A or B (see 5.2.1 and 5.2.2).
118.	Packing not as specified by the referenced document for level C (see 5.2.3).
119.	Marking missing, illegible, incorrect or incomplete (see 5.3).

5. PACKAGING

5.1 Preservation. Preservation shall be level A or C, as specified (see 6.2).

5.1.1 Level A. Each coupling shall be assembled with gasket in place and the nuts drawn hand-tight on the bolts. In quantities as specified (see 6.2), couplings of like description of sizes up to and including 5 inches shall be preserved together in close-fitting boxes conforming to PPP-B-636, W6c, in quantities not to exceed the weight limitation of the box. The couplings shall be cushioned and blocked within the box to prevent free movement. Couplings of size 6 inches or larger shall be individually preserved in a close-fitting box conforming to PPP-B-636, W5c, or W6c, as applicable to the weight of the coupling.

5.1.2 Level C. Couplings shall be preserved in accordance with MIL-STD-1190.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:59Z
Check the source to verify that this is the current version before use.

5.2 Packing. Packing shall be level A, level B, or level C, as specified (see 6.2).

5.2.1 Level A. Couplings preserved as specified in 5.1 shall be packed together in close-fitting boxes conforming to PPP-B-601, overseas type, style optional. Strapping shall conform to ASTM D 3953, type 1 or 2, zinc-coated, size as applicable and ASTM D 4675.

5.2.2 Level B. Couplings shall be packed as specified in 5.2.1 for level A except that boxes shall be domestic type and strapping may be zinc-coated.

5.2.3 Level C. Couplings preserved as specified in 5.1 shall be packed in accordance with MIL-STD-1190.

5.3 Marking. In addition to any special marking required by the contract or order, marking shall be in accordance with MIL-STD-129, method optional. Interior and exterior packing lists are required in accordance with appendix F of MIL-STD-129.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The couplings are intended for use in joining grooved-type pipes conforming to MIL-P-11087, tubes conforming to MIL-T-425 and fittings in a pipeline system for fuel and petroleum products.

6.1.1 Gasket. The gasket is intended for use with petroleum based fuels such as diesel fuels, and jet fuels.

6.2 Acquisition requirements. Acquisition documents should specify the following:


a. Title, number, and date of the specification.
b. Class and type required (see 1.2 and 6.4).
c. Issue of DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1 and 2.2).
d. When a first article is required (see 3.2 and 4.3).
e. When other than commercial finish or MIL-T-704, type A, finish is required (see 3.9).
f. Level of preservation and degree of packing required (see 5.1 and 5.2).
g. Quantity per unit package (see 5.1.1).

6.3 First article. When a first article inspection is required, the item(s) should be a preproduction model. The first article should consist of one or more units. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examinations, approval of the first article test results and disposition of the first articles. Invitation for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection to those bidders offering a product which has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:59Z
Check the source to verify that this is the current version before use.

prior Government approval is presently appropriate for the pending contract. Bidders should not submit alternate bids unless specifically required to do so in the solicitation.

6.4 Part or identifying number (PIN). The PIN to be used for couplings covered acquired to this document are created as follows (see 6.2):

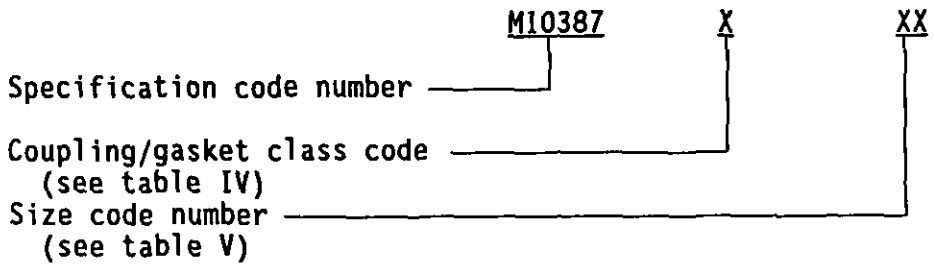

Example: M10387A05 couplings of aluminum alloy and 2 inches in size, conforming to MIL-C-10387.

6.5 Subject term (key word) listing.

Coupling, Aluminum
Coupling, Ductile iron
Coupling, Malleable iron
Steel coupling
Petroleum systems
Pipeline systems

6.6 Supersession data. American Water Works Association's specification AWWA C606, supersedes the portion of MIL-C-10387H, dated 3 March 1982, for the couplings for use with water.

6.7 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:59Z
Check the source to verify that this is the current version before use.

6.8 International standardization agreements. Certain provisions of this specification (for groove dimensions, see figure 1) are the subject of International Standardization Agreement NATO STANAG 37567. When amendment, revision, or cancellation of this specification is proposed which will modify the international agreement concerned, the preparing activity will take appropriate action through international standardization channels including departmental standardization offices to change the agreement or make other appropriate accommodations.

Custodians:
Army - ME
Navy - YD
Air Force - 99

Review activities:
Army - CE
Navy - CG

Air Force - 82
DLA - CS

Preparing activity:
Army - ME

Project 4730-0035

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:59Z
Check the source to verify that this is the current version before use.

GROOVE DIMENSION (INCHES)				
Nominal Pipe Size	A	B	C	D
3/4	1.050 ± .010	0.625 ± .03	0.313 ± .03	0.938 + 0.000 - 0.015
1	1.315 ± .013	0.625 ± .03	0.313 ± .03	1.190 + 0.000 - 0.015
1 1/4	1.660 ± .016	0.625 ± .03	0.313 ± .03	1.535 + 0.000 - 0.015
1 1/2	1.900 ± .019	0.625 ± .03	0.313 ± .03	1.775 + 0.000 - 0.015
2	2.375 ± .024	0.625 ± .03	0.313 ± .03	2.250 + 0.000 - 0.015
2 1/2	2.875 ± .029	0.625 ± .03	0.313 ± .03	2.720 + 0.000 - 0.018
3	3.500 + .035 - .031	0.625 ± .03	0.313 ± .03	3.344 + 0.000 - 0.018
3 1/2	4.000 + .049 - .031	0.625 ± .03	0.313 ± .03	3.834 + 0.000 - 0.020
4	4.500 + .045 - .031	0.625 ± .03	0.375 ± .03	4.344 + 0.000 - 0.020
5	5.563 + .056 - .031	0.625 ± .03	0.375 ± .03	5.295 + 0.000 - 0.022
6	6.625 + .063 - .031	0.625 ± .03	0.375 ± .03	6.455 + 0.000 - 0.022
8	8.625 + .063 - .031	0.750 ± .03	0.438 ± .03	8.441 + 0.000 - 0.025
10	10.750 + .063 - .031	0.750 ± .03	0.500 ± .03	10.562 + 0.000 - 0.027
12	12.750 + .063 - .031	0.750 ± .03	0.500 ± .03	12.531 + 0.000 - 0.030
14	14.000 + .063 - .031	0.938 ± .03	0.500 ± .03	13.781 + 0.000 - 0.030

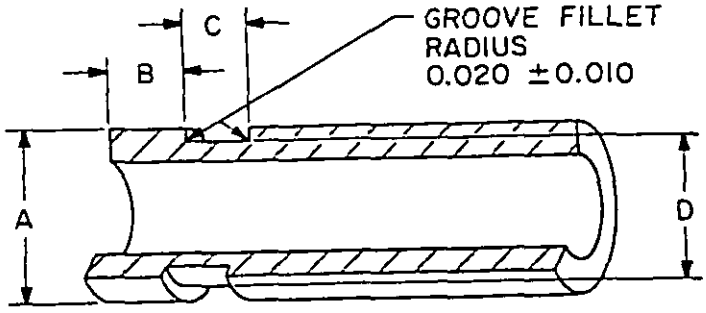


FIGURE 1. Grooved pipe.

X-4970

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:59Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-C-10387J	2. DOCUMENT DATE (YYMMDD) 920410

3. DOCUMENT TITLE
Couplings, Clamp, Pipe; with Bolts and Synthetic-Rubber Gaskets for Grooved-End Pipe

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle Initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (if applicable) (2) AUTOVON	7. DATE SUBMITTED

8. PREPARING ACTIVITY

a. NAME Carolyn B. Johnson	b. TELEPHONE (Include Area Code) (1) Commercial (703) 704-3468	(2) AUTOVON 654-3468
c. ADDRESS (Include Zip Code US Army Belvoir RDE Center ATTN: STRBE-TSE Fort Belvoir, VA 22060-5606	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340	AUTOVON 289-2340

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:59Z
Check the source to verify that this is the current version before use.