MILITARY SPECIFICATION SHEET

CONNECTORS, ELECTRICAL, MODULAR, CONNECTOR FRAME,
TYPE IV, DOUBLE SPAN, CENTER

This specification is approved for use by all Departments and Agencies of the Department of Defense

The complete requirements for acquiring the connector described herein shall consist of this specification and the latest issue of MIL-C-28754


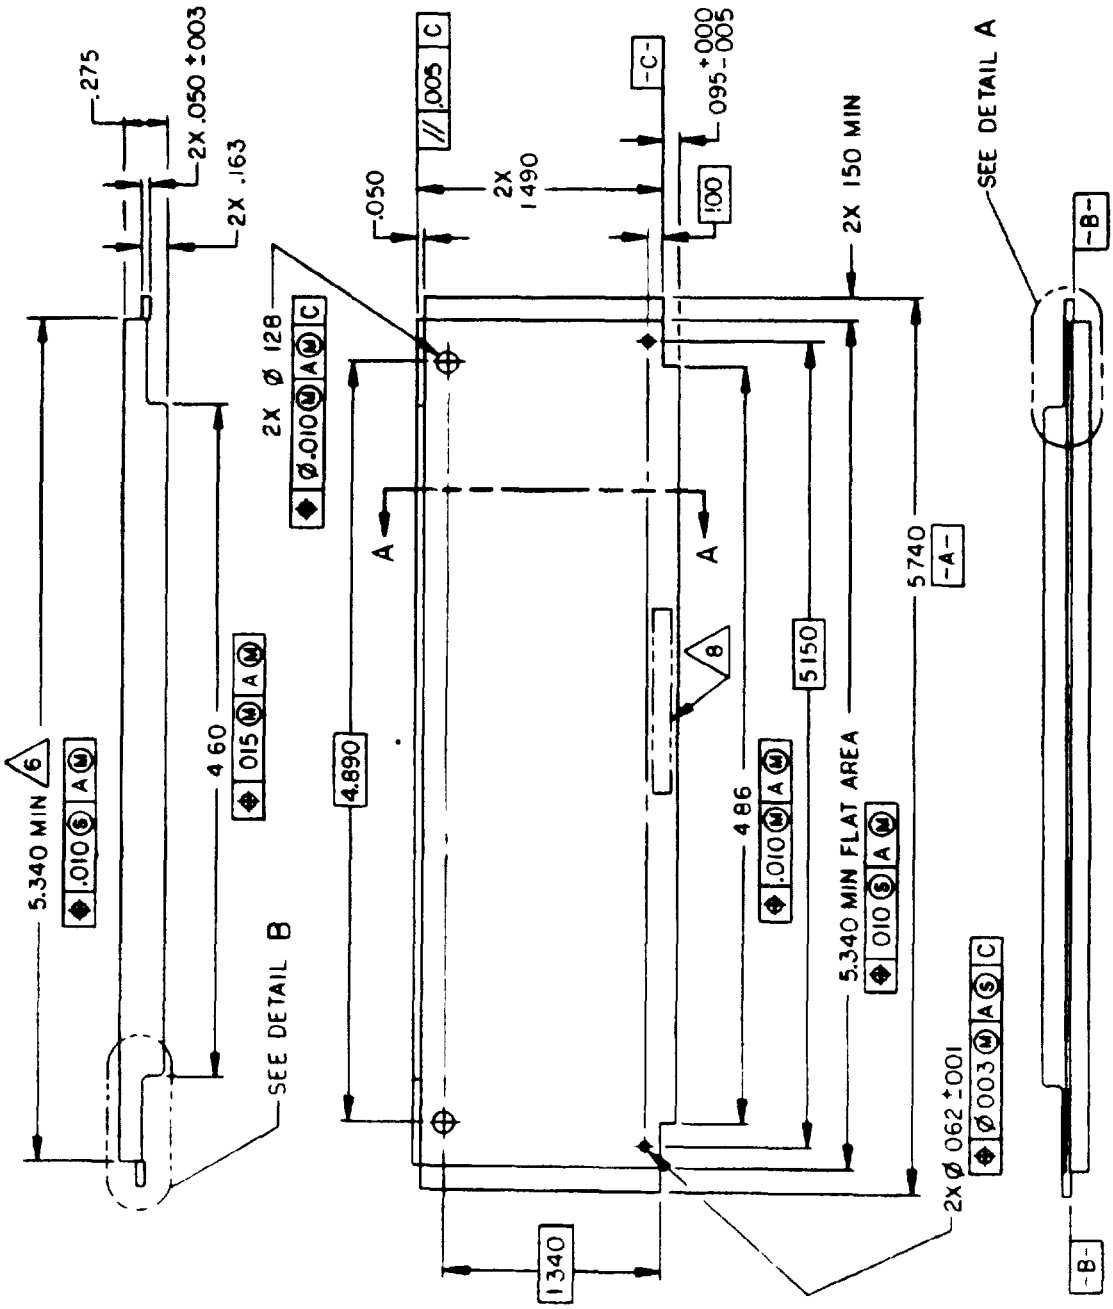



FIGURE 1 Dimensions and configurations

FSC 5935


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T14:49Z
Check the source to verify that this is the current version before use.

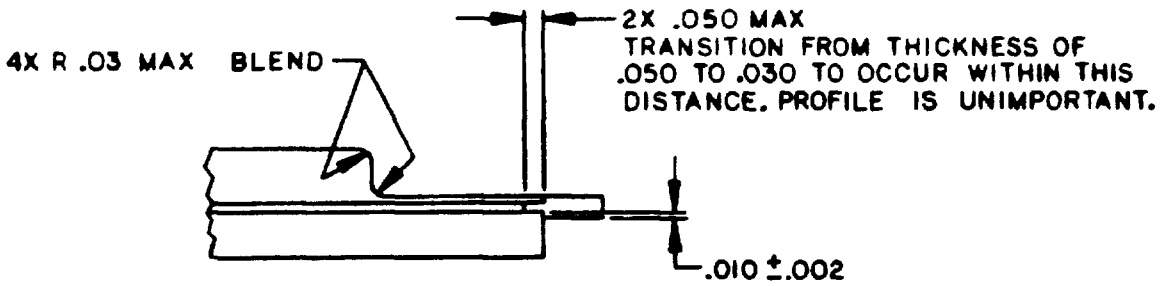

DETAIL A

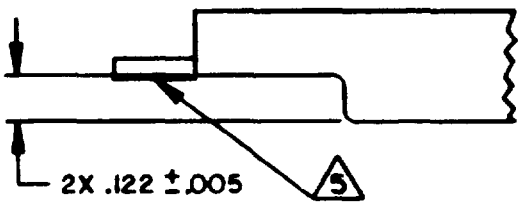

DETAIL B

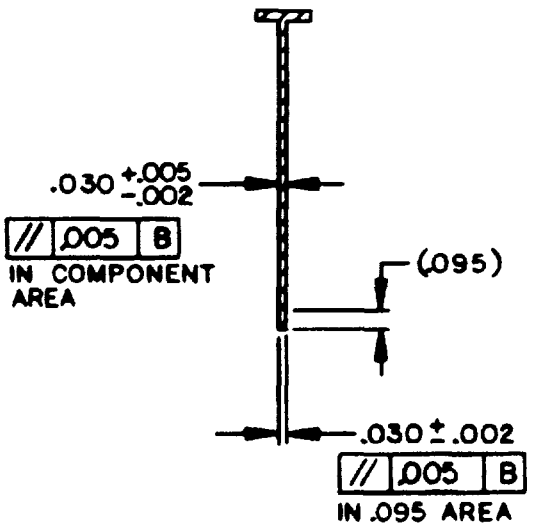

SECTION A-A

FIGURE 1 Dimensions and configurations - continued

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T14:49Z
Check the source to verify that this is the current version before use.

INCHES	MM	INCHES	MM	INCHES	MM	INCHES	MM
001	03	030	76	128	3 25	4 600	116 84
002	05	.050	1.27	150	3.81	4.860	123.45
.003	.08	.062	1.58	163	4 14	4.890	124.21
005	13	.095	2.41	.275	6.99	5.150	130.81
010	25	.100	2.54	1.340	34 04	5 340	135 64
015	.38	122	3 10	1 490	37.85	5 740	145.80

NOTES

1. Dimensions are in inches.
2. Metric equivalents are given for general information only and are based upon 1.00 inch = 25 4 mm.
3. Unless otherwise specified, tolerances are ±.005 (.13 mm) inch for three place decimals, ±.01 (.3 mm) inch for two place decimals and ±2° for angles.
4. Unless otherwise specified, all corner radii shall be .02 (.51 mm) inch rad max.
5. This surface and the 122 dimension shall be flush to .005 maximum step.
6. Top of T surfaces
7. Dimensional limits apply after plating.
8. Frame shall be marked in approximate location shown with part number, manufacturer's number and date code with contrasting ink in characters 06 (1.5 mm) inch high.

FIGURE 1 Dimensions and configurations - continued

Source: https://assist.dla.mil -- Downloaded: 20260-20T14:49Z
Check the source to verify that this is the current version before use.

REQUIPEMENTS

Dimensions and configuration See Figure 1.

Materials: For M28754/67-01, aluminum alloy 6101, ASTM-B-317, T6 extrusion
For M28754/67-02, copper C11000, H01 temper, per ASTM B152-81
For M28754/67-03, copper-invar-copper (20-60-20% by thickness)

Finish For M28754/67-01, anodic coating, MIL-A-8625, Type II, Class 2, black

For M28754/67-02 and -03, electroless nickel per MIL-C-26074, 5 percent phosphorous minimum, Class 1, Grade A, 0015 ± 0005 inch thick, MIL-C-5541, Class 1A, yellow. Within 4 hours after plating, oven bake 275 ± 25°F, 1 hour, for hydrogen relief and adhesion.

Examination· One frame from each plating lot shall be exposed to salt fog per MIL-STD-810, Method 509, Procedure 1, 48 hours, and one frame shall be exposed to oven bake at 375 ± 10°F, 60-90 minutes. Examine each frame, using 6 to 10 power magnification, for loose or blistered coating. Examination results shall be delivered with each order The examined frames shall be retained by the supplier for a period of 6 months.

Stress relief For M28754/67-02 and -03, frames shall receive the following bake cycle prior to plating and after all fabrication steps, 375 ± 10°F for 90 ± 10 minutes.

Military part number· M28754/67- (Dash Number from Table I)

TABLE I

DASH NUMBER	MATERIAL	FINISH
01	Aluminum Alloy	Anodize
02	Copper	Nickel
03	Copper-Invar	Nickel

Qualification information The frame shall meet the following qualification tests of MIL-C-28754, Table IV, Type IV. Subgroup I, Method Paragraph 4 7 1, Subgroup II, Method Paragraph 4 7 11, 4.7.1, Subgroup III, Method Paragraph 4.7.13 and 4.7.1, Subgroup IV, Method Paragraph 4 7 12, 4 7 18, 4 7 19, 4.7.20 and 4.7 1

Number of units to be inspected. Twelve (12) units of each dash number to be qualified shall be inspected.

Supersession data. Supersedes Naval Electronic Systems Command Drawing Number 0102-704-1, -2, -3 and -4, Code Identification Number 28687

Custodians.
Navy - EC

User Activities
Navy - AS

Preparing Activity
Navy - EC

(Project 5935-N252-14)

Source: https://assist.dla.mil -- Downloaded: 202610-20T14:49Z
Check the source to verify that this is the current version before use.