MILITARY SPECIFICATION SHEET

CONNECTORS, ELECTRICAL, MODULAR, CONNECTOR FRAME,
TYPE IV, SINGLE SPAN, CENTER

This specification is approved for use by all Departments and Agencies of the Department of Defense

The complete requirements for acquiring the connector described herein shall consist of this specification and the latest issue of MIL-C-28754


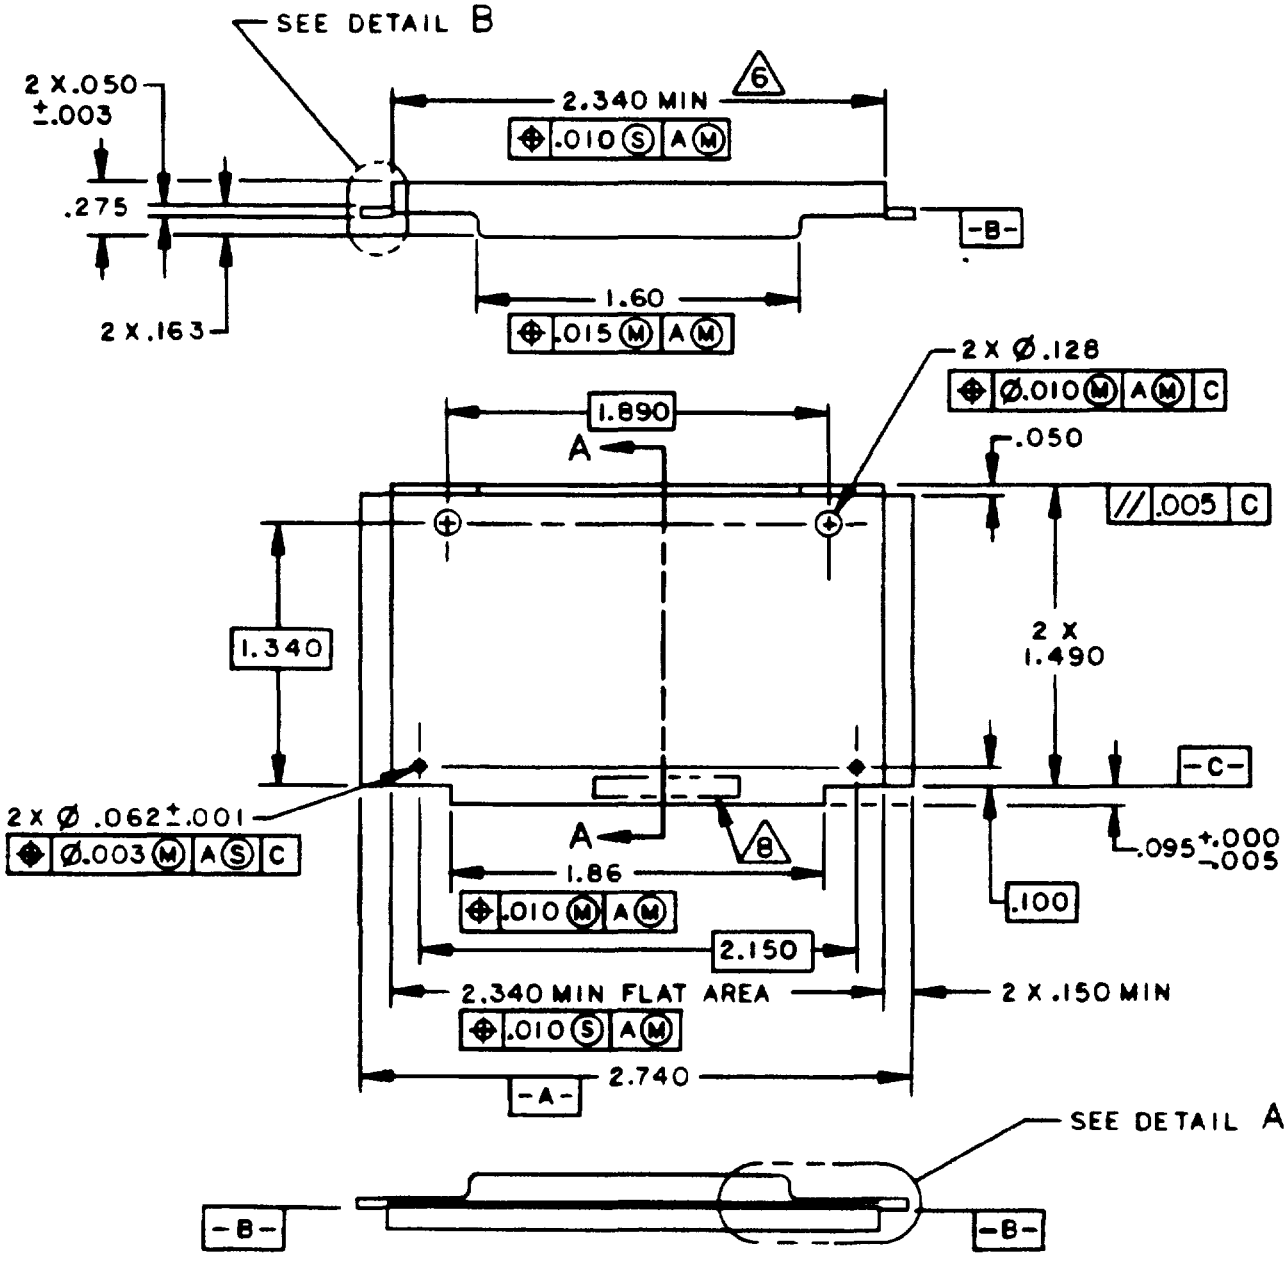



FIGURE 1 Dimensions and configurations

FSC 5935


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T14:50Z
Check the source to verify that this is the current version before use.

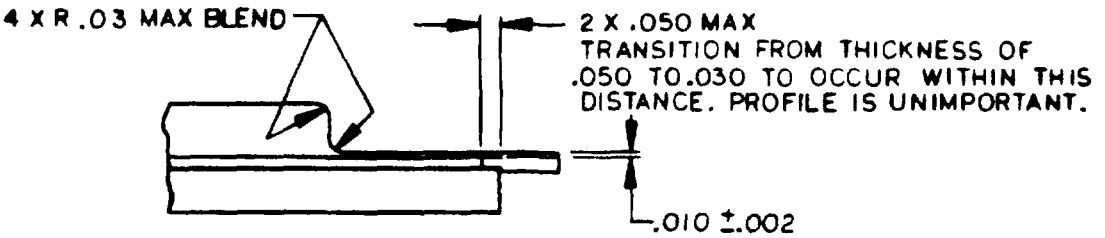

DETAIL A

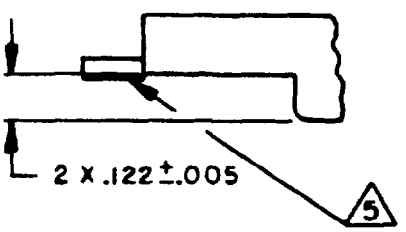

DETAIL B

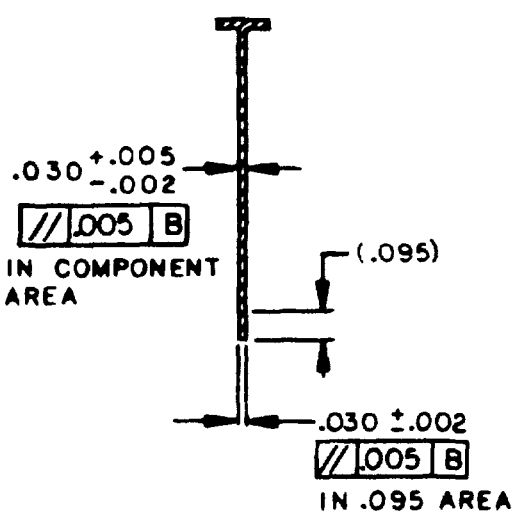

SECTION A-A

FIGURE 1 Dimensions and configurations - continued

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T14:50Z
Check the source to verify that this is the current version before use.

INCHES	MM	INCHES	MM	INCHES	MM	INCHES	MM	INCHES	MM
001	03	015	38	100	2 54	275	6 99	2 150	54 61
002	05	030	76	122	3 10	1 490	37.85	2 340	59 44
003	08	050	1 27	128	3 25	1.600	40 64	2.740	69 60
005	13	062	1 58	.150	3 81	1.860	47 25		
010	25	095	2 41	163	4 15	1 890	48 01		

NOTES

1 Dimensions are in inches.

2 Metric equivalents are given for general information only and are based upon 1 00 inch = 25.4 mm

3 Unless otherwise specified, tolerances are ±.005 (13 mm) inch for three place decimals, ± 01 (3 mm) inch for two place decimals and ±2° for angles

4 Unless otherwise specified, all corner radii shall be .02 (51 mm) inch rad max.

5 This surface and the 122 dimension shall be flush to 005 maximum step

6. Top of T surfaces

7 Dimensional limits apply after plating

8 Frame shall be marked in approximate location shown with part number, manufacturer's number and date code with contrasting ink in characters 06 (1 5 mm) inch high

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T14:50Z
Check the source to verify that this is the current version before use.

REQUIREMENTS

Dimensions and configuration See Figure 1

Materials For M28754/70-01, aluminum alloy 6061, ASTM-B-211, T6 extrusion

For M28754/70-02, copper C11000, H01 temper, per ASTM B152-81

For M28754/70-03, copper-invar-copper (20-60-20 by thickness)

Finish For M28754/70-01, anodic coating, MIL-A-8625, Type II, Class 2, black

For M28754/70-03, electroless nickel per MIL-C-26074, 5 percent phosphorous minimum, Class 1, Grade A, 0015 ± 0005 inch thick, MIL-C-5541, Class 1A, yellow Within 4 hours after plating oven bake 275 ± 25°F, 1 hour, for hydrogen relief and adhesion

Examination One frame from each plating lot shall be exposed to salt fog per MIL-STD-810, Method 509, Procedure 1, 48 hours, and one frame shall be exposed to oven bake at 375 ± 10°F, 60-90 minutes Examine each frame, using 6 to 10 power magnification, for loose or blistered coating Examination results shall be delivered with each order The examined frames shall be retained by the supplier for a period of 6 months

Stress relief For M28754/70-02 and -03, frames shall receive the following bake cycle prior to plating and after all fabrication steps, 375 + 10°F for 90 + 10 minutes

Military part number M28754/70- (Dash Number from Table I)

TABLE I

DASH NUMBER	MATERIAL	FINISH
01	Aluminum Alloy	Anodize
02	Copper	Nickel
03	Copper-Invar	Nickel

Qualification information The frame shall meet the following qualification tests of MIL-C-28754, Table IV, Type IV Subgroup I, Method Paragraph 4 7 1, Subgroup II, Method Paragraph 4 7 11, 4 7 1, Subgroup III, Method Paragraph 4 7 13 and 4 7 1, Subgroup IV, Method Paragraph 4 7 12, 4 7 18, 4 7 19, 4 7 20 and 4 7 1

Number of units to be inspected Twelve (12) units of each dash number to be qualified shall be inspected

Supersession data Supersedes Naval Electronic Systems Command Drawing Number 0102-714-1, -2, -3 and -4, Code Identification Number 28687

Custodians
Navy - EC

Preparing Activity
Navy - EC

(Project 5935-N252-17)

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T14:50Z
Check the source to verify that this is the current version before use.