DDD-B-166

AMENDMENT—2
APRIL 26, 1940

SUPERSEDING
Amendment—1
August 1936

FEDERAL STANDARD STOCK CATALOG

Section IV

(Part 5)

FEDERAL SPECIFICATION

FOR

BELTING; CONVEYOR, NARROW (STITCHED-DUCK)

This amendment was approved on the above date by the Director of Procurement, for the use of all departments and establishments of the Government, and shall become effective not later than December 15, 1940. It may be put into effect, however, at any earlier date after promulgation.

The following changes should be made in Federal Specification DDD–B–166, dated August 15, 1935:

Page 1:

Title. Delete title in its entirety and substitute:

"Belting; conveyor or power-transmission, narrow (stitched-duck)."

Page DDD–B–166—3:

Paragraph **E–9.** Delete paragraph in its entirety and substitute:

E–9. *Water absorption.*—The water absorption shall be not less than 3 percent and not more than 10 percent when tested as described in paragraph F–5. For the light oil finish (white) belting mentioned in paragraphs H–1c, Post Office Department, and H–1d, Public Buildings Administration, Federal Works Agency, the absorption shall be not less than 3 percent and not more than 15 percent when tested as described in paragraph F–5.

Section **E.** Insert paragraphs E–10 and E–11 as follows:

E–10. *Stitching thread.*—The stitching thread shall be made up of not less than 13 strands, the number of yards per pound shall be not less than 650 and not more than 750, and the breaking strength shall be not less than 25 pounds.

E–11. *Deflection after accelerated aging test.*—The specimen shall have a deflection of not less than 2 inches when tested as described in paragraph F–6.

Paragraph **F–5.** Delete paragraph in its entirety and substitute:

239175—40

Source: https://assist.dla.mil -- D
Check the source to verify that this

F–5. *Absorption test.*—A piece of the inspection sample of the finished belt 3 by 3 inches, cut on all 4 edges, shall be immersed in water for 24 hours, and the water absorption shall be determined as a percentage of the conditioned weight of the sample after the free water from its edges and surfaces has been removed.

Section **F.** Insert paragraph F–6 as follows:

F–6. *Accelerated aging test.*—A specimen 4 inches wide, plus or minus ⅛ inch, and 12 inches long, plus or minus ¼ inch, with the long dimension parallel to the lengthwise direction of the belt, is cut at a distance of not less than 3

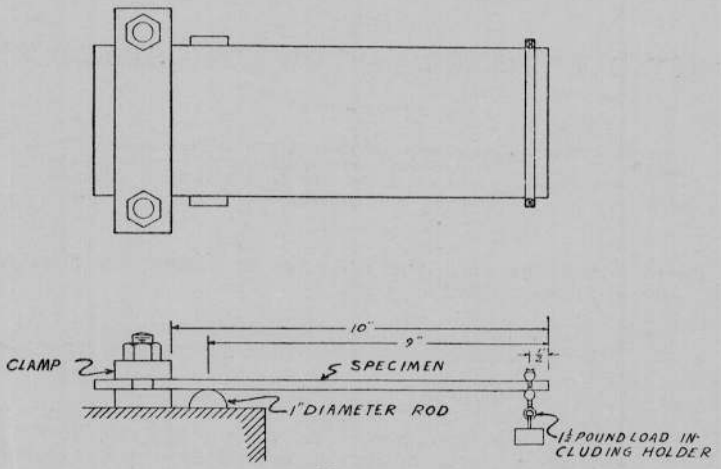


FIGURE 1.

inches from either edge. It shall be free from seams and splices. The specimen shall be suspended in circulating air at a temperature of 100° C., plus or minus 3° C., for a period of 14 days. At the end of this period, it is placed between 2 flat boards, sufficient weight is placed on the top board to hold the specimen parallel to the surfaces of the boards, and it is maintained in this position for 4 hours. A reference mark is placed in the test piece at ½ inch, 9 inches, and 10 inches, plus or minus ⅛ inch, respectively, from the same end of the specimen and at right angles to its long dimension. The specimen is conditioned for at least 16 hours at a temperature of 70 to 75° F. It is then immediately clamped tightly at the 10 inch mark and supported on a 1 inch, plus or minus ⅛ inch, diameter rod at the 9 inch mark. The clamps and rod shall extend across the full width of the

Source: https://assist.dla.mil -- Do
Check the source to verify that this

test piece and its faces shall be horizontal within a tolerance of ¼ inch. A load of 1½ pounds, plus or minus $\frac{1}{16}$ pound, is applied at the ½ inch mark uniformly across the width of the specimen for 5 minutes, and the vertical deflection of the end of the specimen is measured. The specimen is maintained at a temperature of 70 to 75° F. from the time of its removal from the heated air until the deflection is measured. (See Fig. 1).

Page DDD–B–166—4:

Section **H.** Insert paragraphs H–1c and H–1d as follows:

H–1c. *Post Office Department.*—Where specified, a light oil finish (white) belting shall be furnished and the water absorption shall be as described in paragraph E–9.

H–1d. *Public Buildings Administration, Federal Works Agency.*—Where specified, a light oil finish (white) belting shall be furnished and the water absorption shall be as required in paragraph E–9.

Section **I.** Insert paragraph I–5 as follows:

I–5. The belting covered by this specification is intended for either conveyor or power transmission purposes.

Source: https://assist.dla.mil --
Check the source to verify that th