MIL-H-2815F
5 June 1978
SUPERSEDING
MIL-H-2815E
13 February 1973
(See 6.5)

MILITARY SPECIFICATION

HOSE ASSEMBLIES, RUBBER, DIVER'S BREATHING AIR AND GAS SUPPLY

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for rubber hose assemblies for underwater use in supplying air or other breathing gas mixtures to divers at water depths to 600 feet, using surface supplied diving outfits.

1.2 Lengths. The hose assemblies shall be of the following lengths as specified (see 6.2):

3 feet long
3 feet, 9 inches long
100 feet long

2. APPLICABLE DOCUMENTS

2.1 Issues of documents. The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

SPECIFICATIONS

FEDERAL
KK-L-164 - Leather, Cattlehide, Packing, Vegetable-Tanned, Chrome-Tanned, Chrome-Vegetable Retanned.
QQ-B-637 - Brass, Naval: Rod, Wire, Shapes, Forgings, and Flat Products with Finished Edges (Bar, Flat Wire and, Strip).
QQ-C-591 - Copper-Silicon, Copper-Zinc-Silicon and Copper-Nickel-Silicon Alloys: Rod, Wire, Shapes, Forgings, and Flat Products, (Flat Wire, Strip, Sheet, Bar and Plate).

MILITARY
MIL-P-775 - Packaging of Hose, Rubber, Plastic, Fabric, or Metal (Including Tubing); and Fittings, Nozzles and Strainers.

STANDARDS

FEDERAL
FED-STD-162 - Hose, Rubber, Visual Inspection Guide for.
FED-STD-601 - Rubber: Sampling and Testing.

MILITARY
MIL-STD-105 - Sampling Procedures and Tables For Inspection by Attributes.

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Naval Ship Engineering Center, SEC 6124, Department of the Navy, Washington, DC 20362 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 4220

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply:

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)
D 573 - Accelerated Aging of Vulcanized Rubber by the Oven Method.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pa. 19103.)

AMERICAN CONFERENCE OF GOVERNMENTAL INDUSTRIAL HYGIENISTS
Threshold Limit Values (TLV)

(Application for copies should be addressed to the American Conference of Governmental Industrial Hygienists, 1014 Broadway, Cincinnati, Ohio 45202.)

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3. REQUIREMENTS

3.1 First article. When specified (see 6.2.1), the contractor shall furnish two 100-foot and four 3-foot or 3-foot 9-inch sample units for first article inspection and approval (see 4.2 and 6.3).

3.2 Materials. Material shall be as specified herein. Material not definitely specified shall be of the quality regularly used by the supplier in these types of hose assemblies. Material shall be new and free from all defects and imperfections that may adversely affect the serviceability or appearance of the finished product. Prior to submission of finished items for approval, the contractor shall submit to the contracting officer or his authorized representative, evidence that materials conform with all the requirements of this specification.

3.2.1 Inner tube. The basic rubber stock of which the inner tube is fabricated shall be natural rubber, or a synthetic rubber. Reclaimed rubber or rubber containing pine tar or coal tar shall not be used.

3.2.2 Cover. The basic rubber stock of which the cover is fabricated shall be polymerized chloroprene.

3.2.3 Fabric reinforcement. Fabric reinforcement shall consist of two or more plies of braided cotton, rayon, or polyester (see 3.3.2).

3.2.4 Couplings and clamps. The couplings and nut for female coupling shall be made from brass conforming to copper alloy number 464 of QQ-B-637 and the clamps from silicon bronze conforming to copper alloy number 655 of QQ-C-591. Washer material shall be in accordance with KK-L-164. The use of reclaimed material is acceptable.

3.2.5 Organic solvents. The organic solvents used at any stage in the construction of the diver's hose, including the solvents used for rubber compounds for fastening couplings to the hose, for sealing or capping the ends of the hose, for bonding the layers and plies of the hose together, or for any other application which might contribute to the contamination of an air or gas mixture stream passing through the hose, shall conform to the following requirements.

3.2.5.1 Composition. The manufacturer shall certify that only solvents having a Threshold Limit Value (TLV) of not more than 500 milligrams per cubic meter (mg/m^3) (see 4.5.10.1) shall be used.

3.2.6 Other rubber additives. The hose shall contain the minimum quantities necessary of only the purest grades of rubber accelerators, both in the cover and inner tube so as to be as free from odor as possible. The manufacturer shall certify that the following ingredients shall not be used: pine tar, coal tar, benzidine, beta-naphthylamine and derivatives, phosphate plasticizers and aniline.

3.2.7 Coupling lubricants and washer dressing. No coupling lubricants and washer dressings, except water, shall be used.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

3.3 Construction. The hose assembly shall consist of an inner rubber tube, two or more plies of fabric braid reinforcement (see 3.2.3) with a rubber ply between the braids, a cover, couplings and clamps. Each end of the hose shall be capped or sealed with a rubber compound 1/16-inch thick of the same composition as the cover; the cap or seal shall be capable of preventing the ingress of water into the braid.

3.3.1 Tube and cover. The inner tube shall be homogeneous, free from extraneous inclusions, non-porous, water resistant, and of uniform thickness. The tube shall be smooth and free of adhering soapstone dust or other particles. The tube and cover shall be free from pitting, and free from substances such as dirt, grease, or metal shavings which may effect the material characteristics or appearance. The cover may have spiral markings from a tightly wrapped cure and may have pin pricking when specified (see 6.2.1).

3.3.2 Fabric reinforcement. The fabric reinforcement shall consist of two or more plies of braided cotton, rayon or polyester, well embedded in a rubber compound with a rubber ply between the braids. The reinforcement shall be evenly and uniformly braided, free from dirt, knots, lumps, irregularities of twist or other defects.

3.3.3 Couplings. Each 100-foot length of hose shall have one male and one female coupling fitted into alternate ends of the hose. The 3-foot and the 3-foot 9-inch lengths shall be fitted with two female couplings. The couplings shall conform to the dimensions and characteristics shown on figures 1 and 2. Each coupling shall be secured in place by three metal clamps, specified in 3.3.4, and cement. Couplings shall be interchangeable.

3.3.4 Clamps. Each coupling shall be secured on the hose end by means of three metal clamps staggered at 120 degrees. The clamps shall conform to the dimensions and characteristics of those shown on figure 3. Clamps shall be tightened until the clamp depresses the hose so that daylight appears when a straight edge is held along the outside surface of the hose and at 180 degrees to the buckle.

3.4 Length. The lengths of hose shall be as follows, as specified (see 6.2.1):

(a) Three feet plus or minus 1 inch, including couplings.
(b) Three feet, 9 inches plus or minus 1-inch, including couplings.
(c) One-hundred feet plus or minus 1 foot, including couplings.

3.5 Physical requirements. All hose shall conform to the following physical requirements.

Size:	
Inside diameter (inch)	1/2 + 1/32
Outside diameter (inch)	1 + 1/32
Thickness of inner tube (min.)(inch)	0.060
Thickness of cover (min.)(inch)	0.060
Adhesion:	
Between tube and plies of braid (min.)(pounds)	10
Between plies of braid (min.)(pounds)	12
Between plies of braid and cover (min.)(pounds)	10
Initial tensile strength (min.)(pounds-force per square inch)	
Tube	1200
Cover	1800
Elongation (min.)(percent)	
Tube	200
Cover	300

3.6 After oven aging. The tensile strength of the tube and cover, after being subjected to the oven aging test specified in 4.5.3, shall show a change from the initial tensile strength of not more than 25 percent.

3.7 Immersion. After being subjected to the immersion test specified in 4.5.4, the tensile strength of the cover shall show a decrease from the initial tensile strength of not more than 50 percent.

3.8 Change in volume. The change in volume of the cover stock in the special testing fuel, as determined by the method specified in 4.5.5, shall be not greater than 50 percent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

3.9 Hydrostatic pressure.

3.9.1 Bursting strength. The hose shall be constructed so as not to burst at any pressure less than a gage pressure of 2400 pounds per square inch (lb/in^2) (see 4.5.6).

3.9.2 Proof strength. The hose shall be constructed to withstand a gage pressure of 1200 lb/in^2) for 1 minute without exposing imperfections (see 4.5.7).

3.10 Elongation or contraction. The hose shall be so constructed that the length change shall be less than plus 2 or minus 4 percent at a gage pressure of 600 lb/in^2 (see 4.5.8).

3.11 Coupling pull-out strength. The hose and couplings shall be so mated that they will withstand a tension load of 1100 pounds for 1 minute with an internal gage pressure of 600 lb/in^2 (see 4.5.9). Following this test, the hose shall show no signs of imperfections.

3.12 Physiological and off gassing.

3.12.1 Physiological effect. The hose shall not contaminate the air or other breathing mixture through the hose with obnoxious or harmful vapors, gases, or particles (see 4.5.10 and 4.5.11).

3.12.2 Off gassing. Hoses shall not contaminate the gas by amounts greater than those specified in table VI of 4.5.10.2.

3.13 Branding. Hose may be branded by either of the following methods, at the option of the manufacturer.

(a) Each length of hose shall be branded with the manufacturer's name and trademark, the month and year of manufacture and "Diver's H.P." in the cover and vulcanized thereto. Hose 100 feet in length shall have brands inlaid in the cover at least two places on each length, approximately 4 feet from the ends, letters shall be at least 1/4 inch high. Hose 3 and 3 feet 9 inches in length shall have one inlaid brand approximately in the center.
(b) Each length of hose shall be branded by continuously embossing or inlaying in the cover, the manufacturer's name and trademark, the month and year of manufacture and "Diver's H.P." The letters shall be at least 1/4 inch high.

3.14 Hose date. Hose dated more than six months prior to the date submitted for inspection will not be accepted.

3.15 Technical data.

3.15.1 Provisioning technical documentation. Provisioning technical documentation shall be prepared in accordance with the data ordering document specified (see 6.2.2).

3.16 Workmanship. The tube and cover shall be free of pitting, dirt, grease, and metal shavings. The fabric reinforcement shall be uniformly braided, free of dirt, knots, lumps or irregularities of twist.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Material inspection. Material inspection shall consist of certification supported by verifying data submitted to the contracting officer or his authorized representative that the material used in the fabrication of the hose is in accordance with the requirements of this specification prior to start of production. The certification data shall be furnished to the Contracting Officer when specified (see 6.2.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

4.1.2 Submission of test reports. Reports covering the inspection and test for First artcle inspection and the Quality conformance inspection shall be furnished to the Contracting Officer when specified (see 6.2.2).

4.2 First article inspection. First article inspection shall consist of the examination and tests specified in table I (see 6.3). When specified (see 6.2.1), first article inspection shall be conducted at the David W. Taylor Naval Ship Research and Development Center (NSRDC), Code 2843, Annapolis, Md 21042, or a laboratory designated by NSRDC. Test data shall be furnished to the Government inspector when the tests have been successfully completed (see 6.2.2).

TABLE I. First article inspection.

Examination and test	Requirement	Test paragraph
Visual and dimensional examination	FED-STD-162	4.4.1
Offgassing	3.2.5, 3.12.2	4.5.10
Tensile strength and elongation	3.5	4.5.1
Change in volume	3.8	4.5.5
Adhesion	3.5	4.5.2
Oven aging	3.6	4.5.3
Immersion	3.7	4.5.4
Hydrostatic bursting strength	3.9.1	4.5.6
Hydrostatic proof	3.9.2	4.5.7
Longitudinal stability	3.10	4.5.8
Coupling pull-out strength (3 or 3 foot, 9 inch lengths only)	3.11	4.5.9

4.3 Quality conformance inspection.

4.3.1 Lot. For purposes of sampling, a lot shall consist of all hose of the same length made at the same factory, of the same materials, of the same construction, and offered for inspection at the same time.

4.3.2 Sampling for visual and dimensional examination and non-destructive testing. Sampling for visual and dimensional examination and nondestructive testing shall be in accordance with MIL-STD-105.

4.3.3 Sampling for destructive inspection. A random sample of hose shall be selected from each lot of 3-foot hose and 3 foot 9 inch hose, or 3-foot lengths shall be fabricated by the manufacturer from each lot of 100-foot lengths of hose for the test specified in 4.4.3. The number of samples shall be as shown in table III. The samples shall be capped or sealed with 1/16 inch of the tubing rubber compound and equipped with couplings in the same manner as completed hose.

TABLE III. Sampling for destructive inspection.

Number of linear feet of hose in lot	Number of 3-foot hose length in sample
9,000 and under	6
9,001 to 15,000	7
15,001 to 25,000	10
25,001 to 40,000	15
40,001 to 60,000	20
60,001 to 100,000	30
100,001 to 150,000	40
150,001 and over	50

4.4 Nondestructive and destructive inspection.

4.4.1 Visual and dimensional examination. Visual and dimensional examinations shall be in accordance with Class A of FED-STD-162. The AQL shall be 1.0 for major defects and 4.0 for minor.

4.4.1.1 Destructive. The examinations from FED-STD-162 which destroy or alter the sample shall only be made on the 3-foot or 3-foot 9 inch lengths selected in accordance with 4.3.3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

4.4.1.2 Nondestructive. Nondestructive examinations shall be made on all lengths selected in accordance with 4.3.2. Any length of the samples containing one or more major visual or dimensional defects shall be rejected and counted against the AQL for major defects. Any length containing more than four minor defects shall be rejected and counted against the AQL for total defectives. Any length containing four or less minor defects and no major defects shall be counted a minor defective against the AQL for total defectives but shall not be rejected.

4.4.2 Nondestructive inspection. Each sample length of hose selected in accordance with 4.3.2 shall be subjected to the visual and dimensional examination of 4.4.1.2 and the off-gassing test of 4.5.10. After successfully passing this examination and test, the hose shall be subjected to the remaining tests shown in table IV.

4.4.3 Destructive inspection. If the lot has not been rejected as a result of the nondestructive tests of 4.4.2, the 3-foot or 3-foot 9 inch lengths selected or fabricated in accordance with 4.3.3 shall be subjected to the destructive tests shown in table V. If any hose fails one or more of the tests, the entire lot represented by the sample shall be rejected.

TABLE IV. Nondestructive inspection.

Examination and test	Requirement	Test paragraph
Hydrostatic proof	3.9.2	4.5.7
Longitudinal stability	3.10	4.5.8

TABLE V. Destructive inspection.

Examination and test	Requirement	Test paragraph
Tensile strength and elongation	3.5	4.5.1
Adhesion	3.5	4.5.2
Oven aging	3.6	4.5.3
Immersion	3.7	4.5.4
Change in volume	3.8	4.5.5
Hydrostatic bursting strength	3.9.1	4.5.6
Coupling pull-out strength (3 or 3 foot 9 inch lengths only)	3.11	4.5.9

4.4.4 Action in case of failure. Acceptance of the first lot of hose from one manufacturer shall be withheld pending receipt of the test report on the quality conformance inspection samples representing the lot. At the option of the contractor, acceptance shall not be withheld pending receipt of the test report on the quality conformance inspection test samples representing a lot if the contractor has previously furnished acceptable hoses to the Government. However, in this case, if the test report later reveals that the lot was unsatisfactory, four additional sample 3-foot or 3-foot 9 inch sections shall be selected from every lot offered for delivery. The sample sections so selected shall be subjected to the test(s) wherein failure was observed. Lots shall then be accepted only upon receipt of a satisfactory test report on the samples so selected, and shall be rejected if the lot is found to be unsatisfactory. This additional testing shall be discontinued and sampling procedures returned to the normal basis of 4.3.2 and when four successive lots have been accepted.

4.4.5 Disposition of samples. Samples subjected to the destructive tests shall not be submitted with the contract. Samples subjected to the nondestructive tests may be submitted with the contract.

4.5 Test procedures.

4.5.1 Tensile strength and elongation. Tensile strength and elongation shall be conducted as specified in methods 4111 and 4121 of FED-STD-601 using die III, to determine conformance with 3.5.

4.5.2 Adhesion. Adhesion tests shall be conducted in accordance with method 8011 of FED-STD-601, to determine conformance with 3.5.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

4.5.3 Oven aging. The hose shall be subjected to the oven aging test of ASTM D 573-67. The aging period shall be 70 hours at 100 degrees Celsius (°C.) to determine conformance with 3.6.

4.5.4 Immersion test. The immersion test shall be conducted in accordance with method 6111 of FED-STD-601, using distilled water, except that the immersion period shall be 166 hours ± 1/4 hour at 70°C ± 2°C to determine conformance with 3.7.

4.5.5 Change in volume in distilled water. The change in volume test shall be conducted in accordance with method 6211 specified in FED-STD-601 using distilled water, to determine conformance with 3.8, except that the immersion period shall be 166 hours ± 1/4 hour at 70°C ± 2°C.

4.5.6 Hydrostatic bursting strength. The hose shall be subjected to a gage pressure of 2400 lb/in^2 in accordance with method 10011 of FED-STD-601, to determine conformance with 3.9.1.

4.5.7 Hydrostatic proof pressure. The hose, complete with couplings shall be subjected to a gage pressure of 1200 lb/in^2 for 1 minute in accordance with method 10211 of FED-STD-601, to determine conformance with 3.9.2.

4.5.8 Longitudinal stability. The hose shall be subjected to a hydrostatic gage pressure of 500 lb/in^2 in accordance with method 10311 of FED-STD-601, to determine conformance with 3.10.

4.5.9 Coupling pull-out strength. The 3-foot or 3-foot 9 inch lengths, including couplings shall be held in the tensile device by clamping onto the hose couplings. The sample with a constant 600 lb/in^2 internal hydrostatic gage pressure shall be loaded at a rate of 200 pounds of tension per minute until 1100 pounds is reached. The 1100 pound tensile load shall be maintained for 1 minute to determine conformance with 3.11.

4.5.10 Off-gassing tests. Measurements shall be made of the off-gassing of organic compounds from hoses. A Beckman Total Hydrocarbon Analyzer, Model 400, or any equivalent process analyzer employing a hydrogen flame ionization detector (FID) having a range of from 0 to at least 1,000 mg/m^3 methane equivalents (see 4.5.10.1) shall be used. The measurements shall be made only on hoses which have not been flushed with air, gas, or water, or which have been stored at a temperature not lower than 23°C for a period of at least seven days since the hoses were flushed. During the seven day storage period, the ends of the hoses shall either be sealed shut or fastened together so that the confined gas may not escape. Both the analyzer and hoses shall be maintained at a temperature not lower than 23°C. throughout the testing period. The procedure for measuring offgassing rates from hoses is specified hereinafter as the flush test (see 4.5.10.2).

4.5.10.1 Terminology. The hydrogen flame ionization detector of the Total Hydrocarbon Analyzer is sensitive not only to hydrocarbons themselves, but also to related compounds which will ionize in a hydrogen flame. In all paragraphs of 4.5.10 the term hydrocarbon is intended to designate all organic compounds detected by the Total Hydrocarbon Analyzer. Likewise, in all paragraphs of 4.5.10 the term mg/m^3 designates milligrams per cubic meter; the term methane equivalents designates the concentration of methane that will cause the instrument to give the same reading as the air or other gas tested. All units are expressed in terms of measurements made at 23°C. and at a pressure of 760 mm of mercury.

4.5.10.2 Flush test (see 3.12). By this procedure, measurements are made of the increase in the hydrocarbon concentration of a stream of air flowing through the hose at a velocity of 28 liters per minute (1 cubic foot per minute). The temperatures of the hose, air supply, and analyzer shall not be less than 23°C. A diagram of the flow arrangement is shown on figure 4. Before the air passes through the hose, the air shall be clean and shall contain not more than 1 mg/m^3 of hydrocarbons (methane equivalents). The analyzer shall be zeroed with air passing at the stipulated velocity and temperature through the connector tubes only. The hose shall then be inserted in the line and the air stream passed through it. For the ensuing 15 minutes, readings of the hydrocarbon concentration shall be recorded frequently, if not continuously. The hoses shall be rated on the reading at the end of the 15 minute test period. Hoses which contaminate the air by greater amounts than specified in table VI are not acceptable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

TABLE VI. Maximum allowable concentration of hydrocarbons in air passing through hose.

Hose length (feet)	Hydrocarbon concentration as methane equivalents mg/m^3
3	4
3, 9 inch	4
100	100

4.5.11 Special physiological test. Contractor may be requested to arrange for special physiological test to be performed (see 6.2.1). Government Agent requesting the test will stipulate the nature and details of the test at the time the test is requested.

4.6 Inspection of preparation for delivery. Preservation-packaging, packing, and marking shall be inspected to determine conformance with section 5 of this specification.

5. PACKAGING

5.1 Packaging. The hose assemblies shall be packaged in accordance with MIL-P-775 as specified (see 6.2.1).

6. NOTES

6.1 Intended use. It is intended to use the hose assemblies in diver's operations in water depths to 600 feet. The material handled may be fresh air or other breathing gas mixtures.

6.2 Ordering data.

6.2.1 Procurement requirements. Procurement documents should specify the following:

(a) Title, number and date of this specification.
(b) Length required (see 1.2 and 3.4).
(c) Sample units required for first article testing and approval (see 3.1).
(d) If pin pricking on cover is acceptable (see 3.3.1).
(e) That the first article inspection shall be conducted at the David W. Taylor Naval Ship Research and Development Center Code 2843 (see 4.2).
(f) Special physiological test if required (see 4.5.11).
(g) Level of packaging required (see 5.1).

6.2.2 Data requirements. When this specification is used in a procurement which invokes the provision of the "Requirements for Data" of the Armed Services Procurement Regulations (ASPR), the data identified below, which are required to be developed by the contractor, as specified on an approved Data Item Description (DD Form 1664), and which are required to be delivered to the Government, should be selected and specified on the approved Contract Data Requirement List (DD Form 1423) and incorporated in the contract. When the provisions of the "Requirements for Data" of the ASPR are not invoked in a procurement, the data required to be developed by the contractor and required to be delivered to the Government should be selected from the list below and specified in the contract.

Paragraph	Data requirements	Applicable DID
4.1.1	Report, Material Inspection	UDI-T-23741
4.2	First Article Inspection	DI-T-2072
4.3	Quality Conformance Inspection	UDI-T-23473

(Copies of data item descriptions required by the contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.)

6.2.2.1 The data requirements of MIL-H-2815 and any task in section 3, 4, or 5 of the specification required to be performed to meet a data requirement may be waived by the procuring/purchasing activity upon certification by the offeror that identical data were submitted by the offeror and accepted by the Government under a previous contract for identical item procured to this specification. This does not apply to specific data which may be required for each procurement regardless of whether an identical item has been supplied previously (for example, test reports).

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

6.3 First article inspection.

6.3.1 Invitations for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection as to those bidders offering a product which has been previously procured or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending procurement.

6.4 Sub-contracted material and parts. The preparation for delivery requirements of referenced documents listed in Section 2 do not apply when material and parts are procured by the contractor for incorporation into the equipment and lose their separate identity when the equipment is shipped.

6.5 Changes from previous issue. The symbol "#" is not used in this revision to identify changes with respect to the previous issue, due to the extensiveness of the changes.

Custodian:
Army - EA
Navy - SH
Review activities:
Army - MD
DLA - CS
User activities:
Army - ME
Navy - MS

Preparing activity:
Navy - SH
(Project 4220-0212)

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

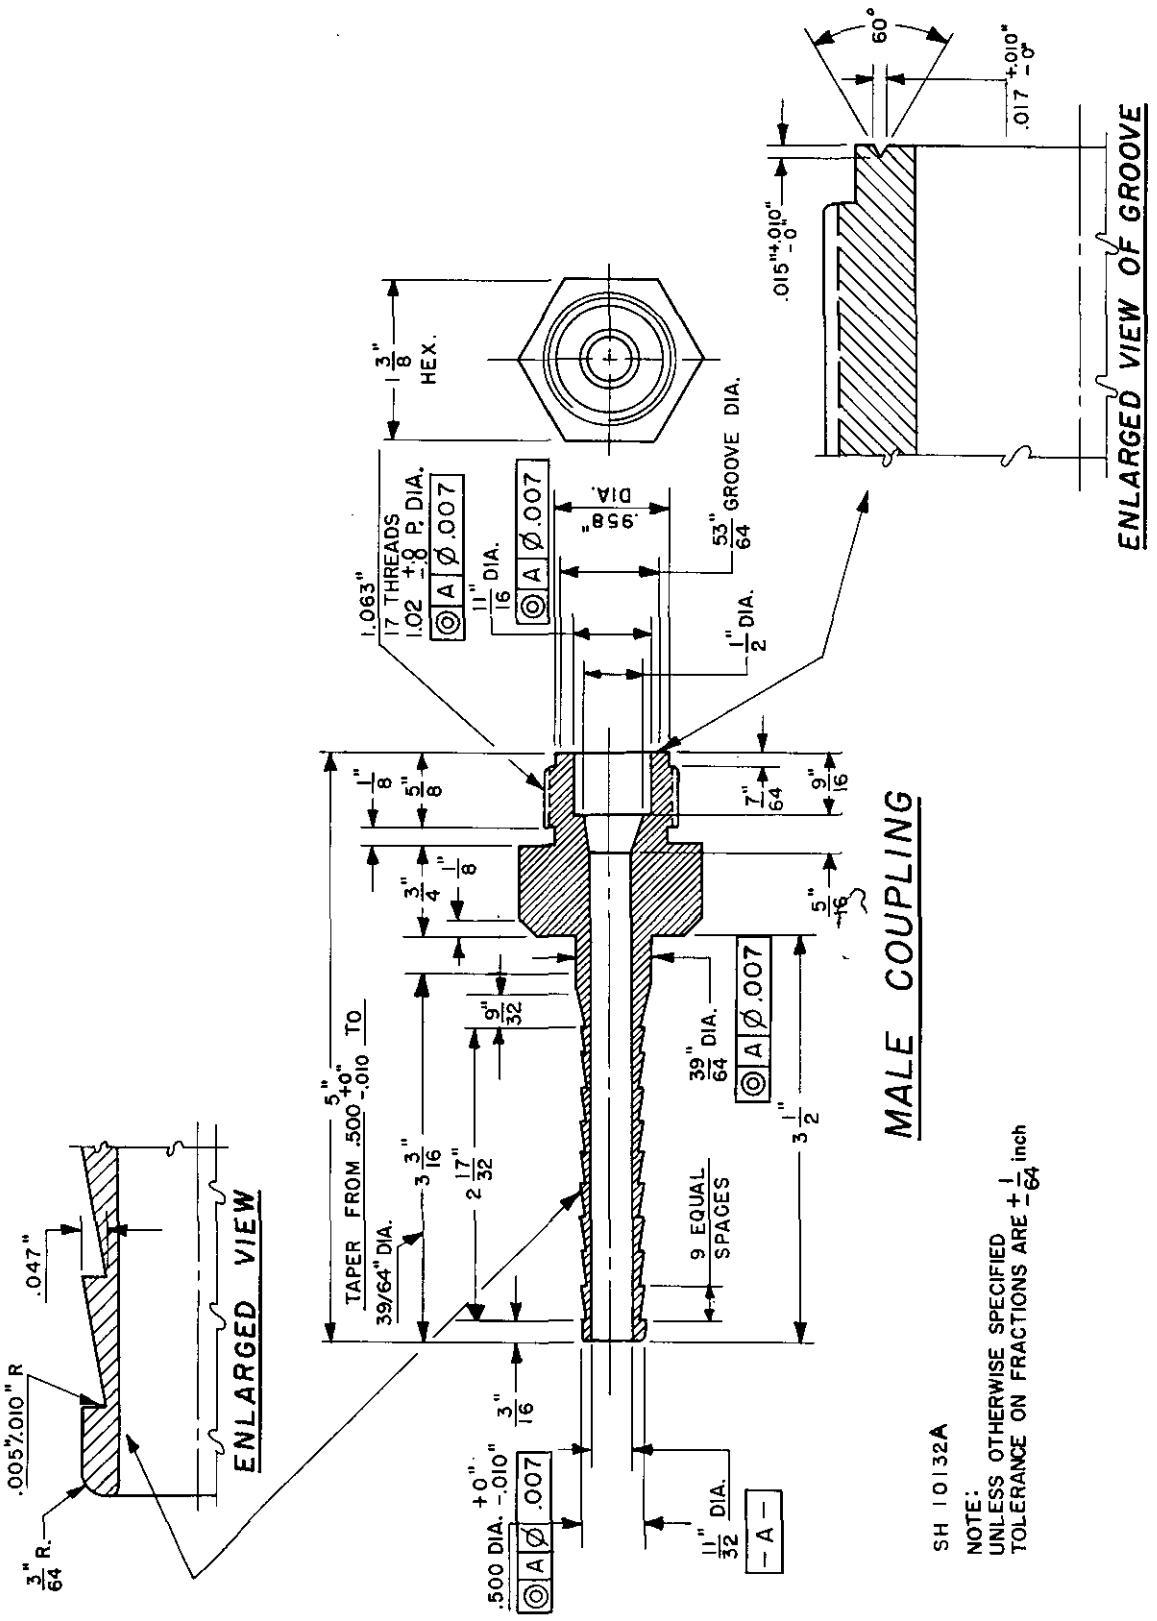


FIGURE 1. Male coupling.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

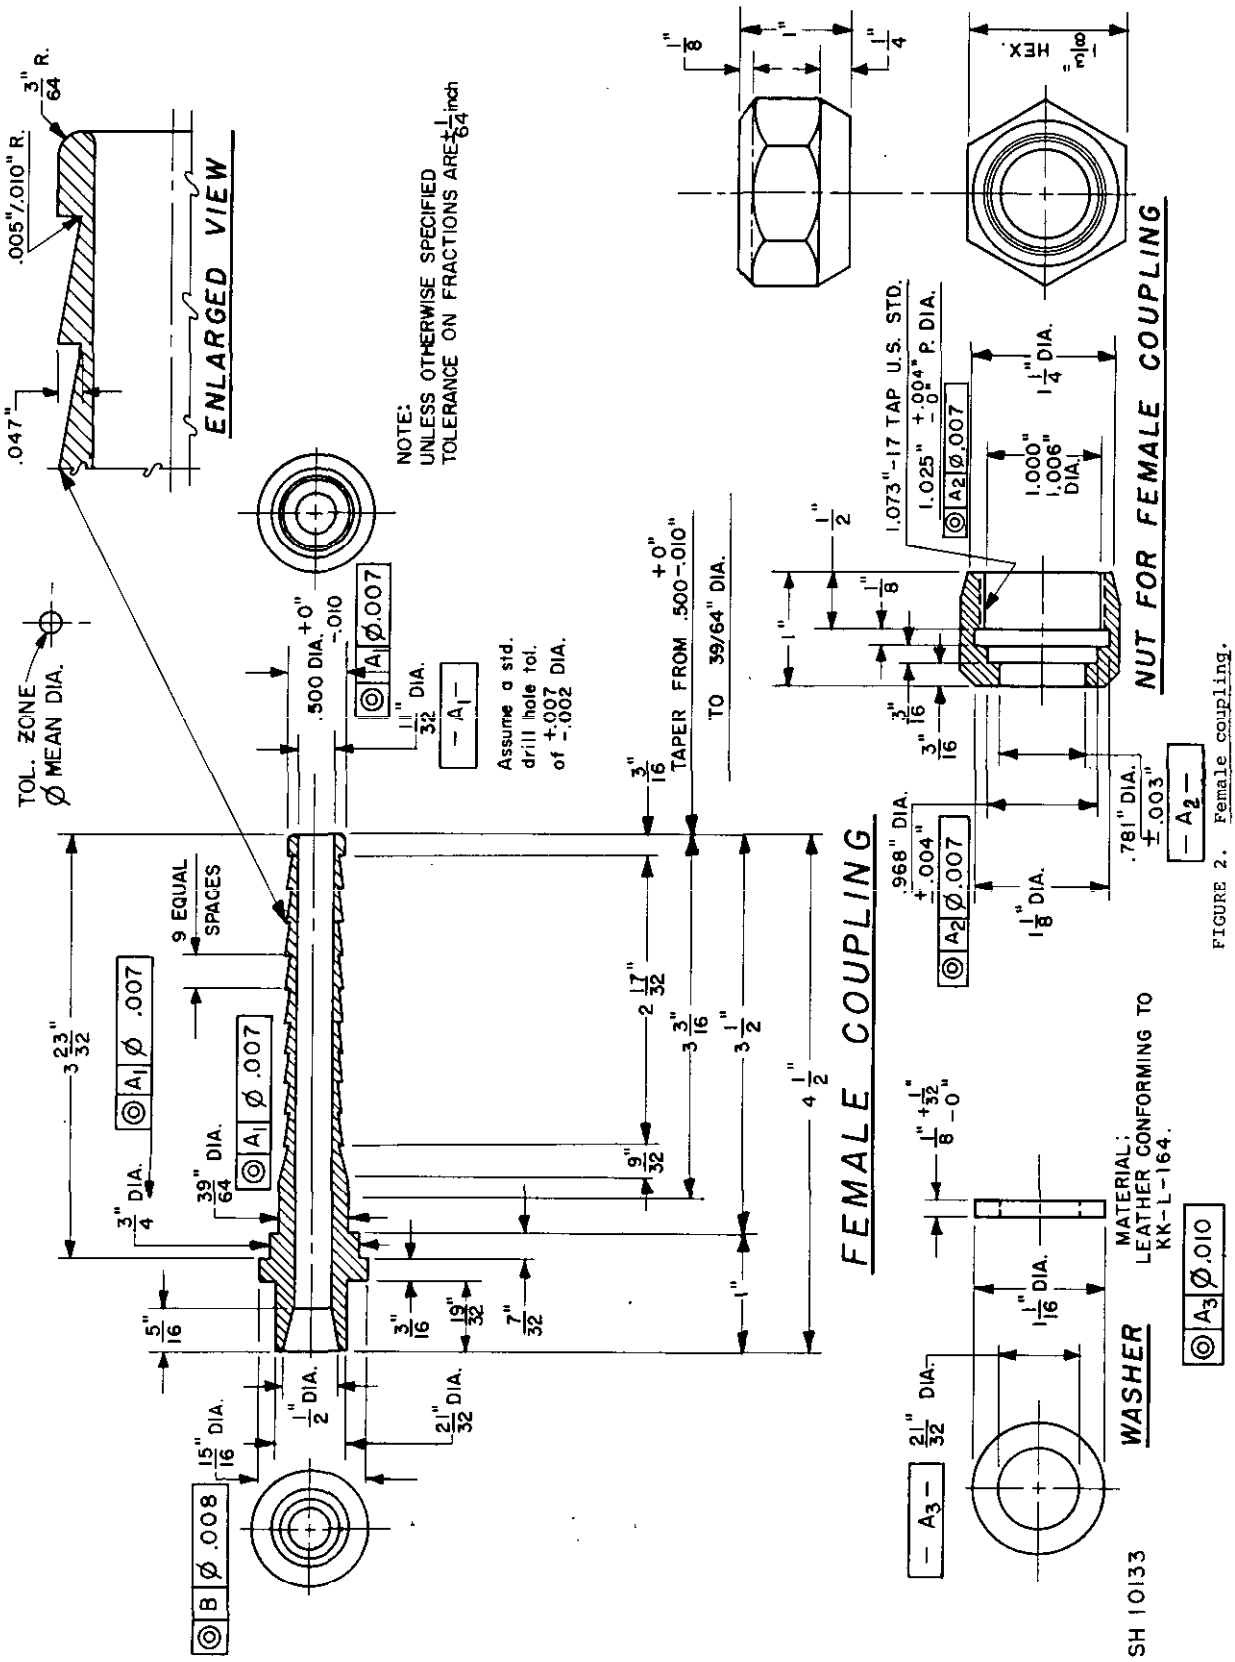


FIGURE 2. Female coupling.

Source: https://assist.dla.mil - Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

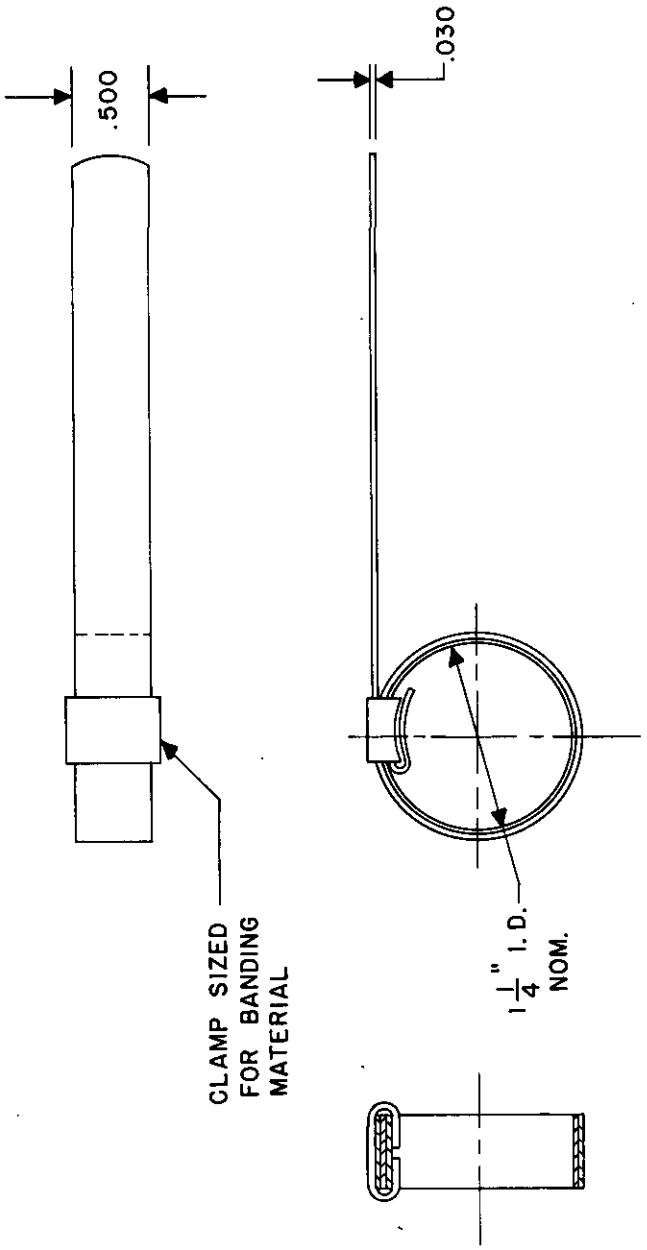


FIGURE 3. Clamp.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

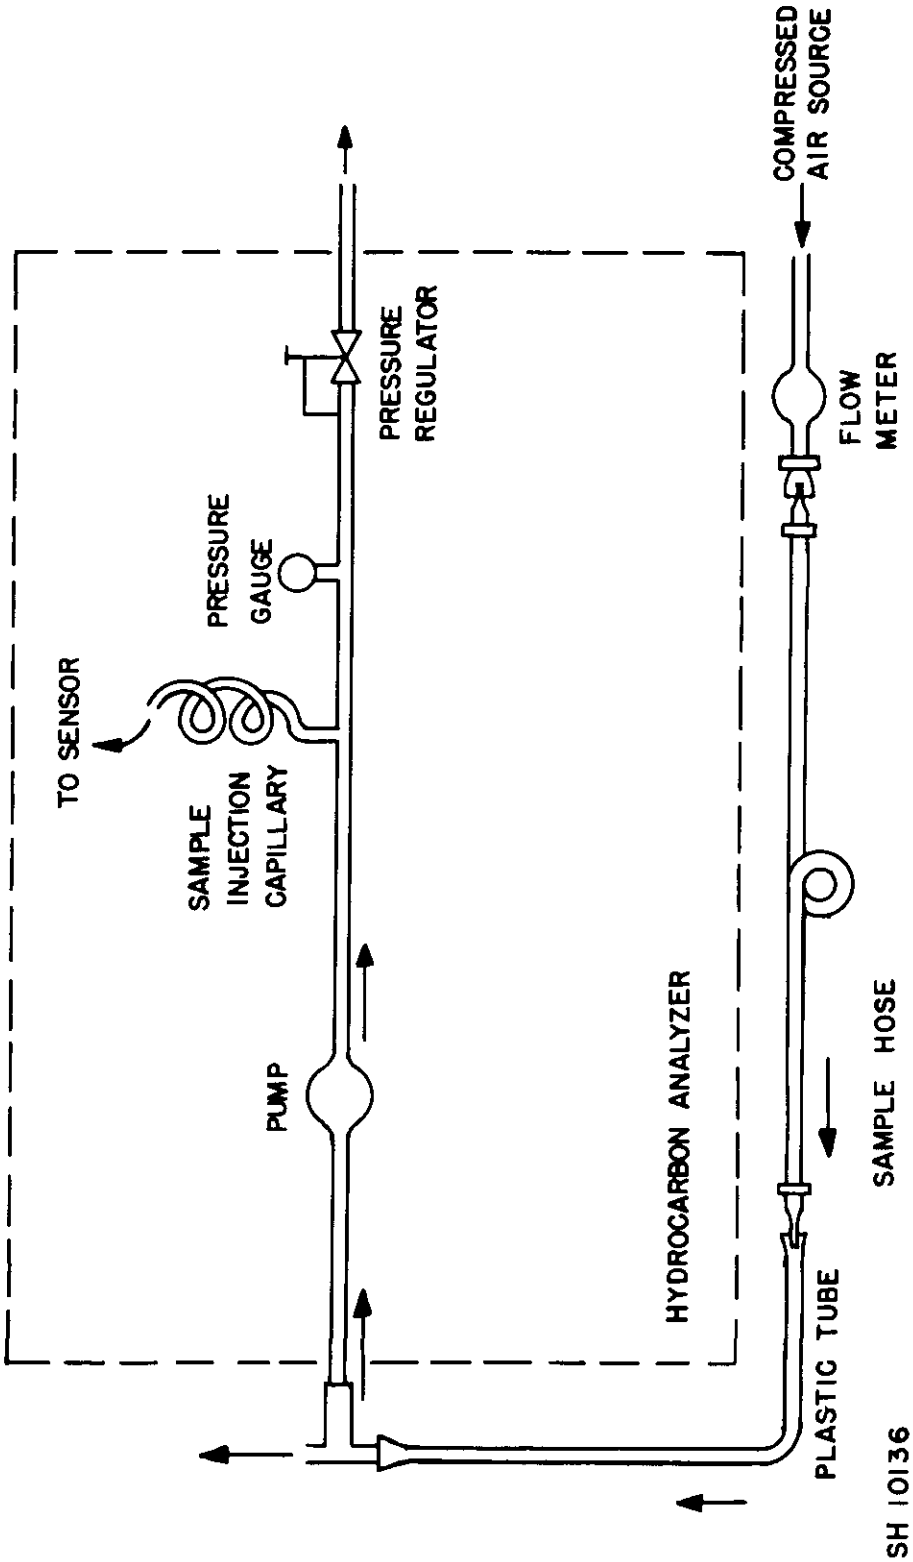


FIGURE 4. Flow diagram of apparatus for measuring the concentration of hydrocarbons in a stream of air or other gas after it has passed through a test hose.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS: This form is provided to solicit beneficial comments which may improve this document and enhance its use. DoD contractors, government activities, manufacturers, vendors, or other prospective users of the document are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity. A response will be provided to the submitter, when name and address is provided, within 30 days indicating that the 1426 was received and when any appropriate action on it will be completed.

NOTE: This form shall not be used to submit requests for waivers, deviations or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

DOCUMENT IDENTIFIER *(Number)* AND TITLE

MIL-H-2815F

NAME OF ORGANIZATION AND ADDRESS OF SUBMITTER

☐ VENDOR ☐ USER ☐ MANUFACTURER

1. ☐ HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE? ☐ IS ANY PART OF IT TOO RIGID, RESTRICTIVE, LOOSE OR AMBIGUOUS? PLEASE EXPLAIN BELOW.

A. GIVE PARAGRAPH NUMBER AND WORDING

B. RECOMMENDED WORDING CHANGE

C. REASON FOR RECOMMENDED CHANGE(S)

2. REMARKS

SUBMITTED BY *(Printed or typed name and address — Optional)*

TELEPHONE NO.

DATE

DD FORM 1426 1 OCT 76

Replaces edition of 1 Jan 72 which may be used.

S/N 0102-LF-001-4260

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.

FOLD

POSTAGE AND FEES PAID
DEPARTMENT OF THE NAVY
DoD-316



OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

Commander, Naval Ship Engineering Center
(SEC 6124C)
Department of the Navy
Washington, DC 20362

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:44Z
Check the source to verify that this is the current version before use.