MIL-I-3158D
7 October 1968
SUPERSEDING
MIL-I-3158C
2 April 1958
(See 6.4 and 6.5)

MILITARY SPECIFICATION

INSULATION TAPE,

ELECTRICAL GLASS-FIBER (RESIN-FILLED),

AND CORD, FIBROUS-GLASS

This specification is mandatory for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers resin treated glass-fiber electrical insulation for use in the insulation of electric cables.

1.2 Classification. Electrical insulation shall be of the following forms and types, as specified (see 6.2):

Tape:
Type SR-1 - Coated, Frayproof (for cable sealing).

Cordage:
Type SR-4 - For cable installation.
Type SR-4.5 - Lacing cord for cable installation.
Type SR-5 - For cable installation (color coded).

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein.

SPECIFICATIONS

FEDERAL

H-B-681 - Brushes, Typewriter.
TT-S-735 - Standard Test Fluids, Hydrocarbon.
PPP-B-566 - Boxes, Folding, Paperboard.
PPP-B-636 - Box, Fiberboard.
PPP-B-640 - Boxes, Fiberboard, Corrugated, Triple-Wall.
PPP-B-676 - Boxes, Setup.
PPP-T-45 - Tape, Gummed, Paper, Reinforced and Plain, For Sealing and Securing.

MILITARY

MIL-Y-1140 - Yarn, Cord, Sleeving, Cloth, and Tape - Glass.

STANDARDS

MILITARY
MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

UNIFORM CLASSIFICATION COMMITTEE
Uniform Freight Classification Rules.

Source: https://assist.dla.mil -- Downloaded: 202610-16T17:14Z
Check the source to verify that this is the current version before use.

(Application for copies should be addressed to the Uniform Classification Committee, 202 Union Station, 516 W. Jackson Boulevard, Chicago, Illinois 60606.)

AMERICAN TRUCKING ASSOCIATIONS, INC.
National Motor Freight Classification Rules

(Application for copies should be addressed to the American Trucking Associations, Inc., 1616 P Street, N. W., Washington, D. C. 20036.)

3. REQUIREMENTS

3.1 Type SR-1. Tape may be made by treating glass-fiber tape of the specified width or by cutting cloth or wider tape after treating, provided the finished tape conforms to this specification.

3.1.1 Uncoated material. The uncoated fabric shall be continuous filament glass-fiber cloth conforming to form 4, class C, cloth number 116 of MIL-Y-1140.

3.1.2 Coating. Unless otherwise specified in the contract or order (see 6.2), the fabric shall be coated with (vinyl, resin suitably compounded and blocked. The coating shall be applied by the knife coating method to both sides of the fabric so that it is completely impregnated and coated. Calendar coating is not permissible. The coating shall be of such a nature as not to permit peeling. The color of the finished material shall be black.

3.1.3 Dimensions. Unless otherwise specified (see 6.2), tape shall be furnished in 25-yard lengths rolled on a 1-1/2 inch diameter core, in 1/2, 1, 2, 3, 4, 5, or 6 inch widths (see 4.4.1.4.2 for measurement of width). The finished material shall have an average thickness of not less than 0.006 inch (measuring not less than 0.0055 inch in any area).

3.1.4 Breaking strength. The breaking strength of the finished tape shall be not less than 80 pounds per inch width (see 4.4.1.1).

3.1.5 Flammability. The length of the burned portion shall not exceed 2.75 inches and no flame indicator on any of the specimens shall show any signs of scorching, burning, or decompositon by flame when tested as specified in 4.4.1.2.

3.1.6 Flexibility. The coating shall not crack or fracture when the tape is tested as specified in 4.4.1.3.

3.1.7 Chemical resistance. There shall be no softening, loosening, or peeling of the coating from the fabric when tested as specified in 4.4.1.5.

3.2 Type SR-4. The material shall consist of glass-fiber cordage, coated with a suitable synthetic resin.

3.2.1 Uncoated material. The glass-fiber cordage, before coating, shall conform to form 2, class C, cordage number EC9-4-3 of MIL-Y-1140.

3.2.2 Coating. Unless otherwise specified in the contract or order (see 6.2), the cordage shall be coated with a suitable synthetic resin composition gray in color.

3.2.3 Dimensions. The diameter of the completed cord shall be 0.063 ± 0.004 inch when measured as specified in 4.4.2.3. The finished material shall be furnished in 1/2 pound spools unless otherwise specified (see 6.2).

3.2.4 Breaking strength. The breaking strength of the finished cordage shall be not less than that specified for the untreated EC9-4-3 cordage of MIL-Y-1140 (see 3.2.1).

3.2.5 Flammability. The compound shall not drip from the specimen during the test and shall not continue to flame (as indicated by flaming additional to that of the Tirrill burner and usually of a different color) after the fifth cycle of flame application, when tested as specified in 4.4.2.2. The cordage shall remain in place during the test.

3.2.6 Blocking. The layers of cord shall not bond to the extent that the coating is removed or visibly damaged when the layer is unwound (see 4.4.2.4).

3.2.7 Coating durability. The looped cords shall not break at less than 40 pounds when tested as specified in 4.4.2.5.

3.2.8 Chemical resistance. There shall be no softening, loosening, or peeling of the coating from the cordage when tested as specified in 4.4.2.6.

Source: https://assist.dla.mil -- Downloaded: 20260-16T17:14Z
Check the source to verify that this is the current version before use.

3.3 Type SR-4.5. The material shall consist of glass-fiber cordage, coated with a suitable synthetic resin.

3.3.1 Uncoated material. The glass-fiber cordage, before coating, shall conform to form 2, class C, cordage number EC9-3-U of MIL-Y-1140.

3.3.2 Coating. Unless otherwise specified in the contract or order (see 6.2), the cordage shall be coated with a suitable synthetic resin composition, white in color.

3.3.3 Dimensions. The diameter of the completed cord shall be 0.045 ± 0.004 inch when measured as specified in 4.4.2.3. The finished material shall be furnished in 1/2 pound spools unless otherwise specified (see 6.2).

3.3.4 Breaking strength. The breaking strength of the finished cordage shall be not less than that specified for EC9-3-U cordage of MIL-Y-1140 (see 3.3.1).

3.3.5 Flammability. The flammability of the compound shall be as specified in 3.2.5.

3.3.6 Blocking. The cordage shall conform to the requirement specified in 3.2.6.

3.3.7 Coating durability. The looped cords shall not break at less than 25 pounds when tested as specified in 4.4.2.5.

3.3.8 Chemical resistance. The chemical resistance of the coating shall be as specified in 3.2.8.

3.4 Type SR-5. The material shall consist of a glass-fiber cordage coated with a suitable synthetic resin.

3.4.1 Uncoated material. The glass-fiber cordage, before coating, shall conform to form 2, class C, cordage number EC9-2-U of MIL-Y-1140.

3.4.2 Coating. The cordage shall be coated with a suitable synthetic resin composition of one of the following colors, as specified (see 6.2), black, white, red, green, or gray.

3.4.3 Dimensions. The diameter of the completed cord shall be 0.035 ± 0.005 inch when measured as specified in 4.3.2.3. The finished material shall be furnished in 1/2 pound spools unless otherwise specified (see 6.2).

3.4.4 Breaking strength. The breaking strength of the finished cordage shall be not less than that specified for the untreated EC9-2-U cordage of MIL-Y-1140 (see 3.4.1).

3.4.5 Flammability. The flammability of the compound shall be as specified in 3.2.5.

3.4.6 Blocking. The cordage shall conform to requirement specified in 3.2.6.

3.4.7 Coating durability. The looped cords shall not break at less than 10 pounds when tested as specified in 4.4.2.5.

3.4.8 Chemical resistance. The chemical resistance of the coating shall be as specified in 3.2.8.

3.5 Workmanship. Workmanship shall be such as to meet all applicable requirements of this specification and any reference subsidiary specification or other document when inspected in accordance with 4.3.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Sampling for quality conformance inspection.

4.2.1 Lot. A lot shall consist of all material of the same form, type, width (type SR-1), and color offered for delivery at the same time.

4.2.2 Sampling for visual and dimensional examination. A sample of rolls or spools of insulation material shall be selected from each lot offered for inspection in accordance with MIL-STD-105 at inspection level I. The Acceptable Quality Level shall be equal to 2.5 percent defective.

Source: https://assist.dla.mil -- Downloaded: 202640-16T17:14Z
Check the source to verify that this is the currentversion before use.

4.2.3 Sampling for quality conformance tests. A sample of rolls or spools shall be selected for each lot in accordance with the appendix to MIL-STD-105 at inspection level S-2, the smallest sample size to be used shall be two. For reduced inspection procedure R-1 may be used. Thirty-five feet of tape from each sample roll or spool of tape, and 200 feet of cordage from each sample spool or roll of cordage are required for the tests of 4.3.2. If any sample roll or spool fails any test this shall be cause for rejection of the lot.

4.3 Quality conformance inspection.

4.3.1 Visual and dimensional examination. Each of the samples selected in accordance with 4.2.2 shall be visually and dimensionally examined to verify compliance with the requirements of this specification not involving tests. Five yards of material shall be unrolled from each sample roll or spool for this examination. Any roll or spool in the sample containing one or more visual or dimensional defects shall be rejected, and if the number of defective rolls or spools in any sample exceeds the acceptance number for that sample, this shall be cause for rejection of the lot represented by the sample.

4.3.2 Quality conformance tests. The quality conformance tests shall be in accordance with Table I.

Table I - Quality conformance tests.

Inspection	SR-1		Requirements paragraph			Inspection paragraph
	Requirements paragraph	Inspection paragraph	SR-4	SR-4.5	SR-5	SR-4, SR-4.5, SR-5
Dimensions	3.1.3	4.6.1.4	3.4.3	3.5.3	3.4.3	4.4.2.3
Breaking strength	3.1.4	4.6.1.1	3.4.4	3.5.4	3.4.4	4.4.2.1
Flammability	3.1.5	4.6.1.2	3.4.5	3.5.5	3.4.5	4.4.2.2
Flexibility	3.1.6	4.6.1.3				
Chemical resistance	3.1.7	4.6.1.5	3.4.8	3.5.8	3.4.8	4.4.2.6
Blocking			3.4.6	3.5.6	3.4.6	4.4.2.4
Coating durability			3.4.7	3.5.7	3.4.7	4.4.2.5

4.4 Test methods.

4.4.1 Tape.

4.4.1.1 Breaking strength. The breaking strength shall be determined on a suitable type of testing machine. The specimens shall be tested in full section, if 2 inches or less in width, and in 2 inch rectangular strips if over 2 inches in width. The initial length of the test specimens between jaws shall be 7 inches, and the pulling jaws shall travel at a uniform rate of 11 to 13 inches per minute. The average of five tests expressed in pounds per inch width shall be taken as the breaking strength. In the case of a break 25 percent or more below the general average, a second test shall be made, and this test shall be included in obtaining the final average.

4.4.1.2 Flammability.

4.4.1.2.1 Test equipment. Test equipment shall comprise the following:

(a) A test chamber 12 inches wide by 14 inches deep by 24 inches high, open at the top, and provided with means for supporting the test specimen in a vertical position by the use of a 1/2 pound weight clamped to the bottom of the specimen to keep it taut during the test.
(b) A Tirrell burner of a nominal base of 3/8 inch, a length of approximately 2 inches above the primary air inlet, and mounted on a 45 degree angle block. In place of the pilot light attachment, the burner shall have a battery operated high voltage sparking device which instantaneously ignites the burner but does not interfere with the flame when gas is turned on at the proper preadjusted flame height and position with respect to the specimen.
(c) A jig at the bottom of the test chamber to insure the correct location of the flame with respect to the sample.
(d) A supply of ordinary illuminating gas at service pressure with the gas supply through a stopcock.
(e) A stopwatch that makes one revolution per minute.
(f) Strips of 3 mil bond paper 1/2 by 4 inches for use as flame indicators.
(g) A typewriter brush conforming to types "I" or "TP" of H-B-681.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T17:14Z
Check the source to verify that this is the current version before use.

4.4.1.2.2 Test specimens. Five test specimens 12 by 1 inch with a bench mark 2 inches from the bottom of each to indicate the point of flame application.

4.4.1.2.3 Test method. A piece of indicator paper shall be stapled to a tape test specimen 8 inches above the bench mark. The indicator paper is affixed in such a manner that it overlaps the test specimen 1/2 inch on either side.

4.4.1.2.3.1 The test specimen shall be secured in the chamber. The flame shall be adjusted to a total length of 5 inches and an inner cone of 1-1/2 inches in a vertical position. The burner, with electrical ignition device connected, shall be placed in front of the sample so that the vertical plane through the burner includes the vertical axis of the test specimen, and so that there is a distance of 1-1/2 inches along the axis of the burner stem between the tip of the burner and the test specimen, which shall be so suspended that 2 inches thereof shall extend below the point of application of the flame. The flame shall be applied to the sample by opening the gas valve for 10 seconds, then closing it. The extinguished tape shall be brushed with a typewriter brush to remove charred resin, and the length of the burned portion determined by subtracting the unburned length of tape from 10 inches. The indicator paper shall be examined for burning, charring, or other damage.

4.4.1.3 Flexibility. A specimen of the material 1 inch in width shall be folded upon itself and creased under pressure of a 1-pound weight. This shall be repeated five times in each direction; then the tape shall be laid flat for 15 minutes and examined for permanent damage.

4.4.1.4 Dimensional examination.

4.4.1.4.1 Thickness. The thickness shall be determined by the use of a dial type micrometer (a 1-inch machinist's micrometer equipped with ratchet device may be used if the results are equivalent). When a dial type micrometer is used, the lower or fixed anvil shall consist of a flat steel plate 2 inches in diameter; the upper or movable member shall consist of a foot having a flat steel face 1/4 inch in diameter and arranged so as to move with its face at all times parallel to the face of the anvil. The movable member shall be of such weight and attached to the operating rod of the micrometer in such a manner that 3 ounces dead weight shall be applied to all thicknesses of samples being measured. The thickness shall be determined as the average of at least 10 readings taken at intervals of approximately 1 foot along the length of the material. If the thickness, so determined, falls outside the specified tolerances, 10 additional readings shall be taken from another section of the material and average with the previous readings. The maximum, minimum, and average values shall be recorded.

4.4.1.4.2 Width. The width shall be determined by the use of a standard steel scale graduated to read to 1/64 inch. The fabric shall lie flat on a smooth surface at the time of measurement. At least 10 measurements shall be made of width and the maximum, minimum, and average values recorded. The average value shall be taken as the tape width.

4.4.1.5 Chemical resistance. A specimen shall be soaked for 24 hours at 25°C. in type II fluid conforming to TT-S-735. The specimen shall then be examined for softening, loosening, or peeling of the coating from the glass-fiber fabric.

4.4.2 Cordage.

4.4.2.1 Breaking strength. The breaking strength shall be determined on a type of testing machine approved by the bureau of agency concerned. The initial test length between the jaws shall be 10 inches and the pulling jaw shall travel at a uniform rate of 11 to 13 inches per minute. (For most uniform and consistent test results the Jute Association type cordage jaws are recommended.) At least 10 breaks shall be taken on each sample. In the case of a break occurring in the jaw the results shall be discarded, and another break shall be made and this result included in the record. The average of 10 tests on each sample shall be reported as the average breaking strength.

4.4.2.2 Flammability.

4.4.2.2.1 Test equipment. The test equipment shall comprise the test equipment as specified in 4.4.1.2.1 (a) through (e).

4.4.2.2.2 Test specimen. The test specimen shall consist of a ceramic tube of 1-1/8 inch outside diameter, 2 inches long with 1/8 inch thick walls. Around the center of the tube, for thermal insulation, shall be wrapped five layers of 3/4 of an inch wide 0.015 inch thick asbestos paper tape. On top of the tape shall be wrapped a single layer of the cordage to be tested having a sufficient number of turns to almost cover the tape. The ends of the cord shall be secured by wrapping or pulling under the succeeding or preceding three turns of cord as is normally done with bindings of this sort.

4.4.2.2.3 Test method. The test specimen shall be supported in the chamber with the axis of the tube horizontal. The flame shall be adjusted to a total length of 5 inches and an inner cone of 1-1/2 inches with the burner in a vertical position. The burner with only the pilot light lighted shall then be

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T17:14Z
Check the source to verify that this is the current version before use.

supported at an angle of 45 degrees with the horizontal and adjusted so that a line extended through its longitudinal axis will intersect the longitudinal axis of the tube at an angle of 90 degrees. The position of the burner shall also be such that the tip of the inner core will just touch the surface of the cordage at the center of the winding. The flame shall be applied to the sample by opening the gas valve for 15 seconds then closing for 15 seconds. The number of cycles at which flaming of the compound ceases, dripping of the compound, continuation of flaming during the off cycle, and any abnormal condition shall be recorded.

4.4.2.3 Diameter. The overall diameter of the cordage shall be determined by stretching the cordage between supports about 2 feet apart with just sufficient tension to hold it straight. A machinist's micrometer shall then be set at just sufficient separation that the cord will pass between the anvils without noticeable drag. This setting shall be recorded as the diameter of the cord at that point and five such measurements shall be made on two separate lengths taken from widely different sections of the sample roll.

4.4.2.4 Blocking. Ten turns of the cordage shall be wound on a 1/4 inch diameter clean metal mandrel under a 2-pound tension and the end secured through holes in the mandrel. Eight turns of cordage shall then be wound on top of the first layer under the 2-pound tension and the ends secured as before. The wound mandrel shall then be placed in an oven controlled at 70° ± 1°C. for 2 hours, removed, and cooled to room temperature. After cooling, the outer layer shall be unwound and examined for evidence of damage to the coating due to adhesion between layers of turns. The first layer shall be examined while still in place for similar evidence of adherence and damage.

4.4.2.5 Coating durability. A suitable type of testing machine as specified in 4.4.2.1 equipped with Jute Association type clamps with 2 inch drums and a 1/2 inch fixed pin as shown on figure 1 shall be used. The gage length shall be adjusted to 13-1/2 inches from center to center of drums. The pulling speed shall be set at a uniform rate of 11 to 13 inches per minute. The ends of a 24 inch length of cord shall be tied together with a square knot to form a loop with a periphery of 17-1/4 inches. This may be facilitated by placing the cord around two rods 3/8 of an inch in diameter which are separated by 8-1/4 inches between their outside edges. The loop shall be positioned with one wrap on the drum of the upper jute clamp as shown on figure 1. The length of the test specimen shall be 72 inches. The end of the 72 inch long specimen shall be fastened in the clamp of the bottom jute jaw, three wraps shall be placed around the drum, the free end shall be inserted through the loop on the upper jaw, and the end shall then be secured around the fixed pin with six wraps followed by a clove hitch (see figure 1). The test specimen should break at the point of contact with the loop. If the loop breaks the test results shall be discarded and another specimen tested for the average. The position of the loop shall be shifted after each test so that a new position is brought in contact with successive test specimens. The average of five tests on each sample shall be reported in pounds.

4.4.2.6 Chemical resistance. A specimen shall be tested as specified in 4.4.1.5.

4.5 Inspection of preparation for delivery. Preservation, packaging, packing, and marking shall be inspected to determine conformance to the requirements of section 5 herein.

5. PREPARATION FOR DELIVERY

(The preparation for delivery requirements specified herein apply only for direct Government procurements.)

5.1 Sub-contracted material and parts. The preparation for delivery requirements of referenced documents listed in section 2 do not apply when material and parts are procured by the supplier for incorporation into the equipment and lose their separate identity when the equipment is shipped.

5.2 Preservation and packaging. Preservation and packaging shall be level A or C, as specified (see 6.2).

5.2.1 Level A.

5.2.1.1 Cleaning. Insulation tape and fibrous glass cord shall be cleaned in accordance with process C-1 of MIL-P-116.

5.2.1.2 Drying. Tape and cord shall be dried in accordance with MIL-P-116.

5.2.1.3 Unit packaging. Insulation tape and cord shall be furnished in rolls or on spools packaged as specified herein in conformance to method III of MIL-P-116.

5.2.1.3.1 Each roll or spool of insulation material shall be enclosed in a bag or wrap of polyetnylene or paper. The bag or wrap shall be sealed in an appropriate manner, except that staples shall not be used. Alternatively, rolls or spools may be individually cartonized in folding or set-up paperboard or fiber boxes conforming to PPP-B-566, PPP-B-676, or PPP-B-636, respectively, at the option of the contractor. Box closure shall be as specified in the box specification or appendix thereto.

Source: https://assist.dla.mil -- Downloaded: 202640-16T17:14Z
Check the source to verify that this is the currentversion before use.

5.2.1.4 Intermediate packaging. Unless otherwise specified (see 6.2), rolls or spools of the same length, width and class shall be packaged in fiberboard boxes conforming to PPP-B-636, domestic. The gross weight of the intermediate packages shall not exceed 20 pounds.

5.2.2 Level C. Rolls and spools shall be packaged in a manner which will afford adequate protection against deterioration and physical damage during shipment from source to first receiving activity.

5.3 Packing. Packing shall be level A, B, or C, as specified (see 6.2).

5.3.1 Level A. Insulation tape or cord packaged as specified (see 6.2), shall be packed in containers conforming to either of the following specifications at the option of the supplier:

Specification	Type or class
PPP-B-636 - Box, fiberboard	Weather-resistant
PPP-B-640 - Boxes, fiberboard, corrugated, triple wall	Class 2

Shipping containers shall be waterproofed, closed, strapped or banded in accordance with the applicable box specification. Shipping containers shall be reinforced with pressure sensitive reinforced filament tape applied in accordance with the applicable box specification. The gross weight of triple wall boxes shall not exceed 250 pounds, of fiberboard boxes, the weight limitation of the applicable box specification.

5.3.2 Level B. Insulation tape or cord packaged as specified (see 6.2), shall be packed in containers conforming to either of the following specifications at the option of the supplier:

Specification	Type or class
PPP-B-636 - Box fiberboard	Domestic
PPP-B-640 - Box, fiberboard, corrugated, triple wall	Class 1

Shipping containers shall be closed, strapped or banded in accordance with the applicable box specification, except that PPP-B-636 containers may be sealed with PPP-T-45 tape. The gross weight of triple wall boxes shall not exceed 250 pounds of fiberboard boxes, the weight limitation of the applicable box specification.

5.3.3 Level C. Insulation tape or cord packaged as specified (see 6.2), shall be packed in containers acceptable to the common carrier and which will insure safe delivery at the destinations in a satisfactory condition at the lowest applicable rate. Containers or method of packing shall comply with Uniform Freight or National Motor Freight classification rules or regulations or other carrier rules as applicable to the mode of transportation.

5.4 Marking. In addition to any special marking required by the contract of order (see 6.2), each unit package, intermediate and exterior container shall be marked in accordance with MIL-STD-129.

6. NOTES

6.1 Intend use.

6.1.1 Type SR-1 material is intended for general use in the installation of electric cables, but particularly for cable sealing in accordance with NAVSEC drawing 9000-S6200-73980.

6.1.2 Types, SR-4 and SR-5 material are intended for use in serving insulating materials used in the installation of electric cables.

6.1.3 Type SR-4.5 material is intended for use as lacing cord in the installation of electrical cables in applications such as switchboards.

6.2 Ordering data. Procurements documents should specify the following:

(a) Title, number, and date of this specification.
(b) Form and type required (see 1.2).
(c) If coating is other than specified (see 3.1.2, 3.2.2 and 3.3.2).
(d) Required width and length of tape (see 3.1.3).
(e) Required length of cordage of other than 1/2 pound spools (see 3.2.3, 3.3.3, and 3.4.3).
(f) Weight of type SR-4 spool, if different than 3.2.3; weight of type SR-4.5 spool, if different than 3.3.3; weight of type SR-5 spool, if different than 3.4.3.
(g) Required color of type SR-5 cordage (see 3.4.2).

Source: https://assist.dla.mil -- Downloaded: 202610-16T17:14Z
Check the source to verify that this is the current version before use.

(g) Level of packaging and packing required (see 5.2 and 5.3).
(i) When gross weight of containers is other than that specified in 5.3.1.
(j) Additional marking, if required (see 5.4).

6.3 The approximate length of cordage per 1/2 pound roll is as follows:

Type	Length in yards per roll
SR-4	75
SR-4.5	210
SR-5	245

6.4 International interest. Certain provisions of this specification are subject of international standardization agreement as cited in ABC-NAVY-STD-1?C. When amendment revision or cancellation of this specification is proposed which will effect or violate the international agreement concerned, the preparing activity will take appropriate reconciliation action through international standardization channels including departmental standardization offices, if required.

6.5 CHANGES FROM PREVIOUS ISSUE. THE OUTSIDE MARGINS OF THIS DOCUMENT HAVE BEEN MARKED "*" TO INDICATE WHERE CHANGES (DELETIONS, ADDITIONS, ETC., FROM THE PREVIOUS ISSUE HAVE BEEN MADE. THIS HAS BEEN DONE AS A CONVENIENCE ONLY AND THE GOVERNMENT ASSUMES NO LIABILITY WHATSOEVER FOR ANY INACCURACIES IN THESE NOTATIONS. BIDDERS AND CONTRACTORS ARE CAUTIONED TO EVALUATE THE REQUIREMENTS OF THIS DOCUMENT BASED ON THE ENTIRE CONTENT AS WRITTEN IRRESPECTIVE OF THE MARGINAL NOTATIONS AND RELATIONSHIP TO THE LAST PREVIOUS ISSUE.

Custodians:
Army - EL
Navy - SH
Air Force - 85

Review activities:
Army - EL
Navy - SH, EC
Air Force - 85

User activity:
Navy - MC

International interest (see 6.4)

Preparing activity:
Navy - SH
(Project 5970-0227)

Source: https://assist.dla.mil -- Downloaded: 202610-16T17:14Z
Check the source to verify that this is the current version before use.

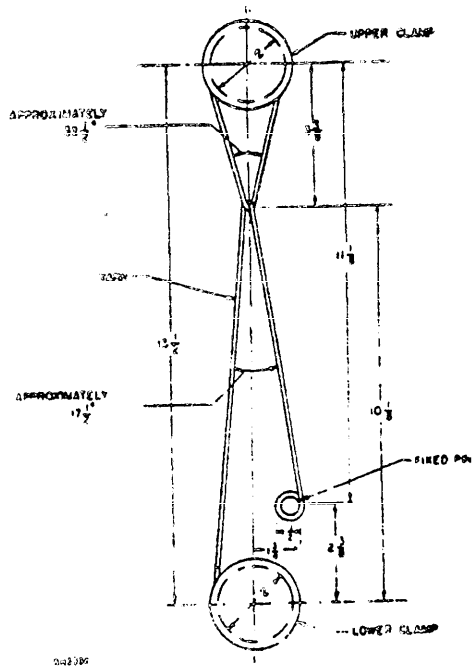


Figure 1 - Diagram for loop test of cordage using Jute Association type clamps with 2-inch drum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T17:14Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D C

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Commander, Naval Ship Engineering Center
Federal & Military & DOD Standardization
Branch
Department of the Navy

Source: https://assist.dla.mil -- Downloaded: 202610-16T17:14Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
3b. ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)*:

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	7b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
7c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T17:14Z
Check the source to verify that this is the current version before use.