INCH-POUND
MIL-F-24032A(SH)
19 October 1989
SUPERSEDING
MIL-F-24032(SHIPS)
31 March 1964
(See 6.7)

MILITARY SPECIFICATION

# FLASK, SEPARATOR, 3000 PSI, K-MONEL

This specification is approved for use by the Naval Sea Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

## 1. SCOPE

1.1 Scope. This specification covers K-Monel high pressure flasks with Monel end plugs for separation of impurities from oxygen in submarine oxygen generator systems.

## 2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDERAL

| | |
|---|---|
| QQ-N-281 | - Nickel-Copper Alloy Bar, Rod, Plates, Sheet, Strip, Wire, Forgings, and Structural and Special Shaped Sections. |
| QQ-N-286 | - Nickel-Copper-Aluminum Alloy, Wrought (UNS N05500). |
| PPP-F-320 | - Fiberboard; Corrugated and Solid, Sheet Stock (Container Grade) and Cut Shapes. |

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Naval Sea Systems Command, SEA 55Z3, Department of the Navy, Washington, DC 20362-5101 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 8120
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

MILITARY

| | |
|---|---|
| MIL-P-116 | - Preservation, Methods of. |
| MIL-T-1368 | - Tube and Pipe, Nickel-Copper Alloy, Seamless and Welded. |
| MIL-L-19140 | - Lumber and Plywood, Fire-Retardant Treated. |
| MIL-E-22200 | - Electrodes, Welding, Covered; General Specification for. |
| MIL-E-22200/3 | - Electrodes, Welding, Covered: Nickel Base Alloy; and Cobalt Base Alloy. |

STANDARDS

FEDERAL

| | |
|---|---|
| FED-STD-H28 | - Screw-Thread Standards for Federal Services. |
| FED-STD-151 | - Metals; Test Methods. |

MILITARY

| | |
|---|---|
| MIL-STD-271 | - Requirements for Non-Destructive Testing Methods. |
| MIL-STD-2073-1 | - DOD Materiel Procedures for Development and Application of Packaging Requirements. |

(Unless otherwise indicated, copies of federal and military specifications, standards, and handbooks are available from the Naval Publications and Forms Center, (ATTN: NPODS), 5801 Tabor Avenue, Philadelphia, PA 19120-5099.)

2.2 Non-Government publications. The following document(s) form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2).

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

| | |
|---|---|
| D 3951 | - Standard Practice for Commercial Packaging. (DOD adopted) |
| E 8 | - Standard Test Methods of Tension Testing of Metallic Materials. (DOD adopted) |

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

## 3. REQUIREMENTS

### 3.1 Material.

3.1.1 Flasks. The material for the flasks shall be seamless K-Monel tubes having chemical composition in accordance with QQ-N-286. Material from which flasks are to be made shall be in the hot finished, hot finished and annealed, or cold drawn and annealed condition. Finished flasks shall be in the annealed and age hardened condition and shall have mechanical properties specified in table I.

TABLE I. Mechanical properties.

| | |
|---|---|
| Yield strength, at 6.625 inches minus 0 inch | 85,000 $lb/in^2$ minimum |
| Tensile strength | 130,000 $lb/in^2$ minimum |
| Elongation | 20.0 percent in 2 inches |

3.1.2 End plugs. End plugs shall be nickel-copper alloy in accordance with class A of QQ-N-281.

3.1.3 Recovered materials. Unless otherwise specified herein, all equipment, material, and articles incorporated in the products covered by this specification shall be new and may be fabricated using materials produced from recovered materials to the maximum extent practicable without jeopardizing the intended use. The term "recovered materials" means materials which have been collected or recovered from solid waste and reprocessed to become a source of raw materials, as opposed to virgin raw materials. None of the above shall be interpreted to mean that the use of used or rebuilt products is allowed under this specification unless otherwise specifically specified.

3.2 Dimensional characteristics. The dimensional characteristics of flasks shall be as shown in table II. Unless otherwise specified herein, the difference between the major and minor diameters shall not exceed 2 percent of the flask outside diameter.

TABLE II. Dimensional characteristics.

| | |
|---|---|
| Capacity | 0.5 cubic feet |
| Outside diameter plus or minus 3/32 inch | 6.625 inches |
| Length plus 2 inches minus 0 inches | 3 feet 10 inches |
| Wall thickness, minimum | 0.375 inch |
| Hydrostatic test pressure | 5000 $lb/in^2$ |
| Applicable figure | 1 |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

3.3 Fabrication. The body of the flask shall be in the form of a straight cylinder as shown on figure 1. Each end shall be hot formed to provide a neck for the end connections (see figure 2). Flasks shall be formed of seamless tubular material.

3.3.1 Annealing. After completion of forging operations, flasks shall be annealed, then rapidly quenched from the annealing temperature.

3.3.2 Age hardening. Flasks shall be age hardened after annealing. Rough and finish machining may be performed before or after age hardening at the option of the contractor. Flasks shall be cleaned of all machining lubricants prior to age hardening.

3.3.3 Neck threads. The neck threads shall be Unified National threads in accordance with FED-STD-H28 (see figure 2).

3.4 Cleaning. Flasks shall be thoroughly cleaned of all loose particles and other contamination by abrasive blast, if necessary, followed by a wash with an acid pickle. The flask shall be thoroughly dried and immediately subjected to the oil free test (see 4.3.4). Oils that come in contact with a flask under production shall be of a type that will fluoresce under an ultraviolet light examination.

3.5 Assembly. Each flask shall be furnished with an inlet and outlet plug, and a drain plug (see figures 3 and 4). End plugs shall be torqued to a minimum of 1000 foot-pounds, and seal welded (see figure 5). Welding shall be done by the shielded metal arc method using Monel welding electrode conforming to type 9N10 of MIL-E-22200 and MIL-E-22200/3. The inlet/outlet plug shall be assembled with inlet pipe and deflector as shown on figures 3 and 6 prior to installation in flask (see figure 1). The Monel (Ni-Cu) overlay (see figure 2) shall be applied using electrodes conforming to type 9N10 of MIL-E-22200 and MIL-E-22200/3. Overlay shall be applied to the flask after annealing and prior to age hardening.

3.5.1 Interchangeability. In no case shall parts be physically interchangeable or reversible unless such parts are also interchangeable or reversible with regard to function, performance and strength.

3.6 Label plate. A label plate shall be made for each flask of 1/16-inch thick aluminum. The label plate shall be attached to the neck of the flask by metal bands. The following information shall be stamped on the plate in 1/4-inch letters:

(a) Manufacturer's name and identification number.
(b) Weight to nearest pound.
(c) Operating pressure - 3000 $lb/in^2$.
(d) Material - QQ-N-286.
(e) Contract number.
(f) Specification number.
(g) Date.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

3.7 Indentations on flask. Indentations, other than those required by a manufacturer for identification of a flask during fabrication, are not permitted on the surface of the flask. Such markings may appear on the neck portion only. They shall be made with a round bottom stamp and shall be not over 1/16 inch deep (see figure 4).

3.8 Workmanship. Flasks shall be free from cracks, and other injurious defects. Threads shall be smooth, properly formed and free from burrs, nicks and gouges. The label plate shall be clear and legible.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in this specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of the manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to accept defective material.

4.2 Sampling.

4.2.1 Lot. A lot shall consist of all flasks from the same heat or melt, and heat treated in the same heat treatment furnace charge.

4.2.2 Test sample. A test sample for tensile and yield tests (see 4.4.2.1) shall be furnished with each lot of flasks. The test sample shall be in the shape of a right circular cylinder having the same inside diameter and wall thickness as the flasks which it represents. The sample shall be of the same heat of K-Monel, and shall be subjected to the same manufacturing processes (except swaging) and heat treatment as the flasks which it represents. The methods of quenching the test sample shall duplicate that of the flasks.

4.3 Visual and dimensional examination. Each flask shall be visually and dimensionally examined to verify conformance to this specification. Flasks shall be clean and free from loose scale, chips, or foreign materials. Any flask containing visual or dimensional defects shall not be offered for delivery.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

4.4 Test procedure.

4.4.1 Chemical analysis. Prior to flask fabrication a sample shall be taken from the pipe, billets or plate of each heat of K-Monel to be used for flask fabrication, and shall be subjected to a chemical analysis to determine conformance to 3.1.1. Sample selection and testing shall conform to FED-STD-151.

4.4.2 Destructive tests. The tests in 4.4.2.1 shall be performed on test specimens cut from the central 12-inch section of the test sample (see 4.2.2).

4.4.2.1 Tensile and yield. Four tensile specimens shall be cut longitudinally from the specified portion of the test sample (see 4.2.2), spaced 90 degrees apart and shall be tested in accordance with ASTM E 8 to determine conformance to tensile, yield and elongation properties specified in table I.

4.4.3 Flask tests.

4.4.3.1 Hydrostatic test. After assembly of end plugs, each flask shall be tested in a water jacket to a test pressure equal to 5/3 the design working pressure of the flask. Cold tap water shall be used for this test. Neither the water nor the flask shall be heated. The test pressure shall be held at least 30 minutes. As a result of this test the flask shall not rupture or show a permanent set exceeding 10 percent of the total volumetric expansion. There shall be no evidence of leakage through any portion of the flask or end plug. Any flask that fails to conform to this test shall not be offered for delivery.

4.4.3.2 Ultrasonic inspection. After the hydrostatic test has been completed, each flask shall be 100 percent inspected over the cylindrical section either in a circumferential direction or longitudinal direction between the heads in accordance with one of the methods prescribed in MIL-STD-271. The equipment shall be calibrated to detect a notch equal to 3 percent of the wall thickness (see 6.3).

4.4.3.2.1 Shear wave testing acceptance criteria. Any flask having a discontinuity indication greater than that produced by the 3 percent calibration notch shall not be offered for delivery. Any flask having a discontinuity equivalent to 50 percent of that produced by the calibration notch, and over 3 inches in length, shall be rejected unless approved by the Command or agency concerned.

4.4.3.2.2 Through wave testing acceptance criteria. For the through wave testing method, a 100 percent loss of back reflection indicates a discontinuity size equal to or greater than the 3 percent calibration notch. Any flask showing such a discontinuity size shall not be offered for delivery.

4.4.3.2.3 Calibration. Ultrasonic inspection equipment shall be recalibrated periodically to ensure optimum results. It shall also be recalibrated if there is any change in frequency or crystal size used.

4.4.3.2.4 Rejection. If the discontinuities are linearly disposed along the flask and the total length of all discontinuities in 12 inches of flask length is 6 inches, the flask shall not be offered for delivery.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

4.4.3.3 Liquid penetrant inspection. End sections shall be inspected by liquid penetrant in accordance with MIL-STD-271. Linear or linearly disposed circular indications as well as indications found in areas where abrupt changes in direction occur shall be treated as defects. Such defects shall be cause for rejection if they are greater than 0.0625 inch in depth. If less than 0.0625 inch deep, they may be faired into the adjacent area at a ratio of four to one by grinding.

4.4.3.4 Oil-free test. Flasks, after cleaning as specified in 3.4, shall be inspected internally by ultraviolet light ("black light": 3200 to 4000 Angstrom units). If there is any evidence of fluorescence on the interior or machined surfaces, the flask shall be recleaned and resubmitted to the oil-free test.

4.5 Inspection of packaging. Sample packages and packs, and the inspection of the preservation, packing and marking for shipment, stowage and storage shall be in accordance with the requirements of section 5 and the documents specified therein.

## 5. PACKAGING

(The packaging requirements specified herein apply only for direct Government acquisition. For the extent of applicability of the packaging or preparation for delivery requirements of referenced documents listed in section 2, see 6.4.)

5.1 General.

5.1.1 Navy fire-retardant requirements.

(a) Treated lumber and plywood. When specified (see 6.2), all lumber and plywood including laminated veneer material used in shipping container and pallet construction, members, blocking, bracing, and reinforcing shall be fire-retardant treated material conforming to MIL-L-19140 as follows:

Levels A and B - Type II - weather resistant.
Category 1 - general use.
Level C - Type I - non-weather resistant.
Category 1 - general use.

(b) Fiberboard. Fiberboard used in the construction of class-domestic, non-weather resistant fiberboard and cleated fiberboard boxes including interior packing forms shall meet the flame-spread index and the specific optic density requirements of PPP-F-320 and amendment thereto.

(c) Cushioning and wrapping materials. The use of excelsior, newspaper, shredded paper (all types), and similar hydroscopic or nonneutral materials and all types of loose fill materials for packaging (preservation and packing) applications such as cushioning, fill, stuffing, and dunnage is prohibited. Materials selected for cushioning and wrapping shall have properties



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

(characteristics) for resistance to fire. Cushioning or wrapping materials, as applicable, shall be provided to prevent item and package damage and to prevent free movement of the container contents.

5.2 Preservation. Preservation shall be level A, C or commercial as specified (see 6.2).

5.2.1 Flask processing. Each flask after completion of testing (see 4.4.3.4) and prior to preservation application shall comply with the cleanliness requirements as specified in 3.4. Openings shall be sealed.

5.2.2 Level A. Each flask shall be wrapped, cushioned and placed in a water-resistant folding, set-up or metal edged paperboard or fiberboard box to meet the unit protection requirements of MIL-P-116, method III. Unit container requirements including intermediate containers when required shall conform to table I, appendix F of MIL-STD-2073-1. Unless otherwise specified (see 6.2), box options such as type, variety, grade, and style shall be at the contractor's option.

5.2.3 Level C. Preservation shall be as specified for level A except that the unit containers shall be of the class-domestic/fire-retardant or nonweather resistant type, class, variety, grade, and style. Method I using pressure-sensitive adhesive tape shall apply for fiberboard box closure.

5.2.4 Commercial. Commercial packaging shall be in accordance with ASTM D 3951.

5.3 Packing. Packing shall be level A, B, C, or commercial as specified (see 6.2).

5.3.1 General requirements for levels A, B, and C. Containers selected (see 5.3.2) shall be of minimum weight and cube consistent with the protection required, and of uniform size.

5.3.2 Levels A, B, and C containers. Flasks preserved as specified (see 5.2), shall be packed in exterior shipping containers for the level of packing specified (see 5.3), in accordance with table VII, exterior shipping container requirements, of MIL-STD-2073-1, appendix C, and herein. Unless otherwise specified (see 6.2), container selection and options shall be at the contractor's option.

5.3.2.1 Caseliners, closure and gross weight.

5.3.2.1.1 Caseliners. Unless otherwise specified (see 6.2), level A shipping containers containing flasks preserved level C or commercial shall be provided with waterproof caseliners in accordance with MIL-STD-2073-1.

5.3.2.1.2 Closure. Container closure, reinforcing, or banding shall be in accordance with the applicable container specification or appendix thereto except that weather-resistant fiberboard boxes shall be closed in accordance with



Source: https://assist.dla.mil - Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

method V and reinforced with non-metallic or tape banding and domestic or fire-retardant fiberboard boxes shall be closed in accordance with method I using pressure sensitive tape.

5.3.2.1.3 Weight. Wood, plywood, and cleated type containers exceeding 200 pounds gross weight shall be modified by the addition of skids in accordance with MIL-STD-2073-1 and the applicable container specification or appendix thereto.

5.3.3 Commercial. Flasks preserved as specified (see 5.2), shall be packed for shipment in accordance with ASTM D 3951 and herein.

5.3.3.1 Container modification. Shipping containers exceeding 200 pounds gross weight shall be provided with a minimum of two, 3- by 4-inch nominal wood skids laid flat, or a skid- or sill-type base which will support the material and facilitate handling by mechanical handling equipment during shipment, stowage and storage.

5.4 Marking, levels A, B, C, and commercial. In addition to any special marking required (see 6.2), interior (unit) packs and shipping containers shall be marked including bar coding for shipment, stowage, and storage in accordance with MIL-STD-2073-1, appendix F.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. High pressure flasks covered by this specification are used for separating impurities from oxygen in submarine oxygen generator systems.

6.2 Acquisition requirements. Acquisition documents must specify the following:

(a) Title, number, and date of this specification.
(b) Issue of DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1 and 2.2).
(c) When fire-retardant material is required (see 5.1.1(a)).
(d) Level of preservation and level of packing required (see 5.2 and 5.3).
(e) Container selection and options, if other than the contractor's (see 5.2.2 and 5.3.2).
(f) When caseliners are not required (see 5.3.2.1.1).
(g) Special markings required (see 5.4).

6.3 Consideration of data requirements. The following data requirements should be considered when this specification is applied on a contract. The applicable Data Item Descriptions (DIDs) should be reviewed in conjunction with the specific acquisition to ensure that only essential data are requested/ provided and that the DIDs are tailored to reflect the requirements of the



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

specific acquisition. To ensure correct contractual application of the data requirements, a Contract Data Requirements List (DD Form 1423) must be prepared to obtain the data, except where DoD FAR Supplement 27.475-1 exempts the requirement for a DD Form 1423.

| Reference Paragraph | DID Number | DID Title | Suggested Tailoring |
|---|---|---|---|
| 4.4.3.2 and appendix | DI-MISC-80653 | Test reports | ---- |

The above DIDs were those cleared as of the date of this specification. The current issue of DOD 5010.12-L, Acquisition Management Systems and Data Requirements Control List (AMSDL), must be researched to ensure that only current, cleared DIDs are cited on the DD Form 1423.

6.4 Sub-contracted material and parts. The packaging or preparation for delivery requirements of referenced documents listed in section 2 do not apply when material and parts are acquired by the contractor for incorporation into the equipment and lose their separate identity when the equipment is shipped.

6.5 Cushioning and wrapping materials (see 5.1.1(c)). Materials having properties for resistance to fire and acceptable for use within unit packs and shipping containers for Navy acquisitions are:

| Material | Specification |
|---|---|
| Paper, kraft, treated (fire-resistant) | A-A-1894 |
| Paper, kraft, wrapping | UU-P-268, type II, grade C or D |
| Fiberboard | PPP-F-320, class - domestic/ fire-retardant |
| Plastic film, flexible, cellular | PPP-C-795, class 3 - fire-retardant |
| Polystyrene expanded, resilient | PPP-C-850, grade SE |
| Plastic, open cell, cushioning | PPP-C-1842, type I, style B |
| Bound fiber | PPP-C-1120, type III or IV, class C |
| Rubber, latex foam | MIL-R-5001, grade A |
| Rubber, cellular | MIL-R-6130, grade A |
| Fibrous glass | MIL-C-17435 |
| Polystyrene foam | MIL-P-19644, type II |
| Rubber, cellular, synthetic | MIL-R-20092, class 5 |
| Polyurethane foam | MIL-P-26514 |
| Polyurethane foam, flexible, open cell | MIL-F-81334 |
| Foam, combustion-retardant, for cushioning supply items aboard Navy ships | MIL-F-87090 |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

6.6 Subject term (key word) listing.

End plugs
Generator
Nickel-copper
Oxygen

6.7 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Preparing activity:
Navy - SH
(Project 8120-N429)



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.


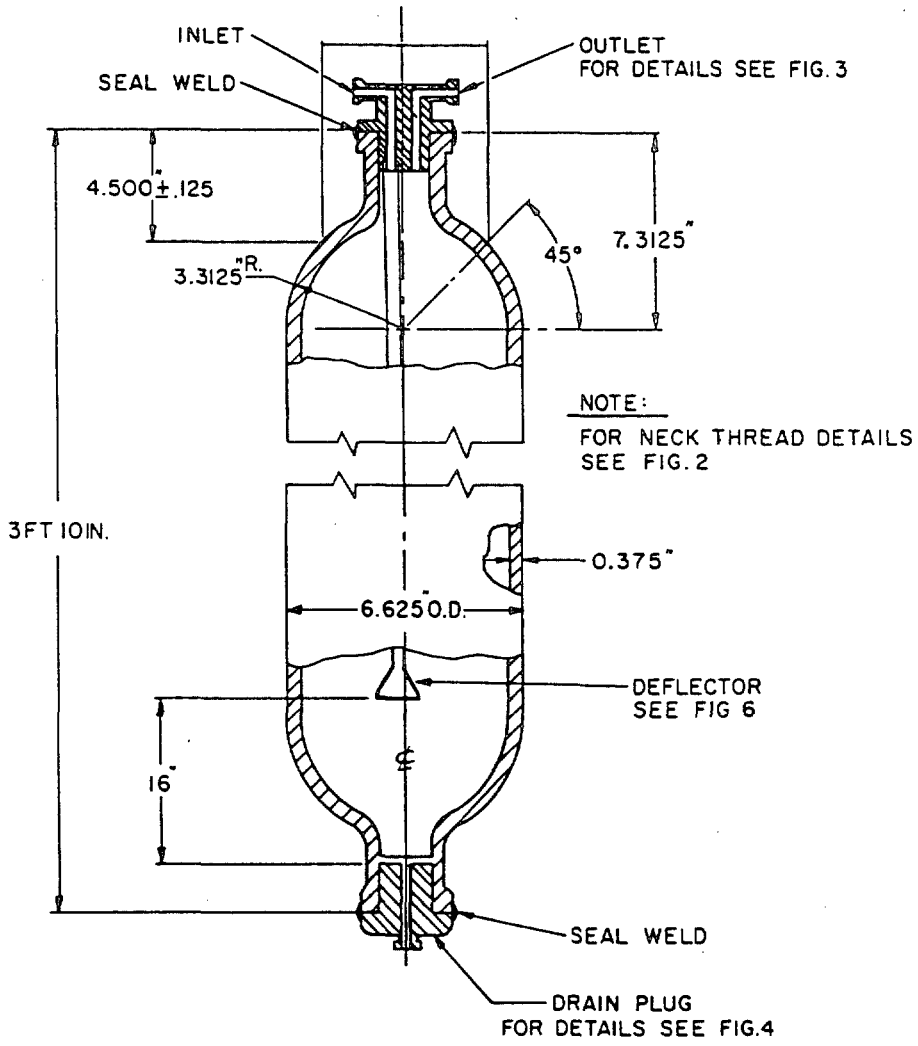



FIGURE 1. Flask assembly.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

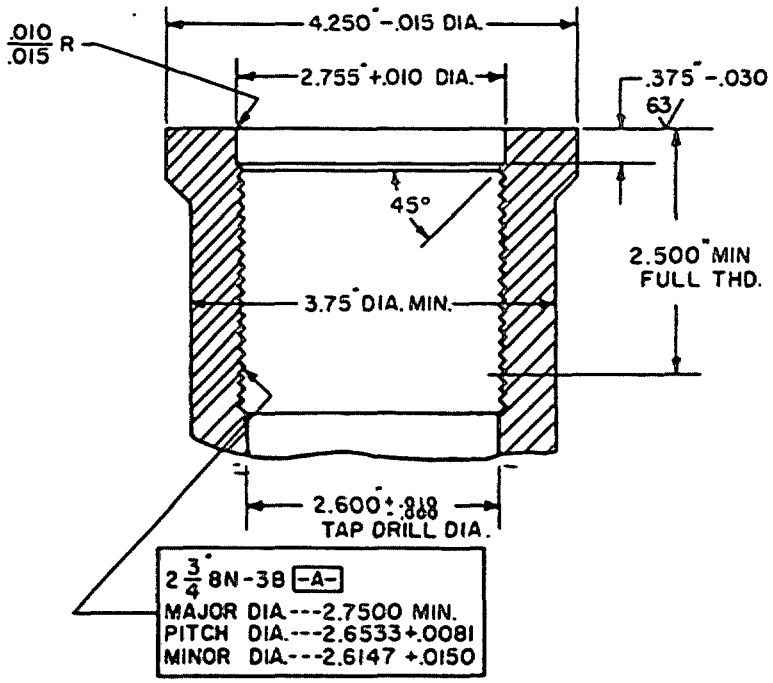


NOTE:

SURFACE -B- MUST BE PERPENDICULAR TO AXIS -A- WITHIN .006 T.I.R.

FIGURE 2. Neck thread details.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.


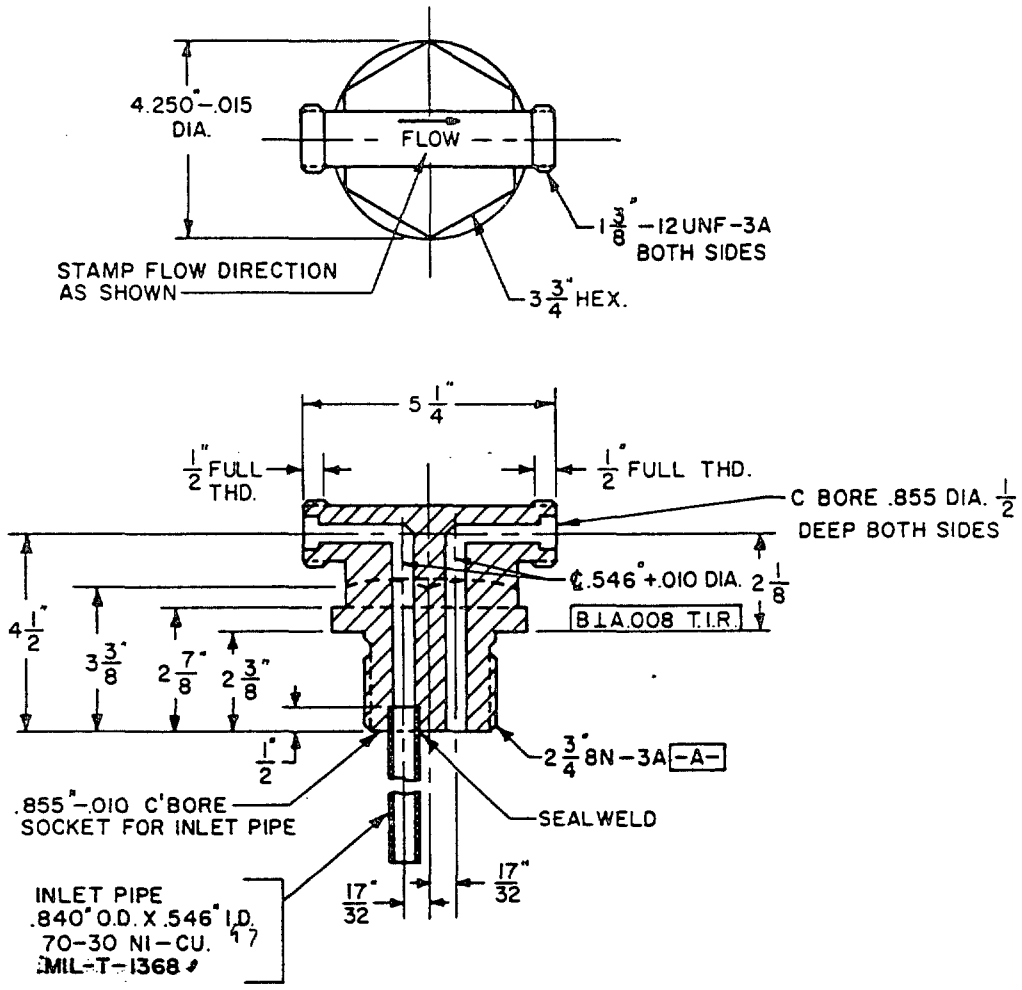



FIGURE 3. Inlet and outlet plug.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

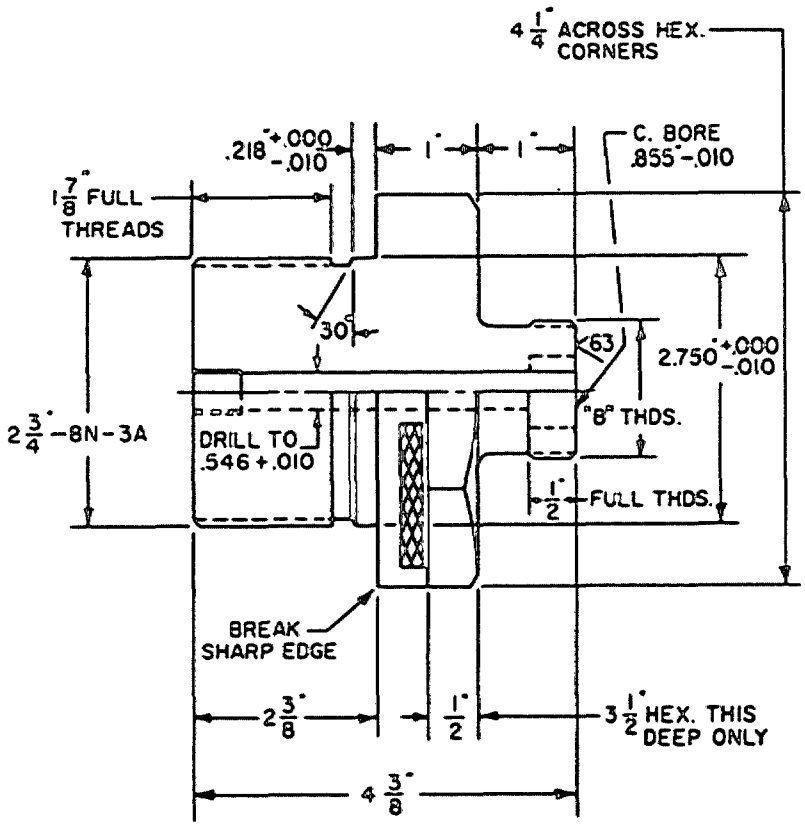


| PLUG TYPE | A | B | NOTE |
|---|---|---|---|
| DRAIN | | 1 3/8"-12 UNF-3A | AT BOTTOM OF FLASK |

FIGURE 4. Plugs for flask assembly.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

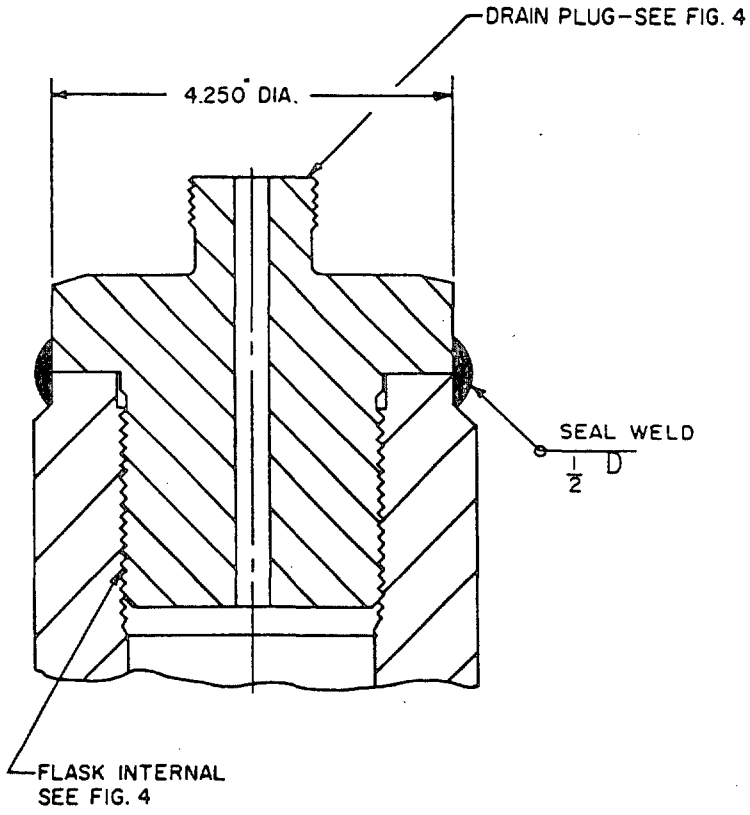



FIGURE 5. Typical plug assembly.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.


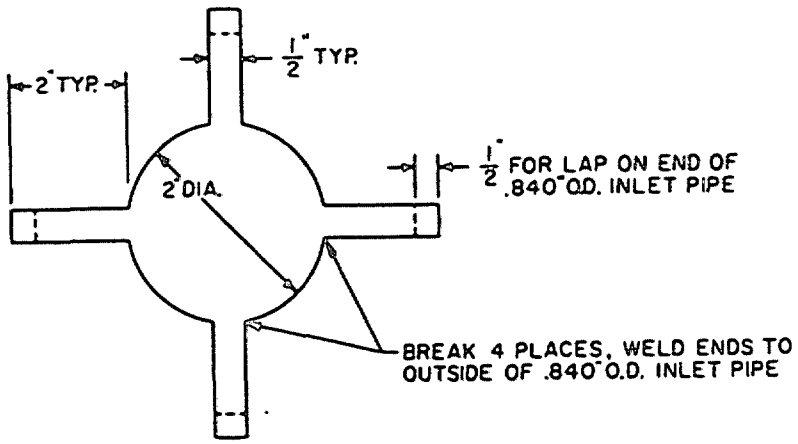



FIGURE 6. Deflector blank.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

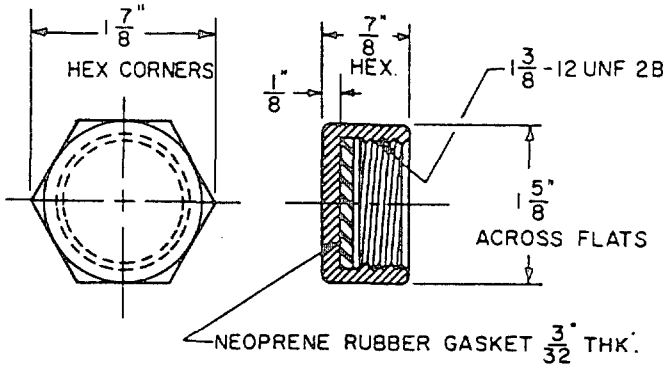


CAP FOR INLET & OUTLET PLUG FIG. 3 AND
DRAIN PLUG FIG. 4
MATERIAL- COMMERCIAL BRASS

FIGURE 7. Seal cap.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

# APPENDIX

## TEST REPORT TECHNICAL CONTENT REQUIREMENTS

10. SCOPE

10.1 Scope. This appendix covers the technical content requirements that shall be included in reports when required by the contract or order. This appendix is mandatory only when data item description DI-MISC-80653 is cited on the DD Form 1423.

20. APPLICABLE DOCUMENTS

This section is not applicable to this appendix.

30. REPORTS

30.1 Reports. When required by the contract or order, reports shall contain the following information:

(a) Ultrasonic indications over 25 percent of that produced by the calibration notch.
(b) Flasks having discontinuities producing a loss in back reflection between 50 percent and 100 percent that are greater than 3 inches in length, plus all other discontinuities producing a loss in back reflection greater than 25 percent.
(c) A sketch orientating all reportable discontinuities longitudinally or circumferentially as found, and indicating their severity and length.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.

# STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

*(See Instructions – Reverse Side)*

| 1. DOCUMENT NUMBER | 2. DOCUMENT TITLE |
|---|---|
| MIL-F-24032A(SH) | FLASK, SEPARATOR, 3000 PSI, K-MONEL |

| 3a. NAME OF SUBMITTING ORGANIZATION | 4. TYPE OF ORGANIZATION *(Mark one)* |
|---|---|
| | ☐ VENDOR |
| b. ADDRESS *(Street, City, State, ZIP Code)* | ☐ USER |
| | ☐ MANUFACTURER |
| | ☐ OTHER *(Specify)*: _____ |

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

| 7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional | b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional |
|---|---|
| c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional | 8. DATE OF SUBMISSION *(YYMMDD)* |

*(TO DETACH THIS FORM, CUT ALONG THIS LINE.)*

DD FORM 02 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil - Downloaded: 2026-10-19T18:46Z
Check the source to verify that this is the current version before use.