MIL-A-60091B (AR)
4 APRIL 1988
SUPERSEDING
MIL-A-60091A (AR)
11 Jun 1987

MILITARY SPECIFICATION

ADHESIVE FOR BONDING DEMOLITION CHARGES TO STRUCTURAL SURFACES

This specification is approved for use within the U.S. Army Armament, Munitions and Chemical Command, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers a one-part, ready to use adhesive, suitable for use in bonding demolition charges to dry, wet and underwater surfaces of all types of structural materials, under all weather conditions.

2.1 Government documents.

2.1.1 Specifications and standards. The following specifications and standards form a part of this specification to the extent specified herein. Unless otherwise specified the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation.

SPECIFICATIONS

MILITARY

MIL-A-48078 -	Ammunition, Standard Quality Assurance Provisions, General Specification for.
MIL-T-60394 -	Tape, Pressure-Sensitive Adhesive Film Foam Double-Coated (For use with Ammunition).

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, U.S. Army Armament, Munitions and Chemical Command, Attn. AMSMC-QA, Picatinny Arsenal, New Jersey 07806-5000 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 1375
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

STANDARDS

FEDERAL

FED-STD-141	-	Paint, Varnish, Lacquer, and Related Materials, Methods of Inspection, Sampling and Testing.

MILITARY

MIL-STD-105	-	Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	-	Marking for Shipment and Storage.
MIL-STD-286	-	Propellant, Solid, Sampling, Examination and Testing.
MIL-STD-1190	-	Minimum Guidelines for Level C Preservation, Packing and Marking.
MIL-STD-1218	-	ACS Chemicals

2.2 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein (except for associated detail specifications, specification sheets or MS standards), the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Qualification. Formulations furnished under this specification shall be products which are qualified for listing on the applicable qualified products list at the time set for opening of bids (see 4.2 and 6.3).

3.1.1 Requalification. Any changes in the formulation or processing of a qualified product will necessitate its requalification. Formulations supplied under contract shall be identical, within manufacuring tolerances, to the approved qualification sample. The qualifying activity may, at its discretion, request complete requalification testing or require only partial requalification in order to determine the significance, impact and acceptability of any proposed formulation change, manufacturing process, or change in manufacturing location.

3.2 Material. The adhesive shall be a one-part ethyl cyanoacrylate-type material compounded with proper stabilizers to meet the requirements of this specification. The manufacturer shall certify that the adhesive complies with this requirement.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

3.3 Color. The color of the adhesive shall be clear when tested as specified in 4.4.1.

3.4 Consistency. The consistency of the adhesive shall be such that it can readily be dispensed from its collapsible metal tube container by being squeezed by hand. The adhesive shall be smooth, clear, and free of lumps after both ambient and -40°F conditioning, when tested as specified in 4.4.2.

3.5 Set time. The set time shall be 10 seconds maximum when tested as specified in 4.4.3.

3.6 Viscosity. The visosity of the adhesive shall be as shown in table I when tested as specified in 4.4.4.

TABLE I. Viscosity.

Test Temperature	Viscosity (cp)
Ambient (25 ± 2°F)	1950 ± 200
-40° ± 2°F	1750 min.

3.7 Adhesive strength. The adhesive shall meet the requirements of 3.7.1, 3.7.2, and 3.7.3.

3.7.1 Strength at low temperature. The adhesive bond between the tape faced metal surface of the T-bar or equivalent apparatus (see 4.4.5) with a 1/8 pound weight attached, and the steel, cement building block, and plywood test panels shall not fail for a period of 24 hours at -40°F. Vertical and horizontal positions of the bond shall be tested separately. Compliance shall be determined in accordance with 4.4.5.

3.7.2 Strength on wet surfaces. The adhesive bond between the tape faced metal surface of the T-bar or equivalent apparatus (4.4.5) with a 1/8 pound weight attached, and the steel, cement building block, and plywood test panels shall not fail for a period of 24 hours. All test surfaces shall be wet. Vertical and horizontal positions of the bond shall be tested separately. Compliance shall be determined in accordance with 4.4.5.

3.7.3 Strength underwater. The adhesive bond between the tape faced metal surface of the T-bar or equivalent apparatus (4.4.5) with a 1/8 pound weight attached, and the steel, cement building block, and plywood test panels shall not fail for a period of 24 hours. All tests shall be performed underwater. Vertical and horizontal positions of the bond shall be tested separately. Compliance shall be determined in accordance with 4.4.5.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

3.8 Compatability with explosives. Adhesive compatability with explosives shall be determined in accordance with 4.4.6.

3.9 Storage stability. The adhesive shall meet the requirements of this specification after a storage period of at least 12 months provided that it has been stored in the original sealed collapsible tubes, original shipping containers and at temperatures not exceeding 70°F.

3.10 Workmanship. The manufacturer shall implement procedures and controls to assure that the process and the product produced are not compromised by foreign materials and contaminants or any other conditions which may degrade the composition. Determination of foreign materials shall be in accordance with 4.4.7.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of section 3 and 5. The inspections set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.2 Classification of inspection.

a. Qualification inspection

b. Quality conformance inspection

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

4.2.1 Qualification tests. Qualification inspection consist of tests for all of the requirements specified in Section 3.

4.2.1.1 Qualification samples. The qualification sample shall consist of tubes of the finished product and in addition, if the final formulation of the product contains solid materials, a one-half gallon sample shall be provided identical in nature to the final product but without the addition of any solids. Sample shall be furnished to the address indicated in 6.3.

4.2.1.2 Retention of qualification. In order to retain qualification of a product approved for listing on the Qualified Products List (QPL), the manufacturer shall be responsive to 4.2.2 and certify in writing, upon the request of the Qualifying activity, certification of product compliance to the requirements contained in this specification. Such certification shall be requested by the Qualifying activity at two year intervals effective from the date of original qualification. The Qualifying activity reserves the right to re-test any qualified product whenever it is deemed in the best interest of the Government to do so.

4.2.2 Periodic qualification re-evaluation. At the option of the Qualifying activity, a re-evaluation shall be performed on tubes sample of product drawn from the first lot, and each production lot thereafter, of product processed under current contract or purchase order. Periodic re-evaluation samples shall be forwarded to the activity responsible for Qualification. (See 6.3.) Samples shall be plainly identified by labels or tags marked with the following information:

Sample for periodic evaluation
Adhesive for bonding demolition charges to structural surfaces
MIL-A-60091B (AR)
Name of manufacturer
Product code number
Date of manufacture
Contract or order number
Lot number

4.2.2.1 Periodic qualification re-evaluation tests. The re-evaluation of products being manufactured under contract shall consist of those tests the qualifying activity determines necessary for product identity, verification, and evaluation. Delivery of a product per contract shall not be delayed pending completion of this test and inspection. The results obtained shall be considered indicative of product quality and production consistency. Failure of a product sample to pass a periodic qualification re-evaluation shall require the acceptance and further shipment of the product to

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

be discontinued until the manufacturer has corrected the conditions which led to the failure and has furnished data, documentation of affidavit to that effect. Further product failure or nonconformance shall constitute a basis for lot rejection and subsequent removal from the QPL.

4.3 Quality conformance inspection. Quality conformance inspection consists of tests for all requirements in section 3 with the exception of compatability with explosives (see 3.9) and storage stability (see 3.9). Inspection lots shall comply with the lot formation provisions of MIL-A-48078.

4.3.1 Examination and testing.

4.3.1.1 Sampling for chemical and physical testing. Representative samples shall be taken by random selection of five containers or boxes from each adhesive lot. Equivalent number of tubes shall be taken so that the aggregate quantity shall be sufficient for the required tests. These samples shall be placed into separate containers which shall be immediately closed and identified with a label indicating the container from which the samples were taken, lot number, nomenclature, and packing date. Prior to conducting lot acceptance tests, these samples shall be permitted to reach room temperature (70 $\pm$ 5°F). These tubes of adhesive shall be used for chemical and physical tests. If the sample fails to meet any of the requirements specified in section 3, the lot shall be rejected. Each required test shall be performed twice. The classification of defects shall be as given in table II.

TABLE II. Classification of defects

Examination/Test	Requirement	Classification
Color	3.3	Major
Consistency	3.4	Major
Set time	3.5	Major
Viscosity	3.6	Major
Adhesive strength	3.7	Major

4.4 Methods of inspection.

4.4.1 Color. The adhesive shall be squeezed from its tube onto a clean surface and visually examined for compliance with 3.3.

4.4.2 Consistency. Two unopened tubes of the adhesive are required for this test. One tube shall be placed at ambient (70 $\pm$ 2°F) conditions for 4 hours. The second tube shall be placed in a

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

low temperature chamber maintained at -40° ± 2°F for 4 hours. Both tubes shall then be removed from the conditioning, allowed to reach room temperature, and the adhesive contents of each squeezed out by hand onto clean, smooth glass surfaces. The adhesive should be spread by means of wooden tongue depressors and visually inspected.

4.4.3 Set time.

4.4.3.1 Apparatus.

a. 2 inch x 1/2 inch x 1/16 inch bright mild steel test plates
b. 5 Ml Centaur pipettes
c. Scotchbrite pad
d. Acetone
e. 1,1,1-Trichloroethane
f. Stopwatch
g. Double sided tape

4.4.3.2 Procedure.

a. Degrease the oily test pieces in 1,1,1-Trichloroethane and dry on a paper towel.

b. Rub the bonding surfaces lightly with scotchbrite to remove any discoloration. Rinse well with acetone and dry on a paper towel. Rinse for a second time in clean acetone and allow the solvent to evaporate (about 30 seconds) at room temperature. Place the test pieces in the humidity cabinet (50% RH) for 15-30 minutes prior to use.

c. Using a 5 µl Centaur pipette, place one drop of adhesive in the center of one of the test pieces and immediately cover with the other to form a T-shaped assembly. Start the stopwatch.

d. Hold the plates firmly with finger pressure, then attempt to break the bond manually by pulling in shear.

e. If the bond fails, repeat the test for further 5 second increments to determine the actual set time.

4.4.4 Viscosity. The viscosity of the adhesive shall be determined with a Cannon-Fenske modified Ostwald viscometere or equivalent in accordance with manufacturer's instructions. The appropriate calibrated constant based on test temperature shall be used to obtain viscosities in centipose.

4.4.5 Adhesive strength. This test is to be performed in conjunction with double-sided tape. (MIL-T-60394)

4.4.5.1 Apparatus and test panels.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

a. Apparatus. The apparatus to be used is shown in figure 1. The tape shall be affixed to the base of the T-bar, then the backing removed when ready for testing. The application of adhesive and bonding to the test panels shall be performed as described for each test condition given below.

b. Test panels. The test panels shall be as specified in table III. Each panel shall be prepared for use in adhesive strength determinations by first being weathered. Weathering shall be accomplished by submerging the test panel for 72 hours in water, then drying for 24 hours at 100°F in an oven or other temperature controlled chamber.


TABLE III. Strength test panels.

Panel material	Dimensions (inches) Width	Width	Thickness	No. Required
Steel-SAE 1020 cold rolled*1	4	4	.035	40
Plywood, fir, 3-ply exterior grade	4	4	1/4	40
Commercial cement building block*2	4	4	1	40

*1 These panels shall be cleaned in accordance with method 2011 of FED-STD-141.

*2 The cement block panels shall be cut or chiseled by suitable means from commercial cement building blocks used in the construction trade. Surfaces are to be reasonably uniform.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

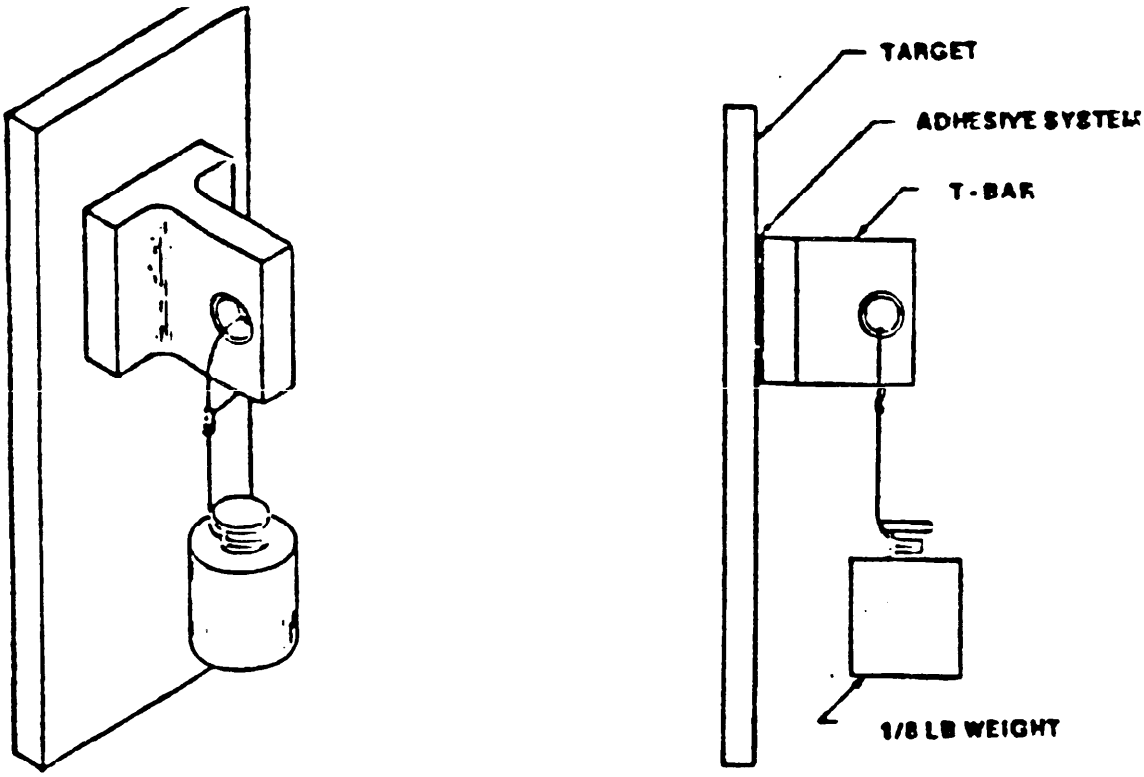

NOTE: The base of the T-bar has one inch square surface area with a 1/8 pound weight (or 60g of brass weights) attached to the T-bar.

Figure 1. T-bar test assembly.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

4.4.5.2 Adhesive strength at low temperature. Each of the test panels (10 of each material) is to be conditioned at -40°F for 4 hours. Any frost that may be present on the panels in the bond area shall be wiped away immediately prior to bonding with the T-bar assembly. The adhesive shall be applied to the tape after the tape backing on the T-bar assembly has been removed. The tape/adhesive surfaces are to be bonded to the panel area by pressing them together firmly for approximately 20 seconds. For each of the panel materials, five of the panels are to be bonded in the horizontal position (panels parallel to test chamber floor), and five are to be bonded in the vertical position (panels perpendicular to test chamber floor). Failure of any adhesive bond to adhere for 24 hours at -40°F shall be cause for rejection of the adhesive lot.

4.4.5.3 Adhesive strength on wet surfaces. Each of the test panels (10 of each material) is to be conditioned by presoaking in tap water for 2 hours. The adhesive is then applied to the tape (without backing), and without wiping, pressed to the test panel as in 4.5.5.2. Vertical and horizontal positions shall be set up as in 4.5.5.2, except that ambient temperatures (70 + 2°F) shall be maintained for 24 hours. Failure of any adhesive bond to adhere for 24 hours at this temperature shall be cause for rejection of the adhesive lot.

4.4.5.4 Adhesive strength underwater. Each of the test panels (10 of each material) is to be conditioned by presoaking in clean water having a sodium chloride content of 2.5 percent for 2 hours. The adhesive is then applied to the tape, without backing, while the assemblies are immersed. There should be a head of water of at least 2 inches. Vertical and horizontal positions shall be set up as in 4.5.5.2, except that the temperature shall be maintained at 70° ± 2°F for 24 hours. The bonds are to be established under water. Failure of any adhesive to adhere for 24 hours under water shall be cause for rejection of the adhesive lot.

4.4.6 Compatability with explosives. Compatability shall be determined in accordance with method 408.1 of MIL-STD-286.

4.4.7 Workmanship. Visually examine the sample for contamination by foreign matter.

5. PACKAGING

5.1 Packaging.

5.1.1 Level A. Not applicable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

5.1.2 Level C. Unless otherwise specified, the adhesive shall be packaged in 3 gram aluminum tubes. All containers shall be packaged in individual, multiple folding, or setup cartons. Each carton shall be closed and sealed to prevent accidental opening.

5.2 Packing. Unless otherwise specified in the contract or purchase order, packing shall be in accordance with MIL-STD-1190. The intermediate pack quantity shall not exceed 150 cartons.

5.3. Marking. Each tube of adhesive shall bear a label warning against contact with skin and to flush with water in case of body contact. Shelf life and other required markings shall be in accordance with MIL-STD-129.

6. NOTES

6.1 Intended use. The item covered by this specification is intended for use in bonding demolition charges to structures.

6.2 Ordering data. See MIL-A-48078.

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are at the time set for opening of bids, qualified for inclusion in the applicable QPL whether or not such products have actually been so listed by that date. The attention of the suppliers is called to this requirement, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. The activity responsible for the QPL is US Army Armament, Munitions and Chemical Command, ATTN: SMCAR-ESC-S, Picatinny Arsenal, NJ 07806-5000

6.4 Contract data requirements. In addition to the normal distribution of records when the adhesive is procured by the Department of the Army, one copy of all test data shall be forwarded to Commander, US Army Armament Research Development and Engineering Center (ARDEC), ATTN: AMSMC-QAR-R(D), and one copy to ATTN: SMCAR-AEE-BP, Picatinny Arsenal, NJ 07806-5000.

6.5 Equivalent test methods. The test methods given in this specification are the official methods to be used. The contractor may request using other methods providing that the proposed method is equivalent in accuracy and precision to the method given in this specification. Prior approval of the Contracting Officer is required for use of equivalent test methods. A description of the

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

proposed method should be submitted through the Contracting Officer to: ARDEC, ATTN: AMSMC-QAR-R(D), Picatinny Arsenal, NJ 07806-5000. This description should include, but not be limited to, the procedures used, the accuracy and precision of the method, and test data to demonstrate the accuracy and precision, and drawings of any special equipment required.

6.6 Subject term (key word) listing.

Adhesive
Supplemental adhesive
Demolition charges

6.7 Changes from previous issue. Asterisks are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Custodian:
Army-AR

Preparing activity:
Army-AR

(Project 1375-A393)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

COMMANDER
US ARMY ARDEC
ATTN: AMSMC-QA
PICATINNY ARSENAL, NJ 07806-5000

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-A-60091B	ADHESIVES FOR BONDING DEMOLITION CHARGES TO STRUCTURAL SURFACES

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR ☐ USER ☐ MANUFACTURER ☐ OTHER *(Specify)*: _____
b. ADDRESS *(Street, City, State, ZIP Code)*	

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T00:08Z
Check the source to verify that this is the current version before use.