MIL-P-13607B(PA)
16 December 1975
SUPERSEDING
MIL-P-13607A(MU)
31 May 1970

MILITARY SPECIFICATION

PADDING MATERIALS, RESILIENT (FOR PACKAGING OF AMMUNITION)

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope.- This specification covers resilient padding materials for military packaging and packing applications inside of water-resistant ammunition containers (see 6.1 and 6.2).

1.2 Classification. - The padding materials shall be of the following types, as specified (see 6.3):

Type I - Flexible.
Type II - Non-flexible.

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposals, form a part of this specification to the extent specified herein.

SPECIFICATIONS

FEDERAL

P-D-680 - Dry Cleaning Solvent
QQ-A-591 - Aluminum Alloy Die Castings
QQ-Z-363 - Zinc - Base Alloy; Die Castings
TT-E-516 - Enamel, Lusterless, Quick-Drying Styrenated Alkyd Type
MMM-A-250 - Adhesive, Water-Resistant (For Closure of Fiberboard Boxes)
MMM-A-260 - Adhesive, Water-Resistant (For Sealing Waterproofed Paper)
PPP-B-601 - Boxes, Wood, Cleated-Plywood
PPP-B-636 - Boxes, Shipping, Fiberboard
PPP-B-1055- Barrier Material, Waterproofed, Flexible

MILITARY

MIL-C-50 - Copper Alloy Numbers 260 (Cartridge Brass, 70 Percent); Steel, Strip, Plate, Bar and Discs

FSC: 8140

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

MIL-B-117 - Bags, Sleeves and Tubing - Interior Packaging
MIL-B-121 - Barrier Material, Greaseproofed, Waterproofed, Flexible
MIL-V-12276 - Varnish, Phenolic, Baking
MIL-B-22191 - Barrier Materials, Transparent, Flexible, Heat Sealable
MIL-A-48078 - Ammunition, Standard Quality Assurance Provisions, General Specification For

STANDARDS

MILITARY

MIL-STD-129 - Marking for Shipment and Storage

FEDERAL

FED-STD-101 - Preservation, Packaging, and Packing Materials: Test Procedures

(Copies of specifications, standards, drawing and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer).

2.2 Other publications. - The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids shall apply.

AMERICAN SOCIETY FOR TESTING AND MATERIALS PUBLICATIONS

ASTM-A109 - Steel, Carbon, Cold-Rolled Strip, Specification for
ASTM-D461 - Felt, Standard Methods of Testing

(Applications for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pennsylvania, 19103).

3. REQUIREMENTS

3.1 Material. - The padding material shall be made from such materials and by such processes as to insure compliance with this specification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

3.2 Form. - The padding material shall be furnished in flat sheets, rolls or cut sizes as specified by the procuring activity (see 6.3).

3.3 Flexibility (Type I only). - The Type I padding material shall withstand a 180 degrees (°) bend without cracking or delaminating when tested as specified in 4.5.2.

3.4 Dimensional Measurements (See 6.3)

3.4.1 Rolls and Sheets. - The width and length of rolls and sheets shall be as specified in the contract or order. A tolerance of plus or minus 1/4 inch shall be permitted on the width of rolls or sheets. The length of any individual roll shall be not less than 95 percent of the specified length. A tolerance of ± 2 1/2 percent or plus or minus 1/2 inch, whichever is less, shall be permitted on the length of sheets.

3.4.2 Cut sizes. - The dimensions of cut sizes and special shapes shall be as specified in the contract or order. Tolerances shall be specified by the ordering activity.

3.4.3 Thickness. - Thickness of the padding material shall be as specified in the contract or order. The thickness tolerance shall be as indicated in Table I, when determined as specified in 4.5.3.

TABLE I

THICKNESS OF PADDING MATERIALS

Nominal Thickness (Inch)	Tolerance (Inch)
.063	± .006
.125	± .013
.188	± .019
.250	± .025
.313	± .031
.375	± .038
.500	± .050

3.5 Specified size. - Dimensions shall conform to the specified sizes given.

3.6 Tensile breaking strength. - The padding material shall have an average breaking strength of 10 pounds minimum (min.) when tested as specified in 4.5.4.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

3.7 Adhesion to steel surfaces. - The padding material shall not adhere nor transfer any softened material to steel surfaces when tested as specified in 4.5.5.

3.8 Compression and springback.

3.8.1 Dynamic load (70° Fahrenheit (F)). - The average load required to compress the padding material 25 percent shall be 5.5 plus or minus (±) 2.0 pounds per square inch (psi). The average load required to compress the material 50 percent shall be 58 ± 19 psi, and upon removal of the load, the material shall return to an average of not less than 89 percent of its original height, when tested as specified in 4.5.6.1.

3.8.2 Static load

3.8.2.1 Room temperature (70°F). - The padding material shall have an average minimum springback of not less than 90 percent, when tested as specified in 4.5.6.2.1.

3.8.2.2 Temperature extremes. - The average percentage of compression at minus (-) 65°F and at 160°F shall not differ from each other by more than one-half of the average percentage of compression obtained at 70°F. The material shall have an average minimum springback of not less than 85 percent at either temperature, when tested as specified in 4.5.6.2.2 and 4.5.6.2.3.

3.9 Dustiness. - The padding material shall have a maximum average weight loss of 0.05 percent due to dusting, when tested as specified in 4.5.7.

3.10 Hydrogen-ion concentration (pH). - The padding material shall have an average pH value of 7.0 ± 1.0, when tested as specified in 4.5.8.

3.11 Corrosion and compatibility with various metals, enamel, and varnish. - The padding material shall not tarnish or corrode brass, steel, aluminum and zinc, and shall be compatible with enamel and with phenolic varnish when tested as specified in 4.5.9. A slight even stain on the uncoated test panels, which is the same size as the padding material specimer shall not be considered defective.

3.12 Workmanship. - The padding material shall be manufactured in such a manner as to provide uniform construction, free from defects that would impair its usefulness. The finished material shall not be tacky, nor stick together to an extent that will cause tearing or injury to the surface when unrolled or when the sheets are separated. It shall be free of trimmings, foreign material or loose fibers.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

3.13 First Article Inspection. - This specification makes provisions for first article inspection. Requirements for the submission of first article samples by the contractor shall be as specified in the contract.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for Inspection and Standard Quality Assurance Provisions. - Unless otherwise specified herein or in the contract, the provisions of MIL-A-48078 shall apply and are hereby made a part of this detail specification.

4.2 Classification of Inspections. - The following types of inspection shall be conducted on this item.

a. First Article Inspection (see 4.3)
b. Quality Conformance Inspection (see 4.4)

4.3 First Article Inspection

4.3.1 Submission. - The contractor shall submit a first article sample as designated by the Contracting Officer for evaluation in accordance with provisions of 4.3.2. The first article sample shall consist of five (5) samples which have been selected from consecutively produced rolls or sheets. Each sample shall consist of five (5) square yards of material.

4.3.2 Inspections to be Performed. - See MIL-A-48078 and Table II specified herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

TABLE II - FIRST ARTICLE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE: Padding Material		SHEET 1 OF 1		DRAWING NUMBER: as applicable
					NEXT HIGHER ASSEMBLY
CATEGORY	EXAMINATION OR TEST	NO OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
	Flexibility	5	-	3.3	4.5.2
	Thickness	5	-	3.4.3	4.5.3
	Tensile Breaking Strength	5	-	3.6	4.5.4
	Adhesion to Steel Surface	5	-	3.7	4.5.5
	Compression and Springback			3.8	
	Dynamic Load (70°F)	5	-	3.8.1	4.5.6.1
	Static Load (70°F)	5	-	3.8.2.1	4.5.6.2.1
	Static Load (-65°F)	5	-	3.8.2.2	4.5.6.2.2
	Static Load (+160°F)	5	-	3.8.2.2	4.5.6.2.3
	Dustiness	5	-	3.9	4.5.7
	Hydrogen-ion Concentration	5	-	3.10	4.5.8
	Corrosion and Compatibility, with Various Metals, Enamel and Varnish	5	-	3.11	4.5.9
	Workmanship (Other than material sticky or tacky)	5	-	3.12	4.4.2.1
	Material sticky or tacky	5	-	3.12	4.4.2.1

NOTES

SARPA QA FORM 2567 FEB 74

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

4.3.3 Rejection. - See MIL-A-48078

4.4 Quality Conformance Inspection

4.4.1 Inspection Lot Formation. - Inspection lots shall comply with the lot formation provisions of MIL-A-48078.

4.4.2 Examination. - Unless otherwise specified in the Classification of Defects and Test tables, sampling plans for major and minor defects shall be in accordance with MIL-STD-105, Inspection Level II (see MIL-A-48078).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE		SHEET 1 OF 1		DRAWING NUMBER
4.4.2.4	Padding Material Rolls and Sheets				as applicable
					NEXT HIGHER ASSEMBLY
CATEGORY	EXAMINATION OR TEST	NO OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
Critical	None defined				
Major B					
131	Width		0.40%	3.4.1	Scale
132	Length		0.40%	3.4.1	Scale
133	Dimension of cut sizes		0.40%	3.4.2	Scale
134	Material sticky or tacky		0.40%	3.12	Visual/Manual
Minor					
201	Evidence of poor workmanship (Other than material sticky or tacky)		0.65%	3.12	Visual

NOTES

SARPA DA FORM 2567 FEB 74

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

4.4.3 Testing

4.4.3.1 Sampling. - Five (5) samples of padding material shall be taken at random from each lot for inspections and tests. The size of each sample shall be sufficient to provide specimens for individual determinations in the tests specified herein.

4.4.3.2 Flexibility (Type I only) (see 3.1). - Major B defect - Six 4X12 inch specimens (three from each principal direction) shall be cut from each of the samples. After conditioning (see 4.5.1), the specimens shall be tested as specified in 4.5.2. If any specimen exhibits evidence of cracking or delamination, it shall be cause for rejection of the lot.

4.4.3.3 Thickness (see 3.4.3) - Minor defect - From each sample, an assembly shall be prepared and tested as specified in 4.5.3. If the average thickness of any assembly fails to comply with the requirement, the lot shall be rejected.

4.4.3.4 Dynamic Load (70°F) (see 3.8.1) - Major B defect- From each sample, an assembly shall be prepared and tested as specified in 4.5.6.1. If any assembly fails to meet the applicable requirements, the lot shall be rejected.

4.4.3.5 Hydrogen-ion concentration (pH). (see 3.10) - Major B defect - Specimens, from each sample, shall be prepared and tested as specified in 4.5.8. If the average value of the specimens, for any sample, fails to meet the applicable requirement the lot shall be rejected.

4.4.3.6 Resubmission. - Padding material which has been rejected for failure to comply with the requirements of this specification may be reworked or replaced to correct the defects, and the lot resubmitted for acceptance. However, prior to resubmission, full particulars concerning previous rejection and the action taken to correct the defects found in the original lot shall be furnished the inspector. Upon resubmission, samples selected in accordance with 4.4.3.1 shall be subjected to all the tests specified in 4.4.3.
Material rejection after retest shall not be resubmitted without specific approval of the procuring agency.

4.4.4 Inspection Equipment. - The inspection equipment required to perform the inspections prescribed in this specification is identified in the Examination (4.4.2) and the Test Methods (4.5) paragraphs herein. The contractor shall submit for approval inspection equipment designs in accordance with the terms of the contract. See Section 6 of MIL-A-48078 and 6.4 herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

4.5 Test Methods and Procedures (see 6.5).

4.5.1 Conditioning of Test Specimens. - The individual specimens and the assemblies of specimens required for the tests specified herein shall be conditioned at a temperature of 70°F ± 2°F (21.1°Centigrade (C) ± 1.1°C) and 65 percent ± 2 percent humidity for a minimum of 24 hours prior to conducting the tests.

4.5.2 Flexibility (Type I). - Each test specimen, after conditioning, shall be folded by hand, perpendicular to the long dimension 180° back on itself, then straightened out, and folded on the same axis 180° in the reverse direction. The edges parallel to the width shall touch when folded but the specimen shall not be creased at the fold. Observations shall be made for evidence of cracking or delamination.

4.5.3 Thickness. - Prepare an assembly from each of the samples of padding material in such a manner that each assembly be comprised of 4X4 inch specimens stacked to approximately 1 inch in height. After conditioning, as specified in 4.5.1, place each assembly between the parallel plates of the test apparatus shown on Figure 1, or in a similar apparatus complying with the functional requirements. The total weight of the top plate shall be 6.0 ± 0.1 pounds. Gently lower the top plate over the top layer of the test assembly. Take measurements at the four corners, between the parallel plates, to the nearest thousandth of an inch. Record the average of the four measurements as the total thickness. Divide the total thickness by the number of layers of padding material in the assembly to determine the average thickness of the material.

4.5.4 Tensile Breaking Strength - Determine the breaking strength in accordance with ASTM D461.

4.5.5 Adhesion to Steel Surfaces. - Prepare one specimen, 2 inches square, for each sample. Place each specimen between two 3 by 3 inch polished steel plates made of cold-rolled steel conforming to ASTM-A109. Evenly place a weight of 9.2 ± 0.1 pounds, including the weight of the top plate, in each specimen. Heat the entire assembly for 4 hours in an oven maintained at 160°F ± 2°F. At the end of the heating period, remove the specimens from the oven and, allow to cool. Make an examination for evidence of adhesion or transference of softened material to the plates.

4.5.6 Compression and Springback

4.5.6.1 Dynamic Load (70°F). - Prepare an assembly from each of the samples of padding material in such a way that each assembly shall be composed of 4X4 inch specimens stacked to approximately 1 inch by height. Condition the assemblies as specified in 4.5.1. Place a square steel plate,

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

larger than the 4 by 4 inch assembly and weighing 1.0 ± 0.1 pound on the assembly. Measure the assembly at the four corners, to the nearest thousandth of an inch, and record the average of the four measurements as the original height. Place the assemblies, including the top 1-pound weight, between two parallel plates (slightly larger than the assembly itself) of a compression machine capable of applying a compression load in the range of 0 to 3000 pounds. The rate of compression load application of the machine shall be 0.5 inch per minute. Compress the padding material 25 percent, and then 50 percent, and record the load necessary to deflect the material at each height. It is recommended that a commercial Deflectometer, or other suitable device, be used as an attachment to the compression machine to automatically record the deflection to one-thousandth of an inch. Immediately remove the load at the completion of the 50 percent compression, and measure the springback 2 minutes after complete release of the load without removing the 1-pound weight. Measure the springback at the four corners and take the average of the four measurements as the springback height. Determine the average load for 25 percent compression, the average load for 50 percent compression and the average springback of the assemblies. Calculate the minimum and maximum values for the 25 percent compression, 50 percent compression and the average springback of the assemblies as follows:

Minimum value shall be $\geq \bar{x} - 3s$

Maximum value shall be $\leq \bar{x} + 3s$

Where:

$\bar{x}$ = average of the assemblies

s = standard deviation (see 6.6)

Accepted minimum and maximum values are given in 3.8.1.

4.5.6.2 Static Load (room and extreme temperatures)

4.5.6.2.1 Test at Room Temperature (70°F). - Prepare an assembly from each of the samples of padding material in such a manner that each assembly shall be composed of 4 by 4 inch specimens stacked to approximately 1 inch in height. Condition the assemblies as specified in 4.5.1 and then place them in the test apparatus shown in Figure 1 or in a similar apparatus complying with the functional requirements. The total weight of the top plate shall be 4.0 ± 0.1 pounds. Gently lower the top plate assembly over the top layer of the padding material. Measure, to the nearest thousandth of an inch, between the parallel plate at each of the four corners of the padding material assembly. The average of these four measurements shall be taken as the original height. Condition the test apparatus, includ-

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

ing padding material with weight added, for one hour at room temperature (70° to 80°F). At the end of the conditioning period, gently add an additional 100 ± 1 pound weight to the top plate assembly. Take measurements, to the nearest thousandth of an inch, between the parallel plates at each of the four corners of the padding material assembly. Calculate the average of these four measurements as the compression height. The percent compression shall be calculated as follows:

$$\text{Percent compression} = 100 \times \frac{(\text{Original height} - \text{Compression height})}{\text{Original height}}$$

Remove the 100 pound weight and after 2 minutes, take measurements between the parallel plates at the four corners. Then, take the average of the four measurements to determine the springback height. Calculate the percent springback as follows:

$$\text{Percent springback} = 100 \times \frac{\text{Springback height}}{\text{Original height}}$$

Calculate the average percent springback of the assemblies tested. Then, calculate the minimum value for the springback assemblies as follows:

Minimum springback shall be $\geq \bar{x} - 3s$

Where:

$\bar{x}$ = average of the assemblies

s = standard deviation (see 6.6)

The accepted minimum value is given in 3.8.2.1.

4.5.6.2.2 Test at minus 65°F - Prepare an assembly from each of the samples as described in 4.5.6.2.1. Prior to testing, condition the assemblies for one hour at minus 65°F + 2°F. After conditioning, subject the assemblies, at minus 65°F + 2°F, to the same compression and springback tests as described in 4.5.6.2.1. Calculate the percent compression and percent springback, and the average percent compression and average percent springback of the assemblies. Then, calculate the minimum value for the springback as follows:

Minimum springback shall be $\geq \bar{x} - 3s$

Where:

$\bar{x}$ = average of the assemblies

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

s = standard deviation (see 6.6)

The accepted minimum value is given in 3.8.2.2.

4.5.6.2.3 Test at 160°F. - Prepare an assembly from each of the samples as described in 4.5.6.2.1. Prior to testing, condition the assemblies for one hour at 160° + 2°F. After conditioning, subject the assemblies, at 160° ∓ 2°F, to the same compression and springback tests as described in 4.5.6.2.1. Calculate the percent compression and percent springback, and the average percent compression and average percent springback of the assemblies. Then, calculate the minimum value for the springback as follows:

Minimum springback shall be $\geq \bar{x} - 3s$

Where:

$\bar{x}$ = average of the assemblies

s = standard deviation (see 6.6)

The accepted minimum value is given in 3.8.2.2.

4.5.7 Dustiness. - The dustiness of the material shall be determined in accordance with FED-STD-101, Method 4011, Procedure A. Determine the average loss in weight of the samples. Calculate the maximum value for the weight loss as follows:

Maximum weight loss shall be $\leq \bar{x} + 3s$

Where:

$\bar{x}$ = average of the samples
s = standard deviation (see 6.6)

The accepted maximum value is given in 3.9.

4.5.8 Hydrogen-ion Concentration (pH). - The pH value shall be determined in accordance with ASTM-D461.

4.5.9 Corrosion and Compatibility with Various Metals, Enamels and Varnish. - For each sample, the following procedure shall be followed:

Cut twenty-seven (27) 3 by 3 inch panels from cold-rolled steel conforming to ASTM-A109, and three each from aluminum, zinc and brass sheets conforming to QQ-A-591, QQ-Z-363 and MIL-C-50 respectively. Polish all panels with 280 grit silicon carbide abrasive paper, wash them with dry cleaning solvent

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

conforming to Type I of P-D 680, wipe with alcohol and allow them to dry. Uniformly coat three of the steel panels with a .001 to .003 inch film of enamel conforming to TT-E-516, and allow to dry for 24 hours. Uniformly coat another three of the steel panels with a .004 to .005 inch film of phenolic varnish conforming to Type I of MIL-V-12276, and allow to bake dry in accordance with the instructions of the varnish manufacturer. Cut eighteen (18) 2 X 2 inch specimens of padding material, at random, from the sample and condition them as specified in 4.5.1. After conditioning, place each of the 18 specimens of padding material on an uncoated steel panel. Center the remaining test panels with their polished or coated sides down, on top of the padding material so as to form sandwich-like assemblies. (The total of 18 assemblies shall consist of three each, steel, brass, zinc, aluminum, enamel, and phenolic varnish test panels). Place a 10-pound weight on top of each assembly, and condition the assemblies with weights for 168 hours at 160° + 2°F. At the end of the conditioning period, remove the test assemblies from the oven and allow them to cool. Examine the assemblies for signs of corrosion, (such as pitting or etching) under a magnification of 20 diameters, for evidence of tarnishing such as dark brown, bluish, or black discoloration on the uncoated panels, and for evidence of non-compatibity with the enamel or varnish such as softening, or tackiness of either the coating or the sample on the coated panels.

5. PREPARATION FOR DELIVERY

5.1 Packaging

5.1.1 Level A

5.1.1.1 Rolls. - Padding material of one thickness, in the length and width specified by the procuring agency (see 6.3) shall be evenly rolled, and each roll secured to prevent unraveling. Each roll shall be wrapped, bagged or inserted into a sleeve or tube. Wrapping material shall conform to PPP-B-1055, Class C-1 or C-2 (a), MIL-P-121, Type I or II, Grade A, Class 1, or MIL-B-22191 Type III. Bags, sleeves or tubes shall conform to MIL-B-117, Type I, Class C requirements. Barrier wraps, bags or sleeves shall have all seams and openings sealed by application of MIL-A-260 adhesive to non-heat sealable material. Heat sealable materials shall have all seams and openings sealed by heat sealing.

5.1.1.2 Flat Sheets. - Padding material of uniform thickness and size in quantities not exceeding 40 pounds, shall be evenly wrapped, bagged or inserted in a bag or sleeve as described in 5.1.1.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

5.1.1.3 Cut sizes. - Padding material cut to specific size and configuration shall be wrapped in barrier material conforming to PPP-B-1055 Class C-1 or C-2 (a) or placed in fiber boxes conforming to PPP-B-636 V3c or V3s. Net weight of wrapper or boxed material shall not exceed 40 pounds. All seams, joints, and closures of the wrap shall be sealed with MMM-A-260 adhesive. Top and bottom flaps of the box shall be sealed by application of MMM-A-250 adhesive over 50 percent or more of the surface area of contact.

5.1.2 Level C. - Padding material shall be packaged in a manner which will insure protection against damage or deterioration of the material during transit.

5.2 Packing

5.2.1 Level A. - Padding material of like size, shape and thickness, packaged as specified, shall be packed in plywood boxes conforming to PPP-B-601, overseas type, Style A or B. Boxes shall be closed and strapped in accordance with requirements contained in the appendix of the box specification. Gross weight of exterior containers shall not exceed 150 pounds.

5.2.2 Level C. - Packaged material shall be packed in a manner conforming to carrier regulations and which will provide adequate protection to the contents from the supply source to the first receiving activity.

5.3 Marking. - Unit and exterior containers shall be marked in accordance with the requirements of MIL-STD-129.

6. NOTES

6.1 Intended Use. - Resilient padding material is intended for fabrication into circular or square pads to furnish tolerance take-up, where required, inside of water resistant ammunition containers to provide tight packing of the ammunition.

6.2 This specification was prepared to increase supply sources for pads (cushioning media) used in packaging ammunition. Previously, these pads were specified by materials, for example:

Wool Felt (Wool and Cotton Blend) - Classification SR5 - Spec C-F-206 (Formerly identified as Item 27, Spec MIL-F-10954).
Wool Felt (Wool and Cotton Blend) - Classification 12R3 - Spec C-F-206 (Formerly identified as Item 10 and 10 1/2, Spec MIL-D-10954).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

Hair Felt - Type IV, Class 2 (Thicknesses of 1/4 inch or greater) - Spec C-F-202 (Thicknesses under 1/4 inch do not possess required tensile strength).

6.3 Ordering Data. - See MIL-A-48078. Procurement documents should also specify:

a. Type required (see 1.2).
b. Whether flat sheets, rolls or cut size are to be furnished (see 3.2).
c. Dimensions of rolls, flat sheets or cut sizes (see 3.4).
d. Level of packaging and packing required (see 5.1 and 5.2).

6.4 Submission of Inspection Equipment Designs for Approval. - See MIL-A-48078. Submit equipment designs, as required, to Commander, Picatinny Arsenal, ATTN: SAPPA-QA-T, Dover, New Jersey 07801.

6.5 Prior approval of the Contracting Officer is required for use of equivalent test methods. A description of the proposed method should be submitted through the Contracting Officer to: Commander, Picatinny Arsenal, ATTN: SARPA-QA-A-P, Dover, New Jersey 07801. This description should include but not be limited to the procedures used, the accuracy and precision of the method, test data to demostrate the accuracy and precision and drawings of any special equipment required.

6.6 Standard deviation. - The standard deviation is calculated as follows:

$$S = \sqrt{\frac{\Sigma (X - \bar{X})^2}{n - 1}}$$

Where:


S = Standard deviation.
Σ = "Sum of"
X = Observed values.
$\bar{X}$ = Arithmetic mean (weighted average of the samples).
n = Number of observations.

Custodian
Army-PA

Preparing Activity:
Army-PA

Project Number: 8140 -

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

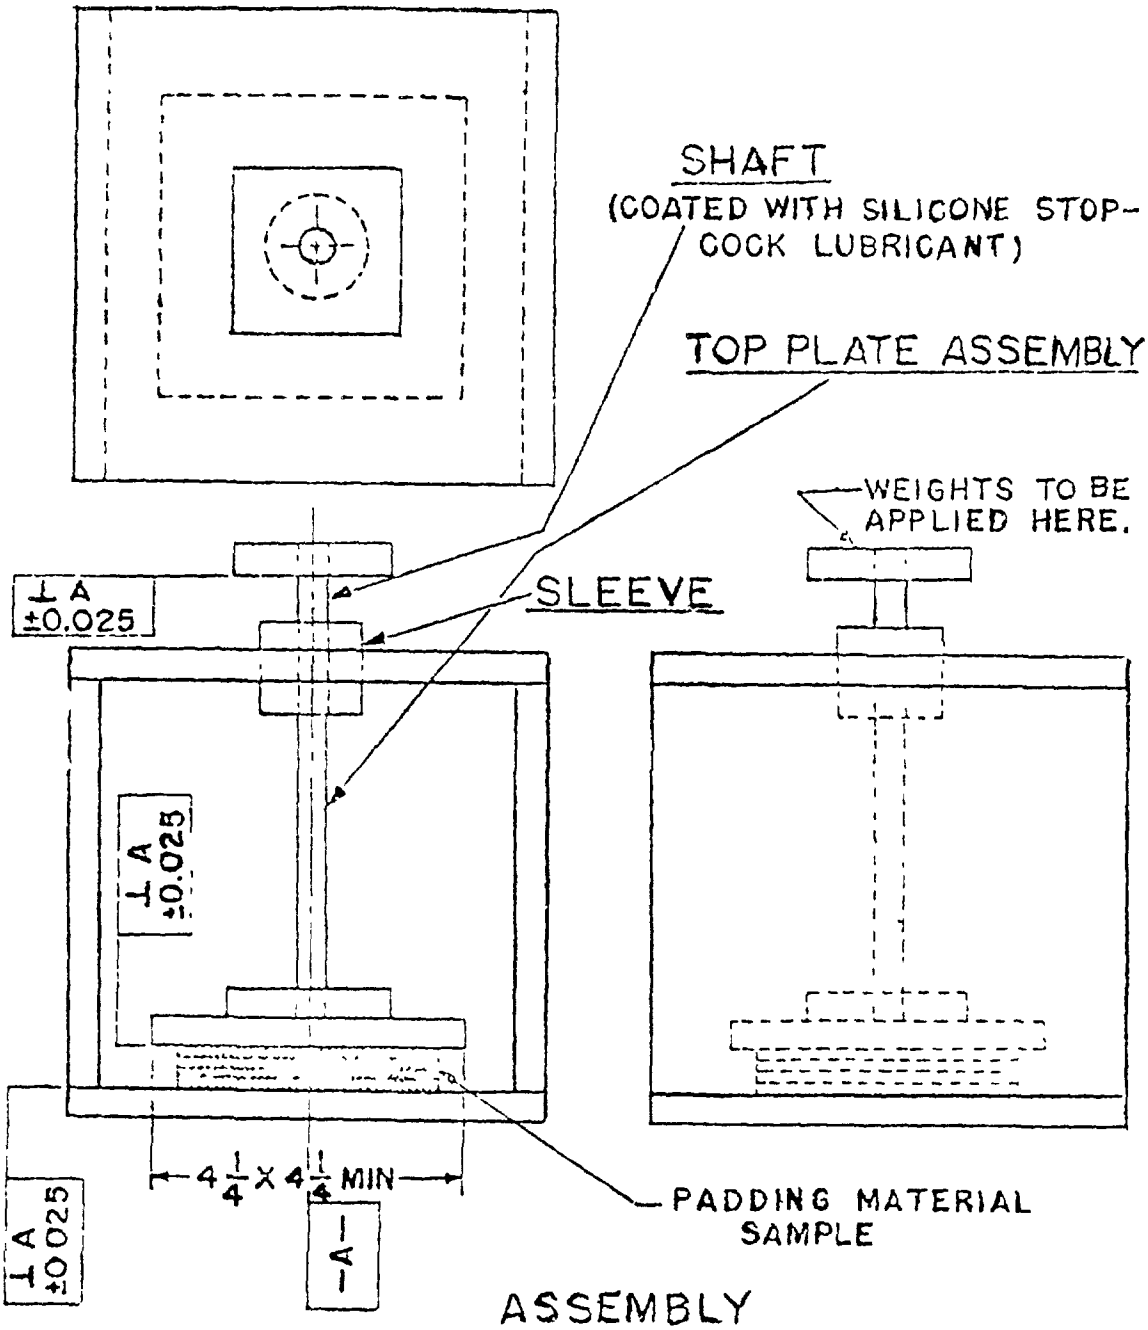

ASSEMBLY
WOOD, CONSTRUCTED
SHELLAC COATED.

COMPRESSION AND HEIGHT MEASURING ASSEMBLY.

ALL DIMENSIONS ARE IN INCHES.

Figure 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems Enter in block 6 any remarks not related to a specific paragraph of the document If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered

NOTE This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO 12062 WASHINGTON D C

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
Picatinny Arsenal
ATTN: SARPA-QA-A
Dover, New Jersey 07801

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1 DOCUMENT NUMBER	2 DOCUMENT TITLE

3a NAME OF SUBMITTING ORGANIZATION	4 TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
b ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)*

5 PROBLEM AREAS

a. Paragraph Number and Wording

b. Recommended Wording

c. Reason/Rationale for Recommendation

6 REMARKS

7a NAME OF SUBMITTER *(Last, First, MI)* – Optional	b WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8 DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426

PREVIOUS EDITION IS OBSOLETE

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:54Z
Check the source to verify that this is the current version before use.