MIL-T-13560D
27 May 1981
SUPERSEDING
MIL-T-0013560C(AR)
10 December 1980,
and MIL-T-13560B
28 December 1973

MILITARY SPECIFICATION

TARGETS, PASTEBOARD AND POLYETHYLENE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 This specification contains requirements not covered by the drawings, and provides quality assurance provisions for the fabrication, assembling and packaging for several types and sizes of pasteboard (fiberboard) and polyethylene targets. (See 6.3)

2. APPLICABLE DOCUMENTS

2.1 Issues of documents. The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein.

SPECIFICATIONS

MILITARY

MIL-P-14232	Parts, Equipment and Tools for Army Materiel, Packaging of
MIL-W-63150	Weapons and Support Materiel Standard Quality Assurance Provisions for

FSC 6920

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, US Army Armament Research and Development Command, Attn. DRDAR-QA, Dover, New Jersey 07801 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

STANDARDS

FEDERAL

FEDERAL TEST METHOD STANDARD NO. 191 - TEXTILE TEST METHODS

MILITARY

MIL-STD-105	Sampling Procedures and Tables for Inspection by Attributes.

DRAWINGS (See 6.2)

US ARMY ARMAMENT RESEARCH AND DEVELOPMENT COMMAND

PRODUCT DRAWINGS

5175649	Disk, Bayonet Practice, M1
6006881	Target, Trapezoidal
8426438	Target, Kneeling
8426556	Target, Prone
12002898	Target, Silhouette, Type "E" Kneeling, Polyethylene
12002899	Target, Silhouette, Type "F" Prone, Polyethylene

PACKAGING DATA SHEETS

P5175649	Disk, Bayonet Practice, M1
P6006881	Target, Trapezoidal
P8426438	Packaging Data Sheet for Board, Target E Kneeling
P8426556	Packaging Data Sheet for Board, Target, Prone
P12002898	Packaging Data Sheet for Target, Silhouette, Type "E"
P12002899	Packaging Data Sheet for Target, Silhouette, Type "F" Prone

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

Source: https://assist.dla.mil -- Downloaded: 202610-18T00:51Z
Check the source to verify that this is the current version before use.

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on the date of invitation for bids or request for proposal shall apply.

TECHNICAL ASSOCIATION OF THE PULP AND PAPER INDUSTRY STANDARDS

T411-OS-76	Thickness (caliper) of Paper and Paperboard
T477-TS-47	Blocking Resistance of Paper and Flexible Materials
T480-OS-72	Specular Gloss of Paper and Paperboard at 75 Degrees
T491-SU-63	Water Immersion Test of Paperboard

(Application for copies should be addressed to the Technical Association of the Pulp and Paper Industry, 1 Dunwoody Park, Atlanta, Ga 30338).

AMERICAN SOCIETY FOR TESTING AND MATERIALS

D747	Method of Test for Stiffness of Plastics by Means of a Cantilever Beam

(Application for copies should be addressed to: American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103)

3. REQUIREMENTS

3.1 Material. Materials shall be in accordance with Drawings (Dwgs.) 5175649, 6006881, 8426438, 8426556, 12002898 and 12002899, as applicable, all associated drawings, and all requirements specified in applicable specifications and standards.

3.2 Targets. The targets shall comply with all requirements specified in Dwgs. 5175649, 6006881, 8426438, 8426556, 12002898 and 12002899, as applicable, all associated drawings, and all requirements specified in applicable specifications and standards.

3.3 Pasteboard targets.

3.3.1 Water absorption. The water absorption of the targets shall be a maximum of ten (10) percent when determined as specified in 4.3.1.2.

Source: https://assist.dla.mil -- Downloaded: 202610-18T00:51Z
Check the source to verify that this is the current version before use.

3.3.2 Blocking. The targets shall show no evidence of blocking (adhesion) when tested as specified in 4.3.1.3.

3.3.3 Delamination. The target shall show no evidence of delamination, (separation of plies) exceeding one-eighth (1/8) inch from the edge of the target when tested as specified 4.3.1.4.

3.3.4 Stiffness (modulus of elasticity). The target shall have a minimum stiffness in the machine direction of 184,000 pounds per square inch (psi) when subjected to the stiffness test specified in 4.3.1.5.

3.3.5 Puncture resistance. The target shall have a minimum puncture resistance of forty (40) pounds when subjected to the water immersion test specified in 4.3.1.6.

3.3.6 Colorfastness to light. The color side of the target shall evidence acceptable colorfastness to light rating when tested as specified in 4.3.1.7.

3.3.7 Gloss. The target shall have a maximum gloss value of twenty (20) units when tested as specified in 4.3.1.8.

3.4 Workmanship. Pasteboard targets shall be free from foreign or undigested matter, discoloration, dirt or oil spots, holes, tears, wrinkles, chaff or scuff marks. Targets shall be trimmed and shall have no ragged, torn, uneven, or crushed edges. All targets shall be clean and free of defects affecting serviceability including rough or broken edges, warpage, distortion, or mutilated areas. All required markings shall be neat and sharply defined.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection and standard quality assurance provisions. Unless otherwise specified herein or in the contract, the provisions of MIL-W-63150 shall apply and are hereby made a part of this specification.

Source: https://assist.dla.mil -- Downloaded: 202610-18T00:51Z
Check the source to verify that this is the currentversion before use.

4.2 Lot formation. Unless otherwise specified in the contract, the lots shall be characterized by homogeneity and be in accordance with the lot formation requirements specified in MIL-STD-105. Lots shall consist of unit packs of one type or kind of pasteboard or polyethylene target, as applicable. Each lot shall have been manufactured and packaged under one contract using essentially the same conditions during the same identifiable production period, and submitted for acceptance by one supplier at one time.

4.2.1 Sampling for inspection and acceptance. Sampling for inspection and acceptance shall be performed in accordance with the provisions set forth in MIL-STD-105 except where otherwise indicated.

4.2.2 Inspection to be performed. Unless otherwise specified, inspection of the targets and packing shall be performed in accordance with the following tables (4.2.2.1 to 4.2.2.7), as applicable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE		SHEET OF	DRAWING NUMBER
3.2.2.1	Disk, Bayonet Practice, M1		1 1	A5175649
				NEXT HIGHER ASSEMBLY
				-
CATEGORY	EXAMINATION OR TEST	NO. OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
CRITICAL	None defined				
MAJOR	None defined				
MINOR					
101	Diameter	Note 1	1.5%	3.2	SMTE
102	Evidence of poor workmanship	Note 1	4.0%	3.4	Visual

NOTES:
1. Inspection Level S-4 of MIL-STD-105 shall be used. If any target fails to comply with the specified requirement, it shall be classed defective.

DRDAR-QA Form 160 Jul 77 Replaces SARPA-QA Form 2567 Feb 74 Which is Obsolete

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE		SHEET	DRAWING NUMBER
2.2.2	Target, Trapezoidal		1 OF 1	B6006881
				NEXT HIGHER ASSEMBLY
				–

CATEGORY	EXAMINATION OR TEST	NO. OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
CRITICAL	None defined				
MAJOR	None defined				
MINOR					
1	Width of wider end	Note 1	1.5%	3.2	SMTE
2	Width of smaller end	Note 1	1.5%	3.2	SMTE
3	Height	Note 1	1.5%	3.2	SMTE
4	Thickness	4.3.1.9	–	3.2	4.3.1.9
5	Color incorrect or not inform	Note 1	2.5%	3.2	Visual
6	Evidence of poor workmanship	Note 1	4.0%	3.4	Visual
	Special Tests				
	Water absorption	4.3.1.2	–	3.3.1	4.3.1.2
	Blocking	4.3.1.3	–	3.3.2	4.3.1.3
	Delamination	4.3.1.4	–	3.3.3	4.3.1.4
	Stiffness	4.3.1.5	–	3.3.4	4.3.1.5
	Puncture resistance	4.3.1.6	–	3.3.5	4.3.1.6
	Colorfastness to light	4.3.1.7	–	3.3.6	4.3.1.7
	Gloss	4.3.1.8	–	3.3.7	4.3.1.8

NOTES:

1. Inspection Level S-4 of MIL-STD-105 shall be used. If any target fails to comply with the specified requirement, it shall be classed defective.

AIR-QA Form 160 Jul 77 Replaces SARPA-QA Form 2567 Feb 74 Which is Obsolete

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE	SHEET	DRAWING NUMBER
4.2.2.3	Target, Kneeling	1 OF 1	B8426438
			NEXT HIGHER ASSEMBLY: -

CATEGORY	EXAMINATION OR TEST	NO. OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
CRITICAL	None defined				
MAJOR	None defined				
MINOR					
201	Width of bottom (19.50)	Note 1	1.5%	3.2	SMTE
202	Distance between longer side and adjacent shorter side (5.50	Note 1	1.5%	3.2	SMTE
203	Distance between longer side and opposite shorter side (14.00)	Note 1	1.5%	3.2	SMTE
204	Total height	Note 1	1.5%	3.2	SMTE
205	Radius incorrect	Note 1	1.5%	3.2	Visual
206	Thickness	4.3.1.9	-	3.2	4.3.1.9
207	Color incorrect or not uniform	Note 1	2.5%	3.2	Visual
208	Evidence of poor workmanship	Note 1	4.0	3.4	Visual
	SPECIAL TESTS				
	Water absorption	4.3.1.2	-	3.3.1	4.3.1.2
	Blocking	4.3.1.3	-	3.3.2	4.3.1.3
	Delamination	4.3.1.4	-	3.3.3	4.3.1.4
	Stiffness	4.3.1.5	-	3.3.4	4.3.1.5
	Puncture resistance	4.3.1.6	-	3.3.5	4.3.1.6
	Color fastness to light	4.3.1.7	-	3.3.6	4.3.1.7
	Gloss	4.3.1.8	-	3.3.7	4.3.1.8

NOTES:

1. Inspection Level S-4 of MIL-STD-105 shall be used. If any target fails to comply with the specified requirement, it shall be classed defective.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE		SHEET 1 OF 1		DRAWING NUMBER B8426556
.2.2.4	Target, prone				NEXT HIGHER ASSEMBLY –
CATEGORY	EXAMINATION OR TEST	NO. OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
RITICAL	None defined				
AJOR	None defined				
INOR					
01	Width of bottom	Note 1	1.5%	3.2	SMTE
02	Height	Note 1	1.5%	3.2	SMTE
03	Radius	Note 1	1.5%	3.2	Visual
04	Thickness	4.3.1.9	–	3.2	4.3.1.9
05	Color incorrect or not uniform	Note 1	2.5%	3.2	Visual
06	Evidence of poor workmanship	Note 1	4.0%	3.4	Visual
	SPECIAL TESTS				
	Water absorption	4.3.1.2	–	3.3.1	4.3.1.2
	Blocking	4.3.1.3	–	3.3.2	4.3.1.3
	Delamination	4.3.1.4	–	3.3.3	4.3.1.4
	Stiffness	4.3.1.5	–	3.3.4	4.3.1.5
	Puncture resistance	4.3.1.6	–	3.3.5	4.3.1.6
	Color fastness to light	4.3.1.7	–	3.3.6	4.3.1.7
	Gloss	4.3.1.8	–	3.3.7	4.3.1.8

Notes:

1. Inspection Level S-4 of MIL-STD-105 shall be used. If any target fails to comply with the specified requirement, it shall be classed defective.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE	SHEET	DRAWING NUMBER
4.2.2.5	Target, Silhouette, Type "E", Kneeling, Polyethylene	1 OF 1	F12002898
			NEXT HIGHER ASSEMBLY: -

CATEGORY	EXAMINATION OR TEST	NO. OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
CRITICAL	None defined				
MAJOR	None defined				
MINOR					
201	Height	Note 1	1.5%	3.2	SMTE
202	Location of slots at bottom from Midline (2)	Note 1	1.5%	3.2	SMTE
203	Thickness	4.3.2.1	—	3.2	4.3.2.1.1
204	Hole between bottom slots missing	Note 1	1.5%	3.2	Visual
205	Color incorrect or not uniform	Note 1	2.5%	3.2	Visual
206	Evidence of poor workmanship	Note 1	4.0%	3.4	Visual

NOTES:

1. Inspection Level S-4 of MIL-STD-105 shall be used. If any target fails to comply with the specified requirement, it shall be classed defective.

DRDAR-QA Form 160 Jul 77 Replaces SARPA-QA Form 2567 Feb 74 which is Obsolete

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE		SHEET 1 OF 1		DRAWING NUMBER
4.2.2.6	Target, Silhouette, Type "F", Prone Polyethylene				D12002899
					NEXT HIGHER ASSEMBLY
					-
CATEGORY	EXAMINATION OR TEST	NO. OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
CRITICAL	None defined				
MAJOR	None defined				
MINOR					
201	Height	Note 1	1.5%	3.2	SMTE
202	Location of slots at bottom from Midline (2)	Note 1	1.5%	3.2	SMTE
203	Thickness	4.3.2.1	-	3.2	4.3.2.1.2
204	Hole between bottom slots missing	Note 1	1.5%	3.2	Visual
205	Color incorrect or not uniform	Note 1	2.5%	3.2	Visual
206	Evidence of poor workmanship	Note 1	4.0%	3.4	Visual

NOTES:
1. Inspection Level S-4 of MIL-STD-105 shall be used. If any target fails to comply with the specified requirement, it shall be classed defective.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

QUALITY CONFORMANCE INSPECTION

CLASSIFICATION OF DEFECTS & TESTS

PARAGRAPH	TITLE	SHEET	DRAWING NUMBER
4.2.2.7	Preservation and packaging of targets	1 OF 1	See 5.1
			NEXT HIGHER ASSEMBLY: -

CATEGORY	EXAMINATION OR TEST	NO. OF SAMPLE UNITS	AQL OR 100%	REQUIREMENT PARAGRAPH	PARAGRAPH REFERENCE /INSPECTION METHOD
CRITICAL	None defined				
MAJOR	None defined				
MINOR					
201	Incorrect number of targets	Note 1	4.0%	Note 2	Visual
202	Marking missing, misleading, incorrect or unidentifiable	Note 1	4.0%	Note 2	Visual
203	Contents exposed	Note 1	4.0%	-	Visual
204	Evidence of poor workmanship	Note 1	4.0%	Note 3	Visual
205	Packaging unsatisfactory	Note 1	4.0%	Notes 2 and 3	Visual

NOTES:

1. Inspection Level S-3 of MIL-STD-105 shall be used. If any pack fails to comply with the specified requirements, the pack shall be classed defective.

2. See applicable packaging data sheet

3. See MIL-P-14232

NOTES:

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

4.2.3 Inspection Equipment. The inspection equipment required to perform the examinations and tests prescribed herein is described in the Paragraph Reference/Inspection Method column in the tables starting with Paragraph 4.2.2.1. The contractor shall submit for approval inspection equipment designs in accordance with the terms of the contract. All inspection equipment and procedures shall be satisfactory to the Contracting Officer. Any change in inspection equipment or procedures shall have prior written approval of the Contracting Officer.

4.3 Test methods and procedures.

4.3.1 Pasteboard targets.

4.3.1.1 Conditioning. The targets to be subjected to the following tests shall be conditioned for not less than forty-eight (48) hours at 73° ± 2° F. and 50 ± 4% relative humidity.

4.3.1.2 Water absorption. Three (3) boxes of targets shall be selected from each lot. One (1) target shall be taken from each box and conditioned in accordance with 4.3.1.1. The three (3) targets shall then be subjected to the water immersion test specified in Technical Association of the Pulp and Paper Industry standard (TAPPI), Method T491-SU. Results shall be to the nearest 1.0 percent. Immersion time shall be not less than 24 hours. If the average increase in weight exceeds the requirement specified in 3.3.1, the lot shall be rejected.

4.3.1.3 Blocking. Three (3) boxes of targets shall be selected from each lot. Three (3) targets shall be taken from each box and conditioned in accordance with 4.3.1.1. The targets shall then be subjected to the blocking test specified in TAPPI standard, Method T477-TS. Dry bulb temperature shall be 140° ± 2° F, Relative humidity 75 ± 2%, Pressure 2.0 p.s.i. If any set of targets fails to comply with the requirement specified in 3.3.2, the lot shall be rejected.

4.3.1.4 Delamination. Two (2) boxes of targets shall be selected from each lot. Two (2) targets shall be taken from each box and conditioned in accordance with 4.3.1.1. The targets shall than be tested as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

4.3.1.4.1 Cold Temperature. The bottom four inches shall be cut from each target and conditioned at 0° F. for not less than 2 hours along with a 12-inch radius mandrel. After conditioning, and at the test temperature, the specimens shall be slowly bent around the mandrel and observed for any signs of delamination or separation of plies. If any specimen fails to comply with the requirement specified in 3.3.3, the lot shall be rejected.

4.3.1.4.2 Ambient temperature. Sample targets shall be selected as specified in 4.3.1.4. Specimens, as specified in 4..3.1.4.1, shall be immersed in water at 75° ± 5° F. for 24 hours. After removal from the water, the specimens shall be bent around the test mandrel at room temperature (73° F.) and observed for delamination (separation of contiguous layers of plies). If any specimen fails to comply with the requirement specified in 3.3.3, the lot shall be rejected.

4.3.1.5 Stiffness (modulus of elasticity). Three (3) boxes of targets shall be selected from each lot. Five (5) targets shall be taken from each box and conditioned in accordance with 4.3.1.1. Each set of five targets shall be subjected to the stiffness test in accordance with ASTM D 747 with the following exceptions: specimen size shall be 2-by 6-inches, the span length shall be four inches, angular deflection shall be 5° and moment weight shall be 20 in.-lbs. The specimens shall be measured and then immersed in water for 24 hours. After immersion, excess water shall be carefully blotted from specimens, exercising care that the specimens are not flexed or compressed. The equation for determining stiffness shall be as follows:

$$\text{Stiffness (M.E.) psi} = \frac{4L \times S^3}{D \times W \times T^3}$$

$$\text{Where } L = \frac{\text{Load-scale reading} \times \text{moment (in-lbs.)}}{100 \times S}$$

Source: https://assist.dla.mil -- Downloaded: 202610-18T00:51Z
Check the source to verify that this is the current version before use.

S = span length (inches)
D = angular deflection = 2S SIN. ½
0 (inches)
W - width of specimen (inches)
T = thickness of specimen (inches)

Results shall be to the nearest 100 psi. If the average stiffness of any set of five (5) targets fails to comply with the requirement specified in 3.3.4, the lot shall be rejected.

4.3.1.6 Puncture resistance. Three (3) boxes of targets shall be selected from each lot. Five (5) targets shall be taken from each box and conditioned in accordance with 4.3.1.1. One (1) specimen each four (4) inches square, shall be cut from each target. The specimens shall be immersed for 24 hours in water at 75° ± 5° F. After removal from the water, the specimen shall be blotted lightly and tested. Any device capable of applying a known amount of weight to a perpendicularly mounted penetrator shall be satisfactory. The penetrator shall be a 0.30-inch rod tapered to a sharp point in 3/4 inch. The specimens shall be placed on a wooden or metal block (approx. 3 inches square and 1 inch thick) with a 1/2 to 1 inch diameter hole through the 1 inch thickness. The resistance to puncture shall be measured by applying the load in 5-pound increments to the penetrator centered over the hole. Complete penetration should take place in less than 5 seconds. If the specimen is not penetrated fully in 5 seconds, the penetrator shall be moved to another section of the specimen and an additional 5-pound weight added. The minimum amount of weight that penetrates each specimen in 5 seconds or less shall be recorded. This procedure shall be repeated on all remaining specimens.

Results shall be to the nearest pound. If the average puncture resistance of any set of five (5) specimens fails to comply with the requirement specified in 3.3.5, the lot shall be rejected.

4.3.1.7 Colorfastness to light. Three (3) boxes of targets shall be selected from each lot. One (1) target shall be taken from each box and and conditioned in accordance with 4.3.1.1. The three (3) targets shall then be tested in accordance with FED TEST METHOD STD-191, Method 5660. Results shall be interpreted as described in, FED TEST METHOD STD-191, Method 5662, the "No standard sample" evaluation procedure. (See 6.4). If any target fails to comply with the requirement specified in 3.3.6, the lot shall be rejected. The exposure to light time shall be a minimum of twenty (20) hours.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

4.3.1.8 Gloss. Three (3) boxes of targets shall be selected from each lot. Five (5) targets shall be taken from each box and conditioned in accordance with 4.3.1.1. The targets shall then be subjected to the gloss determination specified in TAPPI standard Method T480-OS. If the average of any set of five (5) targets fails to comply with the requirement specified in 3.3.7, the lot shall be rejected. Results shall be to the nearest 0.1 unit.

4.3.1.9 Thickness. Ten (10) boxes of targets shall be selected from each lot. One (1) target shall be taken from each box and conditioned in accordance with 4.3.1.1. The thickness of each target shall then be determined in accordance with TAPPI standard Method T411-OS. Measurements shall be to the nearest 0.001 inch. If the average thickness of the ten (10) targets fails to comply with the specified drawing requirement, the lot shall be rejected.

4.3.2 Polyethylene Targets.

4.3.2.1 Thickness. Five (5) boxes of targets shall be selected from each lot. Four (4) targets be taken from each box, and the thickness of each target determined as specified in 4.3.2.1.1 and 4.3.2.1.2, as applicable. If the average thickness of any set of four (4) targets fails to comply with the specified drawing requirement, the lot shall be rejected.

4.3.2.1.1 Target, silhouette, type "E", kneeling, polyethylene (Dwg. F12002898). Six (6) circles shall be incribed on each target as shown on Figure 1. Two (2) thickness measurements shall be taken within each circle. Readings shall be taken on both the flat and angled surfaces.

4.3.2.1.2 Target, Silhouette, Type "F", Prone, Polyethylene (Dwg. D12002899). Three (3) circles shall be inscribed on each target as shown on Figure 2. Two (2) thickness measurements shall be taken within each circle. Readings shall be taken on both the flat and angled surfaces.

4.4 Certification (all targets). The certification provisions of MIL-W-63150 for Certified Test Reports (CTR) shall apply for each lot of targets, pasteboard and polyethylene.

Source: https://assist.dla.mil -- Downloaded: 202610-18T00:51Z
Check the source to verify that this is the currentversion before use.

5. PACKAGING

5.1 Preservation, packaging and marking. The targets covered by this specification shall be preserved, packed and marked in accordance with the following packaging data sheets, as applicable, and satisfactory to the Government.

Part No.	Packaging Data Sheet
5175649	P5175649
6006881	P6006881
8426438	P8426438
8426556	P8426556
12002898	P12002898
12002899	P12002899

6. NOTES

6.1 Ordering Data. Procurement documents shall include the following:

(a) title, number, and date of this specification.
(b) title, number, and date of applicable target drawing.
(c) quantity.
(d) Level of Protection.
(e) title, number, and date of applicable packaging data sheet (with exceptions where required).
(f) color (with exceptions where required).

6.2 Drawings. Drawings and Packaging Data Sheets listed in Section 2 of this specification under the heading "U.S. Army Armament Research and Development Command" (ARRADCOM) may also include drawings prepared by and identified as, Edgewood Arsenal, Frankford Arsenal, Rock Island Arsenal, or Picatinny Arsenal, drawings. Technical data originally prepared by these activities are now under the cognizance of ARRADCOM.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

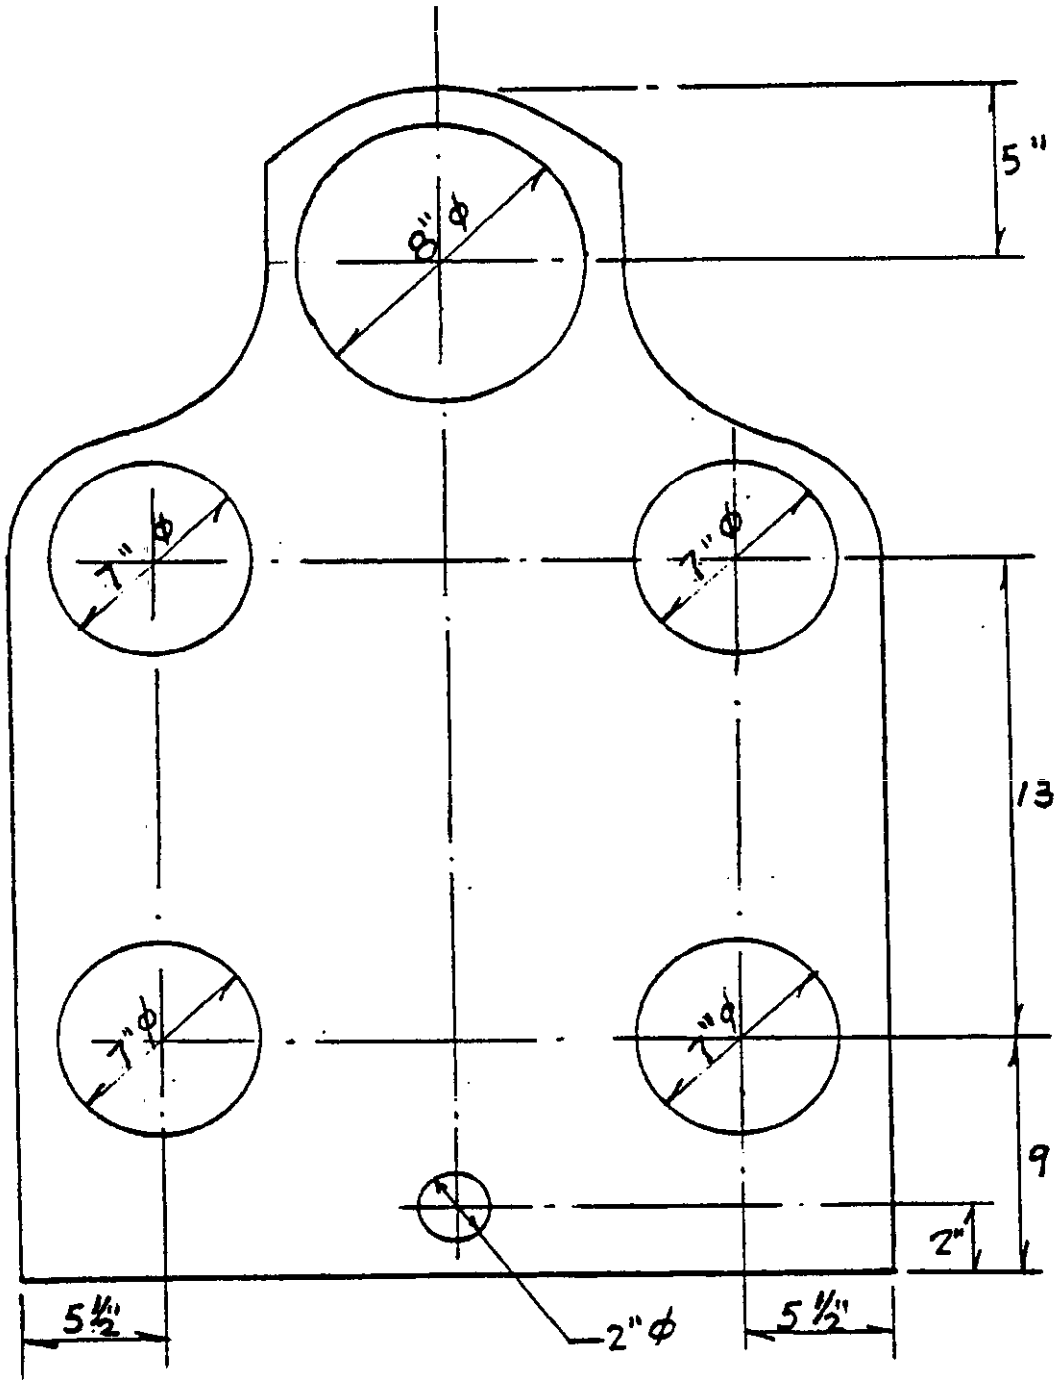


FIGURE 1

NOTE - TOLERANCE ±0.125

Source: https://assist.dla.mil -- Downloaded: 202610-18T00:51Z
Check the source to verify that this is the current version before use.

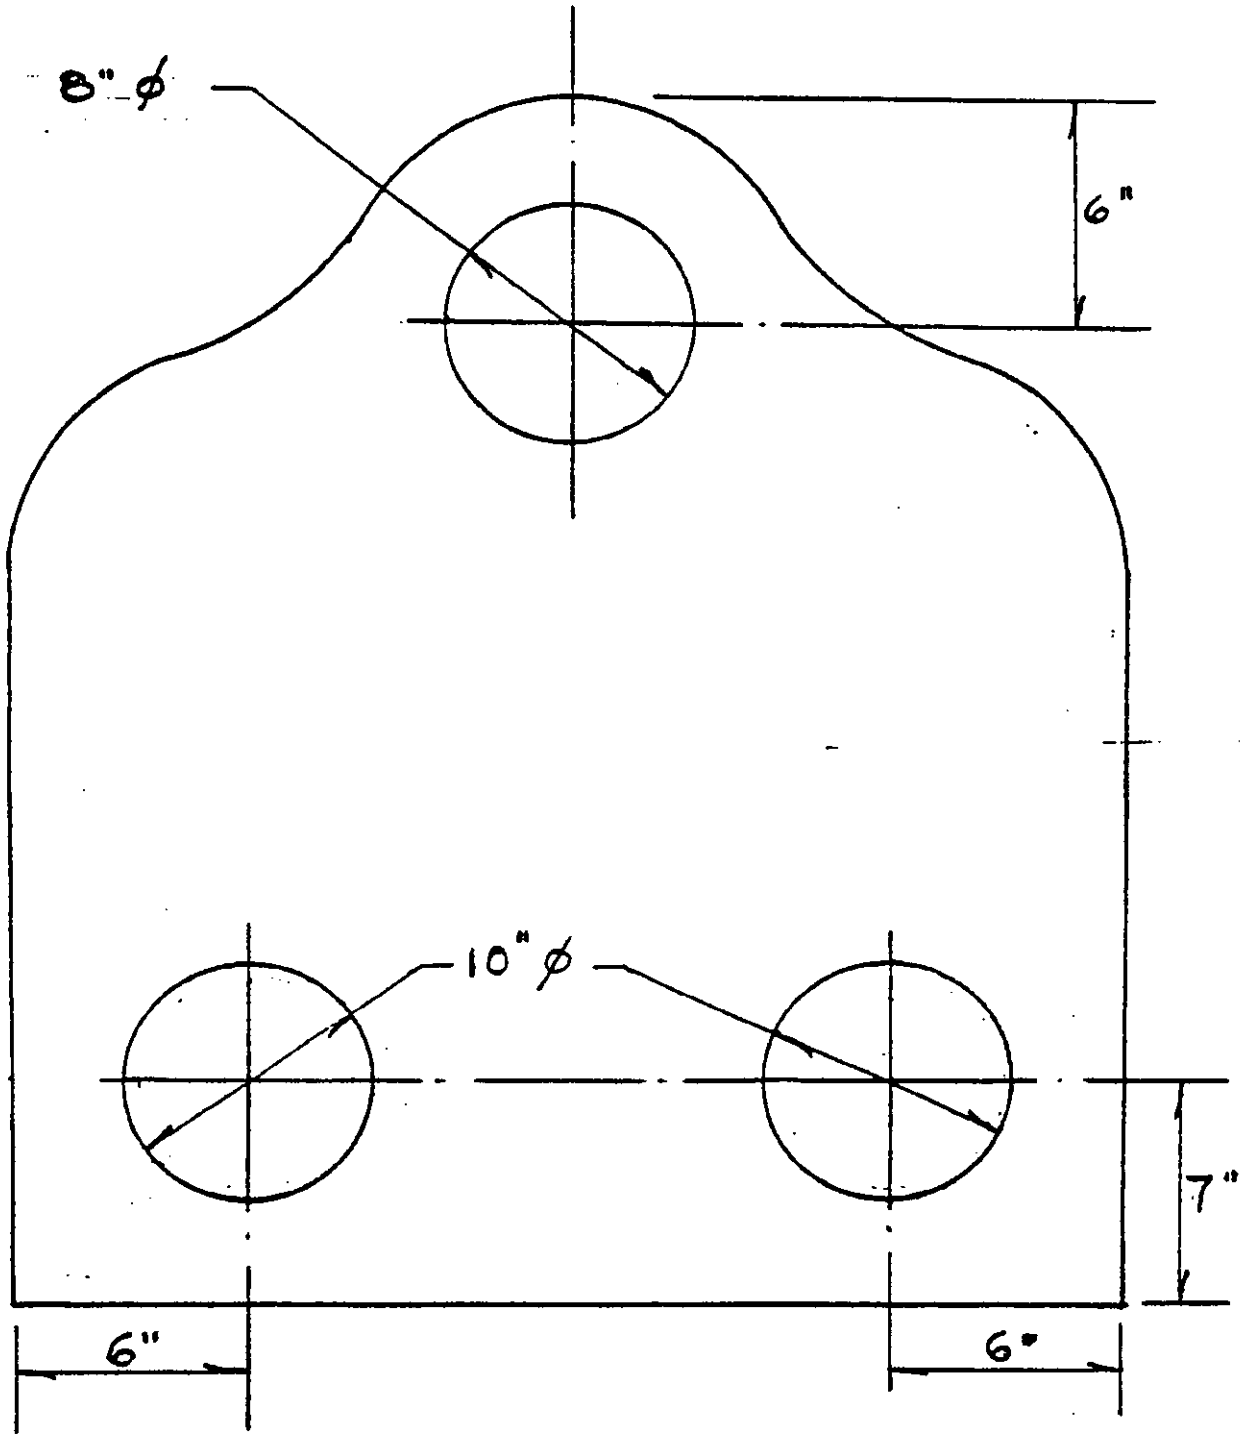


FIGURE 2

NOTE - TOLERANCE ±0.125

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

6.3 Storage. To minimize the effects of natural aging, pasteboard targets should be stored in a cool, dry location. It is suggested that these targets be stored for no longer than three (3) years.

6.4 Colorfastness to light. Methods 5660 and 5662 of FED TEST METHOD STD-191 are intended for determining the colorfastness of cloth to light. For the purpose of a colorfastness requirement for targets, the use of the word "cloth" in Method 5660 shall be deleted and words "pasteboard targets" shall be used.

Custodian:
Army - AR
Navy - TD
Air Force - 99

Review Activities:
Army - None
Navy - None
Air Force - None

User Activities:
Army - None
Navy - MC, OS
Air Force - None

Preparing activity:
Army - AR

Project 6920-0095

Source: https://assist.dla.mil -- Downloaded: 202610-18T00:51Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

BUSINESS REPLY CARD

FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Armament Research and Development Command
ATTN: DRDAR-QAA
Dover, NJ 07801

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS: This form is provided to solicit beneficial comments which may improve this document and enhance its use. DoD contractors, government activities, manufacturers, vendors, or other prospective users of the document are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Attach any pertinent data which may be of use in improving this document. If *there are additional papers, attach to form and place* both in an envelope addressed to preparing activity. A response will be provided to the submitter, when name and address is provided, within 30 days indicating that the 1426 was received and when any appropriate action on it will be completed.
NOTE: This form shall not be used to submit requests for waivers, deviations or clarification of specification requirements on current contracts. Comments submitted on this form do not *constitute or imply* authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

DOCUMENT IDENTIFIER *(Number)* AND TITLE
MIL-T-13560D TARGETS, PASTEBOARD AND POLYETHYLENE

NAME OF ORGANIZATION AND ADDRESS OF SUBMITTER

☐ VENDOR ☐ USER ☐ MANUFACTURER

1. ☐ HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE? ☐ IS ANY PART OF IT TOO RIGID, RESTRICTIVE, LOOSE OR AMBIGUOUS? PLEASE EXPLAIN BELOW.

A. GIVE PARAGRAPH NUMBER AND WORDING

B. *RECOMMENDED WORDING CHANGE*

C. *REASON FOR RECOMMENDED CHANGE(S)*

2. REMARKS

SUBMITTED BY *(Printed or typed name and address — Optional)*

TELEPHONE NO.

DATE

DD FORM 1 OCT 76 1426 EDITION OF 1 JAN 72 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T00:51Z
Check the source to verify that this is the current version before use.