
MILITARY SPECIFICATION SHEET

CABLE, ELECTRIC, FILTER LINE, COMPONENT WIRE, TIN-COATED COPPER CONDUCTOR, RADIO FREQUENCY ABSORPTIVE, 150°C, 600-VOLT

This specification sheet is approved for use by all departments and agencies of the Department of Defense.

The complete requirements for procuring the wire described herein shall consist of this document and the issue in effect of Specification MIL-C-85485.

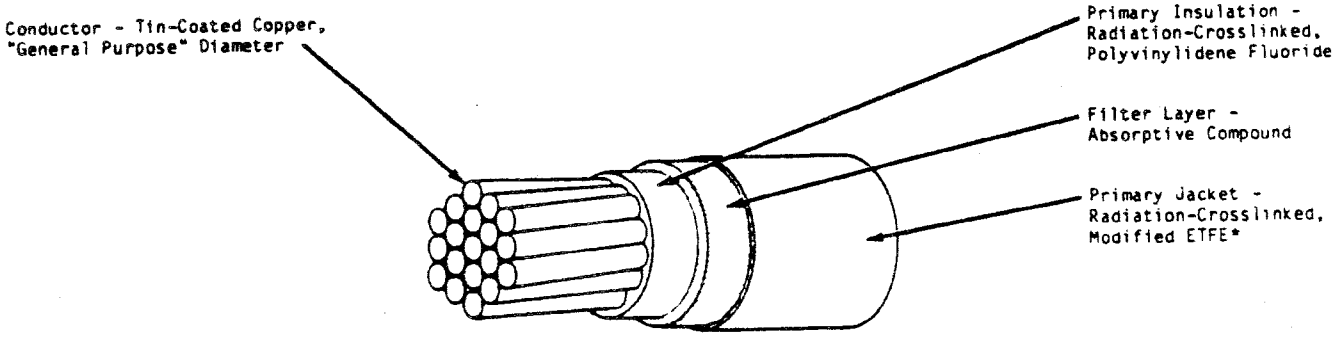

*ETFE - Ethylene-Tetrafluoroethylene Copolymer.

FIGURE 1. GENERAL CONFIGURATION

TABLE I. CONSTRUCTION DETAILS

Part No. 1/	Wire Size	Stranding (number of strands x AWG gauge of strands)	Diameter of Stranded Conductor (inches)		Finished Wire		
			(min)	(max)	Resistance at 20°C (68°F) (ohms/1000 ft) (max)	Diameter (inches)	Weight (lbs/1000 ft) (max)
M85485/9-22-*	22	19 x 34	.029	.033	16.2	.051 ± .003	4.0
M85485/9-20-*	20	19 x 32	.037	.041	9.88	.059 ± .003	5.8
M85485/9-18-*	18	19 x 30	.046	.051	6.23	.070 ± .003	8.7
M85485/9-16-*	16	19 x 29	.052	.058	4.81	.078 ± .004	11.2
M85485/9-14-*	14	19 x 27	.065	.073	3.06	.095 ± .004	16.1
M85485/9-12-*	12	37 x 28	.084	.090	2.02	.112 ± .004	24.0
M85485/9-10-*	10	37 x 26	.106	.114	1.26	.136 ± .006	37.0

1/ PART NO.: The asterisks in the part number column, Tables I, II and III, shall be replaced by color code designators in accordance with MIL-C-85485.

Ⓐ denotes changes

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:56Z
Check the source to verify that this is the current version before use.

Ⓐ TABLE II. PERFORMANCE DETAILS

Part No.	Bend Testing			
	Mandrel Diameter (inches) (±3%)		Test Load (lbs) (±3%)	
	Crosslinking Proof, Immersion and Life Cycle Tests	Cold Bend Test	Crosslinking Proof, Immersion and Life Cycle Tests	Cold Bend Test
M85485/9-22-*	.500	2.00	.75	3.00
M85485/9-20-*	.750	2.50	1.25	4.00
M85485/9-18-*	1.00	3.00	1.75	4.00
M85485/9-16-*	1.00	3.00	2.00	5.00
M85485/9-14-*	1.00	5.00	2.00	5.00
M85485/9-12-*	1.50	6.00	2.50	5.00
M85485/9-10-*	1.50	8.00	2.50	5.00

RATINGS:

TEMPERATURE RATING: 150°C (302°F) maximum continuous conductor temperature.
VOLTAGE RATING: 600 volts (rms) at sea level.

ADDITIONAL REQUIREMENTS:

ATTENUATION (INSERTION LOSS): The wire of this specification sheet, when shielded in accordance with M85485/12-**T1*, shall meet the attenuation requirements of Table III as specified for the applicable size of wire.
BLOCKING: 200° ± 3°C (392° ± 5°F) for 6 hours
COLOR: Primary insulation - natural
Filter layer - black
Primary jacket - light violet
COLOR STRIPING DURABILITY: 125 cycles (250 strokes) (min), 500 grams weight.
CONCENTRICITY: Primary insulation - 50% (min); finished wire - 70% (min).
CROSSLINKING PROOF TEST: 7 hours at 300° ± 3°C (572° ± 5°F).
FLAMMABILITY: 3 seconds (max); 3 inches (max).
HUMIDITY RESISTANCE: Insulation resistance, 5000 megohms for 1000 feet (min).
IDENTIFICATION DURABILITY: 125 cycles (250 strokes) (min), 500 grams weight.
IMMERSION: Diameter increase 5% (max); no cracking, no dielectric breakdown.
INSULATION ELONGATION AND TENSILE STRENGTH: Primary insulation, filter layer and primary jacket pulled together.
Elongation, 50% (min)
Tensile Strength, 3000 lbf/in^2 (min)
INSULATION FLAWS: Primary insulation only
Spark test; 1.5 kilovolts (rms), 60 Hz
Impulse dielectric test; 6.0 kilovolts (peak)
Finished wire
Spark test; 3.0 kilovolts (rms), 60 Hz
Impulse dielectric test; 8.0 kilovolts (peak)
INSULATION RESISTANCE: 5000 megohms for 1000 feet (min)
INSULATION THICKNESS: Primary insulation; 0.002 inch (min)
Filter layer; average 0.0025 inch (min)
Primary jacket; 0.0035 inch (min)
LIFE CYCLE: 168 hours at 200° ± 3°C (392° ± 5°F)
LOW TEMPERATURE-COLD BEND: -65° ± 2°C (-85° ± 4°F) for 4 hours
SHRINKAGE: 0.125 inch (max) at 200° ± 3°C (392° ± 5°F)
SMOKE: 200° ± 2°C (392° ± 4°F); no visible smoke.
SURFACE RESISTANCE: 500 megohm-inches (min), initial and final readings.
THERMAL SHOCK RESISTANCE: Oven temperature, 150° ± 3°C (302° ± 5°F)
Maximum change in measurement, 0.060 inch
THERMAL STABILITY: 1250 hours at 180° ± 3°C (356° ± 5°F). The wire of this specification sheet, when shielded in accordance with M85485/12-**T1*, shall meet the voltage withstand (dielectric) of 1500 volts (rms), 60 Hz, and the stop band attenuation requirements for the applicable size of wire as specified in Table III.
VOLTAGE WITHSTAND (POST-ENVIRONMENTAL): 1500 volts (rms), 60 Hz
WRAP TEST: 6 hours at 200° ± 3°C (392° ± 5°F); no cracking.

Source: https://assist.dla.mil -- Downloaded: 20261O-23T10:56Z
Check the source to verify that this is the current version before use.

TABLE III. ATTENUATION (INSERTION LOSS)

Part No.	Pass Band (dB/ft)			Transition Band (dB/ft)			Stop Band (dB/ft)
	1.0 MHz	10.0 MHz		100 MHz	500 MHz	1000 MHz	1 to 12 GHz
	(max)	(min)	(max)	(min)	(min)	(min)	(min)
M85485/9-22-*	.02	.06	0.20	1.3	12	30	30
M85485/9-20-*	.02	.06	0.20	1.3	12	30	30
M85485/9-18-*	.02	.06	0.20	1.3	13	33	33
M85485/9-16-*	.02	.06	0.20	1.3	13	33	33
M85485/9-14-*	.02	.06	0.20	1.3	13	33	33
M85485/9-12-*	.02	.04	0.20	1.3	12	30	30
M85485/9-10-*	.02	.04	0.20	1.3	12	30	30

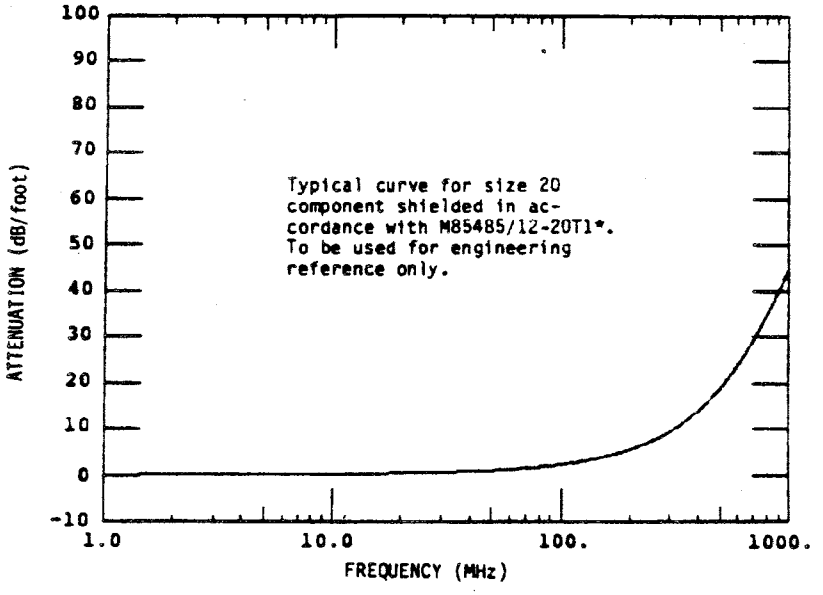


FIGURE 2. ATTENUATION (INSERTION LOSS)

ENGINEERING REFERENCE CURVE

APPLICATION NOTE:

Component wire is an effective radio frequency absorptive wire only when used as a component in a shielded cable.

Qualifying Activity: The activity responsible for this qualified products list is the Naval Air Systems Command, Washington, D.C. 20361.

Custodian:
AF - 85

Preparing activity:
Navy - AS
(Project No. 6145-1065)

Review activity:
AF - 19

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:56Z
Check the source to verify that this is the current version before use.