MIL-B-52919A
29 June 1981
SUPERSEDING
MIL-B-52919
7 December 1976

MILITARY SPECIFICATION

BELTS, V: INDUSTRIAL DRIVE, NARROW TYPE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers endless, narrow, single- and multiple-drive V-belts.

1.1.1 Military specification coverage. This military specification does not include all varieties of the belts as indicated by the title of the specification or which are commercially available, but is intended to cover only those belts generally used by the military.

2. APPLICABLE DOCUMENTS

2.1 Issues of documents. The following documents of the issue in effect on date of invitation for bids or request for proposal form a part of this specification to the extent specified herein:

SPECIFICATIONS

FEDERAL

QQ-S-781	- Strapping, Steel, and Seals.
PPP-B-601	- Boxes, Wood, Cleated-Plywood.
PPP-B-636	- Boxes, Shipping, Fiberboard.

FSC 3030

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: US Army Mobility Equipment Research and Development Command, ATTN: DRDME-DS, Fort Belvoir, VA 22060 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

STANDARDS

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	- Marking for Shipment and Storage.
MIL-STD-130	- Identification Marking of US Military Property.
MIL-STD-294	- Visual Inspection Guide for Rubber V-Belts.
MIL-STD-1188	- Commercial Packaging of Supplies and Equipment.
MS39277	- Belts, "V"; Industrial (Narrow Type), "3V" and "9N" Sectional Designation.
MS39278	- Belts, "V"; Industrial (Narrow Type), "5V" and "15N" Sectional Designation.
MS39279	- Belts, "V"; Industrial (Narrow Type), "8V" and "25N" Sectional Designation.

(Copies of specifications and standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

AMERICAN NATIONAL STANDARDS INSTITUTE (ANSI)

ANSI/ASTM D 471	- Standard Method for Rubber Property, Effect of Liquids.

(Application for copies should be addressed to American National Standards Institute, Inc., 1430 Broadway, New York, NY 10018).

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3. REQUIREMENTS

3.1 Description. The V-belts shall be endless loops having a trapezoidal cross section, measured in inches and millimeters (mm).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

3.2 First article (preproduction model). The contractor shall furnish one or more belts as specified (see 6.2) for examination and testing within the time frame specified (see 6.2) to prove prior to starting production that his production methods will produce belts that comply with the requirements of this specification. Examination and tests shall be as specified in Section 4 and shall be subject to surveillance and approval by the Government (see 6.3).

3.3 Material. Material shall be as specified herein. Materials not specified shall be selected by the contractor and shall be such as to enable the V-belts to meet the performance requirements of this specification (see 6.8).

3.3.1 Cord. Cords shall be natural or synthetic fibers twisted into a cord and treated for low growth and adhesion to the supporting polymer.

3.3.2 Fabric. Fabric shall be woven or knit natural or synthetic fibers impregnated with rubber.

3.3.3 Rubber. Rubber shall be either natural or a synthetic polymer compound.

3.4 Construction. The belts shall consist of tension members (inserts) and a compression member. The members shall be tightly bonded with rubber, forming an integral unit. A cover may be used (see 3.4.3).

3.4.1 Tension members. Tension members shall be either cord or fabric and shall be arranged in a symmetrical pattern parallel to the circumference of the belt and imbedded in the belt structure.

3.4.2 Compression member. The compression member shall form the narrower trapezoidal portion of the belt in the section below the tension members and shall support the belt in the pulleys. The base that forms the inner circumference of the belt may be plain, cogged, or notched. The compression member shall be rubber and may contain cords or fabrics.

3.4.3 Cover. The cover, if used, shall consist of one or more plies of stretchable fabric or cord, frictioned or impregnated for adhesion.

3.5 Dimensions.

3.5.1 Cross-sectional designation. The nominal cross-sectional designation shall be specified in the applicable Military Standard (MS) and as shown below, and the belt angle shall be determined by the rideout and bottom clearance.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

MS39277	3V - 0.38-inch wide by 0.31-inch thick and 9N - 9 mm wide by 8 mm thick.
MS39278	5V - 0.62-inch wide by 0.53-inch thick and 15N - 15 mm wide by 13 mm thick.
MS39279	8V - 1.00-inch wide by 0.91-inch thick and 25N - 25 mm wide by 23 mm thick.

3.5.2 Lengths. The standard effective lengths (see 6.6) and length tolerance shall be as specified for the applicable cross section in MS39277, MS39278, or MS39279.

3.5.3 Rideout and bottom clearance. The position of the top of the belt with respect to the top of the measuring pulley groove (rideout) and bottom clearance between the bottom of the measuring pulley groove and the bottom of the belt shall conform to the tolerances specified in Table I, and shall be tested in accordance with 4.5.2.2.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:11Z
Check the source to verify that this is the current version before use.

TABLE I. Details for dimensional checking of V-belts.

Belt size designation	Pulley O.D.		Pulley effective outside circumference		Pulley groove angle	Pulley groove top width		Pulley groove depth (minimum)	
	±0.005 inch	±0.1 mm	inch	mm	±0.25 degree	±0.005 inch	±0.13 mm	inch	mm
3V	3.820	-	12.000	-	38	0.350	-	0.340	-
9N	-	95.5	-	300	38	-	8.89	-	8.6
5V	7.958	-	25.000	-	38	0.600	-	0.590	-
15N	-	191.0	-	600	38	-	15.24	-	15.0
8V	15.916	-	50.000	-	38	1.000	-	0.990	-
25N	-	318.3	-	1000	38	-	25.40	-	25.1

Belt size designation	Total tension		Rideout (maximum)		Bottom clearance (minimum)	
	pounds	Newtons	inch	mm	inch	mm
5V	100	-	0.10	-	0.08	-
9N	-	445	-	2.5	-	2.0
5V	225	-	0.12	-	0.12	-
15N	-	1000	-	3.0	-	3.0
8V	500	-	0.16	-	0.16	-
25N	-	2225	-	4.1	-	4.1

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

3.6 Breaking strength and elongation. The belts shall have the minimum breaking strength shown in Table II. The elongation of the belts at the minimum specified breaking strength shall not exceed 8 percent.

TABLE II. Breaking strength.

Designation	Breaking strength, minimum	
	Pounds	Kilograms
3V	400	-
9N	-	181
5V	900	-
15N	-	408
8V	2000	-
25N	-	907

3.7 Electrical resistivity. When specified (see 6.2), electrical resistance (see 6.4), shall be not greater than 6 megohms when tested as specified in 4.5.2.4.

3.8 Resistance to temperature extremes. The belts shall not be damaged when exposed to a temperature of 158° F, plus or minus 3.6° F, (70° C, plus or minus 2° C), for 12 hours. The belts shall neither crack nor require a greater torque for the applicable cross-sectional type designations than is specified in Table III while exposed to temperatures of minus 32° F, plus or minus 3.6° F, (36° C, plus or minus 2° C).

TABLE III. Maximum torque requirements.

Cross-sectional type designation	Torque required to start		Torque required to continue	
	ft. lb	N m 1/	ft. lb	N m
3V	25	-	12	-
9N	-	34	-	16
5V	30	-	15	-
15N	-	41	-	20
8V	35	-	20	-
25N	-	47	-	27

1/ Newton meter per radian

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:11Z
Check the source to verify that this is the current version before use.

3.9 Oil resistance. The belt thickness shall increase not more than 20 percent after exposure to ASTM No. 3 oil, and shall decrease (shrink) not more than 1 percent after exposure to ASTM No. 1 oil, when tested as specified in 4.5.2.6.

3.10 Age. When specified (see 6.2), the age of the belts shall be not more than 12 months (four quarters) from the time of manufacture to the date of acceptance.

3.11 Matched sets. When matched sets of belts are required, the individual belts of the matched set shall conform to the dimensional requirements for single belts; however, the maximum length difference between the shortest and longest belts in any one set shall not exceed the matching limits as specified in MS39277, MS39278, and MS39279.

3.12 Marking.

3.12.1 Identification. The belts shall be marked on the outside circumference in accordance with MIL-STD-130. In addition, each belt shall be marked with the dash number in accordance with the applicable MS39277, MS39278, and MS39279 and the manufacturer's name or trademark. When age is specified (see 6.2), the marking shall include the quarter and year (such as 1Q81), or month and year (example Jan 80) or week and year (example 1-80). Ink inprinting or permanent molded marking is acceptable.

3.12.2 Matched sets. Each belt of a matched set shall be marked as specified in 3.12.1. In addition, belts of a matched set shall be tied together and include a tag or label printed with the following notice: "WARNING, THIS IS A MATCHED SET. DO NOT BREAK TIES, EXCEPT AT INSTALLATION."

3.12.3 Special marking. In addition to the applicable marking specified in 3.12.1 and 3.12.2, each belt that is electric resisting (static conducting) shall be marked "SC".

3.13 Workmanship. The belts shall be free of any visible defects listed in MIL-STD-294.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

(a) Preproduction inspection (see 4.3).
(b) Quality conformance inspection (see 4.4).
(c) Inspection of packaging (see 4.6).

4.3 Preproduction inspection.

4.3.1 Examination. Each preproduction belt shall be examined as specified in 4.5.1. Presence of one or more defects shall be cause for rejection.

4.3.2 Tests. Each preproduction belt shall be tested as specified in 4.5.2.1 through 4.5.2.6, as applicable. Failure of any test shall be cause for rejection.

4.4 Quality conformance inspection.

4.4.1 Sampling. Sampling for examination and tests shall be in accordance with MIL-STD-105, Inspection Level S-3.

4.4.2 Examination. Samples selected in accordance with 4.4.1 shall be examined as specified in 4.5.1. AQL shall be 1.5 percent defective for major defects and 2.5 percent defective for minor defects. Major and minor defects are defined in MIL-STD-294.

4.4.3 Tests. Samples selected in accordance with 4.4.1 shall be tested as specified in 4.5.2.1 through 4.5.2.3. AQL shall be 4.0 percent defective.

4.5 Inspection procedure.

4.5.1 Examination. The belts shall be examined for visible defects as specified in MIL-STD-294.

4.5.2 Tests.

4.5.2.1 Length determination. Place the belt specimen on a measuring fixture similar to that shown in Figure 1. The belt size designation, the pulleys, and the tension requirements shall be as specified in Table I. Apply the applicable belt tension and rotate the pulley until the belt has made at least two complete

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

revolutions to seat the belt in the pulley grooves. Recheck the applicable belt tension for conformance as specified in Table I prior to the belt measurement. Calculate the effective length by adding the effective outside circumference of one of the measuring pulleys to twice the measured center distance between the two pulleys. Any belt or matched set of belts that exceeds the length, tolerances or matching limits specified in MS39277, or MS39279 shall constitute failure of this test.

4.5.2.2 Rideout and bottom clearance. Subsequent to the length determination test, with applicable tension and rotated as specified in 4.5.2.1, measure the of the belt and the distance from the bottom of the straightedge to the outer rim of the measuring pulley. Measure bottom clearance by subtracting the actual overall thickness of the belt from the depth of the pulley groove, and to the remainder add or subtract the rideout measurement. Rideout and bottom clearance in excess of the values specified in Table I shall constitute failure of this test.

4.5.2.3 Breaking strength and elongation. Place the belt specimen firmly in the jaws of a vertical tensile machine with a minimum distance of 12 inches between jaws. Operate the test machine at a rate of 3/4 to 2 inches per minute until the minimum breaking strength as specified in Table II for the cross-section being tested has been reached. Record the distance between gage marks. Elongation of more than 8 percent or fracture of the belt specimen prior to reaching the minimum breaking strength shall constitute failure of this test.

4.5.2.4 Electrical resistivity. Place two 5/8-inch diameter metallic contacts on the belt specimen 8-1/2 inches on centers. Moisten each contact with water and press against the belt specimen with the force of 12-1/2 pounds. Measure the resistance between the contacts with an ohmmeter operating at a potential of 500 volts. The ohmmeter shall have a range from zero to 10 megohms with an accuracy of plus or minus 2 percent. A resistivity greater than 6 megohms between contacts shall constitute failure of this test.

4.5.2.5 Temperature. The 8V and 25N cross-sectional type designation shall be required to be temperature tested only when the contractor has not previously furnished belts which have passed the temperature tests (see 6.5).

4.5.2.5.1 Resistance to temperatures. Place the belt in an air oven in an unrestrained, horizontal position and maintain the temperature of the oven at 158° F, plus or minus 3.6° F, (70°C plus or minus 2°C) for 12 hours. At the end of 12 hours, remove the belt from the oven and allow to cool for 30 minutes at room temperature. Then install the belt on the pulley and panel assembly (see Figure 2 and Table IV) and apply belt tension with the applicable weight for the width being tested as specified in Table IV. The tension weights may be applied as shown in Figure 2 or the panel may be turned 90 degrees with the

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:11Z
Check the source to verify that this is the current version before use.

tension pulley at the bottom and the tension weights suspended from the tension pulley. Turn the belt at least two complete revolutions to seat the belt in the pulley grooves, they lock tension pulley in place, removing the force of the tension weights from the belt. Then place the assembly of belts and pulleys in the cold chamber and maintain the chamber at a temperature of minus 32° F, plus or minus 3.6° F, (minus 36° C plus or minus 2° C) for 20 hours. At the end of 20 hours and while in the cold chamber, rotate the pulleys by means of a torque wrench applied to the driver pulley until the belt has been rotated not less than two complete revolutions. Record the torque to start and the torque to continue rotation. Examine the belt rotation. Evidence of cracks, breakage, or torque higher than the applicable value listed in Table III shall constitute failure of this test.

TABLE IV. Dimensions of test pulleys and tension weights.

Designation	Driver and driven pulley			Tension pulley				
	Outside diameter		Groove angle	Outside diameter		Groove angle	Tension weight	
	in.	mm	degrees	in	mm	degrees	lbs	kg
3V	4.75	-	38	2.80	-	36	70	-
9N	-	121	38	-	71	36	-	32
5V	11.80	-	40	7.10	-	38	160	-
15N	-	300	40	-	180	38	-	73
8V	20.00	-	40	18.00	-	40	220	-
25N	-	508	40	-	457	40	-	100

4.5.2.6 Oil-resistance test. Three belt sections each, 3 inches long, shall be immersed in ASTM oil No. 1 and ASTM Oil No. 3, as cited in ANSI/ASTM D 471, at a temperature of 158° F (70° C) for 22 hours. The thickness of each belt section shall be measured at the center and 1.2-inch from each end, before and after the immersion. The percent increase or decrease in thickness of any specimen shall be recorded as the average of the three readings for that specimen. Failure of any specimen to meet the requirements of 3.9 shall be cause for rejection.

4.6 Inspection of packaging.

4.6.1 Quality conformance inspection of pack.

4.6.1.1 Unit of product. For the purpose of inspection, a completed pack prepared for shipment shall be considered a unit of product.

4.6.1.2 Sampling. Sampling for examination shall be in accordance with MIL-STD-105.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

4.6.1.3 Examination. Samples selected in accordance with 4.6.1.2 shall be examined for the following major defects. AQL shall be 2.5 percent defective.

101.	Materials, methods, or containers not as specified.	Each incorrect material, method, or container shall be considered one defect.
102.	Belts or belt sets not preserved as specified or not in the quantities specified.	
103.	Strapping not as specified for Level A.	
104.	Gross weight or size exceeds the limitations of the applicable box specification.	
105.	Marking missing, illegible, incorrect, or incomplete.	

5. PACKAGING

5.1 Preservation. Preservation shall be Level A or Commercial, as specified (see 6.2).

5.1.1 Level A. Each belt set shall be combined as a single unit. Belts of like description or belt sets of like description shall be preserved in the quantity specified (see 6.2) in boxes conforming to PPP-B-636, Class Weather Resistant, style optional. Box closure shall be in accordance with the appendix of the box specification, Method V.

5.1.2 Commercial. Commercial preservation shall be in accordance with MIL-STD-1188.

5.2 Packing. Packing shall be Level A, Level B, or Commercial, as specified (see 6.2).

5.2.1 Level A. The belts, preserved as specified in 5.1, shall be packed in close-fitting boxes conforming to PPP-B-601, Overseas Type, style optional. The gross weight of each box shall not exceed 200 pounds. Strapping shall conform to QQ-S-781, Class 1, Type I or IV, size as applicable. Unless otherwise specified (see 6.2), strapping shall be Finish B. When specified (see 6.2), strapping shall be Finish A.

5.2.2 Level B. The belts, preserved as specified in 5.1, shall be packed in a close-fitting box conforming to PPP-B-636, V3c or V3s. The gross weight or size shall not exceed the limitation of the box specification. Closure and strapping shall be in accordance with the appendix to the box specification.

5.2.3 Commercial. Commercial packing shall be in accordance with MIL-STD-1188.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

5.3 Marking. Marking for military levels of protection shall be in accordance with MIL-STD-129. Commercial marking shall be in accordance with MIL-STD-1188.

6. NOTES

6.1 Intended use. The belts are intended for use in transmitting power in industrial applications, usually in the integral horsepower class, that require one or more belts.

6.2 Ordering data. Procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) MS part number required (see 3.5.1 and applicable MS).
(c) Time frame required for submission of preproduction model and number of belts required (see 3.2).
(d) When belts having electrical resistivity (static conductance) are required (see 3.7).
(e) When belts shall be not more than 12 months old (see 3.10).
(f) Degree or preservation and packing required (see 5.1 and 5.2).
(g) Quantity of belts per container (see 5.1.1).
(h) When strapping shall be other than as specified (see 5.2.1).

6.3 Preproduction model. Any changes or deviations of production belts from the approved preproduction model during production will be subject to the approval of the contracting officer. Approval of the production model will not relieve the contractor of his obligation to furnish belts conforming to this specification.

6.4 Belt standards. The V-belts specified herein conform to the Rubber Manufacturers Association Engineering Standards for Narrow (Industrial) Type Belts. Requirements and test for electrical conductivity are included on a when-specified basis for special purchases, when necessary. Such belts are not normally required in most applications.

6.5 Temperature test. 8V and 25N belts are large and require an oversize temperature-test chamber. Temperature testing of 8V and 25N belts should be required only when the contractor has not previously furnished belts which have passed the temperature tests by supply belts of the smaller types under this specification, or when the 8V and 25N belts differ in material construction or manufacturing process from the smaller type belts previously supplied under this specification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

6.6 Belt standard lengths. To insure that belts made by different manufacturers can be used interchangeably to the same center distance on a belt transmission drive, the length is measured on measuring pulleys and tensioned as specified in 4.5.2.1. The length thus obtained is called the effective outside length. If a belt were laid as a free circle on a flat surface and the outside measured, the length would be approximately equal to the effective outside length. However, the difference between the taped outside and the effective outside length may be different for belts made by different manufacturers. For this reason, the taped length can only be an approximate length. Standard belt lengths (effective lengths) are shown in the Military Standards in each of the cross sections.

6.7 International standardization. Certain provisions of this specification are the subject of International Standardization Agreement ABCA 63. When amendment, revision, or cancellation of this specification is proposed which will affect or violate the international agreement concerned, the preparing activity will take appropriate reconciliation action through international standardization channels including departmental standardization offices, if required.

6.8 Recycled Material. It is encouraged that recycled material be used when practical as long as it meets the requirements of the specification (see 3.3).


Custodians:
Army - ME
Air Force - 99

User activities:
Army - ER, AR
Navy - MC

Preparing activity:
Army - ME

Project 3030-0134


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

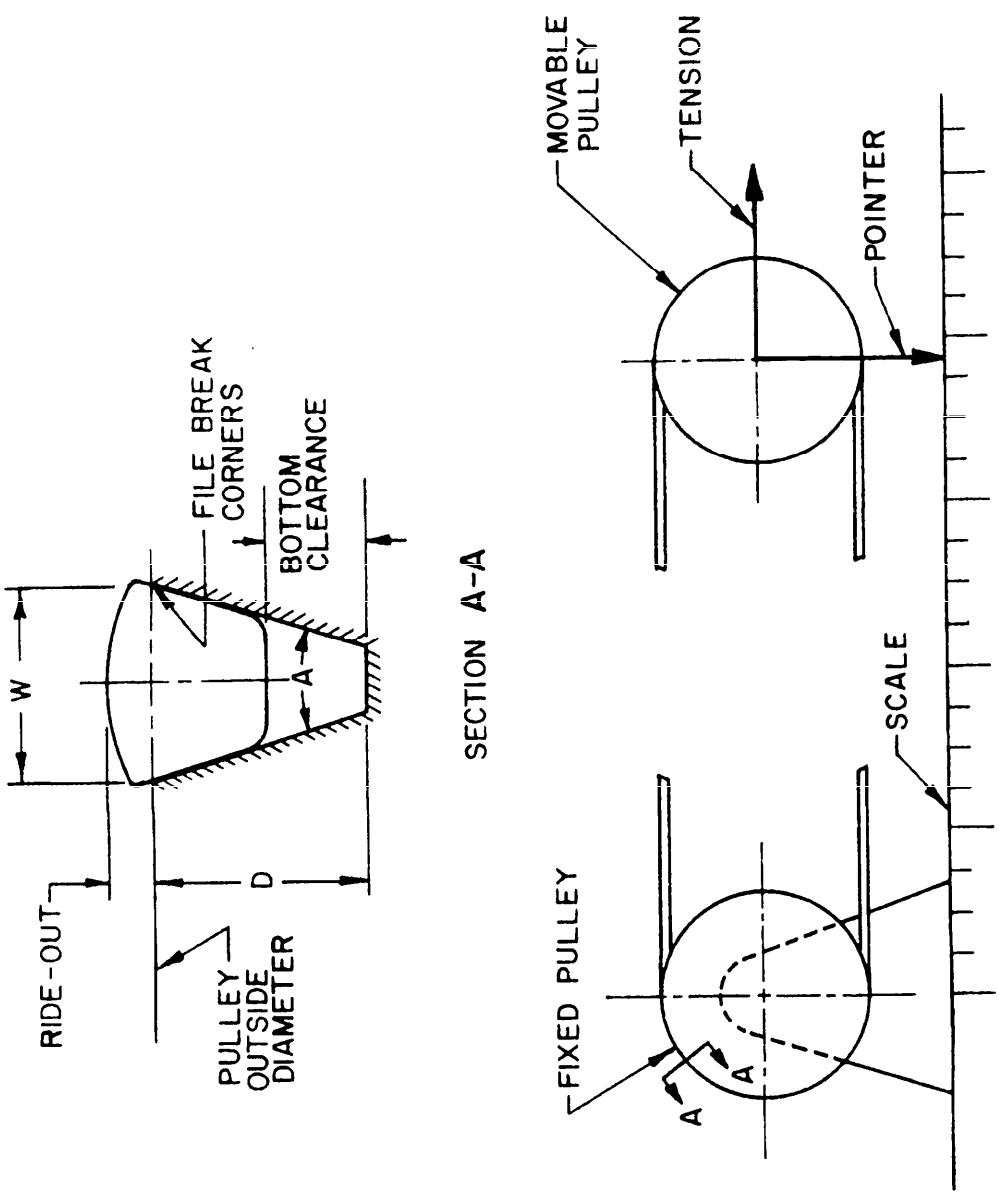

X-213A

FIGURE 1. Test fixture and pulleys for determining belt effective length, rideout and bottom clearance.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

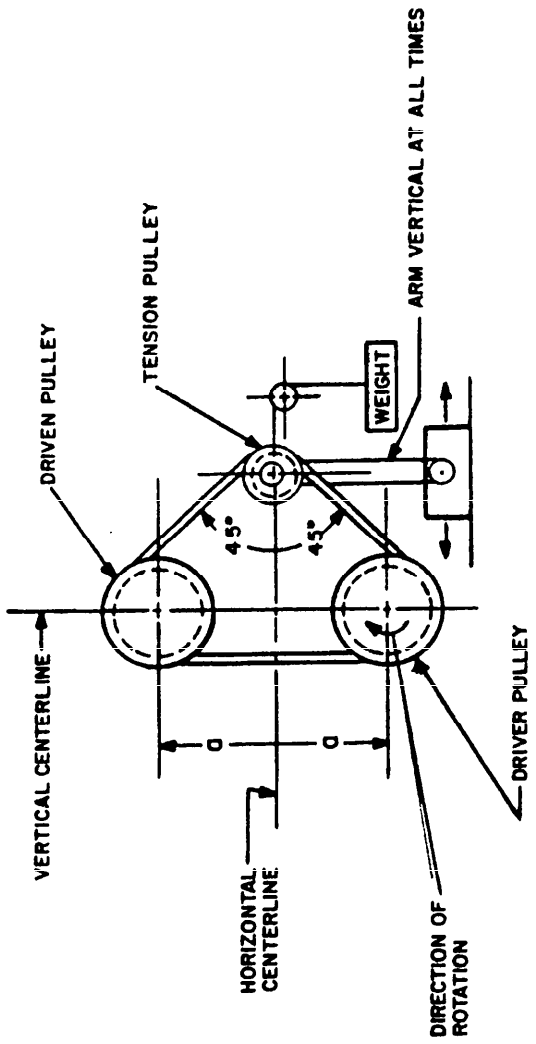

NOTE:
DIMENSION "d" IS ADJUSTED FOR VARIOUS LENGTH BELTS TO MAINTAIN TENSION PULLEY MIDWAY VERTICALLY BETWEEN DRIVER AND DRIVEN PULLEYS.

FIGURE 2. General pulley arrangement for low temperature test.

X-3225A

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:11Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS: This form is provided to solicit beneficial comments which may improve this document and enhance its use. DoD contractors, government activities, manufacturers, vendors, or other prospective users of the document are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity. A response will be provided to the submitter, when name and address is provided, within 30 days indicating that the 1426 was received and when any appropriate action on it will be completed.

NOTE: This form shall not be used to submit requests for waivers, deviations or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

DOCUMENT IDENTIFIER *(Number)* AND TITLE

MIL-B-52919A Belts, V: Industrial Drive, Narrow Type

NAME OF ORGANIZATION AND ADDRESS OF SUBMITTER

☐ VENDOR ☐ USER ☐ MANUFACTURER

1. ☐ HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE? ☐ IS ANY PART OF IT TOO RIGID, RESTRICTIVE, LOOSE OR AMBIGUOUS? PLEASE EXPLAIN BELOW.

A. GIVE PARAGRAPH NUMBER AND WORDING

B. RECOMMENDED WORDING CHANGE

C. REASON FOR RECOMMENDED CHANGE(S)

2. REMARKS

SUBMITTED BY *(Printed or typed name and address — Optional)*	TELEPHONE NO.
	DATE

DD FORM 1 OCT 76 1426 EDITION OF 1 JAN 72 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:11Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

NO POSTAGE
NECESSARY
IF MAILED
IN THE
UNITED STATES

BUSINESS REPLY CARD

FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Mobility Equipment Research and
Development Command
ATTN: DRDME-DS
Fort Belvoir, VA 22060

FOLD

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:11Z
Check the source to verify that this is the currentversion before use.