MIL-C-43637C
21 December 1987
SUPERSEDING
MIL-C-43637B
29 December 1983

MILITARY SPECIFICATION

CLOTH, PLAIN WEAVE, RIPSTOP, NYLON; FOR LINERS

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This document covers nylon cloth suitable for poncho liners.

1.2 Classification. The cloth shall be of the following classes as specified (see 6.2):

Class 1 - Dyed
Class 2 - Natural
Class 3 - U.S. Army Camouflage Pattern 1948 (see 3.3.3)
Class 4 - Woodland Camouflage Pattern (see 3.3.4)

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Documents. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: U.S. Army Natick Research, Development, and Engineering Center, Natick, MA 01760-5014, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 8305

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:54Z
Check the source to verify that this is the currenversion before use.

SPECIFICATIONS

FEDERAL

PPP-P-1133 - Packaging of Synthetic Fiber Fabrics

STANDARDS

FEDERAL

FED-STD-4 - Glossary of Fabric Imperfections
FED-STD-191 - Textile Test Methods

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes

(Copies of documents required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting activity.)

2.1.2 Other Government documents. The following other Government documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues shall be those in effect on the date of the solicitation.

DRAWINGS

U.S. ARMY NATICK RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER

2-1-1516 - Woodland Pattern - 48 inches
2-1-1516B - Woodland Pattern - 60 inches

Rules and Regulations Under the Textile Fiber Products Identification Act

(Application for copies should be addressed to the Federal Trade Commission, Pennsylvania Avenue at Sixth Street, N.W., Washington, DC 20580-0001.)

2.2 Other publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted shall be those listed in the issue of the DODISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS shall be the issues of the nongovernment documents which are current on the date of the solicitation.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

AMERICAN ASSOCIATION OF TEXTILE CHEMISTS AND COLORISTS (AATCC)

Chromatic Transference Scale

(Application for copies should be addressed to the American Association of Textile Chemists and Colorists, P.O. Box 12215, Research Triangle Park, NC 27709-2215.)

(Technical society and technical association documents are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document shall take precedence. Nothing in this document, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Standard sample. The dyed and finished cloth shall match the standard sample for shade and appearance and shall be equal to or better than the standard sample with respect to all characteristics for which the standard sample is referenced (see 6.3).

3.2 Material.

3.2.1 Yarn. The yarn used shall be bright, multifilament nylon.

3.3 Color.

3.3.1 Class 1. The color of class 1 cloth shall be as specified and shall match the standard sample (see 6.2 and 6.3).

3.3.2 Class 2. The color of the class 2 cloth shall be natural (unbleached).

3.3.3 Class 3, printing. The 4-color U.S. Army Camouflage Pattern 1948 shall be obtained by roller or automatic screen printing using four rollers or screens as appropriate for the Light Green 354, Dark Green 355, Brown 356, and Black 357 areas of the pattern. The printing shall be accomplished with either organic dyes or resin bonded pigment colors to provide a match to the several shades of the pattern and to provide the infrared reflectance levels specified in 3.9.1. The use of disperse type dyes shall be prohibited.

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:54Z
Check the source to verify that this is the currentversion before use.

3.3.3.1 Class 3, pattern execution. Unless otherwise specified, the pattern shall reproduce the standard sample in respect to design, colors, and registration of the respective areas, and to the measurements of the repeat. In general the repeat shall be 16.75 inches ± 0.75 inches in the warp direction. The various areas of the pattern shall be properly registered in relation to each other and present defined sharp demarcations with a minimum of feathering or spew. Each pattern area shall show solid coverage. Skitteriness exceeding that shown by the standard sample in any of the printed areas shall not be acceptable (see 6.3).

3.3.4 Class 4, printing. The color of the class 4 finished cloth shall be the Woodland camouflage pattern obtained by roller or screen printing using four rollers or screens as appropriate for the Light Green 354, Dark Green 355, Brown 356, and Black 357 areas of the pattern.

3.3.4.1 Class 4, pattern execution. The pattern shall reproduce the standard sample in respect to design, colors, and registration of the respective areas and the measurements of the repeat. In general, the repeat shall be 27.25 inches (+1.25, -2.5 inches) in the warp direction. The various areas of the pattern shall be properly registered in relation to each other and present definite sharp demarcations with a minimum of feathering or spew. Each pattern area shall show solid coverage. Skitteriness exceeding that shown by the standard sample in any of the printed areas shall not be acceptable. When the standard sample is not referenced for pattern execution or design, the pattern on the base cloth shall match the standard Woodland camouflage pattern Drawing 2-1-1516 or 2-1-1516B, as applicable (see 6.2 and 6.3).

* 3.3.5 Matching. The color of the finished cloth shall match the standard sample when viewed under filtered tungsten lamps that approximate artificial daylight and that have a correlated color temperature of 7500 ± 200K, with illumination of 100 ± 20 foot candles, and shall be a good match to the standard sample under incandescent lamplight at 2300 ± 200K.

3.3.6 Colorfastness.

* 3.3.6.1 Class 1. The dyed and finished cloth shall show fastness to laundering, perspiration, and crocking equal to or better than the standard sample or equal to or better than a rating of "good" to laundering and perspiration and shall show an AATCC Chromatic Transference Scale rating for crocking not lower than 3.5 when tested as specified in 4.2.3.

* 3.3.6.2 Classes 3 and 4. The finished camouflage printed cloth shall show fastness to laundering and perspiration, equal to or better than the standard sample or equal to or better than a rating of "good" for each of the pattern colors except Black 357 which shall be equal to or better than a

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

rating of "fair" when tested as specified in 4.2.3. Fastness to crocking shall be equal to or better than the standard sample or shall have an AATCC Chromatic Transference Scale rating not lower than 3.5 for all the pattern areas, except Black 357 which shall have an AATCC Chromatic Transference Scale rating not lower than 1.5, when tested as specified in 4.2.3.

3.4 Physical requirements. The finished cloth shall conform to the physical requirements specified in table I when tested as specified in 4.2.3.

TABLE I. Physical requirements

Weight, ounces per sq yd, maximum	Yarns per inch, minimum		Breaking strength, lbs, minimum		Tearing strength, lbs, minimum	
	Warp	Filling	Warp	Filling	Warp	Filling
1.1	120	120	42	42	5	5

* 3.4.1 Width. The width of the cloth shall be as specified (see 6.2) and shall be the minimum acceptable width inclusive of the selvage when fly shuttle looms or shuttleless with tuck-in selvage looms are used. For all other shuttleless looms, the width measurement shall be made between the last warp yarn on each side excluding the protruding fringe(s).

3.5 Weave. The ripstop weave pattern for the cloth shall be as shown in figure 1. Reinforcement ribs in both warp and filling shall form a uniform pattern of squares. There shall be a minimum of 6.5 repeats of the pattern per inch in both directions.

3.6 Finish. The cloth shall be scoured and heat treated. Classes 3 and 4 cloth shall be heat treated prior to printing. The heat treating shall be done so that the cloth meets the requirements of 3.7 and 3.8.

3.7 Dimensional stability. The cloth shall show no appreciable distortion or puckering, nor shall there be more than 2.0 percent dimensional change in either warp or filling, when tested as specified in 4.2.3.

* 3.8 Nonfibrous materials. The total chloroform-soluble and water-soluble material content of the finished cloth shall not exceed 1.0 percent for all classes, except class 3 which shall not exceed 4.0 percent, when tested as specified in 4.2.3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

3.9 Reflectance.

3.9.1 Class 3. The infrared reflectance values, measured at one micron, of the pattern colors shall be as specified in table II when tested as specified in 4.2.3 (see 3.3.3).

TABLE II. Class 3 infrared reflectance values

Color	Percent
Light Green 354	52 (minimum)
Dark Green 355	32 ± 4
Brown 356	22 ± 4
Black 357	10 (maximum)

* 3.9.2 Class 4. The colors in the 4-color camouflage printed finished cloth shall meet the spectral reflectance requirements for the visible/near-infrared wavelength range 600 to 860 nanometers (nm) as specified in table III, when tested as specified in 4.2.3.

TABLE III. Spectral reflectance (percent) requirements, class 4

Wavelengths (nm)	Black 357		Light Green 354		Dark Green 355 and Dark Brown 356	
	min	max	min	max	min	max
600	-	10	-	20	-	13
620	-	10	-	20	-	13
640	-	10	-	20	-	13

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

TABLE III. Spectral reflectance (percent) requirements, class 4 - Continued

Wavelengths (nm)	Black 357		Light Green 354		Dark Green 355 and Dark Brown 356	
	min	max	min	max	min	max
660	-	10	-	20	-	13
680	-	10	20	-	10	-
700	-	10	33	-	25	-
720	-	10	45	-	40	-
740	-	10	50	-	50	-
760	-	10	50	-	50	-
780	-	10	50	-	50	-
800	-	10	50	-	50	-
820	-	10	50	-	50	-
840	-	10	50	-	50	-
860	-	10	50	-	50	-

3.10 pH. The pH value of the finished cloth shall be not lower than 5.0 nor higher than 8.5 when tested as specified in 4.2.3.

3.11 Length and put-up. Unless otherwise specified (see 6.2), the finished cloth shall be in continuous lengths, each not less than 75 yards. Each length shall be put-up in full width rolls as specified in 5.1.

3.12 Fiber identification. Each roll shall be labeled or ticketed for fiber content in accordance with the Rules and Regulations Under the Textile Fiber Products Identification Act.

3.13 Marking. The face side of the cloth shall be identified by applying a stamping on that side of the cloth with the word "FACE" at each end of the roll.

3.14 Workmanship. The finished cloth shall conform to the quality established by this document. The demerit points per 100 square yards when calculated as specified in section 4 shall not exceed the established maximum point value.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in this document where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this document shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirement in the document shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.1.2 Certificates of compliance. When certificates of compliance are submitted, the Government reserves the right to inspect such items to determine the validity of the certification.

4.2 Quality conformance inspection. Unless otherwise specified, sampling for inspection shall be performed in accordance with MIL-STD-105.

4.2.1 Component and material inspection. In accordance with 4.1, components and materials shall be inspected in accordance with all the requirements of referenced documents unless otherwise excluded, amended, modified, or qualified in this document or applicable purchase document.

4.2.2 End item examination.

4.2.2.1 Yard-by-yard examination. Each roll in the sample shall be examined on the face side only (printed side for classes 3 and 4). When the total yardage in the roll does not exceed 100 yards, the entire yardage in the roll shall be examined. When the total yardage in the roll exceeds 100 yards, only 100 yards shall be examined. All defects, defined in Section III of FED-STD-4, that are clearly noticeable at normal inspection distance (3 feet) shall be scored and assigned demerit points as listed in 4.2.2.1.1. No linear yard (increments of 1 yard on the measuring device of the inspection machine) from any one roll within the sample shall be penalized more than four points.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

The sample size shall be 20 rolls selected from 20 containers. The lot shall be unacceptable if the points per 100 square yards of the total yardage examined exceeds 35 points. The lot shall be unacceptable if the points per 100 square yards of two or more individual rolls exceeds 53 points. If no individual roll exceeds 53 points per 100 square yards, the lot shall be acceptable with respect to this characteristic. If one roll in the sample size of 20 exceeds 53 points per 100 square yards, a second sample of 20 rolls shall be examined for individual roll quality only. The lot shall be unacceptable if one or more rolls in the second sample exceeds 53 points per 100 square yards. Point computation for lot quality and individual roll quality shall be as follows:

$$\frac{\text{Total points scored in sample} \times 3600}{\text{Contracted width of cloth (inches)} \times \text{Total yards inspected}} = \text{Points per 100 square yards}$$

4.2.2.1.1 Demerit points. Demerit points shall be assigned as follows:

For defects 3 inches or less in any dimension	- one point
For defects exceeding 3 inches, but not exceeding 6 inches in any dimension	- two points
For defects exceeding 6 inches, but not exceeding 9 inches in any dimension	- three points
For defects exceeding 9 inches in any dimension	- four points

The following defects, when present, shall be scored four points for each yard in which they occur:

Width less than specified
Objectionable odor
Overall uncleanness
Uneven weaving throughout
Skitteriness of pattern exceeds that shown by standard sample (classes 3 and 4)
Pattern design not equal to the standard sample (classes 3 and 4)
Excessive feathering or spew of pattern (classes 3 and 4)
Pattern repeat less than 16 inches or more than 17.5 inches (class 3)
Warpwise pattern repeat less than 24.75 inches or more than 28.50 inches (class 4)

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

4.2.2.2 Length examination. During the yard-by-yard examination, each roll in the sample shall be examined for length. Any length found to be less than the minimum specified or more than 2 yards less than the length marked on the ticket shall be considered a defect with respect to length. The lot shall be unacceptable if two or more rolls in the sample are defective in respect to length. The lot shall be unacceptable if the total of the actual lengths or rolls in the sample is less than the total of the lengths marked on the tickets.

4.2.2.3 Shade and appearance examination. During the yard-by-yard examination, each roll in the sample shall be examined for shade and finish appearance. Any roll in the sample off shade, shaded side to side, shaded side to center, or shaded end to end, or any roll that does not have the same appearance as the standard sample shall be cause for rejection of the entire lot represented by the sample.

4.2.2.4 Roll identification examination. During the yard-by-yard examination, each roll in the sample shall be examined for the defects listed below. The lot shall be unacceptable if two or more rolls in the sample contain one or more of the following defects:

Not labeled or ticketed in accordance with the Rules and Regulations Under the Textile Fiber Products Identification Act

Face identification missing from either or both ends

Face identification on the wrong side

4.2.3 End item testing. The cloth shall be tested for the characteristics listed in table IV. The methods of testing specified in FED-STD-191, wherever applicable, and as listed in table IV shall be followed. The physical and chemical values specified in section 3, except where otherwise specified, apply to the average of the determinations made on a sample unit for test purposes as specified in the applicable test method. The sample unit shall be 3 1/2 continuous yards full width of the finished cloth. The lot shall be unacceptable if one or more sample units fail to meet any requirement specified. All test reports shall contain the individual values used in expressing the final results. The sample size (number of sample units) shall be in accordance with the following:

Lot size (yards)	Sample size (sample units)
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:54Z
Check the source to verify that this is the current version before use.

TABLE IV. End item tests

Characteristic	Requirement paragraph	Test method
Nylon:		
Multifilament	3.2.1	Visual 1/
Identification	3.2.1	1530 2/
Luster	3.2.1	2/
Colorfastness to:		
Laundering	3.3.6	5614 and 3/
Perspiration	3.3.6	5680 and 3/
Crocking	3.3.6	5651 and 3/
Weight	3.4	5041
Yarns per inch	3.4	5050
Breaking strength	3.4	5104
Tearing strength	3.4	5134
Weave	3.5	Visual 1/
Finish:		
Scouring	3.6	2/
Heat treating	3.6	2/
Dimensional stability	3.7	4.3.1
Nonfibrous material	3.8	2611
Refectance:		
Class 3	3.9.1	4.3.2.1
Class 4	3.9.2	4.3.2.2
pH	3.10	2811

1/ One determination shall be made on each sample unit and the results reported as "pass" or "fail".

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:54Z
Check the source to verify that this is the currentversion before use.

2/ Unless otherwise specified, a certificate of compliance shall be submitted and will be acceptable for the stated requirement.

3/ On camouflage pattern cloth, the colorfastness test shall be performed on each color in the pattern for both the standard sample, when applicable, and the submitted specimen. The individual colors of the pattern shall be so selected that only the specific color being evaluated is included as the test area of the submitted specimen and the standard sample.

4.2.4 Packaging examination. The examination shall be in accordance with the quality assurance provisions of PPP-P-1133.

4.3 Methods of inspection.

4.3.1 Dimensional stability test. The test specimen shall be a square of cloth a minimum 20 inches by 20 inches. Before marking and measuring for dimensional change, the specimen shall be in equilibrium with Standard Conditions as defined in FED-STD-191. The specimen shall be laid without tension on a flat surface and shall be inscribed with an 18-inch square approximately equidistant from the edges having sides parallel to the warp and normal filling directions. The marked specimen shall be placed in a preheated oven and maintained at a temperature of 280° ± 20°F for a period of 2 hours. The specimen may be looped over a rod or laid flat on a rack both of which shall be made of low-conductivity (nonmetallic) material and have free air circulation on both sides. Promptly remove the specimen from the oven, allow to cool on a flat surface, and then bring to equilibrium under Standard Conditions. Measure each side of the inscribed square for dimensional change in both the warp and filling directions (two measurements each for the warp and filling per specimen). Each change in dimension shall be reported to the nearest 0.1 percent. The specimen shall also be visually compared with the original unheated cloth for any appreciable distortion or puckering.1/

1/ Appreciable means a change that is immediately noticeable when comparing the tested specimen with the original. If closer inspection is required to make apparent a slight change, the change is not considered appreciable.

4.3.2 Reflectance tests.

* 4.3.2.1 Class 3, infrared reflectance. The infrared reflectance shall be determined at one micron relative to a barium sulfate standard white reference using a spectrophotometer sensitive in this range (see 6.8 and 6.9). Readings shall be made on four layers of each specified color, taken at random from a

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:54Z
Check the source to verify that this is the currentversion before use.

minimum of two pattern repeats, while backed with cloth cotton sateen Olive Green 107. The specimen shall be turned 90 degrees between a minimum of two readings to obtain an average infrared reading that shall be reported separately for each shade.

* 4.3.2.2 Class 4, spectral reflectance measurements in the visible/near-infrared. Spectral reflectance data shall be obtained from 600 to 860 nm, at 20 nm intervals on a spectrophotometer (see 6.8) relative to a barium sulfate standard, the preferred white reference standard. Other white reference materials may be used, provided they are calibrated to absolute white; e.g., Halon, magnesium oxide, or vitrolite tiles (see 6.9). The spectral bandwidth shall be less than 26 nm at 860 nm. Reflectance measurements may be made by either the monochromatic or polychromatic mode of operation. When the polychromatic mode is used, the spectrophotometer shall operate with the specimen diffusely illuminated with the full emission of a source that simulates either CIE Source A or CIE Source D65. The specimen shall be measured as a single layer, backed with sufficient layers of the same fabric and shade to reach optimum thickness. Measurements will be taken on a minimum of two different areas, and the data averaged. The specimen shall be viewed at an angle no greater than 10° from normal, with the specular component included. Photometric accuracy of the spectrophotometer shall be within 1 percent, and wavelength accuracy within 2 nm. The standard aperture size used in the color measurement device shall be 1.0 to 1.25 inches in diameter. When the measured reflectance values for any color at four or more wavelengths do not meet the limits specified in table III, it shall be a test failure.

5. PACKAGING

5.1 Put-up and preservation. Put-up and preservation shall be level A or Commercial as specified (see 6.2).

5.1.1 Levels A and Commercial. The cloth shall be put-up and preserved in accordance with the applicable requirements of PPP-P-1133.

5.2 Packing. Packing shall be level A, B, or Commercial, as specified (see 6.2).

5.2.1 Levels A, B, and Commercial. The cloth shall be packed in accordance with the applicable requirements of PPP-P-1133.

5.3 Marking. In addition to any special marking required by the contract or purchase order, shipments shall be marked in accordance with the applicable requirements of PPP-P-1133.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

6. NOTES

6.1 Intended use. The cloth is intended for use as the outer covering for batting used in liners and ponchos. It is not intended for either the manufacture or repair of parachutes.

6.2 Ordering data. Acquisition documents should specify the following:

a. Title, number, and date of this document.
b. Class required (see 1.2).
c. Color required for class 1 (see 3.3.1).
d. Woodland camouflage pattern drawing if required (see 3.3.4.1).
e. Width of cloth required (see 3.4.1).
f. Length of roll if other than specified (see 3.11).
g. Selection of applicable levels of put-up, preservation, and packing (see 5.1 and 5.2).

6.3 Standard sample and pattern drawing. For access to the standard shade samples (see 3.1), the Army Camouflage Pattern 1948 (see 3.3.3.1), and the Woodland camouflage pattern drawings, if applicable (see 3.3.4.1), address the contracting activity issuing the invitation for bids.

6.4 Dyestuff formulation for Olive Green 106. A suggested, but not mandatory, dyestuff formulation for Olive Green 106 is as follows:

Neutral Premetallized Olive Green B
Acid Yellow 151

6.5 Dyestuff formulation for class 3 dyed ground shade Light Green 354. A suggested, but not mandatory, dyestuff formulation for the dyed ground shade Light Green 354 to be overprinted for the class 3 cloth, Camouflage pattern, is as follows:

- Dyed Light Green 354 ground shade

Acid Yellow 28
Premetallized Dark Green 2 BL
Premetallized Brilliant Green 3 BL

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:54Z
Check the source to verify that this is the current version before use.

6.6 Dyestuff formulation for class 3 resin bonded pigments. The following suggested, but not mandatory, resin bonded pigments for the class 3 printed cloth can be used to match each shade and to produce the specified infrared reflectance values:

Light Green 354	Dark Green 355
Pigment Yellow 2GL R. B. 90	Pigment Yellow 2 GL R. B. 90
Pigment Green 2G R. B. 40	Pigment Blue RL, R. B. 20
Pigment Red 2BH R. B. 60	Pigment Red 2BH R. B. 60
Pigment Orange 2RG R. B. 52	Pigment Black 4GL R. B. 10

Brown 356	Black 357
Pigment Yellow 2GL R. B. 90	Pigment Black 4GL R. B. 10
Pigment Red 2BH R. B. 60	
Pigment Green 2G R. B. 40	
Pigment Black 4GL R. B. 10	

6.7 Dyestuff formulation for class 4, Woodland camouflage print. The dyed ground Light Green 354, and the printing of Dark Green 355, Brown 356, and Black 357 may be accomplished by varying the amounts of the following dyestuffs:

Acid Blue 229	Acid Orange 154
Acid Blue 239	Acid Orange 156
Acid Blue 258	Acid Red 256
Acid Yellow 127	Acid Red 259
Acid Yellow 151	Acid Brown 45
Acid Yellow 219	Acid Black 64
	Acid Black 172

Carbon black may be included in the black area of the pattern only.

* 6.8 Spectrophotometer. Suitable spectrophotometers for measuring spectral reflectance in the visible/near-infrared are the Diano Hardy, Diano Match Scan, Hunter D54P-IR, Hunter VIS/NIR spectrocolorimeter and Macbeth 1500 with IR option (see 4.3.2.1 and 4.3.2.2).

* 6.9 White standard. Barium sulfate of suitable quality for use as a white reference standard is available from the Eastman Kodak Company. The same source has available magnesium reagent (ribbon) and Halon. Suitable tiles can be obtained from the National Bureau of Standards or the instrument manufacturers.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

* 6.10 Subject term (key word listing).

Cloth, plain weave, nylon
Liner
Poncho liner

6.11 Changes from previous issue. The margins of this document are marked with an asterisk (*) to indicate where changes (additions, modifications, corrections, deletions) from the previous issue were made. This was done as a convenience only, and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content, as written, irrespective of the marginal notations and relationship to the last previous issue.

Custodians:

Army - GL
Navy - NU
Air Force - 99

Review activities:

Army - MD
Air Force - 82
DLA - CT

User activity:


Navy - MC

Preparing activity:

Army - GL

Project No. 8305-0157

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

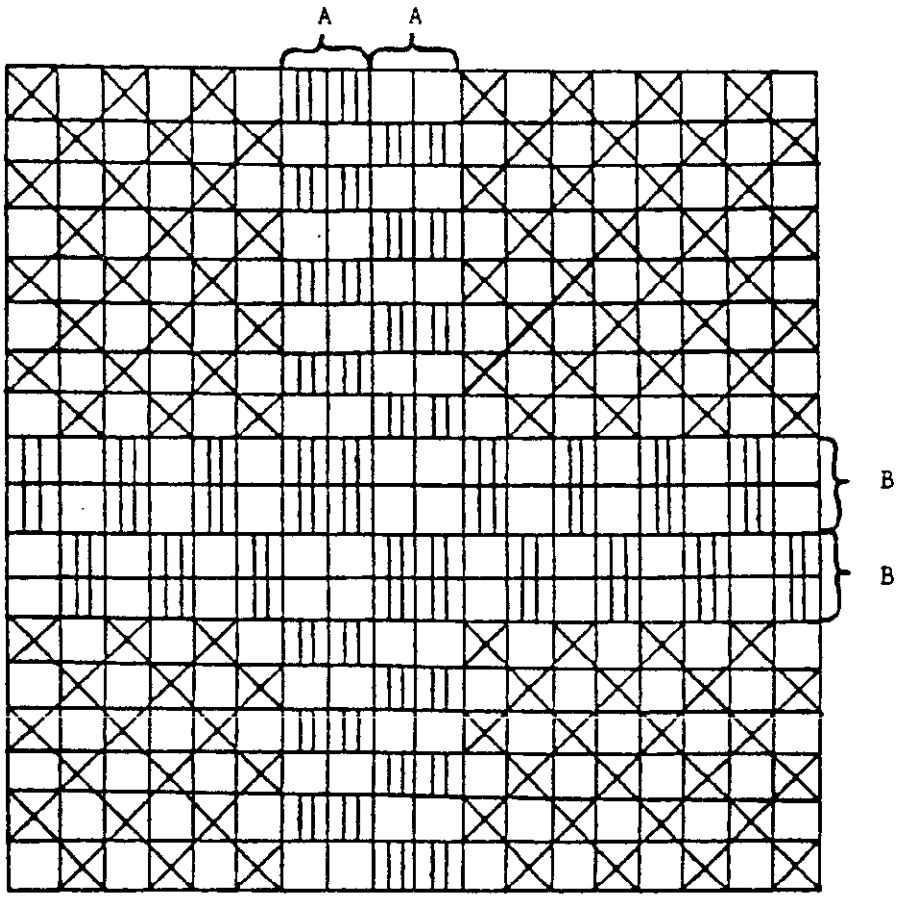

A = Two warp ends woven as one

B = Two filling picks per shed

FIGURE 1. Ripstop weave pattern.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:54Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

US Army Natick Research, Development, and
Engineering Center
Natick, MA 01760-5014

NO POSTAGE
NECESSARY
IF MAILED
IN THE
UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300
STRNC-ES

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Natick Research, Development,
and Engineering Center
ATTN: STRNC-ES
Box 14A
Natick, MA 01760-5014

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:54Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-C-43637C	Cloth, Plain Weave, Ripstop, Nylon; For Liners

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

NATICK/OP, 1 Apr 84

Source: https://assist.dla.mil - Downloaded: 2026-02-10T21:54Z
Check the source to verify that this is the current version before use.