W-T-1604A
September 12, 1973
SUPERSEDING
Int. Fed. Spec. W-T-001604 (GSA-FSS)
August 31, 1970

FEDERAL SPECIFICATION

# TAPE, PERFORATOR TYPE, POLYESTER BASE

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

## 1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers the requirements for unpunched polyester base perforator type tape, of three different compositions, in roll form, for punched program automatic data processing (see 6.1).

1.2 Classification.

1.2.1 Compositions. Perforator type tape covered by this specification shall be of the following compositions, as specified (see 6.2).

Compositions:

A - Polyester film.
B - Polyester film - metalized polyester film.
C - Polyester film - aluminum foil - polyester film.

## 2. APPLICABLE DOCUMENTS

2.1 The following documents of the issues in effect on the date of invitation for bids, or request for proposal, form a part of this specification to the extent specified herein:

Federal Specifications:

PPP-B-591 - Boxes, Fiberboard Wood-Cleated.
PPP-B-601 - Boxes, Wood, Cleated Plywood.
PPP-B-621 - Boxes, Wood, Nailed and Lock Corner.
PPP-B-640 - Boxes, Fiberboard, Corrugated, Triple Wall.
PPP-T-76 - Tape, Pressure-Sensitive Adhesive Paper, (For Carton Sealing).

Federal Standards:

Fed. Std. No. 123 - Marking For Domestic Shipment (Civil Agencies).

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, D. C. 20402.

(Single copies of this specification and other Federal Specifications required by activities outside the Federal Government for bidding purposes are available without charge from Business Service Centers at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Fort Worth, Denver, San Francisco, Los Angeles, and Seattle, Washington.

(Federal Government activities may obtain copies of Federal Specifications, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:34Z
Check the source to verify that this is the current version before use.

Military Specifications:

MIL-P-116 - Preservation; Methods of.
MIL-B-40314 - Boxes, Water-Resistant, Paperboard, Folding, Set-Up and Metal-Stayed.

Military Standards:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless a specific issue is identified, the issue in effect on date of invitation for bids, or request for proposal shall apply:

American Society For Testing and Materials (ASTM) Standards:

D 638 - Test for Tensile Properties of Plastics.
D 882 - Tests for Tensile Properties of Thin Plastic Sheeting.

(Application for copies should be addressed to the American Society, for Testing Materials, 1916 Race Street, Philadelphia, Pennsylvania 19103.)

National Motor Freight Traffic Association, Incorporated, Agent:

National Motor Freight Classification.

(Application for copies should be addressed to the American Trucking Association, Inc., Tariff Order Section, 1616 P Street, N. W., Washington, DC 20036.)

Uniform Classification Committee, Agent:

Uniform Freight Classification.

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, IL 60606.)

3. REQUIREMENTS

3.1 General. The tape supplied under this specification shall have been specifically designed for use on high speed perforator tape punchers, duplicators, and readers. The tape shall be new and shall have been tested for conformance to the requirements as specified herein.

3.2 Qualification. The item furnished under this specification shall be a product that has been tested, and passed the qualification tests specified herein, and has been listed or approved for listing on the applicable Federal Qualified Products List (QPL) (see 4.3 and 6.3). The general rules and regulations governing Federal Qualified Products Lists, as covered by the "Provisions Governing Qualification" (Appendix 4-A to GSA Federal Standardization Handbook FPMR 101-29), shall apply (see 6.4).

3.2.1 Process change. Qualification once established, applies only to those tapes manufactured by the same process used to make the tapes that passed the qualification tests. All proposed process changes shall be reported to the qualification activity (see 6.5), with a statement by the supplier as to the general nature of the changes and the extent of such changes on the delivered product. The qualifying activity reserves the right to require six weeks notice, and sufficient samples of the new product for quality assurance tests, from the supplier prior to delivery of products manufactured under any such change in process. The foregoing requirement does not in any way relieve the manufacturer of delivery requirements, quality control, and testing necessary to insure that all products delivered under this specification are equal to those products originally submitted for qualification.



Source: https://assist.dla.mil -- Downloaded: 202640-26T11:34Z
Check the source to verify that this is the current version before use.

3.3 Component parts. Component parts shall consist of individual rolls of tape, wound on cores that meet the requirements of 3.5 and packaged in accordance with the requirements of Section 5, as specified (see 6.2).

3.4 Materials.

3.4.1 Composition A. The tape shall be constructed of a single layer, or of two layers suitably bonded and laminated together, of polyester plastic film or equivalent that meets the requirements of this specification and the intended use (see 6.1).

3.4.2 Composition B. The tape shall be constructed of a layer of polyester plastic film or equivalent and a layer of aluminum metalized polyester plastic film or equivalent, suitably bonded and laminated together to meet the requirements of this specification and the intended use (see 6.1). The minimum thickness of each layer or lamination shall be 0.0008 inch. At least one of the polyester plastic layers shall be metallized on the side next to the adhesive.

3.4.3 Composition C. The tape shall be constructed of a layer of polyester plastic film or equivalent, a layer of aluminum foil, and a layer of polyester plastic film or equivalent, suitably bonded and laminated together to meet the requirements of this specification and the intended use (see 6.1). The minimum thickness of each plastic layer or lamination shall be 0.0008 inch.

3.4.4 Toxic compounds. Compounds which produce toxic effects under conditions normally encountered in Government service shall not be used.

3.4.5 Flammable materials. Flammable materials which will ignite from a match flame and when so ignited will continue to burn in a still carbon dioxide atmosphere, shall not be used.

3.5 Cores. Each roll of tape shall be wound on a 2-inch ± 1/8 inch inside diameter core that has a wall thickness of between 1/8 and 1/4 inch. The length of the core shall be equal to the specified tape width with a tolerance of ± 1/16 inch.

3.6 Physical dimensions.

3.6.1 Length. Unless otherwise specified in the contract or purchase order (see 6.2), the tape shall be supplied in two minimum lengths of 1200 feet and 1800 feet.

3.6.2 Width. The tape shall be supplied in widths in accordance with table I (see 6.2).

3.6.3 Thickness. Tape of each particular composition shall be supplied in the thickness(es), for tape of that composition, as specified in table II (see 6.2). Tape thickness tolerance shall be ± 0.0003 inch.

TABLE I. Tape Widths

| Width dimension (Fractional inch) | Width dimension (Decimal inch) | Width tolerance (inch) |
|---|---|---|
| 11/16 | 0.687 | ± 0.003 |
| 7/8 | 0.875 | ± 0.003 |
| 1 | 1.000 | ± 0.003 |

TABLE II. Tape Thickness

| Tape Composition | Tape Thickness (Inch) |
|---|---|
| Composition A | 0.0030 |
| | 0.0037 |
| Composition B | 0.0026 |
| | 0.0030 |
| Composition C | 0.0032 |
| | 0.0037 |



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:34Z
Check the source to verify that this is the current version before use.

3.7 Physical properties. The physical properties of the tape shall be as specified in table III.

TABLE III. Physical Properties

| Characteristic | Requirements Thickness (see table II) 0.0026 | 0.0030 | 0.0032 | 0.0037 | Units | Test Methods |
|---|---|---|---|---|---|---|
| Light Transmission (maximum) | 2.5 | 2.5 | 2.5 | 2.5 | Percent | Para. 4.6.4.1 |
| Tensile Properties (minimum) (1 percent offset yield point, force at 3 percent elongation, and force at break) | 35 | 38 | 41 | 44 | Lbs. per inch width | Para. 4.6.4.2 |
| Strip Delamination, (minimum) as received; | 150 | 150 | 150 | 150 | Grams per inch wide | Para. 4.6.4.3 |
| After 24 hours at 165 ± 2°F. and 40 to 50 percent relative humidity (for laminated tapes only) | 170 | 170 | 170 | 170 | | |
| Shrinkage (maximum) After 2 hours at 185 ± 2°F. and 0 to 30 percent relative humidity. | 0.25 | 0.15 | 0.15 | 0.15 | Percent | Para. 4.6.4.4 |

3.8 Color. The tape shall be supplied in the below listed colors, as specified (see 6.2). The coloring shall be an integral part of the tape. When color is not specified the tape shall be supplied in the color blue.

Tape Colors:

| | | |
|---|---|---|
| Blue | Green | Gray |
| Red | Gold | Black |

3.9 Wind. The tape shall be wound with the color side on the outside of the roll. The tape pile shall be smoothly wound to form an integral mass and shall not be loose either axially or circumferentially. There shall be no visible folds, buckling, cinching, spoking, or gaps between the tape layers. The edges of the wound tape shall be in a single plane and there shall be no protruding tape layers or group of layers. The plane of the tape pile shall be perpendicular to the reel axis. The tape shall unwind freely without sticking. The outer end of the tape shall be fastened to the adjacent layer in such a way that it is retained securely in shipment and handling but can be pulled loose without cutting and without damage to the tape.

3.10 Splices. All tape shall be continuous and free of splices.

3.11 Workmanship and uniformity. The tape shall have a uniform consistency and appearance on each side, without any streaks, light spots, or blank areas. There shall be no markings or codes on the surface of the tape or laminated between layers. The tape shall be clean, free from dirt, oil, foreign matter, scratches, scuffs, cracks, creases, blisters, pits, tears, cuts, and other defects which would render the tape unsuitable for its intended use.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:34Z
Check the source to verify that this is the current version before use.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements, as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.2 Classification of inspection. The inspections specified herein are classified as follows:

(a) Qualification inspection (see 4.3).
(b) Quality conformance inspection of end item (see 4.4).
(c) Acceptance inspection (see 4.5).
(d) Examination of preparation for delivery (see 4.7).

4.3 Qualification inspection. Qualification inspection shall be conducted at a laboratory designated by the qualifying activity (see 6.5). Qualification inspection shall consist of the examinations and tests listed in table IV. The results of the examinations and tests shall be compared with the specified requirements. Failure to conform to any requirement shall be counted as a defect and the tape represented by that sample shall not be approved for inclusion on the applicable Qualified Products List.

4.3.1 Qualification of tape of a particular composition and thickness shall constitute qualification of all tape of that particular composition and thickness regardless of width and length.

4.3.2 Sampling for qualification inspection. The sample unit for qualification inspection shall be 1200 feet of 1-inch wide tape wound on a core as specified herein. Sample size shall consist of 10 reels of each particular composition and thickness for which qualification is desired. Samples for qualification inspection shall be selected by the Government.

4.4 Quality conformance inspection of end item. In accordance with 4.1, the contractor shall be responsible for the performance of the quality conformance inspections. The contractor shall select a sample number of units from each lot of tape offered for delivery. The sample units shall be selected in accordance with 4.4.2 and the contractor shall subject the sample unit to the appropriate examinations and tests of table IV to determine compliance with the specification requirements. All necessary test equipment and facilities required to conduct the subject examinations and tests shall be furnished by the contractor. Alternate test techniques and equipment may be used by the contractor subject to review and approval by the contracting officer that such techniques and equipment are in fact adequate to insure compliance with specification requirements.

TABLE IV. Examinations and Tests

| Examinations and Tests | Requirement Paragraphs | Test Paragraphs |
|---|---|---|
| Group A | | |
| General Examination | 3.3, 3.4.1, 3.4.2, 3.4.3, 3.5 3.8, 3.9, 3.10, and 3.11 | 4.6.2 |
| Group B | | |
| Physical Dimensions | 3.6 | 4.6.3 |
| Group C | | |
| Light Transmission | 3.7 | 4.6.4.1 |
| Group D | | |
| Tensile Properties | 3.7 | 4.6.4.2 |
| Strip Delamination (laminated tape only) | 3.7 | 4.6.4.3 |
| Group E | | |
| Shrinkage | 3.7 | 4.6.4.4 |



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:34Z
Check the source to verify that this is the current version before use.

4.4.1 Report of quality conformance inspection. The contractor shall maintain a complete record of all production test results for the duration of the contract. A copy of all production test results shall be forwarded with each shipment of tape to the activity receiving the tape. The record shall include the information necessary to identify the lot, the inspector, and the date of test.

4.4.2 Sampling for quality conformance inspections. Sampling for quality conformance inspections shall be in accordance with MIL-STD-105 and as specified herein.

4.4.2.1 Lot. A lot shall consist of only those rolls of tape (selected for delivery by the contractor) of one composition, width, thickness, length, and color. Small orders, may be grouped as one lot for sample submission purposes.

4.4.2.2 Sampling for group A examinations and tests. Sampling for group A examinations and tests shall be in accordance with MIL-STD-105, Inspection Level S-3, at an acceptance quality level (AQL) of 6.5 defects per hundred units.

4.4.2.3 Sampling for group B examinations and tests. Sampling for group B examinations and tests shall be in accordance with MIL-STD-105, Inspection Level S-2, at an acceptance quality level (AQL) of 4 defects per hundred units.

4.4.2.4 Sampling for group C examinations and tests. Sampling for group C examinations and tests shall be in accordance with MIL-STD-105 Inspection Level S-3, at an acceptance quality level (AQL) of 2.5 defects per hundred units.

4.4.2.5 Sampling for group D examinations and tests. The sample size for group D examinations and tests shall be two rolls of tape per lot (see 4.4.2.1). Failure to conform to any requirement of the group D examinations and tests shall be counted as a defect, and the lot represented by the sample shall be rejected.

4.4.2.6 Sampling for group E examinations and tests. The group E examinations and tests shall be performed initially and thereafter only when the formulation of the tape or the manufacturing process has been changed. The sample size for group E examinations and tests shall be two rolls of tape of the particular composition and thickness offered. Failure to conform to any requirement of the group E examinations and tests shall be counted as a defect, and the tape represented by the sample shall be rejected.

4.5 Acceptance inspection. At the Government's option, when deemed necessary, acceptance inspection shall be required on all lots offered for delivery (see 6.2). Acceptance inspection shall be performed either at the manufacturer's facility under the direction of a Government Quality Assurance Specialist or at a Government laboratory. Such acceptance inspection will normally consist of the group A, B, C, and D examination and tests given in table IV and sampling and acceptance will be determined in accordance with 4.4.2.2, 4.4.2.3, 4.4.2.4, and 4.4.2.5.

4.6 Examinations, tests, and measurements.

4.6.1 Test environment. Except when otherwise specified, all measurements and tests shall be performed at an ambient temperature of 70° F. ± 5° F. and a relative humidity of between 45 and 55 percent.

4.6.2 General examination. Sample units, selected in accordance with 4.4.2.2 shall be examined for the defects set forth in table V.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:34Z
Check the source to verify that this is the current version before use.

TABLE V. Defects in Construction, Appearance, Workmanship, and Core Dimensions

| Examine | Major Defects |
|---|---|
| Color | Not as specified. |
| Wind | Color side not toward the outside of the roll.<br>Tape pile not smoothly wound; loose with visible folds, buckling, cinching, spoking, or gaps between tape layers.<br>Protruding tape layers, or groups of layers.<br>Plane of the tape pile not perpendicular to the reel axis.<br>Tape not wound on core.<br>Core crushed, broken, mutilated, or collapsed. |
| Appearance | Surface not clean; presence of excessive dirt, lint, fuzz, or other foreign matter.<br>Presence of translucent blemishes, holes, tears, creases, or wrinkles.<br>Color not uniform throughout roll; bare spots. |
| Construction | Tape does not unroll evenly and uniformly; tape sticks. Roll not continuous; any splices, joints, seams, tears, or breaks within the roll. |
| Length of core | Not within ± 1/16 inch of tape width. |
| Thickness of core wall | Greater than 1/4 inch or less than 1/8 inch. |
| Inside diameter of core | Inside diameter of core not within specified dimensions. |

4.6.3 Physical dimensions measurements.

4.6.3.1 Tape length. The tape length shall be measured for conformance to the requirements of 3.6.1.

4.6.3.2 Tape width. The tape width shall be measured for conformance to the requirements of 3.6.2. Five measurements per sample roll of tape shall be made spaced approximately six inches apart.

4.6.3.3 Tape thickness. The tape thickness shall be measured for conformance to the requirements of 3.6.3. Measurements shall be made at five randomly selected points throughout each sample roll of tape, spaced at intervals of not less than five feet.

4.6.4 Physical properties measurements.

4.6.4.1 Light transmission. Light transmission shall be measured using a light transmission tester as shown in the engineering sketch, figure 1, or equal. The essential elements of the light transmission tester are; an internally blacked metal tube, with a light source at one end, and a specimen holder, photoelectric detector, and indicator at the other end; arranged to measure the light transmitted from the source through the specimen holder and onto the photoelectric detector. The light source shall be a 12 volt, 36 watt, lamp with a single transverse filament, operated at about 10 volts, ac or dc. The lamp supply voltage should be 12 volts adjustable over a range of not less than ± 4 volts, but once set, voltage shall remain constant ± 1 percent. The specimen holder shall be so constructed that the specimen can be fed through the tube so that it is centered, with its plane normal to the axis of the transmitted radiant flux. The specimen, when in position, must be held flat, firm, and smooth against the specimen holder mask. The specimen holder mask shall have an aperture of 0.073-inch diameter. The photocell mask shall have an aperture of 0.144-inch diameter. The light sensor shall be a silicon solar cell and shall be large enough to cover the photocell aperture. The spectral response of the photocell should extend through the visible spectrum and peak at 800 to 900 millimicrons in the near infrared. The response to incident light intensity should be substantially a linear function from no light to maximum light. The indicator should be a dc moving coil microameter with 500 ohms nominal impedance, 50 microamp full scale deflection,



Source: https://assist.dla.mil -- Downloaded: 202640-26T11:34Z
Check the source to verify that this is the current version before use.

4.6.4.1 Light Transmission (cont). linearity within 1 percent, and a scale length of at least 4 inches. Check the apparatus for a minimum indicator reading (no light reaching detector) and then adjust the lamp voltage for a maximum indicator reading (no specimen in holder, maximum light reaching detector). The percent of light transmitted through the specimen shall be calculated in accordance with the following:

$$\text{Percent light transmission} = \frac{i_m - i_o}{i_{100} - i_o} \times 100$$

Where: $i_m$ = meter reading with tape sample in place

$i_{100}$ = meter reading with maximum light reaching detector

$i_o$ = meter reading with no light reaching detector

Three randomly selected one-foot sections from each sample roll of tape shall be fed through the tape holder and the percent light transmission calculated at ten randomly selected spots on each section for conformance to the requirement specified in table III.

4.6.4.2 Tensile properties test. Tensile properties shall be measured using a testing machine as described in ASTM Standard D 882 for Method A testing. A strip of tape not less than 7 inches in length shall be clamped in the grips set for an initial separation of 4 inches. The test specimen shall be clamped in the testing machine taking care to align the long axis of the specimen with an imaginary line joining the points of attachment of the grips to the machine. The grips shall be tightened evenly and firmly to the degree necessary to prevent slipping of the specimen during the test. The rate of grip separation shall be 12 inches per minute. Not less than three specimens per sample roll of tape shall be tested. A force strain diagram shall be obtained. Means shall be provided for calibration of the strain axis. The 1.0 percent offset yield strength shall be determined as described in the appendix to ASTM Standard D638. The tangent (approximating the initial slope) to the force-strain curve shall be obtained by drawing a straight line between the origin and the point on the curve corresponding to one half the specified force (see table III). If the force-strain curve between these two points deviates by more than 0.1 percent elongation from the straight line drawn, a new straight line shall be drawn from the origin to one quarter of the specified force. The 1.0 percent offset yield strength determined in this manner, the force corresponding to 3 percent elongation and the force at break shall equal or exceed the value listed in table III for the particular type of tape being evaluated. In the event that the breakage of a particular tape occurs prior to reaching the 1.0 percent offset yield strength or 3 percent elongation, the force at break shall equal or exceed the value listed in table III.

4.6.4.3 Strip delamination. Strip delamination shall be measured in accordance with the following procedure. Cut a six-inch length of the tape. Soak the last two inches of the strip in dichloromethane, until the lamination adhesive is dissolved. Delaminate the soaked end of the strip and allow to dry. Clamp one of the laminates to an elevated point. To the other laminate, clamp a dead weight (that can be slowly increased in weight) pulling in a downward direction. Slowly increase weight until there is a self-continuing delamination action. Upon completion of the delamination, weigh the weight for conformance to the requirement in table III. Cut six strips from each roll of tape in the sample. Perform the test on three strips at 75° ± 5°F. and on three strips after they have been subjected to a temperature of 165° ± 5°F. and a relative humidity of 40 to 50 percent for not less than 24 hours. Report results in grams per inch of width for conformance to the requirement in table III.

4.6.4.4 Shrinkage. The tape shall be tested for shrinkage in accordance with the following procedure. Five 10-inch minimum lengths of tape from each sample roll shall be measured and shall then be placed in a temperature - humidity chamber and subjected to a temperature of 185°F ± 2°F and a relative humidity of 0 to 30 percent for a period of two hours ± 6 minutes. The lengths of tape shall then be brought back to "test environment" (see 4.6.1.1) by opening the test chamber door and allowing the temperature in the chamber to stabilize to the "test environment" and remain at the "test environment" for at least one hour. The lengths of tape shall then be measured again. Calculate the shrinkage, in percent, for conformance to the shrinkage requirement given in table III.



Source: https://assist.dla.mil -- Downloaded: 202640-26T11:34Z
Check the source to verify that this is the current version before use.

4.7 Examination of preparation for delivery. Interior and exterior examinations shall be made to determine whether the packaging, packing, marking, materials, and contents comply with the requirements in Section 5, as specified (see 6.2). Select sample units from end item inspection lots in accordance with MIL-STD-105, inspection level S-2, with an AQL of 4 defects per hundred units. The lot size shall be the number of shipping containers in the end item inspection lot. A sample unit for interior examination shall be one shipping container, fully packed, selected just prior to closing and sealing. A sample unit for exterior examination shall be one shipping container, fully prepared for delivery. Examine the samples for the defects listed in table VI.

TABLE VI. Preparation for Delivery Defects

| Examine | Defects |
|---|---|
| Interior Preservation and Packaging | Use of improper or defective materials.<br>Quantity in unit package not as specified.<br>Quantity in exterior container not as specified.<br>Incorrect packaging method applied.<br>Cushioning or padding omitted.<br>Cushioning inadequate for the physical protection of the item.<br>Unsealed, punctured, or improperly sealed bag, wrap, or envelope.<br>Damaged or otherwise defective rolls. |
| Exterior Packing and Marking | Use of improper or defective materials.<br>Type, grade, class, and style of shipping container not as specified.<br>Marking incorrect, incomplete, illegible, omitted; improper size, location, sequence, or method of application.<br>Inadequate application of components such as: incomplete closure of case liners, container flaps, loose or inadequate sealing, strapping, or stapling.<br>Bulged or distorted container.<br>Special marking or labeling (when required) omitted. |

5. PREPARATION FOR DELIVERY

5.1 Packaging. Packaging shall be level A, B, or C, as specified (see 6.2).

5.1.1 Level A. Each roll of tape shall be packaged in accordance with method 1A-8 of MIL-P-116. Each bagged roll shall be placed in a container conforming to MIL-B-40314 or PPP-B-640, class 2. The container shall be closed with tape conforming to PPP-T-76.

5.1.2 Level B. Packaging shall be the same as for level A, except that each bagged roll shall be placed in a container conforming to PPP-B-640, class 1.

5.1.3 Level C. The tape shall be packaged to insure protection during shipment and safe delivery to destination.

5.2 Packing. Packing shall be level A, B, C, as specified (see 6.2).

5.2.1 Level A. Packaged rolls of tape shall be packed in exterior containers conforming to PPP-B-640, class 2; PPP-B-621, class 2; PPP-B-601, overseas type; or PPP-B-591, overseas type. Containers shall be strapped in accordance with the appendix of the applicable container specification.

5.2.2 Level B. Packaged rolls of tape shall be packed in exterior containers conforming to PPP-B-640, class 1; PPP-B-621, class 1; PPP-B-601, domestic type; or PPP-B-591, domestic type.

5.2.3 Level C. The tape packaged as specified in 5.1 shall be packed to comply with the National Motor Freight Classification or the Uniform Freight Classification rules.



Source: https://assist.dla.mil -- Downloaded: 202640-26T11:34Z
Check the source to verify that this is the current version before use.

5.3 Marking. Unless otherwise specified (see 6.2), marking shall be in accordance with 5.3.1 or 5.3.2, as applicable.

5.3.1 Civil agencies. In addition to the marking required by Fed. Std. No. 123 and the contract or purchase order, the shipping container shall be marked with an identification as: Tape, Unpunched, Perforator Type; the composition designation; the width, thickness, and length; color; a part number; a lot number; date of manufacture; the contract number; and Federal stock number, if available.

5.3.2 Military agencies. In addition to the marking required by MIL-STD-129 and the contract or purchase order, the shipping containers shall be marked with an identification as: Tape, Unpunched, Perforator Type; the composition designation; the width, thickness, and length; color; a part number; a lot number; date of manufacture; the contract number; and Federal stock number, if available.

6. NOTES

6.1 Intended use. Perforator tape covered by this specification is intended for use on photoelectric and electro-mechanical readers of computers and other types of automation and data processing equipment demanding the ultimate in dimensional stability and freedom from wear after prolonged usage.

6.2 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number, and date of this specification.
(b) Quantity of item required.
(c) Tape composition (see 1.2.1 and 3.4).
(d) Width required (see 3.6.2).
(e) Thickness required (see 3.6.3).
(f) Length required (see 3.6.1).
(g) Color required (see 3.8).
(h) Inspection responsibility, if other than specified (see 4.1).
(i) Specify acceptance inspection when required. Also specify place of inspection (see 4.5).
(j) Levels of packing and packaging required (see 5.1 and 5.2).
(k) Special markings, if required (see 5.3).

6.3 With respect to products requiring qualification, awards will be made only for such products as have, prior to the time set for opening of bids, been tested and approved for inclusion on Qualified Products List QPL-W-T-1604, whether or not such products have actually been so listed by that date. The attention of suppliers is called to this requirement and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. The activity responsible for the qualified products list is the Federal Supply Service, General Services Administration, Washington, D. C. 20406, and information pertaining to qualification of products may be obtained from that activity. Application for qualification tests shall be made in accordance with "Provisions Governing Qualification" (see 6.4).

6.4 Copies of "Provisions Governing Qualification" may be obtained upon application to Director, Standardization Division, Federal Supply Service, General Services Administration, Washington, D. C. 20406.

6.5 Qualifying activity. The term qualifying activity as used herein shall mean the General Services Administration.

MILITARY INTERESTS:

Custodians:
Army - EL
Navy - AS
Air Force - 84

User Activities:
Navy - AS
Air Force - 84, 70

Preparing Activity:
GSA - FSS



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:34Z
Check the source to verify that this is the current version before use.

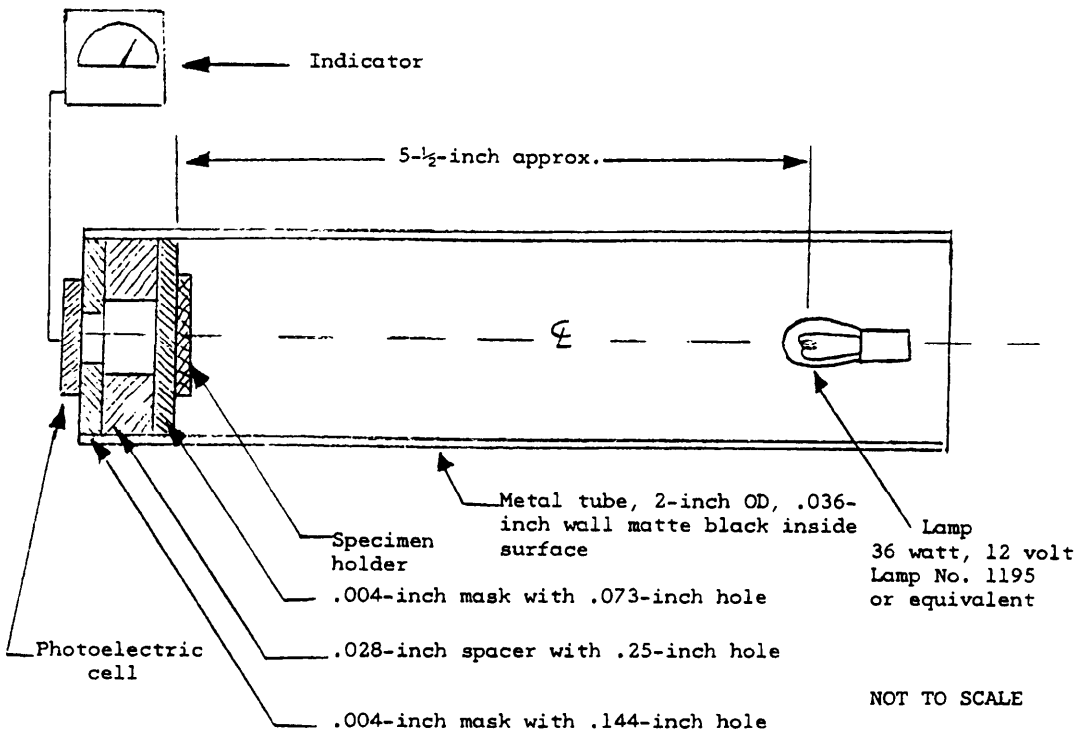



FIGURE 1 - Light Transmission Meter

Orders for this publication are to be placed with General Services Administration, acting as an agent for the Superintendent of Documents. See section 2 of this specification to obtain extra copies and other documents referenced herein. Price 15 cents each.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:34Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:34Z
Check the source to verify that this is the current version before use.