A-A-2566
March 25, 1988

# COMMERCIAL ITEM DESCRIPTION

## BAR, WRECKING

The General Services Administration has authorized the use of this commercial item description in preference to Federal Specification GGG-B-101, Type V, Class 1, Style A and Class 2.

This commercial item description covers wrecking bars.

## SALIENT CHARACTERISTICS

Material. The material used in the manufacture of the bars shall be either tool steel or an alloy steel. The chemical composition of the material and the heat treatment employed shall be such as to produce bars to withstand the specified tests. All forgings shall be of uniform quality, free from defects and imperfections that may affect their serviceability or durability. Special quality, fine grain, hot rolled or cold finished carbon steel may also be used.

Design. The bars, otherwise meeting the requirements of this specification, may be the manufacturer's standard design.

Finish. The bars shall be free from burrs, roughness and excessive oxide scale. The body of the bars shall be either lacquered, enameled, painted, or have an oil-coated natural finish. The work ends of Type V bars shall have a satin finish, and shall be oil or phosphate coated, lacquered or painted.

Type V, wrecking. For a minimum distance of 2-3/4 inches from each end, wrecking bars shall have a hardness value of not less than 20 nor more than 45 on the Rockwell C scale, or a hardness reading of not less than 226 nor more than 421 on the Brinell scale.

Class 1, gooseneck and pinch-point. Class 1 bars shall have one end bent in the form of a gooseneck and the opposite end in the form of a pinch-point.

Style A with claw. Style A bars shall have the gooseneck provided with a slotted claw suitable for pulling nails. The bars shall not fracture nor show a permanent set in excess of 1/32 inch when tested in accordance with physical test. The opposite end shall be wedge-shaped and shall be offset at an angle of 30 degrees ± 5 degrees from the longitudinal axis of the bar. The bar shall conform to table I and be similar to figure 1.

Table I. Type V, class 1, style A wrecking bar, gooseneck with claw and pinch-point.

| | Dimensions | | | | | | | | | Test load | Load Distance from end |
|---|---|---|---|---|---|---|---|---|---|---|---|
| | A | D | E | F | H | J | K | L | M | | |
| Size Number | +1.000 Inches | +1/32 Inch | +1/8 -1/16 Inch | +1/8 Inches | Min Inch | Min Inches | +1/16 Inch | Min Inches | +1/32 Inch | Pounds | Inches |
| 1 | 12 | 1/16 | 3/4 | 1 | 1/2 | 3/4 | 1/4 | 1-1/16 | 1/16 | 150 | 8 |
| 2 | 18 | 1/16 | 15/16 | 1-1/8 | 5/8 | 1 | 5/16 | 1-1/8 | 1/16 | 150 | 14 |
| 3 | 24 | 1/16 | 1 | 1-3/8 | 3/4 | 1-5/16 | 7/16 | 1-3/16 | 1/16 | 125 | 20 |
| 4 | 30 | 1/16 | 1 | 1-3/8 | 3/4 | 1-5/16 | 7/16 | 1-3/16 | 1/16 | 100 | 26 |
| 5 | 36 | 1/16 | 1 | 1-3/8 | 3/4 | 1-5/16 | 7/16 | 1-3/16 | 1/16 | 75 | 32 |

| Size Number | National Stock Number |
|---|---|
| 1 | 5120-00-223-7218 |
| 2 | 5120-00-293-2384 |
| 3 | 5120-00-224-1393 |
| 4 | 5120-00-293-0665 |
| 5 | 5120-00-242-0762 |

FSC 5120

DISTRIBUTION STATEMENT A. Approved for Public Release; Distribution is Unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:24Z
Check the source to verify that this is the current version before use.

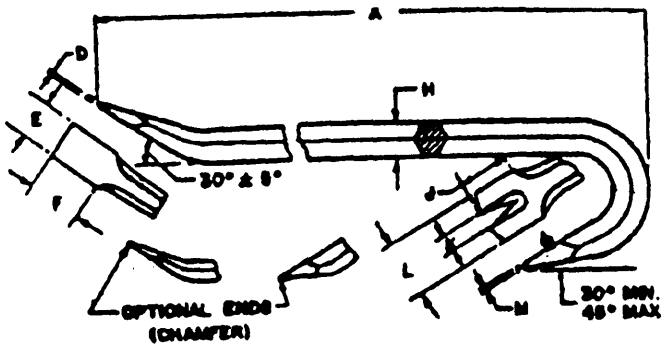



FIGURE 1. Type V, class 1, style A gooseneck and pinch-point with claw wrecking bar.

Class 2, offset claw and pinch-point. Class 2 bars shall have the ends offset in opposite directions at an angle of 30 degrees ± 5 degrees from the longitudinal axis. Both ends shall be wedge-shaped with one end provided with a slotted claw suitable for pulling nails. The bars shall be furnished in lengths of 30 or 36 inches as specified. Class 2 bars shall not fracture nor show a permanent set in excess of 1/32 inch when tested in accordance with physical test. The bars shall conform to table II and the dimensions shown in figure 2.

Table II. Type V, class 2, wrecking bar, offset claw and pinch-point.

| Size Number | Dimensions A +1.000 Inches | D +1/32 Inch | E +1/8 -1/16 Inch | F ±1/8 Inches | H Min Inch | J Min Inches | K ±1/16 Inch | L Min Inches | M ±1/32 Inch | Test load Pounds | Load Distance from end Inches |
|---|---|---|---|---|---|---|---|---|---|---|---|
| 4 | 30 | 1/16 | 1 | 1-3/8 | 3/4 | 1-5/16 | 7/16 | 1-3/16 | 1/16 | 180 | 26 |

| Size Number | National Stock Number |
|---|---|
| 4 | 5120-00-180-0873 |

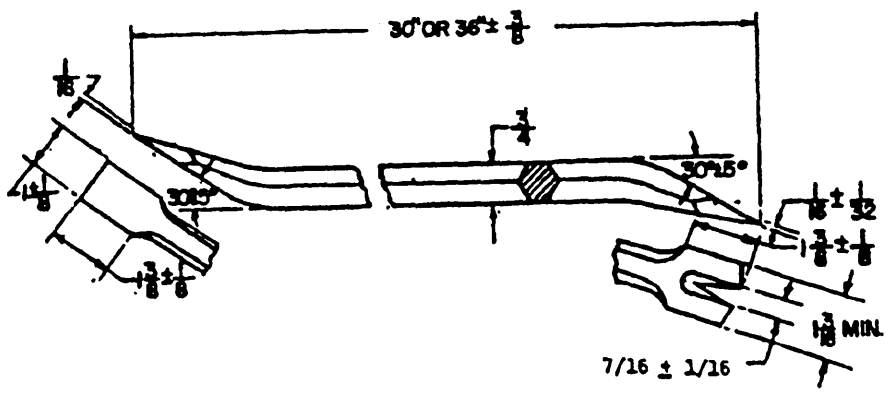



FIGURE 2. Type V, class 2, wrecking bar, offset claw and pinch-point.

Identification marking. Each wrecking bar shall be etched or stamped in a permanent and legible manner with the manufacturer's name or identifying symbol of such known character that the source may be readily identifiable, part number, and country of origin.

Workmanship. All bars shall be free from imperfections which may affect their safety, appearance, serviceability, or durability.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:24Z
Check the source to verify that this is the current version before use.

QUALITY ASSURANCE PROVISIONS

Sampling for inspection. Sampling shall be in accordance with MIL-STD-105, Sampling Procedures and Tables for Inspection by Attributes, except where otherwise specified herein. The lot size shall consist of all bars offered for acceptance at one time. The sample unit is one wrecking bar.

Visual inspection. Each bar from the sample lot shall be examined for workmanship and marking requirements. The inspection level shall be I with an acceptable quality level (AQL) of 2.5 defects per hundred units.

Dimensional inspection. Each bar from the sample lot shall be examined for dimensional requirements. The inspection level shall be S-4 with an acceptable quality level (AQL) of 2.5 defects per hundred units.

Testing of end item. The inspection level shall be S-3 with an acceptable quality level (AQL) of 4.0 percent defective.

Hardness test. Hardness test shall be in accordance with ASTM E18 or ASTM E10. The impressions shall be taken 1/2 inch from the end tested. The manufacturer shall certify that both the cutting edge end and the taper end have been similarly hardened.

Physical test. A test load as shown in table I for the appropriate size (overall length) of the bar being tested shall be applied to the body at a point 4 inches from one end, and the opposite end secured. The load being applied shall be perpendicular to the body in a direction such as to straighten the offset or gooseneck. The wrecking bar, after being tested, shall indicate no fracture or permanent set in excess of 1/32-inch from original shape.

Regulatory requirements. The offeror/contractor is encouraged to use recovered materials in accordance with Public Law 94-580, as amended, to the maximum extent practicable.

Preservation, packaging, packing, labeling, and marking. Preservation, packaging, packing, labeling, and marking shall be as specified in the contract or order.

Notes.

The issue of referenced documents in effect on date of invitation for bid or request for proposal shall be used to determine compliance with the stated requirements.

ASTM standards are available from American Society For Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.

Military standards are available from Naval Publications and Forms Center, 5801 Tabor Avenue, Philadelphia, PA 19120.

MILITARY INTERESTS:

Military Coordinating Activity
Army - GL

Custodians
Army - GL
Air Force - 99

Review Activities
Air Force - 84

PREPARING ACTIVITY:

GSA/FSS



Source: https://assist.dla.mil -- Downloaded: 202610-26T08:24Z
Check the source to verify that this is the current version before use.